

Magnetic correlations and antiferromagnetic order in La_{2-x} Sr_x CuO₄

Autor(en): **Borsa, F. / Corti, M. / Rega, T.**

Objekttyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **62 (1989)**

Heft 6-7

PDF erstellt am: **27.04.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116101>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

MAGNETIC CORRELATIONS AND ANTIFERROMAGNETIC ORDER IN $\text{La}_{2-x} \text{Sr}_x \text{CuO}_4$

F.Borsa, M.Corti, T.Regia, A.Rigamonti and J.Ziolo
Department of Physics A.Volta, Pavia (ITALY)

Abstract: From ^{139}La and ^{63}Cu NQR relaxation it is found that the Cu⁺⁺ long-range in-plane magnetic correlation is strongly limited by mobile charge defects introduced by the Sr doping. Both NQR relaxation and specific heat measurements indicate that at low temperature the antiferromagnetic order is restored at $T_N(x)$ as a consequence of a freezing of the mobile defects.

The ^{139}La and ^{63}Cu spin-spin and spin-lattice relaxation measurements for x ranging from 0 to $x=0.3$ and in the temperature range 1.6–450 K, when analyzed in terms of the possible relaxation mechanisms allow one to conclude that over most of the x and T range the relaxation is controlled by the Cu⁺⁺ – Cu⁺⁺ in plane (2D) magnetic correlation length ξ (1).

An x and T dependence of ξ , which is unconventional with respect to the behavior of 2D doped Heisenberg paramagnets is deduced through standard relationships of the relaxation rate T_1^{-1} vs ξ . On the basis of an interpretative model whereby the degree of magnetic correlation that would result from the strength of the Cu⁺⁺ – Cu⁺⁺ exchange coupling is controlled by an effective correlation time, one derives

$$1) \xi(x, T) = \frac{1}{\sqrt{n(x, T)}} = \frac{1}{\sqrt{x}} e^{-b/2xT} \quad (\text{in lattice units})$$

where $b/2x$ is an effective activation energy with $b \approx 0.9$ K that has been deduced by the low T behavior of T_1^{-1} for various x (see Fig.1).

When the magnetic order is restored at low temperature as a consequence of the decrease of the concentration of the mobile defects $n(x, T)$ (see Eq.1), one observes a peak in (T_1^{-1}) and a small anomaly in the specific heat $C_p(T)$. The maximum value $(T_1^{-1})_{\max}$ is about the same for all x although $T_N(x)$ ranges from ~300 to ~2 K. This is taken as an indication that the ordering is triggered by a 2D correlation length ξ_{2D} which is about the same at $T \approx T_N$, regardless the x value. This unexpected result could imply an interplane coupling J' which sharply decreases with x or which is not in competition with the thermal fluctuations.

No information can be derived from the NQR data on the character of the 3D order, i.e. antiferromagnetic vs spin-glass. However the anomalies in C_p around T_N are in favour of a 3D antiferromagnetic state. In Fig.2 we show the phase diagram for our samples as deduced from a variety of measurements.

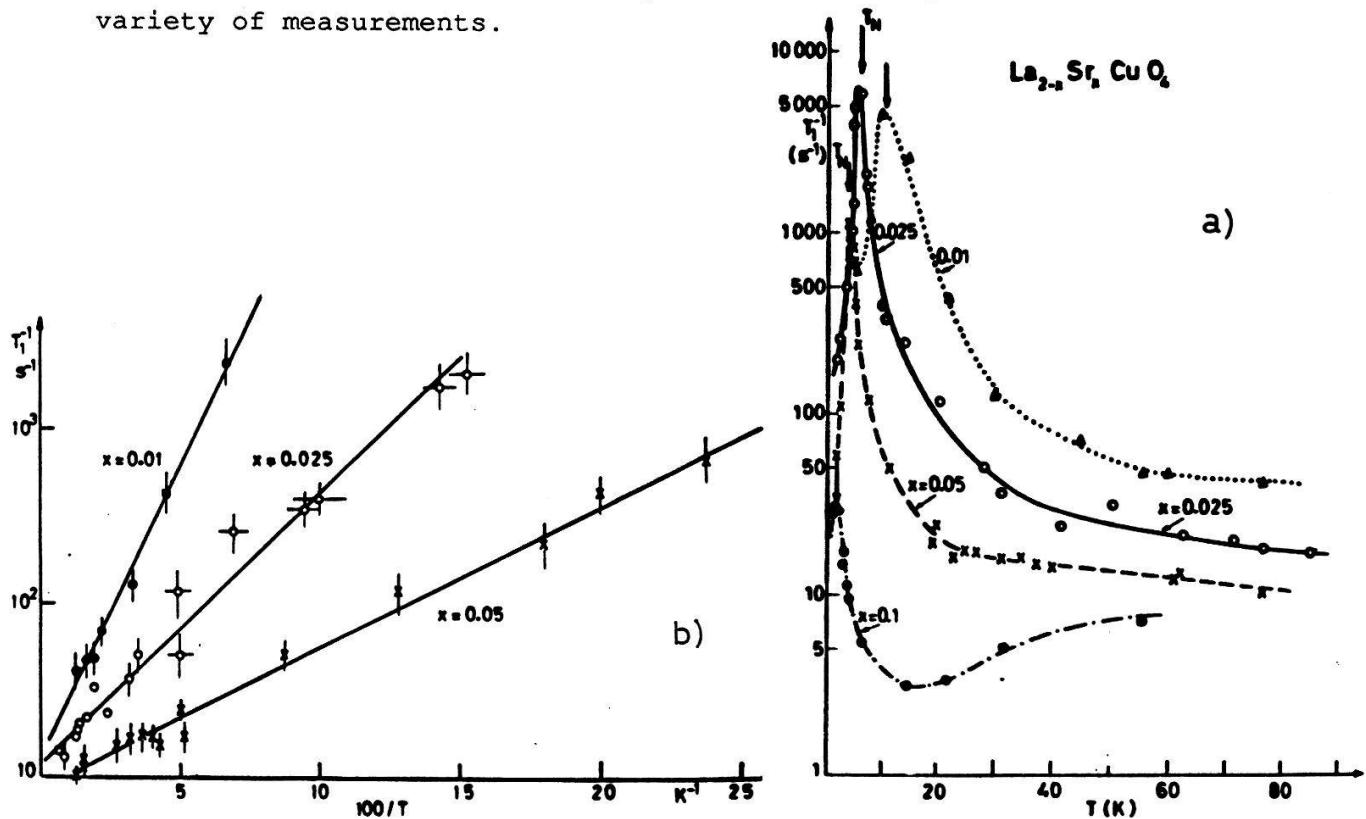


Fig.1 - (a) Temperature behaviours of the ^{139}La relaxation rates for different x in $\text{La}_{2-x} \text{Sr}_x \text{CuO}_4$. (b) Evaluation of the activation energy for ξ ; note that according to the interpretative model $T_1^{-1} \propto n^{-1} = \xi^2$

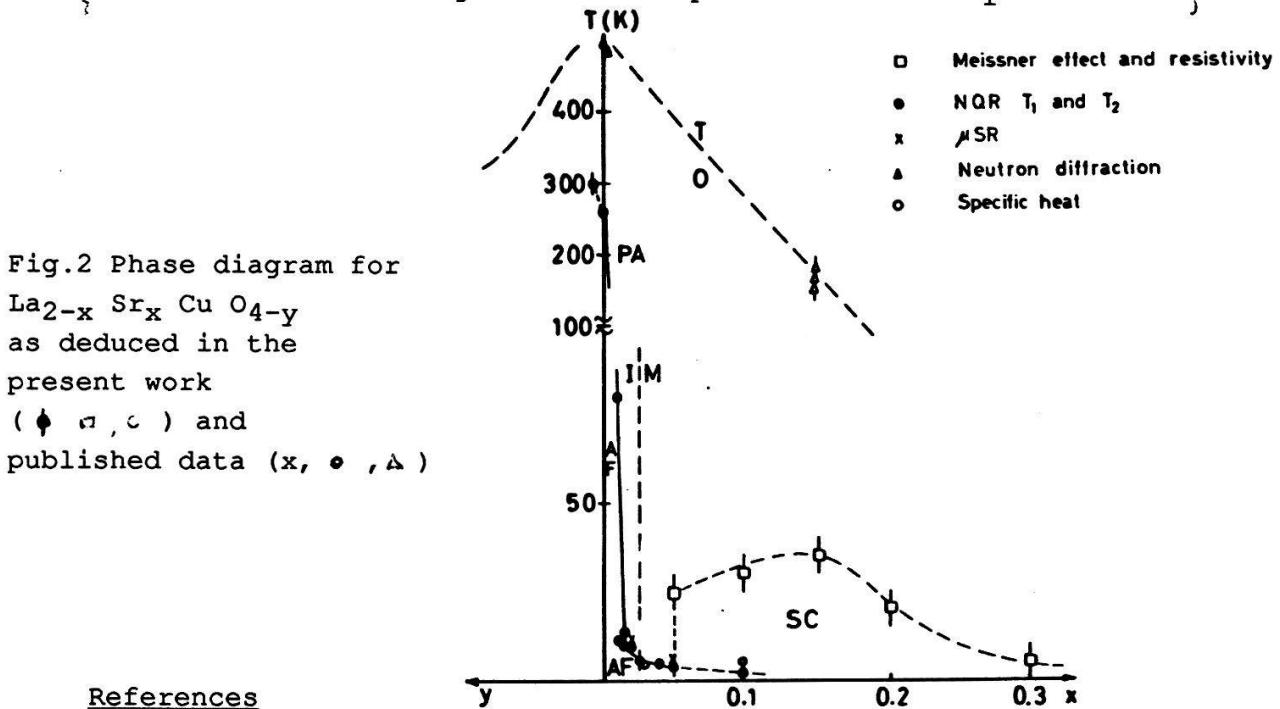


Fig.2 Phase diagram for $\text{La}_{2-x} \text{Sr}_x \text{CuO}_4-y$ as deduced in the present work ($\blacklozenge, \square, \circ$) and published data (\times, \bullet, Δ)

1. F.Borsa, M.Corti, T.Regia, A.Rigamonti, Nuovo Cimento D (in press)