

Electronic transport properties of FePS₃

Autor(en): **Grasso, V. / Neri, F. / Patanè, S.**

Objektyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **62 (1989)**

Heft 6-7

PDF erstellt am: **19.04.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116076>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

ELECTRONIC TRANSPORT PROPERTIES OF FePS_3

V. Grasso, F. Neri, S. Patanè, L. Silipigni

Istituto di Struttura della Materia, Università di Messina

Salita Sperone 31, P.O. Box 57, 98166 S. Agata - Messina, Italy.

M. Piacentini

Dipart. di Energetica, Università La Sapienza, 00185 Roma, Italy.

Abstract: a.c. and d.c. conductivity and photoconductivity measurements on FePS_3 compound have been carried out as a function of both temperature and frequency. The results, showing a semiconductor-like behaviour, have been interpreted on the basis of the so-called transition metal ion weakly interacting model.

1.-Introduction

FePS_3 belongs to the transition metal thiophosphates MPS_3 family, whose characteristic layered structure allows the intercalation of alkali ions or organic molecules in its Van der Waals gap. Due to its complex crystalline structure a complete band structure calculation is still lacking, although some semi-empirical models have been proposed. We have successfully interpreted the NiPS_3 and MnPS_3 electrical transport properties using a model in which the M-S interaction is weak and ionic in nature [1]. The aim of the present work is to obtain more detailed information on the electronic states energy distribution, through the interpretation, on the basis of the above model, of the d.c. and a.c conductivity and photconductivity measurements.

2.-Results and discussion

ac and dc conductivity and photoconductivity measurements as a function of both temperature and frequency have been carried out in a cryostat under high vacuum, using a phase detection technique.

Fig.1 shows the temperature dependence of both dark and photo conductivities. The σ_a curve is temperature activated with two different activation temperature energy values: 0.58 eV in the high

temperature range and 0.09 eV in the low temperature one. For Fe^{2+} ion the d^6 ground state configuration is $(t_{2g})^4(e_g)^2$ corresponding to a ${}^5T_{2g}$ state. On the basis of the M weakly interacting model [1] and not considering the d level substructure, we set the Fermi level on the Fe^{2+} d^6 ground state. As reported in the literature, FePS_3 behaves as a p-type material, just like NiPS_3 and MnPS_3 compounds [2,3]. Considering the 0.58 eV σ_a activation energy value we suggest, in analogy, that the conduction process is by holes and takes place in the $3p_z$ valence band. The small σ_a activation energy value, calculated in the low temperature region, may be due to a hopping conduction mechanism involving the 3d localized states. As shown in fig.1, the σ_p curve is temperature activated only in the high temperature region. On the basis of the selection rules for electric and magnetic dipole induced transitions and considering the 1.59 eV fundamental absorption edge value detected in FePS_3 [4], the 0.49 eV σ_p activation energy represents the energy separation between the $3p_x p_y$ and $3p_z$ bands, involving a recombination process, just like in NiPS_3 and MnPS_3 [2,3].

As shown in Fig. 2 ac conductivity σ_{ac} is almost linear dependent on frequency ($s=0.89$ in $\sigma_{ac}=A\omega^s$) and independent on temperature below about 400K. At higher temperatures a progressively stronger temperature dependence is observed. Such results are consistent with a semiconductor-like behaviour, supporting the conclusions drawn above for dc measurements.

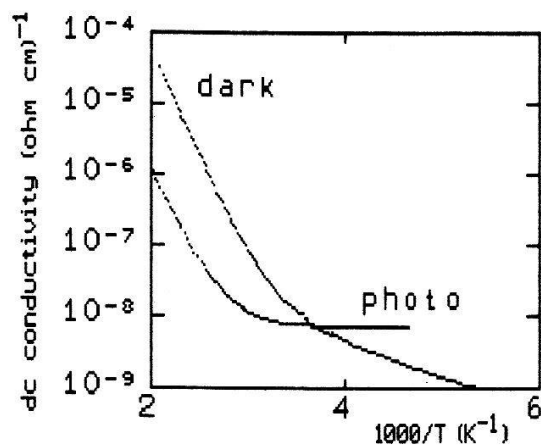


Fig. 1

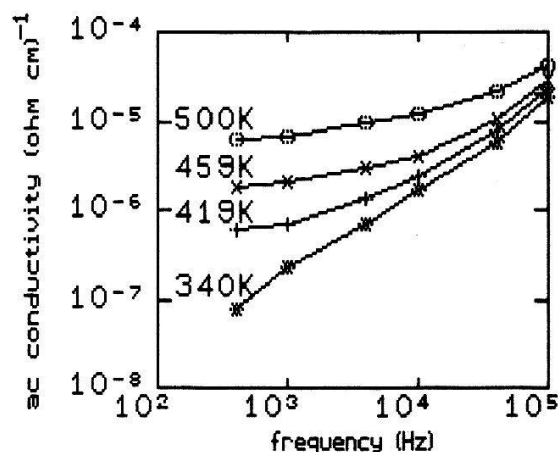


Fig. 2

3.- References

- [1] M. Piacentini et al., Chem. Phys **65**, 289 (1982)
- [2] V. Grasso et al., Phys. Rev. **B37**, 4419 (1988)
- [3] V. Grasso et al., J. Phys.: Condensed Matter (1989)
- [4] P.J.S. Foot et al., Mat. Res. Bull. **15**, 189 (1980)