

# **Dynamic magneto-optical study of the intermediate state, current-voltage characteristic**

Autor(en): **Dutoit, B. / Rinderer, L.**

Objekttyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **62 (1989)**

Heft 6-7

PDF erstellt am: **27.04.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116146>

## **Nutzungsbedingungen**

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

## **Haftungsausschluss**

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

## DYNAMIC MAGNETO-OPTICAL STUDY OF THE INTERMEDIATE STATE, CURRENT-VOLTAGE CHARACTERISTICS.

**B. Dutoit et L. Rinderer,** Institut de Physique Expérimentale, Université de Lausanne, CH-1015 Lausanne.

### Abstract.

Systematic measurements of current-voltage characteristics have been performed on superconducting samples in the intermediate state. Single crystalline lead plate samples were always of the same section but with different edges geometries. The magnetic field is normal to the plate. Our observations show that the current-voltages curves look is strongly dependant of the single crystal edge form, flux penetration and flux-flow mechanisms are different. With a single crystal with one sharp edge we can see different voltages depending of the current sense. These measurements are confirmed by optic dynamic observation of the magnetic flux in the sample.

### Methods.

The magneto-optical observation technique previously published (1) was used to make visual the motion of intermediate state structures in single crystalline plates of lead. These are prepared in a matrix made of two glass plates with stainless steel pieces cut in a way to obtain the required form. To avoid adherence, a carbon film is deposited with an alcohol flame on the surfaces in contact with the sample. Fused metal is injected in the matrix, who moves regular in a sharp temperature gradient of about  $20^{\circ}\text{C}$  centered on the fusion temperature.

The sample is directly placed in helium bath, in a way to have good thermal exchanges. It's a four wire electrical arrangement, a particular care has to be given to currents contacts to permit intensities to  $80 \text{ A}$  without excess heating. Voltage probes are gold electrodes  $15 \text{ mm}$  distant on the back face of the sample, a great care is necessary in wiring, to avoid voltage jumps due to field variations. Potential is measured with a Keithley 180 nanovoltmeter, and we disabled all filters. Acquisition is made with a real time VME bus system. A video recording of magnetics structures is simultaneously performed.

Three samples are compared in this paper: the first is of rectangular section  $3\text{mm}$  width and  $0.5 \text{ mm}$  thick. The second has one sharp edge as we can see on figure 1., the third has two sharp edges.

### Measurements.

After optical determination of the critical field, when all superconducting zones disappeared, a measurement of current-voltage characteristics is done for reduce fields from  $0.2$  to  $1$  with a step of  $0.1$ . We then obtain a graphic like the one of figure 2, where we see critical currents and flux-flow resistivities. The same

Geometry of the flux-flow in the sample

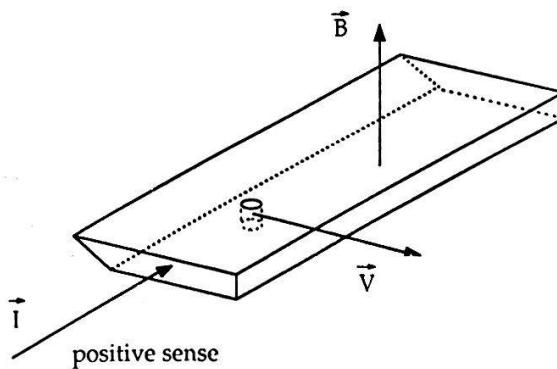


Figure 1.


measurements can be done for the two sense of current and field. Those are DC measurements, and each is made after a steady state is reached. Current, voltage, field and temperatures are recorded simultaneously.

### Observations.

It is interesting to remark that the critical current at flux-flow starting is very different with only the edge geometry changed. On figure 3, the first curve is the one of a normal sample with quadratic section. The second is for a sample with one sharp edge, as we see on figure 1, the flux penetrating the sample by the modified edge, we remark that currents densities are lightly lower. The next curve is from the same sample but with reverse current, we can see a drastic diminution of critical currents densities.

The last curve is the one of a sample with two sharp edges, and shows critical currents about 70% lower comparing to the normal sample. Magneto-optic observations shows a macroscopic shielding current flowing around the sample, influenced by the modifications done to the edges. The structure parameter is different depending of the flux coming thru a sharp edge or not.

Figure 2.

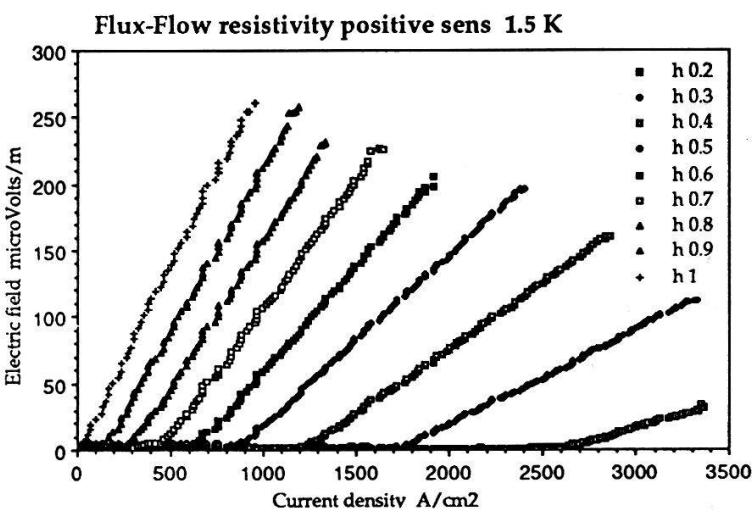

### Conclusions.

These measurements use samples where we tend to eliminate pinning effects, this is well shown by the quasi absence of a non linear part in the current-voltage characteristics. The only remaining pinning forces are those of surface, more precisely from the edges of the sample, and that is where we found the more significant effects. By modifying edges we also change the screening current, which has also a great importance on critical current.

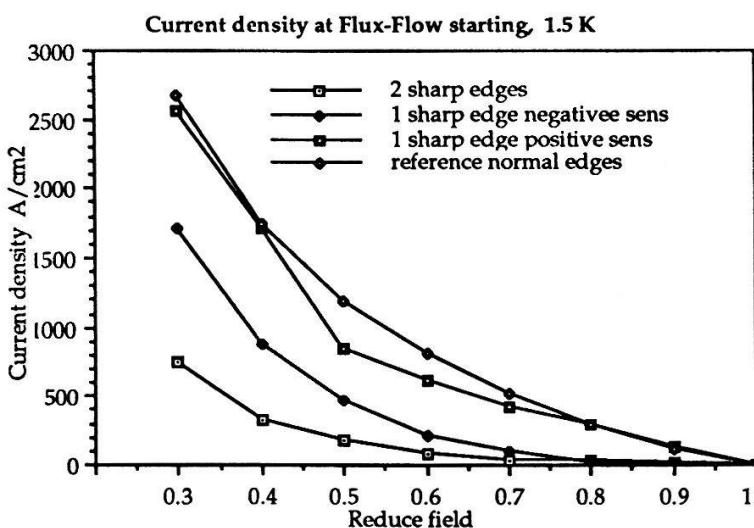


Figure 3.

We have to thank the Fond National Suisse pour la Recherche Scientifique who made us able to do these experiments.

(1) B. Dutoit & L. Rinderer HPACK vol 22 No 2/3 191 1989