

**Zeitschrift:** Archives des sciences [1948-1980]  
**Herausgeber:** Société de Physique et d'Histoire Naturelle de Genève  
**Band:** 14 (1961)  
**Heft:** 10: Colloque Ampère

**Artikel:** Measurements of nuclear magnetic relaxation in some vinyl polymers during the conversion process  
**Autor:** Bonera, G. / De Stefano, P. / Rigamonti, A.  
**DOI:** <https://doi.org/10.5169/seals-739646>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 10.08.2025

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

# Measurements of nuclear magnetic relaxation in some vinyl polymers during the conversion process

by G. BONERA, P. DE STEFANO and A. RIGAMONTI

Istituto di Fisica, Università di Pavia

---

It is well known that the N.M.R. techniques have been variously employed for studying the properties of polymers [1]. In particular some groups of researchers [2-9] have studied the line width, some [8, 10-13] have investigated the structure of the resonance line for those polymers in which amorphous and crystalline regions are present; some [3, 14-17] have studied how the line width varies when the polymer is subjected to temperature changes such as to induce transitions.

Other researchers [18] have measured the chemical shift of the resonance signal of some vinyl polymers and have been able to bring out small differences which the stereospecificity produces in the high resolution spectrum [19].

By means of spin-echo techniques it has been possible to measure the nuclear relaxation times of several polymers [20-23]; in particular the presence of more than one phase in the structure of some polymers has been demonstrated [22, 24, 25] by studying the return of the nuclear magnetization components to thermal equilibrium.

It can be seen that a great number of researchers have been concerned with the properties of polymers; very little attention has been however devoted to their formation process. We started a systematic investigation of the conversion process of some vinyl monomers into the corresponding polymers by measuring the nuclear relaxation times  $T_1$  and  $T_2$  with the technique of fast adiabatic passages. A study of the  $\gamma$  ray induced polymerization of ethyl acrylate has been performed by Shibata et al. [26] by means of line width measurements; we believe however that measurements of relaxation times are more significant and can give a clearer insight into the polymerization process.

The vinyl compounds we have hitherto studied are styrene, methyl-metacrylate and vinyl acetate. The mass polymerization of styrene and

of M.M.A. has been obtained either by keeping the sample at 90° C or by exposing it to ultraviolet light from a mercury-arc lamp, whereas the mass polymerization of vinyl acetate has been obtained without subjecting the sample to any particular treatment. It is well known that the polymers of these compounds are soluble in the corresponding monomer: the percent of polymer present in the syrup during the conversion process has been estimated from the increase of its refraction index measured using a standard sodium light refractometer [27].

The compounds we have studied have several non-equivalent protons and, in principle, should have different  $T_1$ 's. However the return of the magnetization to its equilibrium value, which we have studied with a method previously described [28], has been found exponential within experimental error. This means that the  $T_1$ 's of the various non-equivalent protons are little different from one another; we shall therefore speak of spin-lattice relaxation time  $T_1$  of the monomer. During the polymerization process however, we have observed two spin-lattice relaxation times  $T_1$  very different from one another. The existence of these two spin-lattice relaxation times has been revealed with the technique of adiabatic passages.

It is known [28] that if one performs two successive fast adiabatic passages through the resonance separated by an interval of time  $\tau$  between them, the height of the signal due to the second passage depends on  $\tau$ . It is possible to choose an interval of time  $\tau$  between the two passages such that the second signal is null; this happens for  $\tau = T_1 \ln 2$ .

If however two groups of protons having spin-lattice relaxation times  $T_{1l}$  and  $T_{1s}$  differing enough from one another are present in a sample, it is possible to choose such experimental conditions that the passage through the resonance is fast for the protons whose spin-lattice relaxation time  $T_{1l}$  is longer and it is slow for the protons whose spin-lattice relaxation time  $T_{1s}$  is shorter. Under these conditions the signal due to the second passage can never be made null. More precisely if  $\tau = T_{1l} \ln 2$  this signal has the shape of a dispersion signal: it is a slow passage signal due to the protons with the shorter relaxation time.

In figure 1 three recordings performed on a sample of styrene for three different values of  $\tau$  are reproduced; the percent of polymer in the syrup styrene-polystyrene was 30%.

By measuring the length of the time interval  $\tau$  for which the second signal is a dispersion signal it is possible to evaluate the spin-lattice relaxa-

tion time  $T_{1l}$ . One can see from figure 1 that such an evaluation can be made with a fair accuracy.

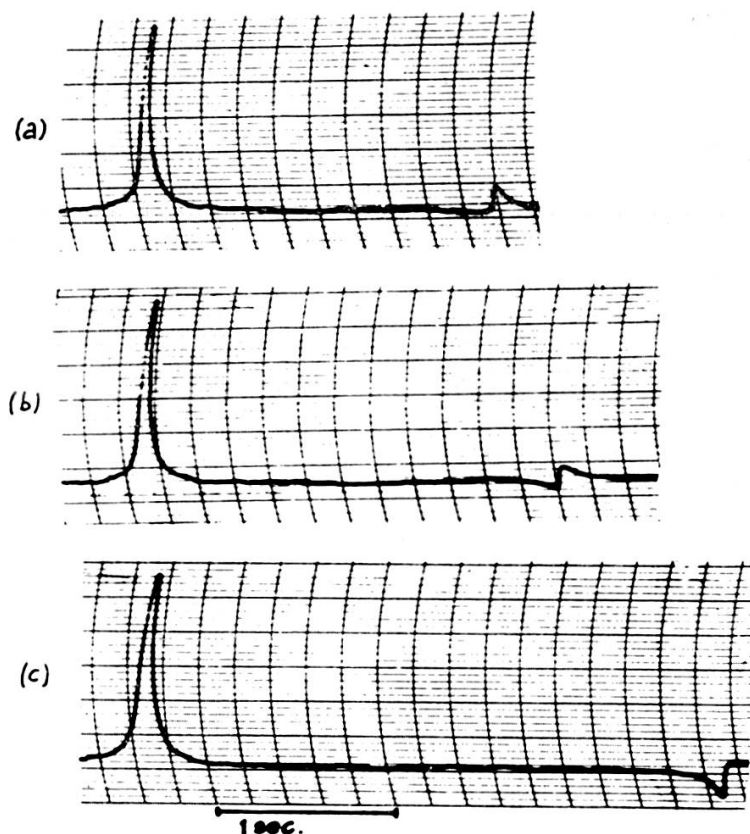


Fig. 1.

Three recordings obtained for a sample of styrene with 30% of polystyrene. In recording *a*) the time elapsed between the two adiabatic passages is  $\tau < T_{1l} \ln 2$ ; in recording *b*)  $\tau = T_{1l} \ln 2$  and in recording *c*)  $\tau > T_{1l} \ln 2$ .

An accurate enough measurement of the relaxation time  $T_{1s}$  is also possible. We choose the experimental conditions so that the passage through the resonance is fast with respect also to this relaxation time and then we perform a succession of passages so frequent that the signals due to the protons with relaxation time  $T_{1l}$  are practically cancelled out owing to a saturation effect. In these conditions we obtain a sequence of fast adiabatic passage signals relative to the protons with shorter relaxation time only. From such a sequence we are able to evaluate  $T_{1s}$  [29].

Considerations of a general character and the fact that the height of the dispersion signal increases with increasing concentration of polymer in the monomer-polymer syrup lead us to believe that the relaxation time

$T_{11}$  is to be attributed to the monomer protons and the time  $T_{11}$  to the polymer protons.

The experimental results we have obtained for the spin-lattice relaxation time  $T_{11}$  of styrene during polymerization are shown in figure 2 and 3. The polymerization, both the thermal one and that induced by ultraviolet rays, as well as the measurement of the relaxation times took place in presence of oxygen.

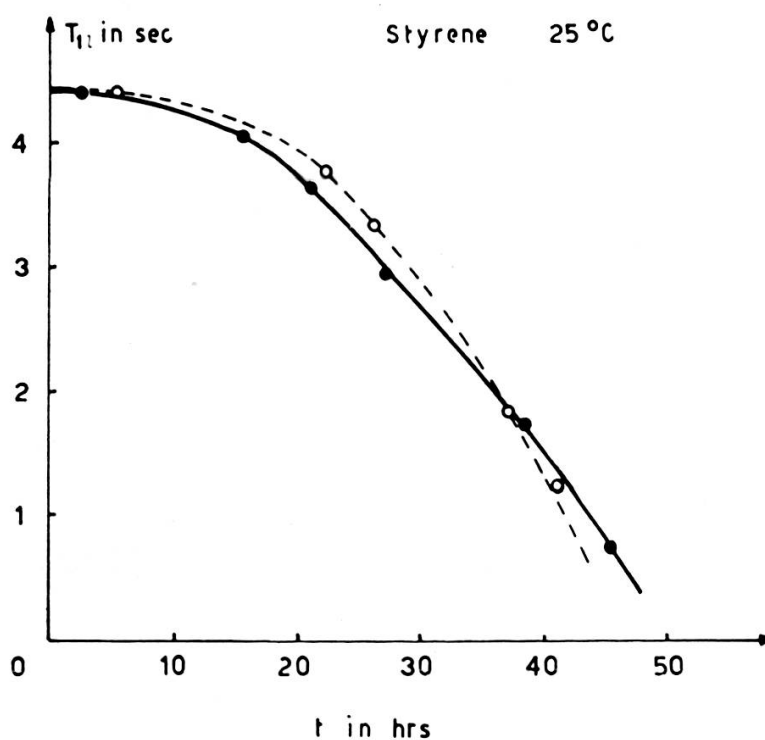


Fig. 2.

Spin-lattice relaxation time  $T_{11}$  for styrene vs. time  $t$  of duration of the thermal treatment (full line) and of the exposition to ultraviolet light (dashed line). The sample was kept continuously at 90° C and under ultraviolet exposition respectively, except the short interruptions necessary for the measurements.

The measurements were performed at 25° C.

In Table I the percent of polymer and the viscosity of the syrup during thermal polymerization of styrene are shown. For ultraviolet light induced polymerization only the percent of polymer is given: measurements of viscosity were occasionally performed and showed an increase of the viscosity of the syrup like that found during thermal polymerization.

From the results shown in Table I it is possible to see that the polymer concentration increases with time following an exponential law, in agree-

ment with the general assumptions about the polymerization kinetics one is allowed to make [30, 31], provided that a short inhibition period is taken into account. These results are consistent with those obtained by several researchers [27].

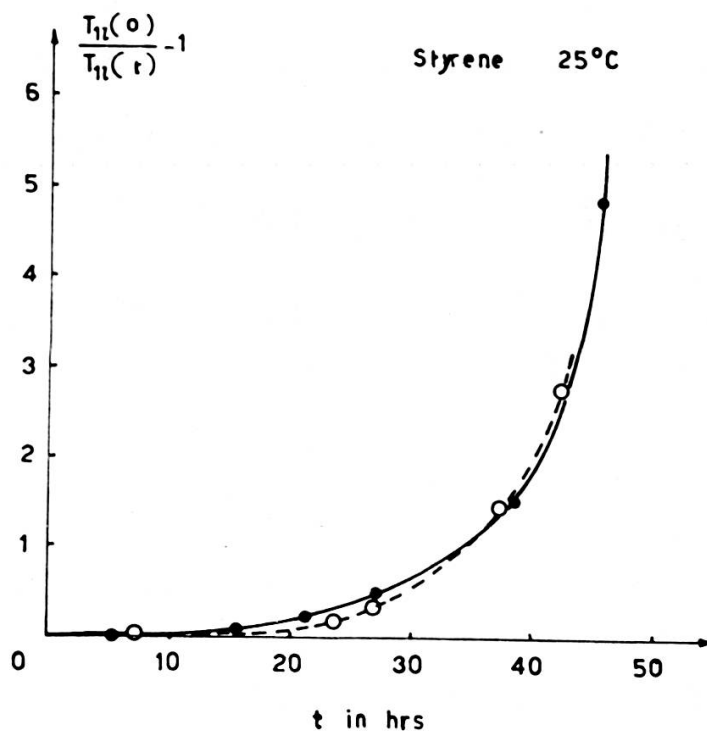


Fig. 3.

$T_{1l}(0)/T_{1l}(t) - 1$  vs. time  $t$  of duration of the thermal treatment (full line) and of the exposition to ultraviolet light (dashed line) for styrene.

TABLE I

Thermal polymerization			Ultraviolet induced polym.	
$t$ in hrs	%	$\eta$ in poises	$t$ in hrs	%
0	0	$0.73 \cdot 10^{-2}$	0	0
3	0	$0.73 \cdot 10^{-2}$	2	0
4.5	—	$22 \cdot 10^{-2}$	4	0
14.5	13	32	7	3
17.5	—	$\approx 60$	20	15
20	23	$\approx 200$	23.5	22
24	32		26.5	27.5
32	50		42.5	53
63	$\approx 90$			

We see that, during the first twenty hours of the process, the viscosity increases of several orders of magnitude, while the spin-lattice relaxation time  $T_{1l}$  decreases only slightly. It is not possible therefore to assume that during the polymerization process the spin-lattice relaxation time  $T_{1l}$  decreases with the increasing of viscosity following a law of the form  $T_{1l} \propto \frac{k}{\eta}$ , as required by the theory of B.P.P. [32]. We may say that the monomer molecules although trapped among the polymer chains retain most of their degrees of freedom.

The polymerization of M.M.A. was induced by ultraviolet light and took place in vacuo: in fact oxygen strongly inhibits this polymerization. The spin-lattice relaxation time of the M.M.A. monomer at the beginning of the conversion process was 7,2 sec.; after a 120 hour exposition to ultraviolet light it had decreased to 0,5 sec.

The dependence of  $T_{1l}(0)/T_{1l}(t) - 1$  on the exposition time is similar to that already discussed for styrene.

As regards the vinyl acetate we have so far studied only its polymerization at room conditions and in the absence of atmospheric oxygen. The time necessary for this polymerization has been several months: the plot of  $T_{1l}$  vs.  $t$  is shown in figure 4.

Measurements of spin-spin relaxation time  $T_2$  [33] were occasionally performed for all three the compounds only at low percentages of polymer: the  $T_2$  we measured is relative to the protons with longer  $T_1$  only and was found to be in general little different from the corresponding  $T_{1l}$ .

As regards the shorter spin-lattice relaxation time, which we attributed to the polymer protons, accurate enough measurements were possible only for high concentrations of polymer. Because of the experimental error, which is still very large, the values we have obtained are only indicative.

For a sample of styrene with 60% of polymer we found  $T_{1s} = 3 \cdot 10^{-2}$  sec. For a sample of M.M.A. with 50% of polymer we obtained  $T_{1s} = 1,8 \cdot 10^{-2}$  sec. As the polymerization proceeded these values have been decreasing slightly.

As to the vinyl acetate we found  $T_{1s} = 19 \cdot 10^{-2}$  sec. 117 days after the beginning of the polymerization; after 8 more days we found  $T_{1s} = 5 \cdot 10^{-2}$  sec.

These values we found for  $T_{1s}$  seem to us to be larger than those one would expect from considering the size of the polymer chains and the very high values of the viscosity. It must therefore be admitted that also at very high polymer concentrations some hindered motions of the chains are possible.

The results hitherto obtained seem to point out that measurements of nuclear relaxation can give new information for a microscopic interpretation of the polymerization process. Besides the measurement of the nuclear relaxation times seems to be more effective than the measurement of the line width of the resonance signal.

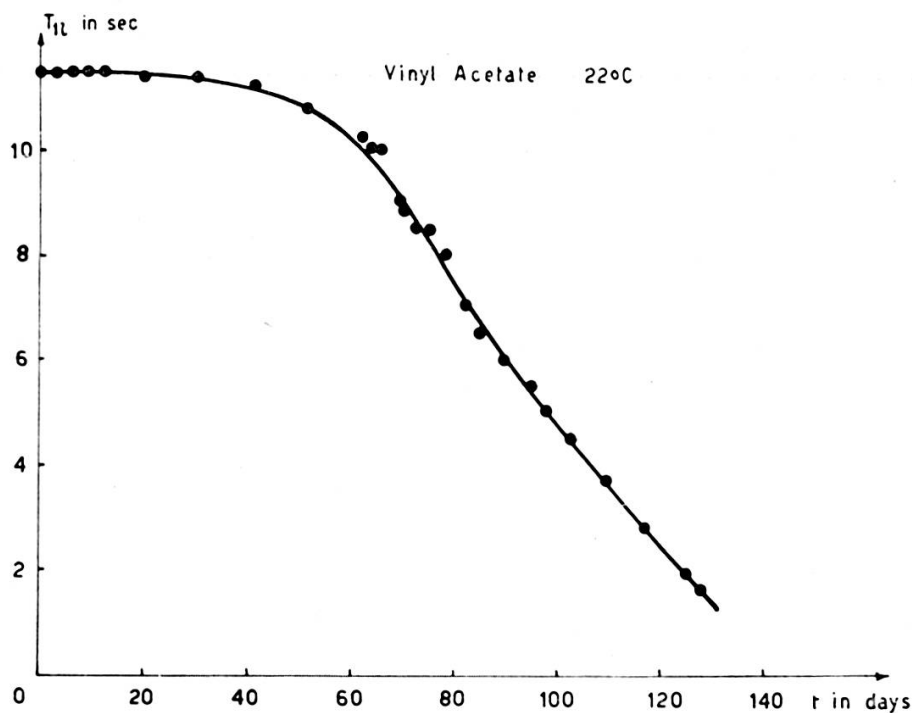


Fig. 4.

Spin-lattice relaxation time  $T_{1l}$  for oxygen-free vinyl acetate vs. time  $t$  elapsed from the beginning of the polymerization process.

The AA are grateful to Prof. L. Giulotto for the interest he has shown in this work and for his useful suggestions.

They thank the Consiglio Nazionale delle Ricerche, which with its financial aid has made it possible to undertake this research.

#### BIBLIOGRAPHY

1. POWLES, J. G., *Polymer*, **1**, 219, 1960.
2. ALPERT, N. L., *Phys. Rev.*, **75**, 398, 1949.
3. HONNOLD, V. R., F. McCaffrey and B. A. Mrowca, *Phys. Rev.*, **94**, 1414, 1954.



4. POWLES, J. G., *J. Polym. Sci.*, **22**, 79, 1956.
  5. COLLINS, R. L., *Bull. Amer. Phys. Soc.*, **2**, 103, 1957.
  6. —, *J. Polym. Sci.*, **27**, 67, 1958.
  7. POWLES, J. G. and J. A. E. KAIL, *J. Polym. Sci.*, **31**, 1183, 1958.
  8. REMPEL, R. C., H. E. WEAVER, R. H. SANDS, R. L. MILLER, *Jour. Appl. Phys.*, **28**, 1082, 1957.
  9. SLICHTER, W. P. and E. R. MANDELL, *Journ. Appl. Phys.*, **30**, 1473, 1959.
  10. WILSON, C. W. and G. E. PAKE, *J. Polym. Sci.*, **10**, 503, 1953.
  11. COLLINS, R. L., *Bull. Amer. Phys. Soc.*, **1**, 216, 1956.
  12. FUSCHILLO, N., E. RHIAN and J. A. SAUER, *J. Polym. Sci.*, **25**, 381, 1957.
  13. WILSON, C. W. and G. E. PAKE, *J. Chem. Phys.*, **27**, 115, 1957.
  14. HOLROYD, L. V., R. S. CODRINGTON, R. S. MROWCA and E. GUTH, *J. Appl. Phys.*, **22**, 696, 1951.
  15. ODAYIMA, A., J. SOHMA and M. J. KOIKE, *J. Chem. Phys.*, **23**, 1959, 1955.
  16. BANAS, E. M. and B. A. MROWCA, *Phys. Rev.*, **98**, 1548, 1955.
  17. SAUER, J. A. and A. E. WOODWARD, *Rev. Mod. Phys.* **33**, 88, 1960.
  18. BOVEY, F. A., G. V. D. TIERS and G. FILIPOVICH, *J. Polym. Sci.*, **38**, 73, 1959.
  19. KERN, R. J. and J. V. PARTINGER, *Nature*, **185**, 236, 1960.
  20. LOWE, I. J., L. O. BOWEN and R. E. NORBERG, *Phys. Rev.*, **100**, 1243, 1955.
  21. NOLLE, A. W., *Phys. Rev.*, **98**, 1560, 1955.
  22. MCCALL, P. W., D. C. DOUGLASS and E. W. ANDERSON, *J. Chem. Phys.*, **30**, 1272, 1959.
  23. POWLES, J. G. and A. HARTLAND, *Nature*, **186**, 26, 1960.
  24. WILSON, C. W. and G. E. PAKE, *Phys. Rev.*, **89**, 896, 1953.
  25. POWLES, J. G. and K. LUSZCZYNSKI, *Physica's Grav.*, **25**, 455, 1959.
  26. SHIBATA, S., I. KIMURA and T. SINTA, *J. Phys. Soc. Japan*, **13**, 1546, 1958.
  27. SCHILDKNECHT, C. E., Vinyl and related polymers, Wiley & Sons, 1952.
  28. BONERA, G., P. L. CHIODI, G. LANZI and A. RIGAMONTI, *Nuovo Cimento*, **17**, 198, 1960.
  29. CHIAROTTI, G., G. CRISTIANI, L. GIULOTTO and G. LANZI, *Nuovo Cimento*, **12**, 519, 1954.
  30. D'ALELIO, G. F., Fundamental Principles of polymerization, Wiley & Sons, 1952.
  31. CHARLESBY, A., Atomic Radiation and Polimers, Pergamon Press, 1960.
  32. BLOEMBERGEN, N., E. M. PURCELL and R. V. POUND, *Phys. Rev.*, **73**, 679, 1948.
  33. BONERA, G., P. L. CHIODI, L. GIULOTTO, G. LANZI, *Nuovo Cimento*, **14**, 119, 1959.
-