

**Zeitschrift:** Archives des sciences et compte rendu des séances de la Société  
**Herausgeber:** Société de Physique et d'Histoire Naturelle de Genève  
**Band:** 55 (2002)  
**Heft:** 1

**Artikel:** Radovanite,  $\text{Cu}_2\text{Fe}^{+3}(\text{As}^{+5}\text{O}_4)(\text{As}^{+3}\text{O}_2\text{OH}_2)_2\text{H}_2\text{O}$ , a new mineral : its description and crystal structure  
**Autor:** Sarp, Halil / Guenee, Laure  
**DOI:** <https://doi.org/10.5169/seals-740292>

### Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 04.08.2025

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

Archs Sci. Genève	Vol. 55	Fasc. 1	pp. 47-55	Juin 2002
-------------------	---------	---------	-----------	-----------

# RADOVANITE, $\text{Cu}_2\text{Fe}^{+3}(\text{As}^{+5}\text{O}_4)(\text{As}^{+3}\text{O}_2\text{OH})_2\text{H}_2\text{O}$ , A NEW MINERAL: ITS DESCRIPTION AND CRYSTAL STRUCTURE

BY

**Halil SARP<sup>1</sup> & Laure GUENEE<sup>2</sup>**

(Ms. received 5.4.2002, accepted 30.5.2002)

## ABSTRACT

**Radovanite,  $\text{Cu}_2\text{Fe}^{+3}(\text{As}^{+5}\text{O}_4)(\text{As}^{+3}\text{O}_2\text{OH})_2\text{H}_2\text{O}$ , a new mineral: its description and crystal structure.** - Radovanite,  $\text{Cu}_2\text{Fe}^{+3}(\text{As}^{+5}\text{O}_4)(\text{As}^{+3}\text{O}_2\text{OH})_2\text{H}_2\text{O}$ , occurs at the old copper mines of Roua (Alpes-Maritimes, France), associated with cuprite, native copper, malachite, trippkeite, olivenite and al-godonite. It forms aggregates (2mm in diameter) formed by small equidimensional crystals or slightly elongated crystals along a or b (0.15 x 0.08 x 0.02 mm maximum dimension). The megascopic color is green pistachio. The mineral is not twinned and has no cleavage. It is orthorhombic, Pnma,  $a=9.585(1)$ ,  $b=13.143(1)$ ,  $c=8.0884(7)$  Å,  $V=1018.9(2)$  Å<sup>3</sup>,  $Z=4$ ,  $d_{\text{meas}}=3.9(1)$  and  $d_{\text{calc}}=3.83(1)$  g/cm<sup>3</sup>. The strongest lines in the X-ray powder diffraction pattern ( $d_{\text{obs}}$  in Å, (hkl),  $I_{\text{vis}}$ ) are : 6.88, (011), 25; 6.179, (101), 90; 3.241, (122), 40; 3.090, (202), 100; 2.710, (240) (321), 25; 2.214, (251) (223), 25. Mohs' hardness could not be measured because of the small grain size. Luster is vitreous transparent, streak is green; crystals are biaxial (-) with  $\alpha=1.80(1)$ ,  $\beta=1.84(1)$ .  $\gamma=1.86(1)$  at 589 nm;  $2V_{\text{obs}}=65(5)^\circ$ ,  $2V_{\text{calc}}=70(3)^\circ$ . It is pleochroic with  $\gamma$  = green pistachio,  $\beta$  = yellow green,  $\alpha$  = light green to colorless. The optical orientation is  $a=\beta$ ,  $b=\gamma$  and  $c=\alpha$ . The crystal structure was solved by direct methods (MoK $\alpha$  radiation) and refined using 1027 observed unique reflections to  $R=0.059$ ,  $R_w=0.023$ . The structure of radovanite is formed by a three-dimensional network formed by pairs of edge-sharing  $\text{CuO}_5$  square pyramids and  $\text{FeO}_6$  octahedra interconnected by  $\text{AsO}_4$  tetrahedra and  $\text{AsO}_3$  triangles. The water molecule is fixed in a structure cavity by hydrogen bonds of its two hydrogen atoms and of the OH group which is shared between the  $\text{CuO}_5$  square pyramid and  $\text{AsO}_3$  triangle.

**Key-words:** radovanite, new mineral, powder pattern, crystal structure, arsenate-arsenite, copper, iron, hydrogen bonding.

## INTRODUCTION

Radovanite,  $\text{Cu}_2\text{Fe}^{+3}(\text{As}^{+5}\text{O}_4)(\text{As}^{+3}\text{O}_2\text{OH})_2\text{H}_2\text{O}$ , is a new mineral discovered in samples collected by Danielle Mari, Gilbert Mari and Pierre Rolland in the old copper mines of Roua, which are situated in the northwestern part of the Alpes-Maritimes department (France).

The mineral name honours Dr. Radovan Černý, crystallographer at the University of Geneva, Switzerland.

<sup>1</sup> Département de Minéralogie du Muséum d'histoire naturelle de la Ville de Genève, 1, route de Malagnou, CP 6434, CH-1211 Genève 6, Suisse.

<sup>2</sup> Laboratoire de Cristallographie, Université de Genève, 24 quai Ernest-Ansermet, CH-1211 Genève 4, Suisse.

The mineral and mineral name have been approved by the Commission on New Minerals and Mineral Names of the International Mineralogical Association.

The type material is preserved in the Department of Mineralogy of the Natural History Museum of Geneva, Switzerland, under reference no. 478.004.

## OCCURRENCE

The new mineral described occurs in the Roua copper deposits in the upper part of the Var valley (the Daluis gorge) at the western margin of the Barrot Dome. The metallogeny and geology of this Dome have been studied by VINCHON (1984) and MARI (1992). In the Roua ore deposit, the cupriferous mineralisation is hosted in a gangue formed by dolomite, calcite and aragonite, and consists of native copper, cuprite, domeykite, algodonite, koutekite, native gold and native silver. Detailed mineralogical study of this ore deposit produced several secondary, rare and unknown mineral species (SARP *et al.*, 1999, 2000, 2001). The new mineral described here forms aggregates, associated with cuprite, native copper, malachite, trippkeite, olivenite and algodonite.

## PHYSICAL AND OPTICAL PROPERTIES

Radovanite occurs as aggregates of maximum size 2 mm in diameter, which are formed by small equidimensional crystals or slightly elongated crystals along a or b of maximum size 0.15 x 0.08 x 0.02 mm (Fig.1). The most developed forms are (101), (011), (001), (010), (hk0) and (hkl). The mineral is not twinned and has no cleavage. The crystals are green pistachio, transparent, with vitreous luster and green streak. The mineral is brittle with conchoidal fracture. The Mohs' hardness could not be measured. The density measured by flotation in heavy liquid, is 3.9(1) g/cm<sup>3</sup> and the calculated density is 3.83(1) g/cm<sup>3</sup> (based on the ideal formula) and 3.79(1) g/cm<sup>3</sup> (based on the empirical formula). The mineral is very slowly soluble in HCl. It is nonfluorescent and has medium pleochroism:  $\gamma$  = green pistachio,  $\beta$  = yellow green,  $\alpha$  = light green to colorless. Radovanite is biaxial negative, with  $\alpha = 1.80(1)$ ,  $\beta = 1.84(1)$ ,  $\gamma = 1.86(1)$  (determined at 589 nm),  $2V_{\text{obs}} = 65(5)^\circ$  and  $2V_{\text{calc}} = 70(3)^\circ$ .

The index of refraction  $\gamma$  had to be measured rapidly due to the fact that the mineral is attacked by Cargille's liquids of refractive index  $> 1.84$ . The optical orientation is:  $a = \beta$ ,  $b = \gamma$ ,  $c = \alpha$ .

## CHEMICAL COMPOSITION

Crystals of radovanite were chemically analysed with a Cameca electron microprobe, using a beam size of 12  $\mu\text{m}$ , an operating voltage of 15kV, and a beam current of 30 nA. Qualitative examination showed only Cu, As, Fe, Al and P. For quantitative analysis, FeAsS (Fe,As), CuO (Cu), pyroxene (Al) and apatite (P) were used as standards.

The results are given in Table I. The H<sub>2</sub>O content was estimated by difference due to insufficient sample. The empirical formula based on 11 oxygen atoms is:  $\text{Cu}_{1.93}\text{Fe}^{+3}_{0.92}\text{Al}_{0.01}\text{P}_{0.02}\text{As}^{+5}_{1.01}\text{As}^{+3}_{2.01}\text{H}_{4.15}\text{O}_{11}$  and the idealized formula,  $\text{Cu}_2\text{Fe}^{+3}$

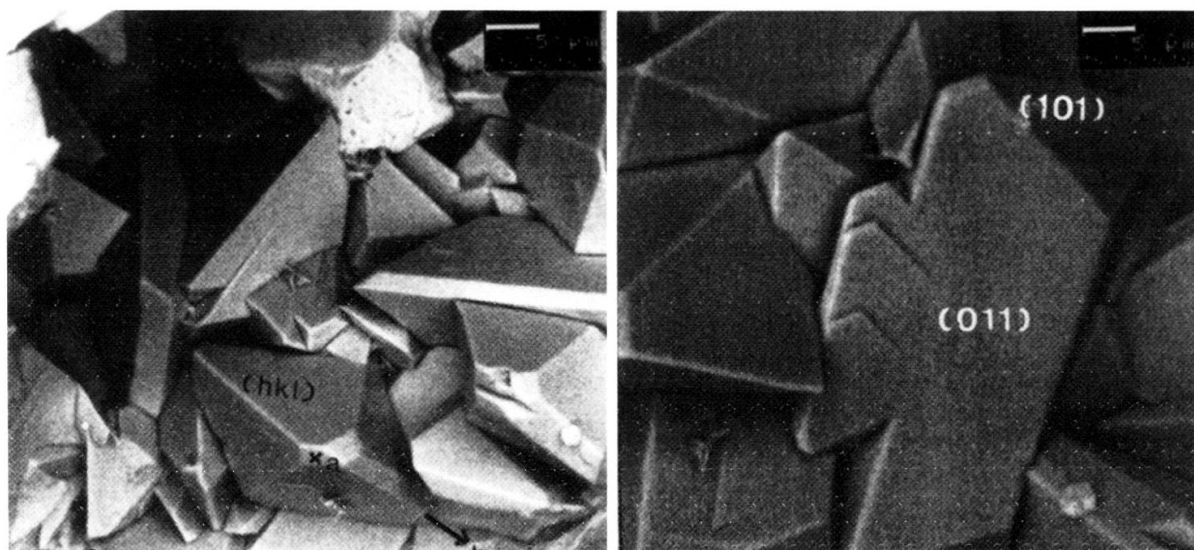


FIG. 1.

SEM images of radovanite crystals, a) equidimensional crystals, b) elongated crystals along a axis.

$(\text{As}^{+5}\text{O}_4) [\text{As}^{+3}\text{O}_2(\text{OH})]_2\text{H}_2\text{O}$ , was confirmed by structure determination. In some crystals, the  $\text{Al}_2\text{O}_3$  content increases and there is a replacement between  $\text{Fe}^{+3}$  and Al giving the following formula:  $\text{Cu}_2(\text{Fe}^{+3}_{0.5}\text{Al}_{0.5})(\text{As}^{+5}\text{O}_4)(\text{As}^{+3}\text{O}_2\text{OH})_2\text{H}_2\text{O}$ . This last formula will represent radovanite-Al. The only ferrous end-member has been studied in detail.

The Gladstone-Dale constants of MANDARINO (1981) along with the oxide proportions, determined from the electron-microprobe data and from the crystal structure, lead to identical Kc values of 0.220. The value of Kp, calculated using the average index of refraction (1.833), and the calculated density from the empirical formula, is 0.220. For the same average index of refraction and the calculated density from the idealized formula, Kp is 0.217. The compatibility index is 0.000 for the empirical formula, and 0.014 for the idealized formula, indicating superior compatibility index (MANDARINO, 1981) between the physical and chemical data.

TABLE I. Chemical analysis [wt.%] of radovanite.

		Average of 4 analyses	Range of 4 analyses	Standard deviation	Ideal formula
Fe (8.9)	CuO	26.3	24.5 – 27.2	1.0	27.08
			8.8 – 9.0	0.3	
	$\text{Fe}_2\text{O}_3^*$	12.7			13.59
	$\text{Al}_2\text{O}_3$	0.04	0.03 – 0.04		
As (39.0)	$\text{P}_2\text{O}_5$	0.3	0.2 – 0.3		
			38.7 – 39.3	0.4	
	$\text{As}_2\text{O}_5^{**}$	19.93			19.55
	$\text{As}_2\text{O}_3^{**}$	34.32			33.66
	$\text{H}_2\text{O}^{***}$	6.41			6.12

\* In the structure, Fe is +3

\*\* Calculated in relation with structural formula

\*\*\* By difference

TABLE II. X-ray powder diffraction data for radovanite (d in Å)

(hkl)	d(calc.)	d(obs.)	I(vis.)	(hkl)	d(calc.)	d(obs.)	I(vis.)
011	6.889	6.88	25	240	2.710	2.710	25
020	6.572	6.56	10				
101	6.182	6.179	90	321	2.708		
111	5.594	5.585	<5	042	2.550	2.551	20
200	4.793	4.789	5	302	2.507	2.510	<5
201	4.123	4.119	5	400	2.396	2.395	5
002	4.044	4.041	<5	251	2.217	2.214	25
211	3.934	3.924	<5				
220	3.872	3.871	20	223	2.213		
102	3.726	3.725	5	060	2.191	2.190	<5
112	3.585	3.584	5	152	2.148	2.148	5
221	3.493	3.489	<5	162	1.888	1.890	5
022	3.444	3.443	<<5	432	1.865	1.864	5
122	3.241	3.241	40				
202	3.091	3.090	100	501	1.865		
301	2.972	2.973	5	253	1.752	1.751	10
141	2.901	2.897	15	502	1.732	1.733	5
				452	1.622	1.621	10
311	2.898						

## X-RAY CRYSTALLOGRAPHY

Powder-diffraction data (Table II) were obtained using a Gandolfi camera (114.6 mm in diameter, Ni-filtered  $\text{CuK}\alpha$  radiation). The relative intensities of the reflections were estimated visually. A single-crystal of radovanite, 0.038 x 0.031 x 0.019 mm in size, was examined by the precession method (Ni-filtered  $\text{CuK}\alpha$ ) and the same crystal was measured on a Stoe IPDS diffractometer with monochromatized  $\text{MoK}\alpha$  radiation and image plate detector in  $\varphi$ -oscillation scanning-mode with limits  $-11 < h < 11$ ,  $-16 < k < 13$ ,  $-9 < l < 9$ . A total of 4818 reflections (1027 unique,  $R_{\text{int}} = 0.085$ ) was measured up to  $\Theta = 25.6^\circ$ . Lattice parameters were refined on the basis of 2000 reflections with  $3^\circ < \Theta < 25.5^\circ$ :  $a = 9.585(1)$ ,  $b = 13.143(1)$ ,  $c = 8.0884(7)$  Å,  $V = 1018.9(2)$  Å<sup>3</sup>,  $a : b : c = 0.7293 : 1 : 0.6154$ . Data reduction and analytical absorption correction were done using the program X-RED (STOE & CIE, 1999). The structure was solved in the space group  $\text{Pnma}$  by direct methods with program GENTAN from the *Xtal3.7* package (HALL *et al.*, 2000), and refined on  $F^2$  (without hydrogen atoms) with program LSLS from the *Xtal3.7* package using all 1027 unique reflections weighted  $1/\sigma^2$ . The refinement converged to  $R = 0.059$ ,  $R_w = 0.023$  and  $Goof = 0.81$  with 86 parameters, including anisotropic-displacement parameters of all atoms. The largest residuals in the difference-Fourier map were  $-1.87$  and  $1.88$  e/Å<sup>3</sup>.

## CRYSTAL STRUCTURE

Atom coordinates, standardized by the program STRUCTURE TIDY (GELATO & PARTHE, 1987), and equivalent isotropic-displacement parameters for non-hydrogen atoms are given in Table III, and a list of selected interatomic distances is given in Table IV. The structural projections along three crystallographic axes are given in the Fig. 2.

TABLE III. Atom positions and displacement parameters for radovanite.

Atom	x	y	z	$U_{eq}$ (Å <sup>2</sup> )
Cu	0.2535(1)	0.13718(9)	0.7512(2)	0.0142(5)
Fe	0	0	1/2	0.0083(9)
As1	0.0095(2)	1/4	0.5392(2)	0.0070(6)
As2	0.29252(9)	0.06939(8)	0.3001(1)	0.0123(4)
O1	0.0039(8)	0.1455(5)	0.4230(7)	0.013(3)
O2	0.1147(6)	0.0308(4)	0.702(1)	0.012(3)
O3	0.3248(6)	0.0264(5)	0.8747(9)	0.017(4)
O4 - OH	0.3997(7)	0.0814(6)	0.483(1)	0.026(4)
O5	0.3806(8)	1/4	0.818(2)	0.018(6)
O6 - H <sub>2</sub> O	0.078(1)	1/4	0.024(2)	0.035(7)
O7	0.1653(8)	1/4	0.635(1)	0.011(5)

The equivalent isotropic atomic displacement parameters are expressed as  $U_{eq} = (1/3)\sum_i \sum_j U_{ij} a_i^* a_j^* a_i \cdot a_j$ .

TABLE IV. Selected interatomic distances (Å) for radovanite.

Cu-O3	1.894(7)	Fe-O3	1.992(6)
Cu-O7	1.947(6)	Fe-O3	1.992(6)
Cu-O2	1.969(6)	Fe-O1	2.012(6)
Cu-O5	1.994(6)	Fe-O1	2.012(6)
Cu-O4	2.683(8)	Fe-O2	2.013(7)
		Fe-O2	2.013(7)
As1-O1	1.665(6)		
As1-O1	1.665(6)	As2-O2	1.775(6)
As1-O7	1.684(9)	As2-O3	1.793(7)
As1-O5	1.69(1)	As2-O4	1.810(7)
Range of edges within CuO <sub>5</sub> square pyramid:		2.450(9) - 3.51(1)	
Range of edges within FeO <sub>6</sub> octahedron:		2.774(9) - 2.917(9)	
Range of edges within As1O <sub>4</sub> tetrahedron:		2.69(1) - 2.77(1)	
Range of edges within As2O <sub>3</sub> triangle:		2.450(9) - 2.722(9)	
O4...O6	2.80(1)	O6...O4	2.80(1)

Atom coordination and bond valences were analysed by the program IVTON (BALIC ZUNIC & VICKOVIC, 1996). There are one Cu, one Fe and two As sites in the structure. The geometry of polyhedral coordination around Cu is a square pyramid, around Fe an octahedron, around As1 a tetrahedron, and around As2 a triangle. No hydrogen atoms were detected in the difference-Fourier map, therefore the concept of bond valences (BROWN & KANG KUN WU, 1976) was used to locate the hydrogen bonds. The data of BRESE & O'KEEFFE (1991) were used to calculate the bond valences for all non-hydrogen atoms (see Table V). Valence sums for cations are in good agreement with their corresponding ionic charges. The sum for O6 (0) indicates the presence of a water molecule not included in the coordination of cations. The sum for O4 (1.02) indicates the presence of OH group. The sums for all other oxygen atoms range from 1.83 to 2.21, thus



TABLE V. Bond valence (vu) table for radovanite.

	Cu	Fe	As1	As2	H1	H2	H3 <sup>a</sup>	H3 <sup>b</sup>	$\Sigma_{\text{excluding H's}}$	$\Sigma_{\text{including H'}}$
O1		2 x 0.51	2 x 1.32						1.83	1.83
O2	0.46	2 x 0.50		1.04					2.00	2.00
O3	0.56	2 x 0.53		0.99					2.08	2.08
O4-OH a	0.07			0.95	0.20		0.80		1.02	2.02
O4-OH b	0.07			0.95			0.20	0.80	1.02	2.02
O5	0.43 x 2		1.23						2.09	2.09
O6-H2O					0.80	1		0.20	0	2.00
O7	0.48 x 2		1.25						2.21	2.21
$\Sigma$	2.00	3.08	5.12	2.98	1	1	1			

The bond valences for hydrogen atoms were fixed to 1.

Left and right multipliers refer to equivalent bonds for cations and oxygens, respectively.

indicating that they probably do not act as proton acceptors in  $\text{H}\cdots\text{O}$  bonds. This result and the analysis of interatomic distances between oxygen atoms show that possible hydrogen bonds can occur only between O6 and O4 atoms. However, it would mean two hydrogen bonds between two oxygen atoms. We therefore prefer a model where one hydrogen atom does not participate in any hydrogen bond. Based on the dependence of  $\text{H}\cdots\text{O}$  bond valence on  $\text{O}\cdots\text{O}$  distance (assuming stretched  $\text{O}-\text{H}\cdots\text{O}$  bond angles) according to BROWN & ALTERMATT (1985) we propose in Table V possible hydrogen bonds. The water molecule oxygen O6 and the hydroxyl group oxygen O4 each yield one  $\text{O}-\text{H}$  and accept one  $\text{H}\cdots\text{O}$  bond. The hydrogen bonds form a zig-zag chain along b-axis (see Fig. 2a,2c). This model requires that the true symmetry of the structure is lower, when the hydrogen atoms are included, which stays to be confirmed. The second hydrogen of the water molecule is not localized in this model, which again stays to be confirmed. The most probable candidate as an acceptor for this hydrogen bond is O1, which is slightly undersaturated (Table V). However, the distance O1-O6 is 3.58(1) Å, which is too long to attribute any energy to that hydrogen bond. The topology of the framework structure of radovanite can be described as  $\text{M}_1=\text{T}_2-\text{M}_1=\text{M}_1-\text{M}_2-\text{T}_1-\text{M}_1$  according to the classification of EBY & HAWTHORNE (1993), where  $\text{M}_1$  is  $\text{CuO}_4\text{OH}$  square pyramid,  $\text{M}_2$  is  $\text{FeO}_6$  octahedron,  $\text{T}_1$  is  $\text{AsIO}_4$  tetrahedron and  $\text{T}_2$  is  $\text{As}_2\text{O}_2\text{OH}$  triangle. Important structural motifs of radovanite (Fig. 2),  $\text{Cu}_2\text{Fe}(\text{AsO}_4)(\text{AsO}_2\text{OH})_2\text{H}_2\text{O}$ , are similar as those in lironite,  $\text{Cu}_2\text{Al}(\text{AsO}_4)(\text{OH})_4\text{H}_2\text{O}$  (BURNS *et al.*, 1991): linear  $[\text{Fe}(\text{AsIO}_4)\varphi_4]$  chain ( $\varphi_4$  = unspecified ligand) extending along [010], and edge-sharing dimer  $[\text{Cu}_2\text{O}_6(\text{OH})_2]$  formed from two  $\text{CuO}_4\text{OH}$  square pyramids. In lironite this dimer is formed from two  $\text{CuO}_2(\text{OH})_2(\text{H}_2\text{O})_2$  octahedrons, and Al substitutes Fe. The cross linkage between the chains and the dimers is the same in radovanite and in lironite with one important difference: the cross linkage of dimers by  $\text{As}_2\text{O}_2\text{OH}$  triangles in radovanite is absent in lironite. In the place of missing apical oxygen atom, which transform  $\text{CuO}_6$  octahedron in lironite to  $\text{CuO}_5$  square pyramid in radovanite, there is a large cavity where the water molecule is fixed only by hydrogen bonds (Fig. 2a.). The structural similarity of the orthorhombic radovanite and pseudo-orthorhombic (monoclinic angle  $\beta=91.32^\circ$ ) lironite can be seen also by similarity of lattice parameters:  $a_{\text{radovanite}} \sim c_{\text{lironite}}$ ,  $b_{\text{radovanite}} \sim a_{\text{lironite}}$ ,  $c_{\text{radovanite}} \sim b_{\text{lironite}}$ .



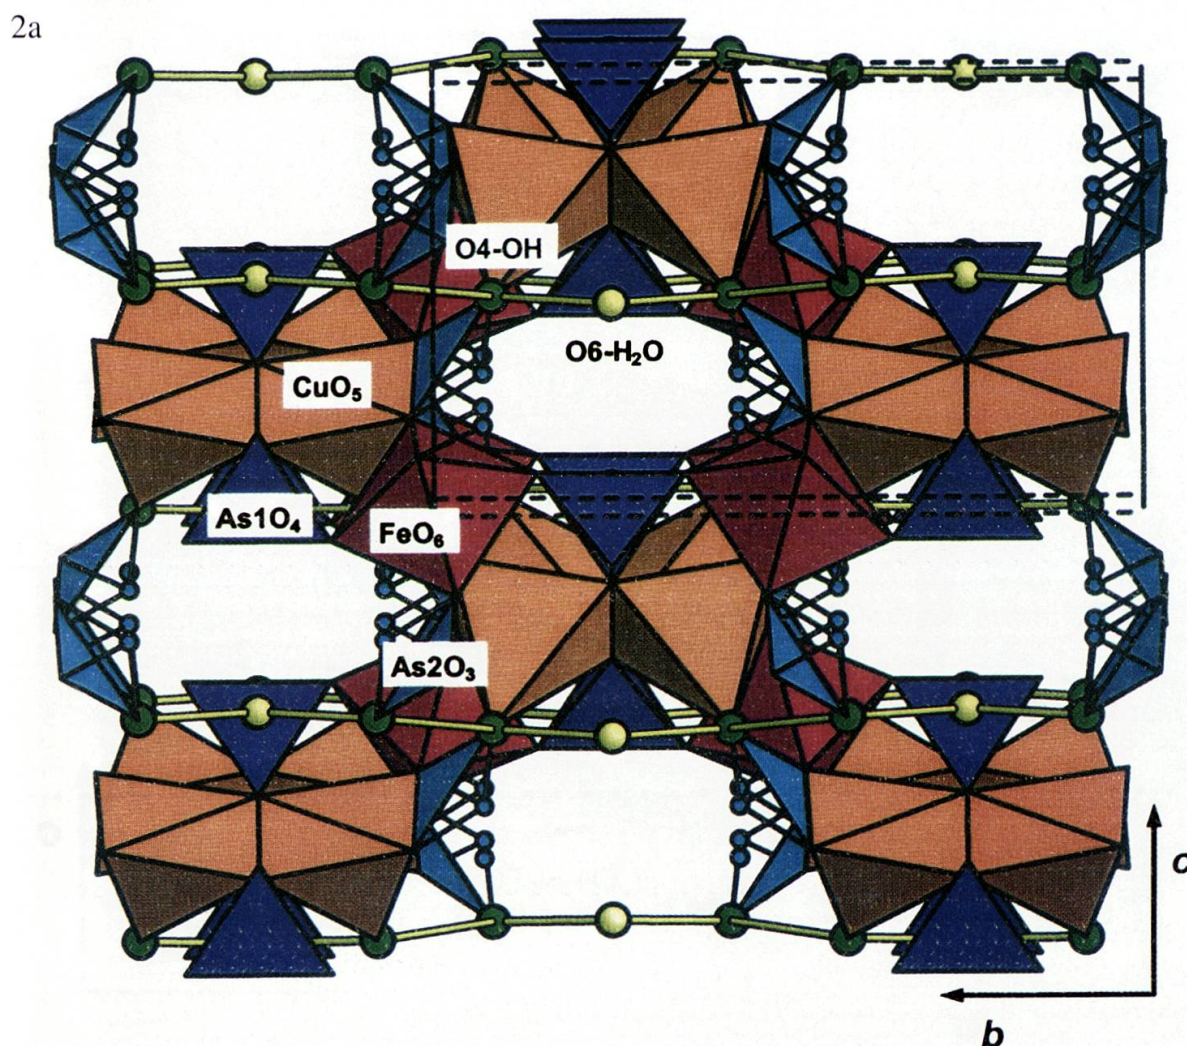


FIG. 2.

The structure of radovanite viewed approx. Down to a) [100], b) [010] and c) [001]. CuO<sub>5</sub> square pyramids are in orange, FeO<sub>6</sub> octahedra in red, As<sub>2</sub>O<sub>3</sub> triangles in sky blue and As1O<sub>4</sub> tetrahedra in blue. The As<sub>2</sub> atoms in As<sub>2</sub>O<sub>3</sub> triangles are shown as small spheres, the oxygen atoms O4-OH and O6-H<sub>2</sub>O participating in the hydrogen bonds as larger spheres. Hydrogen bonds are shown as thick lines, the outlines of the unit cell are dashed.

### RÉSUMÉ


RADOVANITE, Cu<sub>2</sub>Fe<sup>+3</sup>(As<sup>+5</sup>O<sub>4</sub>)(As<sup>+3</sup>O<sub>2</sub>OH)<sub>2</sub> H<sub>2</sub>O,

UN NOUVEAU MINÉRAL: SA DESCRIPTION ET SA STRUCTURE CRISTALLINE

Radovanite, Cu<sub>2</sub>Fe<sup>+3</sup>(As<sup>+5</sup>O<sub>4</sub>)(As<sup>+3</sup>O<sub>2</sub>OH)<sub>2</sub> H<sub>2</sub>O, un nouveau minéral, a été découvert dans les mines de cuivre de Roua (Alpes-Maritimes, France). Le minéral et son nom ont été homologués par la Commission Internationale des nouveaux minéraux de l'Association Internationale de Minéralogie (I.M.A.). Le minéral est orthorhombique, son groupe d'espace est Pnma. Les paramètres de la maille élémentaire sont  $a = 9,585(1)$ ,  $b = 13,143(1)$ ,  $c = 8,0884(7)$  Å. Il est optiquement biaxe (-) avec  $\alpha = 1,80(1)$ ,  $\beta = 1,84(1)$ ,  $\gamma = 1,86(1)$ . La structure atomique a été affinée en utilisant 1027 réflexions uniques observées jusqu'à  $R = 0.059$ ,  $R_w = 0.023$ .

**Mots-clés:** radovanite, nouveau minéral, diagramme de poudre, structure cristalline, arseniate-arsenite, cuivre, fer, liaison d'hydrogène.



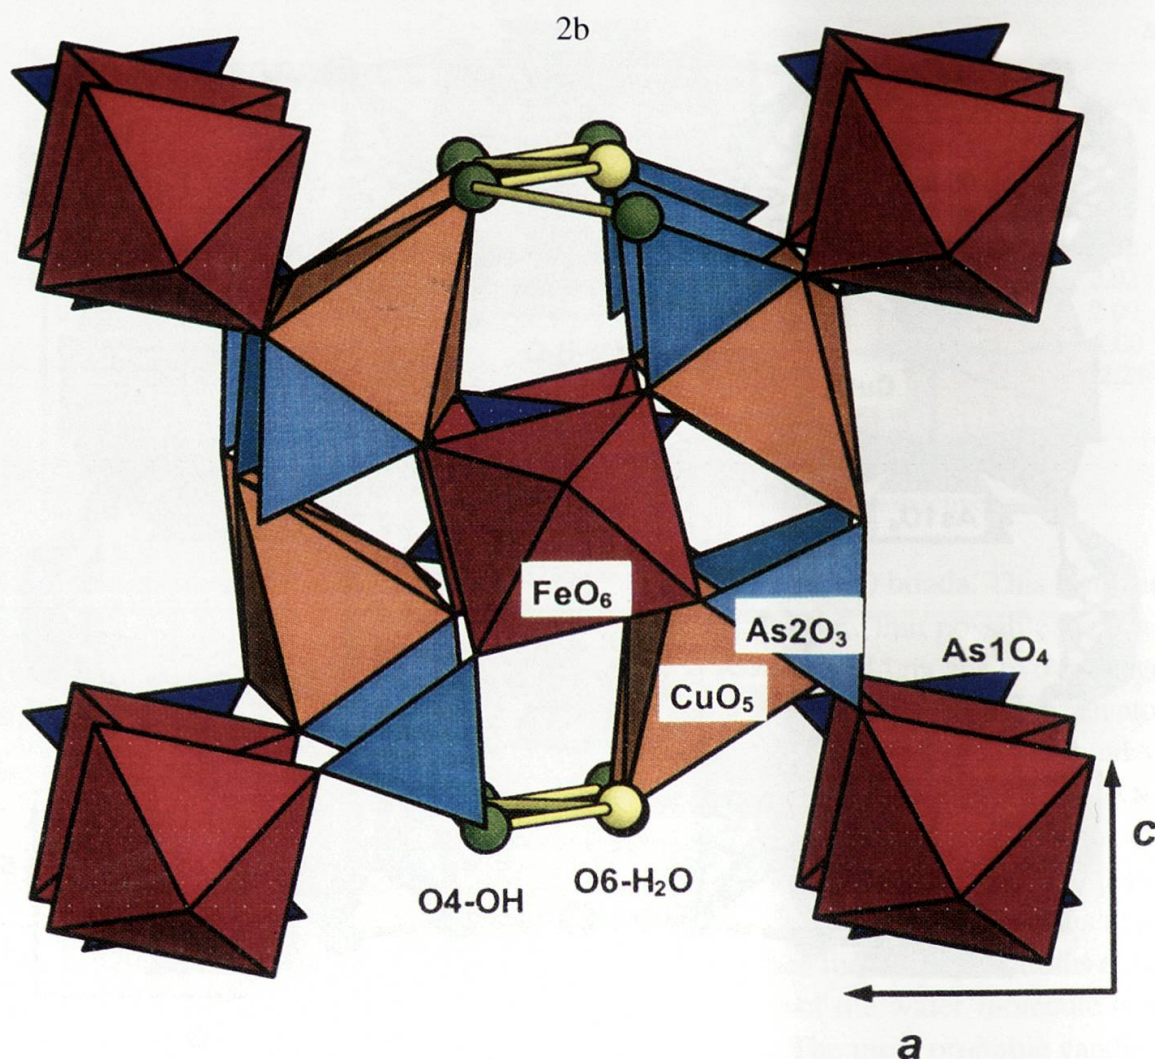


### ACKNOWLEDGEMENTS

We thank to Radovan Černý for his comments on the crystal structure, J. Wüest for the scanning electron microscope photographs and Professor J. Bertrand for reviewing the manuscript.

### REFERENCES

- BALIC ZUNIC, T. & I. VICKOVIC. 1996. IVTON – program for the calculation of geometrical, aspects of crystal structures and some crystal chemical applications. *J. Applied Cryst.*, 29, 305-306.
- BRESE, N.E. & O'KEEFFE, M. 1991. Bond valence parameters for solids. *Acta Cryst.*, B47, 192-197.
- BROWN, I.D. & D. ALTERMATT. 1985. Bond valence parameters obtained from a systematic analysis of the inorganic crystal structure database. *Acta Cryst.*, B41, 244-247.
- BROWN, I.D. & KANKUN WU. 1976. Empirical parameters for calculating cation-oxygen bond valences. *Acta Cryst.*, B32, 1957-1959.
- BURNS, P.C., R.K. EBY & F.C. HAWTHORNE. 1991. Refinement of the Structure of Liroconite, a Heteropolyhedral Framework Oxysalt Mineral. *Acta Cryst.*, C47, 916-919.
- EBY, R.K. & F.C. HAWTHORNE. 1993. Structural relations in copper oxysalt minerals. I. Structural hierarchy. *Acta Cryst.*, B49, 28-56.
- GELATO, L.M. & E. PARTHE. 1987. STRUCTURE TIDY – a computer program to standardize crystal structure data. *J. Applied Cryst.*, 20, 139-143.



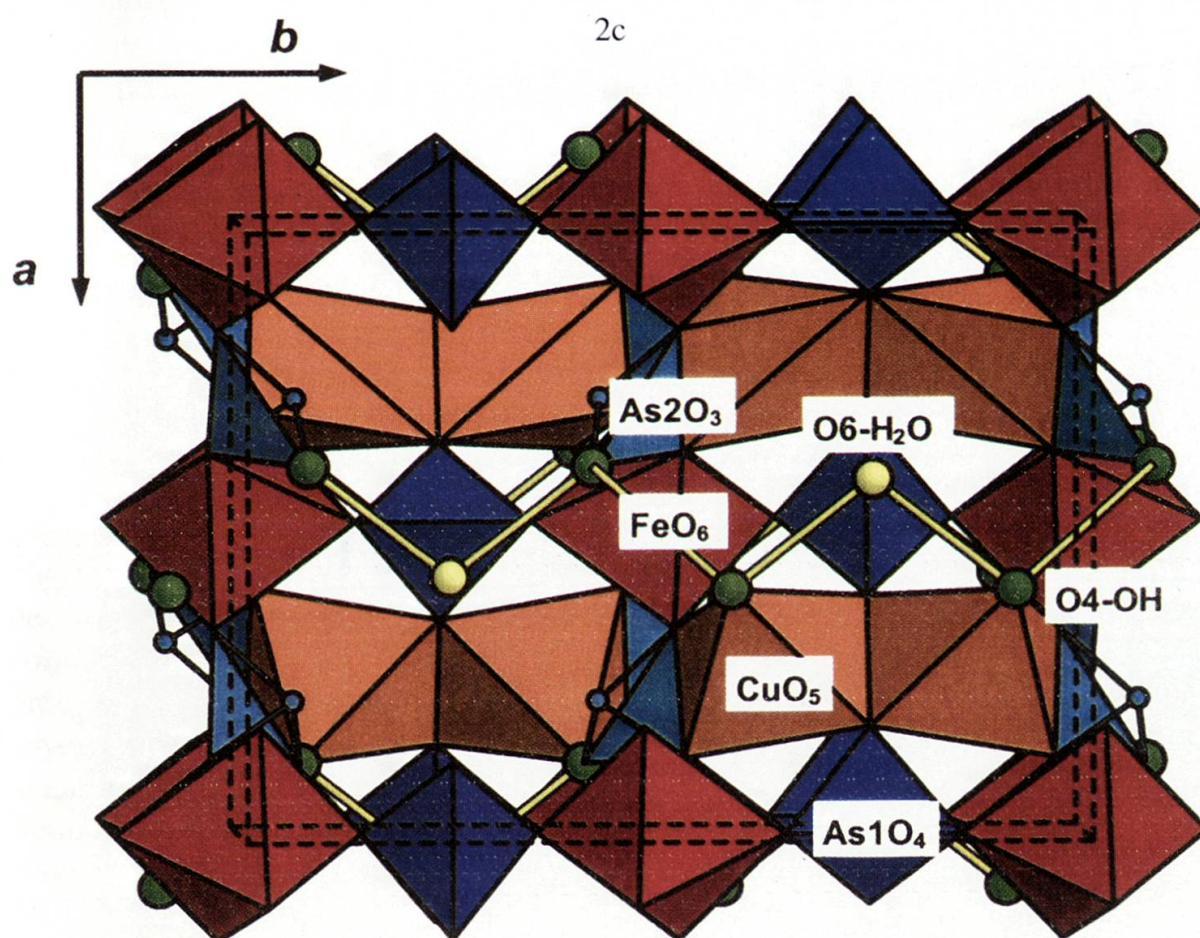

HALL, S.R., D.J. DU BOULAY & R. OLTHOF-HAZEKAMP. 2000. Eds. *Xtal 3.7 System*. University of Western Australia.

MANDARINO, J.A. 1981. The Gladstone-Dale relationship: part IV. The compatibility concept and its applications. *Can. Mineral.*, 19, 441-450.

MARI, G. 1992. Les anciennes mines de cuivre du Dôme de Barrot (Alpes-Maritimes). *Ed. Serre*, Nice, 112 p.

SARP, H. & R. CERNY. 1999. Gilmarite,  $\text{Cu}_3(\text{AsO}_4)(\text{OH})_3$ , a new mineral: its description and crystal structure. *Eur. J. Mineral.*, 11, 549-555.

SARP, H. & R. CERNY. 2000. Rollandite,  $\text{Cu}_3(\text{AsO}_4)_2 \cdot 4\text{H}_2\text{O}$ , a new mineral: its description and crystal structure. *Eur. J. Mineral.*, 12, 1045-1050.

SARP, H., R. CERNY, L. GUENEE. 2001. Rouaite,  $\text{Cu}_2(\text{NO}_3)(\text{OH})_3$ , un nouveau minéral: sa description et sa structure cristalline (Alpes-Maritimes, France). *Riviera Scientifique*, 85, 3-12.

SARP, H., R. CERNY. 2001. Theoparacelsite,  $\text{Cu}_3(\text{OH})_2\text{As}_2\text{O}_7$ , a new mineral: its description and crystal structure. *Archs Sci. Genève*, 54, 7-14.

STOE & Cie. 1999. X-RED (Version 1.19) and IPDS Software (Version 2.92). *Stoe & Cie*, Darmstadt, Germany.

VINCHON, C. 1984. *Sédimentogenèse et métallogénèse du Permien du Dôme de Barrot (Alpes-Maritimes)*. Thèse d'Etat. Document B.R.G.M., no. 70, 445 p.

