

Zeitschrift: IABSE congress report = Rapport du congrès AIPC = IVBH
Kongressbericht

Band: 2 (1936)

Artikel: Characteristic features of welding

Autor: Roš, M.

DOI: <https://doi.org/10.5169/seals-3279>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 17.04.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

III a 4

Characteristic Features of Welding.

Charakteristische Merkmale der Schweißung.

Caractéristiques propres à la soudure.


Dr. Ing. h. c. M. Roš,

Professor an der Eidg. Techn. Hochschule und Direktionspräsident der Eidg. Materialprüfungs- und Versuchsanstalt für Industrie, Bauwesen und Gewerbe, Zürich.

As regards the strength and deformation properties, the quality of the structure of the weld material, including that of the transition zone, is fundamental. Weld metal is in fact a form of steel casting; its structure is heterogeneous and anisotropic — Fig. 1 —, and the theory of constant strain-energy of deformation holds good only if account is taken of the anisotropic condition. In practice, no guarantee can be given that *weld material is free from pores and slags*. *Shrinkage-cracks* in the outer surfaces and in the interior of the weld material are, as a matter of fact, rare occurrences, but occasionally they may be present — Fig. 2 —. Pores, slag inclusions and cracks must be considered equivalent to a *mechanical imperfection*. *Thermal influences* give rise, on the surface, to the structure known by the name of Widmannstaetten with transcrystallization — Fig. 3 — and in the transition zone to the formation of sorbite, troostite — Fig. 1 — and — in steels containing less than 0.15 % carbon — also martensite — Fig. 4 — which on account of its brittleness promotes the formation of cracks. So far as the material itself is concerned, welding *cannot* therefore be considered equivalent to riveting — Fig. 5 —.


By metallurgical means such as proper choice of the electrodes, correct procedure with pre-heating of the steel when necessary — Fig. 6 —, heat treatment without stress (up to the lower transition-temperature at the most) or annealing (beyond the upper transition-temperature) combined with suitable precautions in design — i. e. reduction of thermal stresses — Fig. 7 —, proper choice of type of connection — Fig. 8 — and shape — Fig. 9 — the mechanical-characteristics of the welded connection may be made to approximate to those of the riveted connection.

The series of tests and precautions is completed by examination of the welders based on the results of mechanical and deformation tests, either on plates specially welded both in the normal and overhead position or on specimens of suitable shape (round or oval) removed from work carried out in actual practice, combined with X-ray examinations.

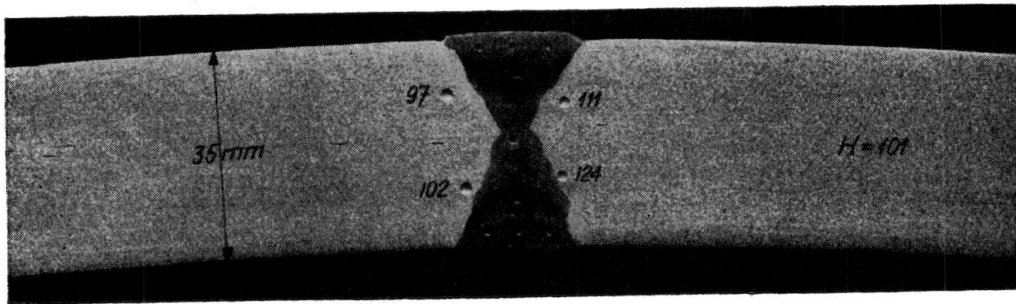


$$\beta_z \cong 38 \text{ kg/mm}^2$$


$$\sigma_u \cong 16 \text{ kg/mm}^2$$

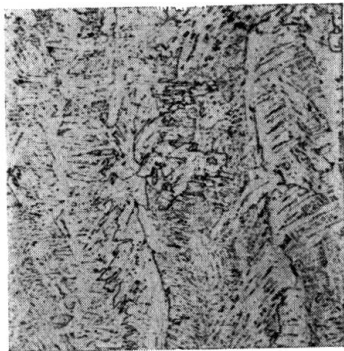


Coarse Widmannstaetten structure in weld metal.

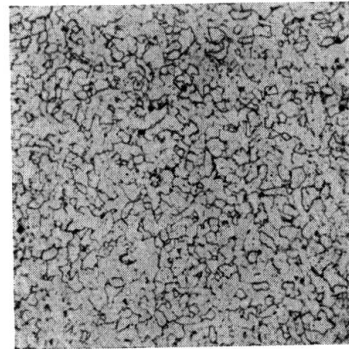

Fine, normalised structure in weld metal.

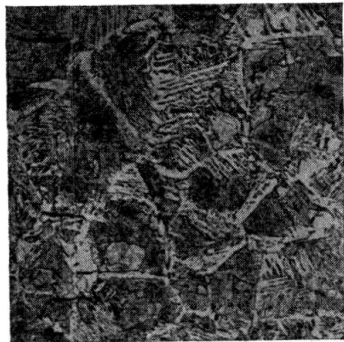

Thermally altered structure, ferrite and sorbite, transition zone.

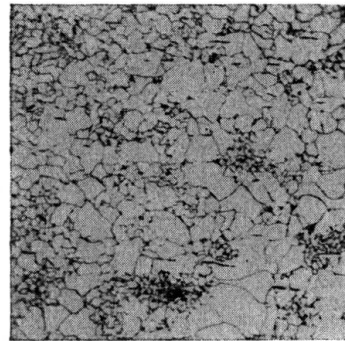

Thermally altered structure ferrite and degenerated perlite, transition zone.




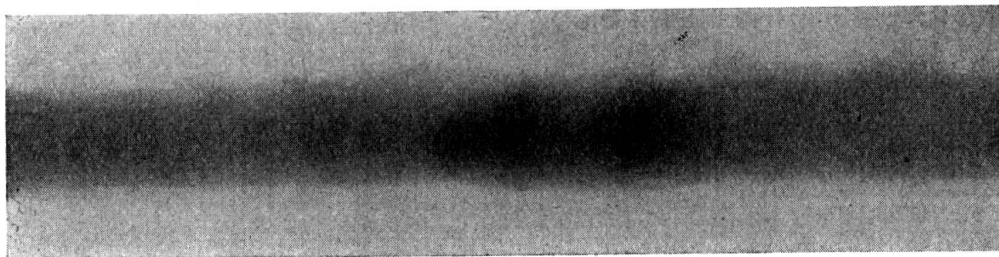


Fig. 1.


Arc weld free from defects, in normal structural steel.
Heterogeneity of the weld metal structure.

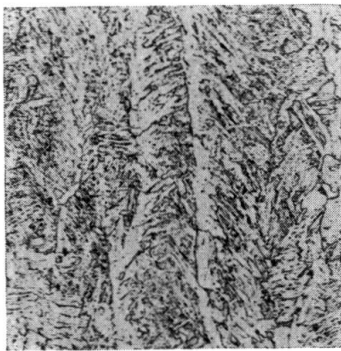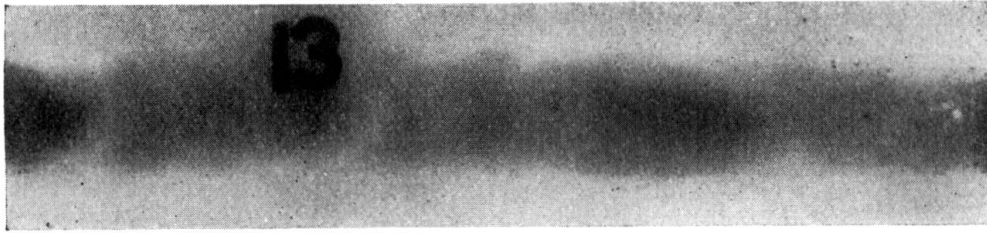


Coarse Widmannstaetten structure, weld metal, last layer.

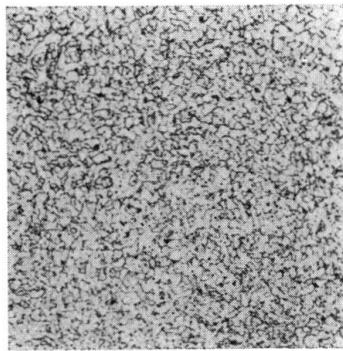

Fine, normalised change in structure, weld metal.

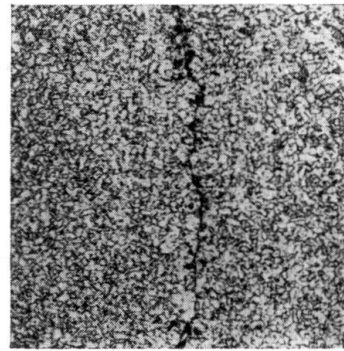



Fine, normalised change in structure with microscopic crack, weld metal.

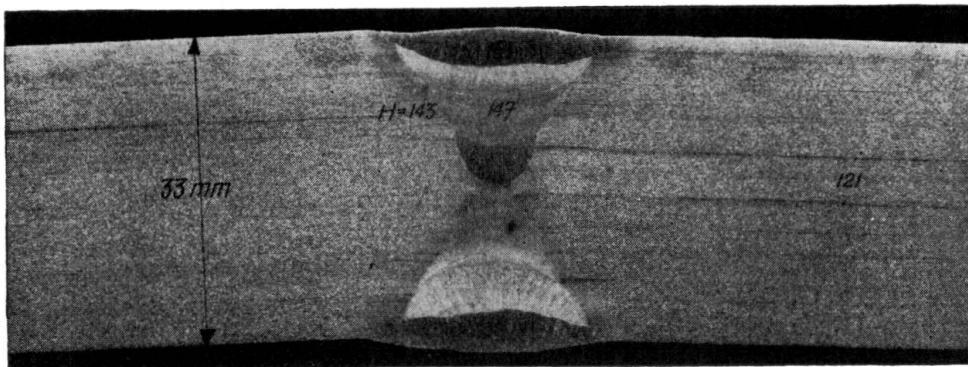


$$\beta_z \cong 44 \text{ kg/mm}^2 \quad \sigma_u \cong 17 \text{ kg/mm}^2 \quad \frac{1}{2} \sigma_w \cong 27 \text{ kg/mm}^2$$

Fig. 2.


Arc weld of superior quality in steel containing 0.25 % C.
Microscopic cracks in weld metal.

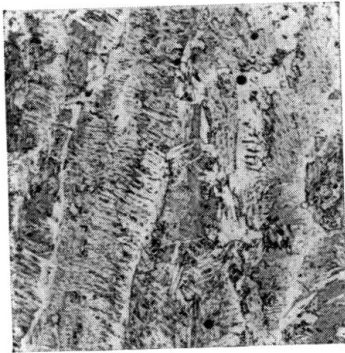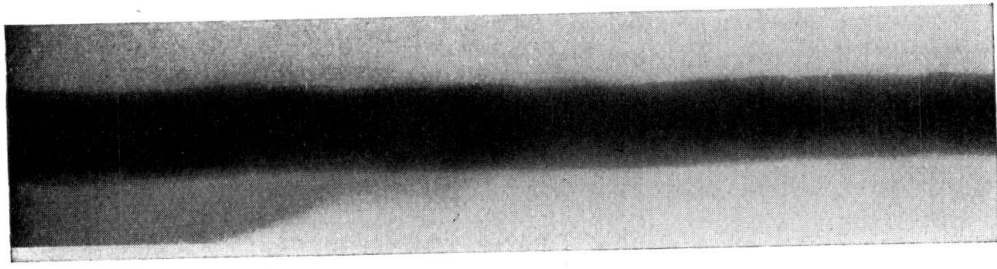


Widmannstaetten structure,
weld metal.

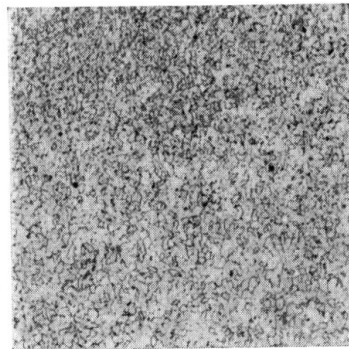

Fine alteration in structure,
weld metal.

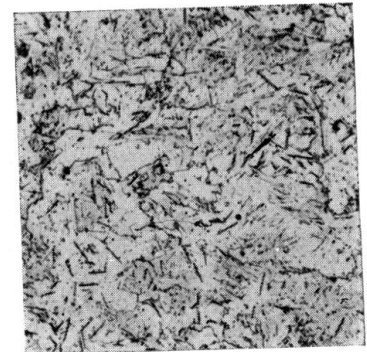

Local enrichment of nitride
inclusions, weld metal.

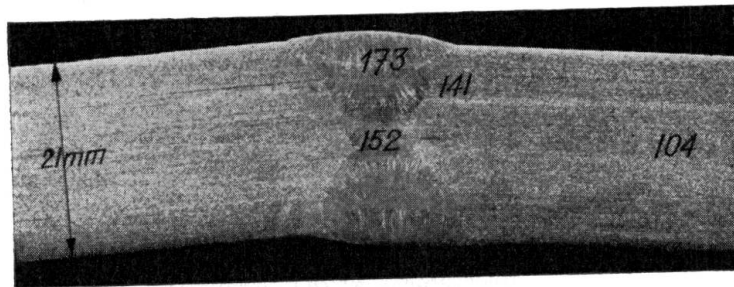

$$\beta_z \cong 38 \text{ kg/mm}^2 \quad \sigma_u \cong 18 \text{ kg/mm}^2 \quad \frac{1}{2} \sigma_w \cong 26 \text{ kg/mm}^2$$


Fig. 3.

Arc weld free from defects, in normal structural steel.
Widmanstaetten structure with transcrystallisation.


Siemens-Martin steel with 0.20—0.25% C.



Temperature: -10° C.
Martensite with traces of troostite due to quenching effect.

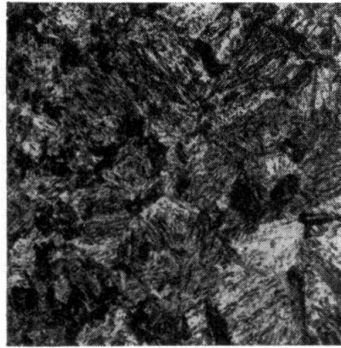

Temperature: 25° C.
Martensite with troostite due to quenching effect.

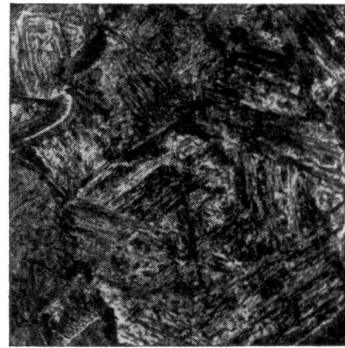

Temperature: 50° C.
Martensite with little troostite, traces of ferrite.

Fig. 4.

Formation of Martensite in the transition zone immediately at the junction of the weld metal with Siemens-Martin steel plate.

Temperature of the Siemens-Martin steel, when welded, -10° , $+25^{\circ}$ and 50° C.




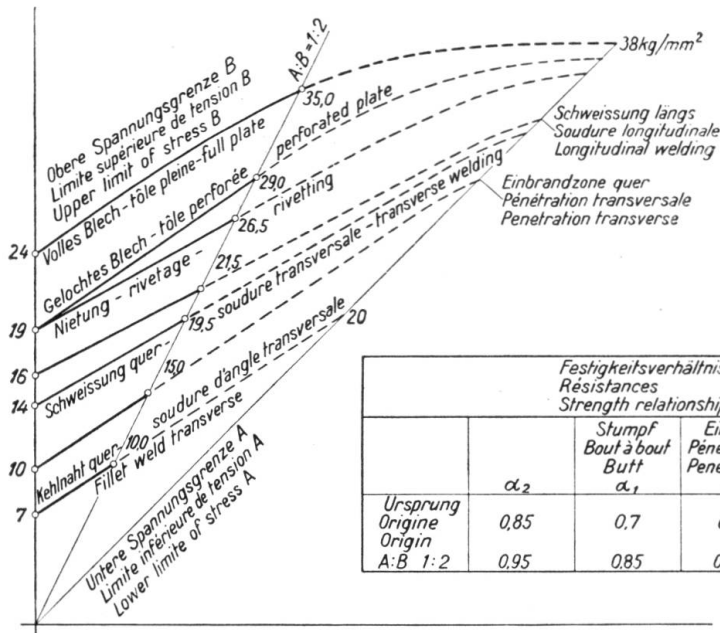


Fig. 5.

Tensile fatigue strength in relation to the lower limit of stress.

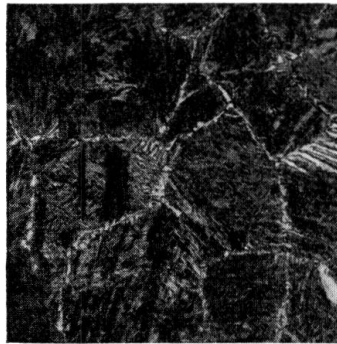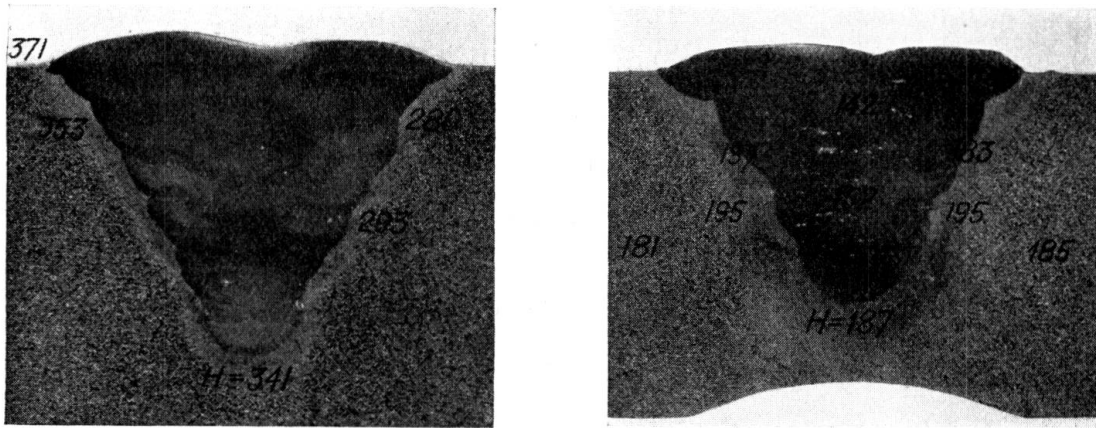

Not pre-heated, formation of Martensite.

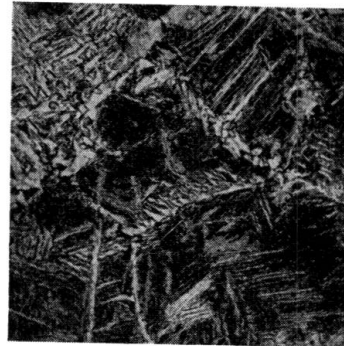

Pre-heated, no formation of Martensite.

Fig. 6.


Electrically welded cast steel, carbon content 0.28 %.

Welding without pre-heating:

High hardness number in the transition zone, formation of Martensite.

Welding with pre-heating:

Normal hardness number, no formation of Martensite.

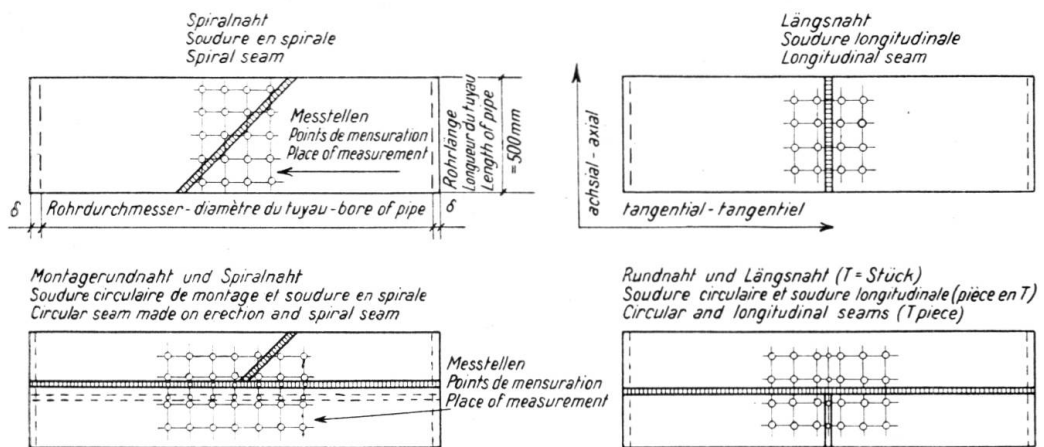

Nature of weld seams, where measured.

Fig. 7 a.

Internal stresses of weld seams, annealed and not annealed.

Maximum values of internal stresses as measured.

annealed or not	Nature of weld seams where measured	Reduced internal tensile stresses in kg/cm ²	
		axial	tangential
annealed	Longitudinal X-seam	+ 1010	+ 1060
not annealed	Longitudinal X-seam	+ 1620	+ 2460
annealed	Spiral X-seam	+ 280 + 447	+ 727 + 336
not annealed	Circular and longitudinal U-seams	+ 2070	+ 2070

Fig. 7 b.


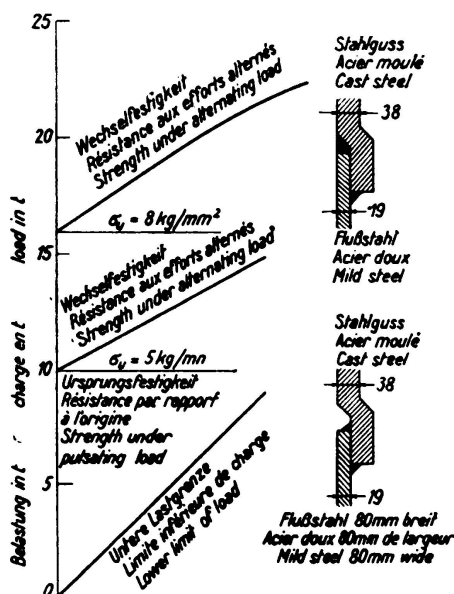


Fig. 8 a.

Increased resistance to alternating stress through suitable weld connections between cast steel and mild steel.

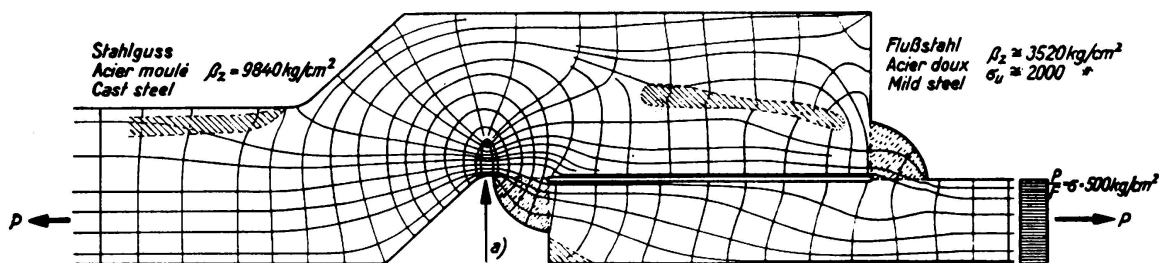

a) Navier-Hooke stresses, by calculation $\frac{P}{F} + \frac{M}{W}$: $\sigma_{\max} = 2,8 \sigma = 1400 \text{ kg/cm}^2$.

Resistance of the connection to pulsating stress: $\sigma_u \approx 500 \text{ kg/cm}^2$.

Concentration of stress at base of notch as determined optically: $\sigma_{\max} = 5 \sigma = 2500 \text{ kg/cm}^2$.

Fig. 8 b.

Stress conditions at base of notch.

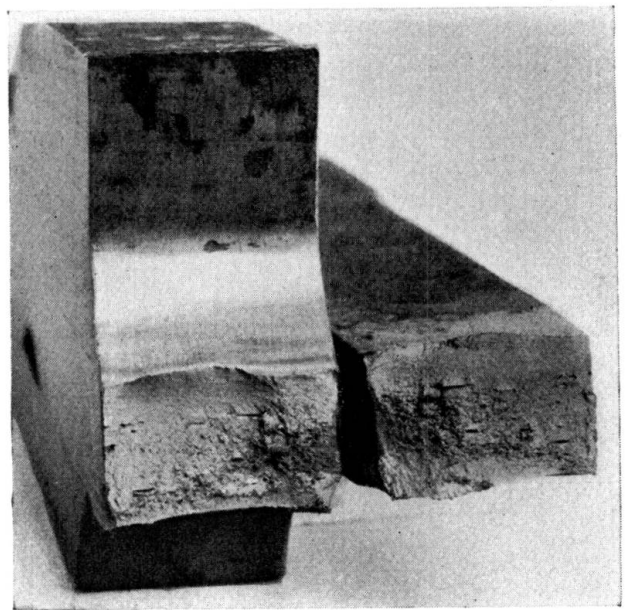
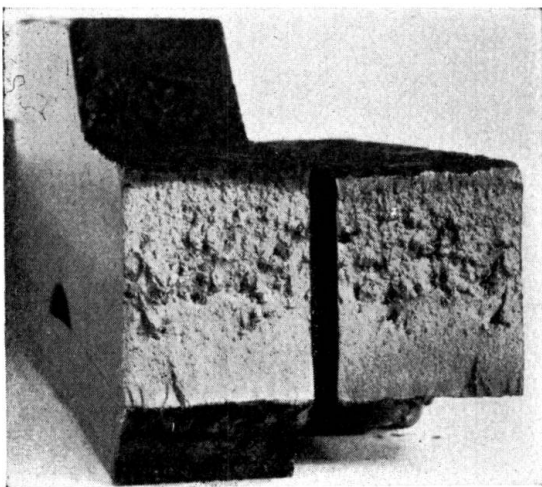
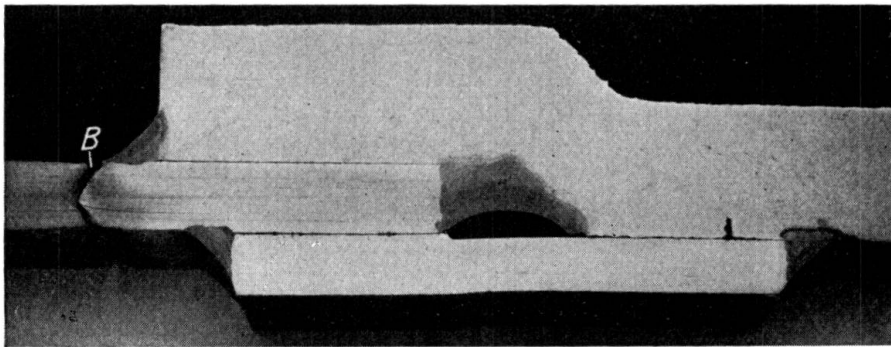
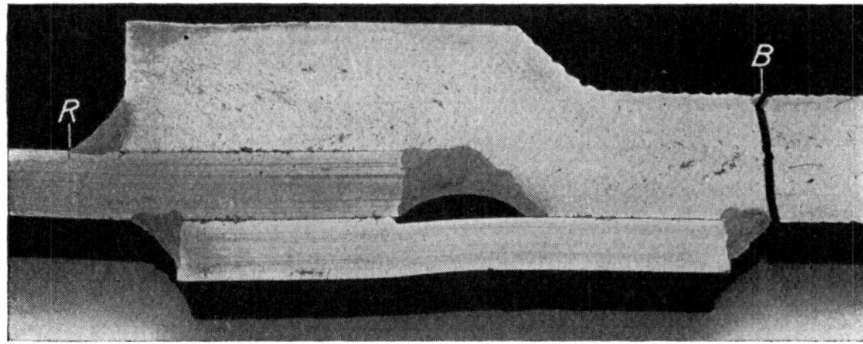


Fig. 9.

Welded connections between cast steel and mild steel.
Increased resistance to pulsating stress by grinding the weld seams.