

Zeitschrift: IABSE congress report = Rapport du congrès AIPC = IVBH
Kongressbericht

Band: 13 (1988)

Artikel: Polymer mortar-sealing materials for laying-down caissons

Autor: Kobayashi, Tatsuo / Ohta, Wataru / Hasegawa, Keiichi

DOI: <https://doi.org/10.5169/seals-13152>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 22.02.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>



Polymer Mortar-Sealing Materials for Laying-Down Caissons

Etanchéité de caissons à l'aide de composés mortier-polymères

Abdichtung von Senkkästen mit Kunststoffmörteln

Tatsuo KOBAYASHI

Dr. Eng.
Yokohama Rubber Co.
Tokyo, Japan

Wataru OHTA

Technical Manager
Yokohama Rubber Co.
Tokyo, Japan

Keiichi HASEGAWA

Chief Engineer
Yokohama Rubber Co.
Tokyo, Japan

We have been challenging to apply polymer materials to civil engineering constructions, especially sealing materials, anticorrosion system, buffer system against ship collisions, microwave absorbers and so forth.

This present paper proposes the application criteria of polymer mortar-sealing materials to caissons in laying-down caisson method from among them. (Fig.1)

The laying-down caisson method is one of foundation methods which can be achieved to maintain the security and the reliability of economical construction work in the severe environment of the sea. According to apply this method, it is necessary to seal the clearance between the cutting edge of the caisson and the uneven surface of the sea bed.

Requirements for mortar-sealing materials are as follows.

- 1) To seal in low reaction forces of sealing materials.
- 2) To be easy of work with few submarine work.
- 3) To keep functions against severe natural conditions.
- 4) To have reliability of the sealing material, and to have no use for repair

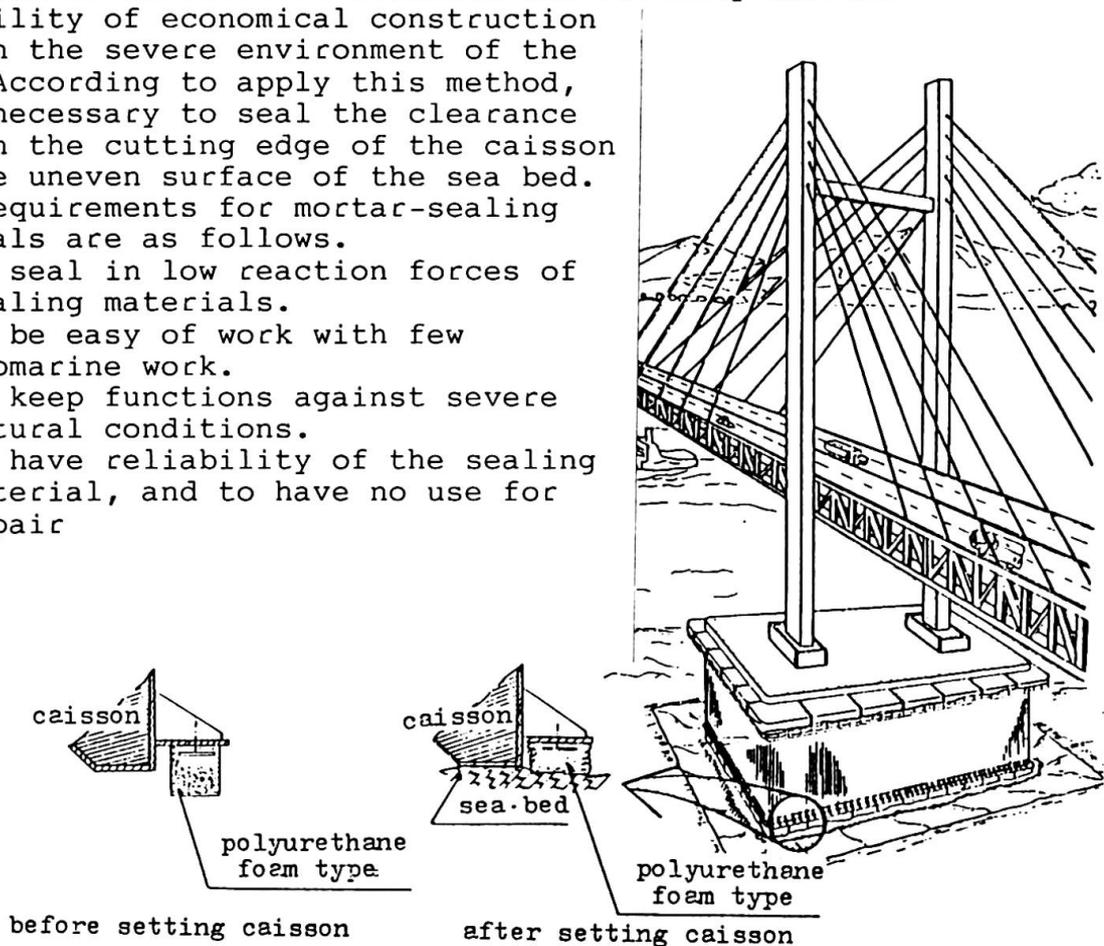


Fig.1 The sponge mat for deep sea concrete works

Usual mortar-sealing materials which are applied to small caissons less than 25m in water depth are not satisfied with the all requirements for a lot of divers work.(Fig.2)

In case of less than 25m in water depth, the cloth reinforced flexible tube or the sponge mat of low-density-type has been applied and achieved perfect seal with no divers work.

In case of more than 25m in water depth, it is necessary for us to evaluate not only polymer materials but the construction of the sealing material due to the above requirements and others such the unevenness height of seabed, the toughness under the high-speed compression, etc. Sponge mat, developed under the guidance of the Honshu-Shikoku Bridge Authority, was concluded to be the best sealing materials in the condition of less than 500mm unevenness. (Fig.3 and Table 1)

Above the unevenness height 500mm, we can recommend the combined type, which combines large scale cloth reinforced flexible tubes in the shape of bellows-type and low-density polyurethane foam.(Fig.4)

As the civil engineering developed, the mortar sealing materials are refined and enlarged various uses.

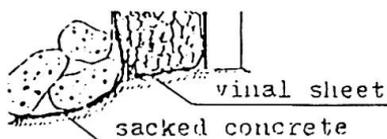


Fig.2 Usual mortar-sealing materials

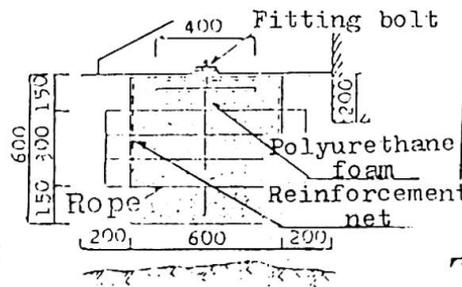


Fig.3 The sponge mat

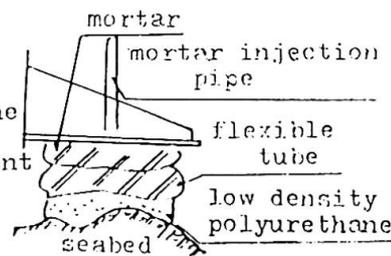


Fig.4 Combined type

Table-1 Actual results of the Sponge Mat for caisson foundations in the Honshu-Shikoku Bridge

Construction name		Substructure works for the South Bisan-Seto bridge			Substructure works for the Mitsuishi istand bridge	
		(5P)	(7A)	(6P)	(3P)	(2P)
Place		The Inland Sea in Kagawa prefecture			The Inland Sea in Okayama prefecture	
Customer		Honshu-Shikoku Bridge Authority				
General Contractor (Caisson Maker)		Taisei JV (Nippon Kokan)	Kajima JV (Mitsui JV)	Kajima JV (Mitsubishi JV)	Nishimatsu JV (Nippon Kokan)	Nishimatsu JV (Sumitomo JV)
Year of execution		1980	1981~1982	1982	1983	1984
Natural Conditions	Depth of water(m)	32	50	50	25	28
	Current velocity(kt)	6	4	4	4	4
Dimensions of Caisson	size(m)	27×59×38	59×75×55	38×59×55	29×45×30.5	25×46×32.5
	weight(t)	5000	19500	9700	5000	2800
Sealing Conditions	object	Prepacked-concrete-mortar sealing			tremie-concrete mortar sealing	consolidation mortar sealing
	Sealing Pressure(t/m ²)	14	16	13	15	3.4
	Unevenness of rock-beds(mm)			200~300		
Spong Mat	Type		600H			400H
	Total length (m)	167	400	189	148	136