

Zeitschrift: IABSE congress report = Rapport du congrès AIPC = IVBH
Kongressbericht

Band: 13 (1988)

Artikel: Properties of fibre glass reinforced cement composites

Autor: Komloš, Karol / Babál, Bohumil / Vaniš, Matej

DOI: <https://doi.org/10.5169/seals-12963>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 09.08.2025

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Properties of Fibre Glass Reinforced Cement Composites

Caractéristiques du béton renforcé de fibres de verre

Eigenschaften von mit Glasfasern bewehrtem Beton

Karol KOMLOŠ

Chief scientist
Inst. of Constr.
Bratislava, Czechoslovakia

Bohumil BABÁL

Scientist
Inst. of Constr. and Archit.
Bratislava, Czechoslovakia

Matej VANIŠ

Assoc. Prof.
Slovak Techn. Univ.
Bratislava, Czechoslovakia

Jana KOZÁNKOVA

Research worker
Slovak Techn. Univ.
Bratislava, Czechoslovakia

SUMMARY

The paper deals with the testing of long term resistance of fibre glass in the alkaline medium of Portland cement. The applied Czechoslovak alkali resistant fibre glasses were incorporated into the Portland cement matrix. The long term ageing process was studied. Some of the specimens were stored in water, and the rest were dry cured. The modulus of rupture was determined at the age of 28, 90, 180, and 360 days. The composite texture was studied by the SEM method.

RÉSUMÉ

L'étude examine la résistance à longue durée des fibres de verre dans le milieu alkalin du ciment Portland. Les fibres de verre tchécoslovaques ont été utilisées pour renforcer la matrice de ciment Portland. La résistance à longue durée a été examinée sur des éprouvettes. Une partie de celles-ci était stockées dans l'eau, une autre partie dans un environnement sec. La résistance à la flexion a été déterminée après 28, 90, 180, 360 jours. La microstructure des ciments à fibres de verre a été étudiée par la méthode SEM.

ZUSAMMENFASSUNG

Dieser Beitrag befasst sich mit der Untersuchung der Langzeitbeständigkeit von Glasfasern in der alkalischen Portlandzement-Matrix. Verwendet wurden tschechoslowakische, alkalibeständige Glasfasern, die in die Zementmatrix eingebettet wurden. Die Langzeitbeständigkeit wurde an Prüfkörpern untersucht. Ein Teil dieser Prüfkörper wurde im Wasser, ein anderer Teil wurde trocken gelagert. Die Biegezugfestigkeit wurde im Alter von 28, 90, 180, 360 Tagen ermittelt. Das Verbundwerkstoffgefüge wurde mittels der SEM Methode untersucht.



1. INTRODUCTION

The extension of fibre reinforced cement composites /FRC/ to the field of building materials plays a peculiar role of its own in the already wide and well-established area of application for composite materials. Glass fibre reinforced cement and concrete GRC/, with its rapidly increasing applications in construction /e.g. cladding panels, permanent formwork, small components, hydraulics and marine applications/, is a composite material consisting of a cement or concrete matrix reinforced by a small proportion of glass fibres.

The function of the fibres in the relatively brittle cement matrix is to delay and control the tensile cracking of the material so that an unstable and uncontrolled tensile crack growth is transformed into a slow controlled crack growth. It is this unique characteristic of fibre reinforcement that gives the composite properties of post-cracking tensile resistance, increased tensile strain capability and enhanced energy absorption.

The basic problem of GRC application is the attack by the alkalis associated with hydrating cements. This problem is being solved either by applying alkali resistant glass fibres provided with effective coating materials, e.g. Cem-FIL 1 and Cem-FIL 2 fibres of following composition: $\text{SiO}_2 = 62.5\%$; $\text{ZrO}_2 = 16.3\%$; $\text{NaO}_2 = 14.8\%$; $\text{Al}_2\text{O}_3 = 0.85\%$; $\text{CaO} = 5.05\%$; $\text{K}_2\text{O} = 0.3\%$, produced by Pilkington Brothers Ltd in Great Britain, or by decreasing the alkalinity of the cement matrix, e.g. the procedure developed by l'Industrielle de Préfabrication in France, which enables the application of E-glass fibres.

In Czechoslovakia much attention has been paid to the problem of alkali resistance of glass fibres, and the result of these studies was the development of two types of alkali resistant glass fibres. Glass fibres REZAL and ESAP are of low zirkonium dioxyd content, SVÚS 16 belongs to the high zirkonium dioxyd content.

In our previous work [1] we studied the suitability of several methods of determining the chemical resistance of glass fibres in alkaline media. These investigations have shown that the autoclave test method has a more severe effect on the glass fibres than the standard method. The most deteriorous effects were obtained with a NaOH and Na_2CO_3 mix as the reacting solution. The submitted paper, which is a continuation of the above study, deals with the long-term alkali resistance of Czechoslovak glass fibres incorporated in the cement matrix.

2. EXPERIMENTAL PROGRAMME

2.1. Materials and mixes

A Portland cement type 400 was used to manufacture the cement paste. The physico-mechanical properties of the applied cement fulfilled the requirements of the Czechoslovak Standard ČSN 722121. As fibre reinforcement REZAL, ESAP, and SVÚS 16 alkali-resistant glass fibres were applied. Their chemical composition is given in Table 1. The fibre length was 36 mm. The water/cement ratio of the cement paste was 0.370. The following fibre weight fractions of glass fibres were incorporated into the cement paste: 0.4; 1.0; 1.6; 2.2; 3.3; and 4.4 per cent. The batches were mixed in

Components in weight%	SiO ₂	ZrO ₂	BaO	Na ₂ O	Al ₂ O ₃	CaO	Fe ₂ O ₃	TiO ₂
Fibre Type								
REZAL	59,29	4,97	9,94	10,4	5,10	10,3	—	—
ESAP	65,70	4,95	6,80	10,5	4,60	7,3	0,15	—
SVUS16	58,30	11,40	—	14,3	—	8,6	—	7,4

Table 1 Glass fibre chemical composition

laboratory pan mixer, and the fibres were incorporated into the cement paste in such a way to ensure an uniform and random distribution in the cement matrix.

2.2. Casting, curing and testing

The mixes were compacted in steel moulds on a vibrating table /50 Hz; 0.35 mm/. Three specimens 40x40x160 mm could be manufactured simultaneously in these moulds. Together with the fibre reinforced specimens, plain specimens were cast. For each investigated parameter six specimens were manufactured. The obtained values are the mean strength values determined on these specimens.

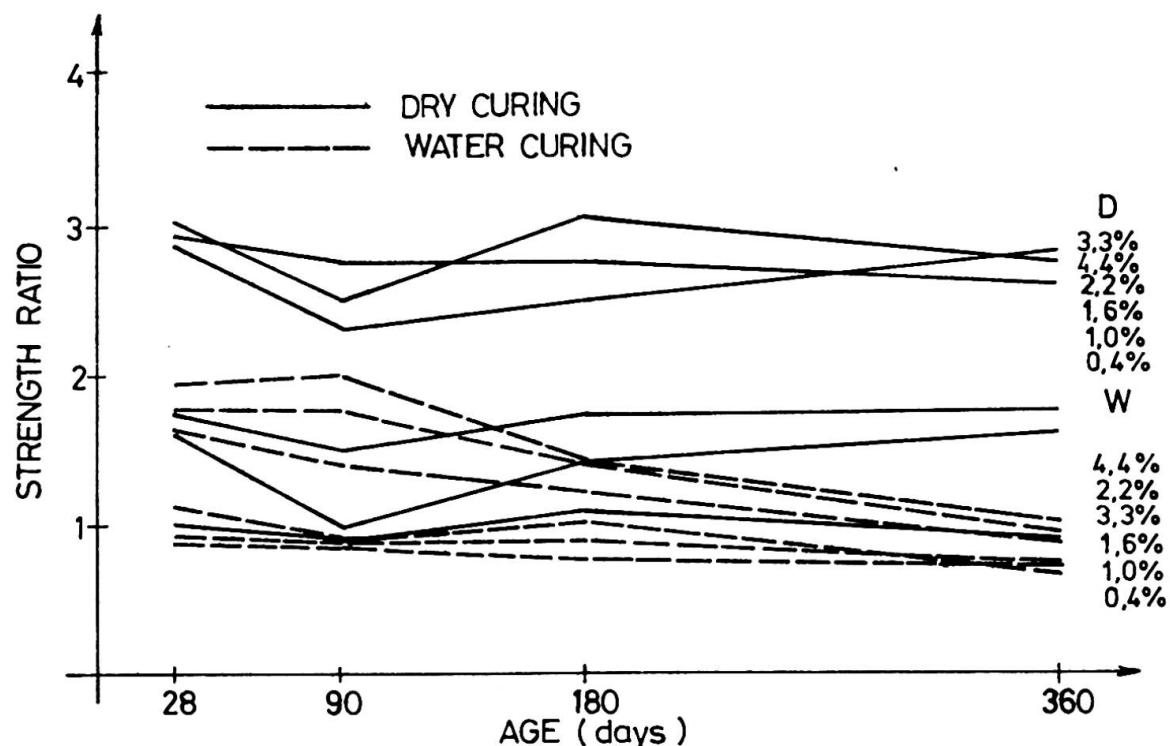


Fig. 1 Strength ratio versus composite age relationship – fibre typ: REZAL

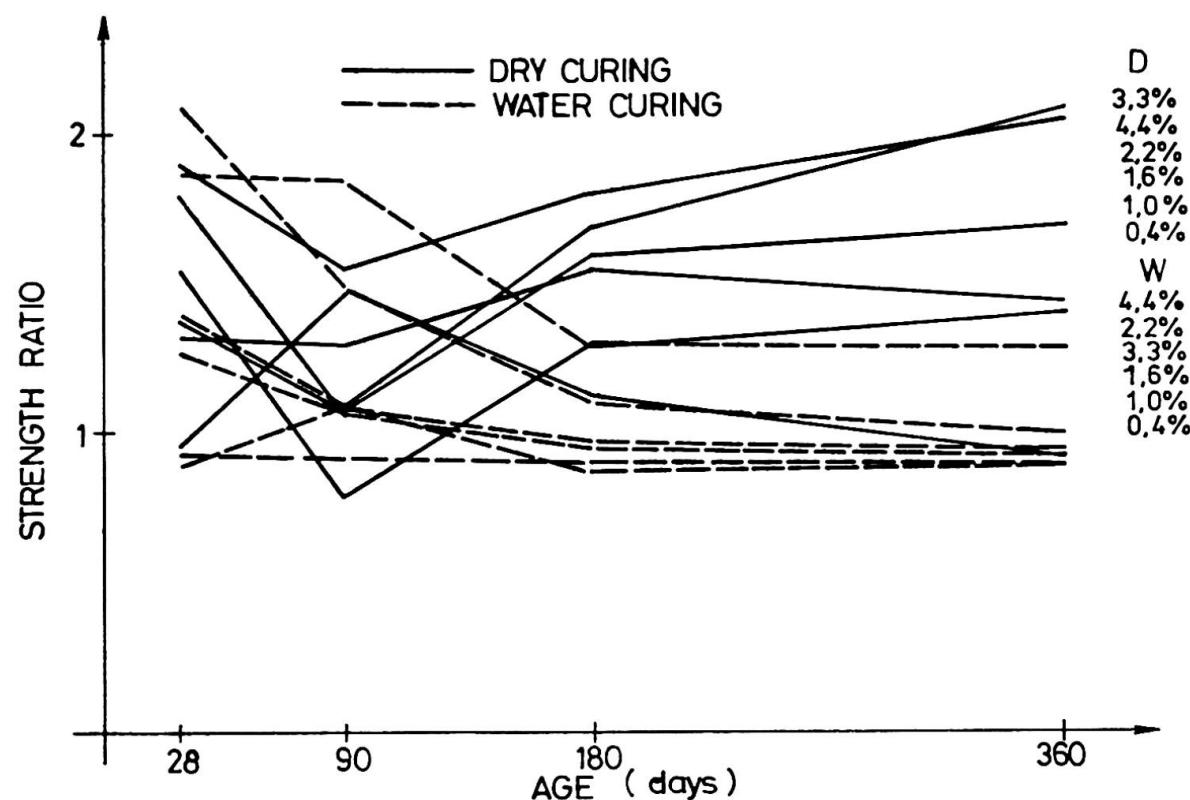


Fig. 2 Strength ratio versus composite age relationship - fibre type: ESAP

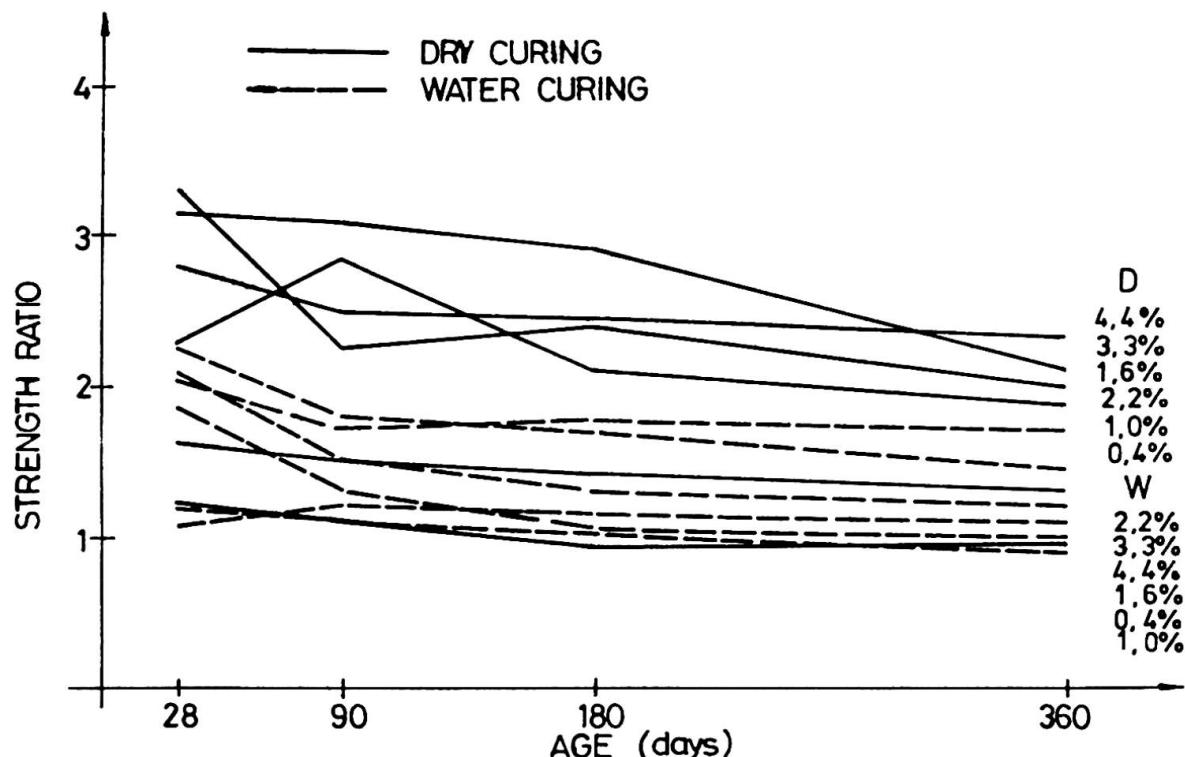


Fig. 3 Strength ratio versus composite age relationship - fibre type: SVUS 16



Fig. 4 SEM of REZAL fibres in the cement matrix /360 days, water curing, fibres: 4.4%

the age of the tested specimen reinforced with a fibre weight fraction of 0.4; 1.0; 1.6; 2.2; 3.3; and 4.4 is plotted. The flexural strength ratio is the ratio

$$\frac{\text{strength of reinforced matrix}}{\text{strength of plain matrix}}$$

The investigations carried out have shown that the specimens stored in water exhibit considerably lower strength than specimens dry cured. The strength of composites of low glass fibre content, stored for 360 days in water, can decrease to the strength of the cement matrix. This phenomenon is in good agreement with results published abroad, as well as with our results obtained earlier [2]. The obtained results show - more pronounced in the case of dry curing - that with the raise of fibre weight fraction, we obtain an increase in the composite strength. The drop

One half of the manufactured specimens was dry cured, and the second half cured in water.

After casting the specimens were cured in moulds for 48 hours in a moist room /20°C, 90 per cent R.H./, and after the moulds were removed, one half of specimens was stored in dry environment /20°C, 60 per cent R.H./, and the second half was stored in water /20°C/. The specimens were tested at the age of 28, 90, 180, and 360 days. The specimens were tested in flexural strength /three point loading being used/. A 25 kN testing machine with a constant loading rate of 6 mm/min. was applied.

2.3. Results and discussion

The results of investigations carried out are summarized in Fig. 1 to 3. In These figures the relationship between the flexural strength ratio and



Fig. 5 SEM of ESAP fibres in the cement matrix /360 days, water curing, fibres: 4.4%

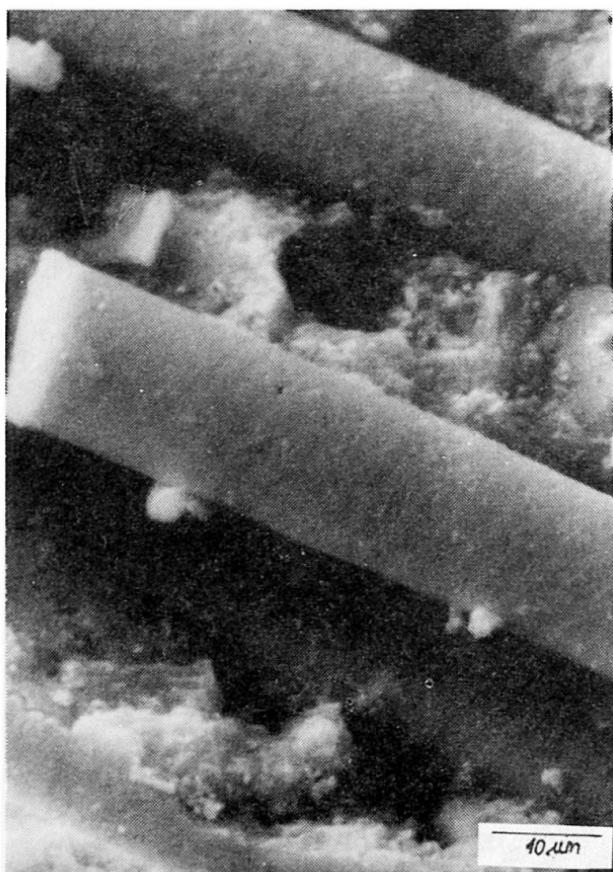


Fig. 6 SEM of SVUS 16 fibres in the cement matrix /360 days, water curing fibres: 4.4%

the cement matrix. Only further investigations, now being carried out, can clear all the problems connected with the alkali resistance of the tested glass fibres.

of strength around the composite age of 90 days, in the case of dry curing /see Fig.1 and 2/, can be effected by non uniform shrinkage, or by partial debonding in the fibre-matrix interface, initiated also by the shrinkage process.

After the strength tests were carried out, samples were taken in order to be investigated under the SEM. According to these investigations we may say that the fibre shape remained unchanged, even in the case of water curing, and that the fibre surface is covered with smaller and larger particles of hydration products /see Fig.4 to 6/.

3. CONCLUSIONS

The investigated glass fibre types have shown a considerably high alkali resistance. Within the testing period of one year glass fibres of low as well as of high zirkonium dioxyd content show similar behaviour in

REFERENCES

1. VANÍŠ M., KOMLOŠ K., Contribution to the Methods of Determining the Chemical Resistance of Glass Fibres in Alkaline Media. Proceedings - Durability of Glass Fiber Reinforced Concrete, Symposium, Chicago, November 1985, pp.222-229.
2. VANÍŠ M., KOMLOŠ K., Vlastnosti sklenného vlákna typu Rezal, odolného voči alkalickému prostrediu. Sklář a keramik, 36, 1986, august, pp.225-230.