

**Zeitschrift:** IABSE surveys = Revue AIPC = IVBH Berichte  
**Band:** 2 (1978)  
**Heft:** S-6: Lamellar trearing

**Artikel:** Lamellar trearing  
**Autor:** Chapeau, W.  
**DOI:** <https://doi.org/10.5169/seals-44329>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 09.04.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

**Lamellar Tearing**  
Arrachement lamellaire  
Lamellares Aufreissen

**W. CHAPEAU**

Dr.-Ing.  
Université de Liège  
Liège, Belgium

**SUMMARY**

This survey, founded on a large literature study [19], gives some examples of practical welded joints in which lamellar cracks were found, describes the mechanism of the lamellar cracking development and deduces the necessary conditions for its appearance. Afterwards, it gives the preventive measures generally used to avoid the phenomenon, describes the destructive and non destructive techniques used to assess lamellar tearing susceptibility and gives, finally, a description of the usual repairing methods. Some necking measurements, carried out on short transverse tensile tests, enable to deduce the minimal values of necking necessary to avoid the lamellar cracking phenomenon.

**RÉSUMÉ**

Cette revue, basée sur une importante étude bibliographique [19], donne quelques exemples de joints soudés où des fissures par arrachement lamellaire furent découvertes, et décrit le mécanisme de développement de la fissure d'arrachement lamellaire et en déduit les conditions nécessaires à son apparition. Elle énumère les mesures préventives généralement mises en œuvre pour éviter l'apparition du phénomène, décrit les méthodes destructives et non destructives utilisées dans le but d'évaluer la susceptibilité à l'arrachement lamellaire et donne, enfin, la description des méthodes habituelles de réparation. Quelques valeurs de striction mesurées sur des éprouvettes de traction prélevées en travers, permettent d'estimer les valeurs minimales de cette striction, nécessaires pour éviter le phénomène de fissuration par arrachement lamellaire.

**ZUSAMMENFASSUNG**

Im vorliegenden Bericht, der sich auf eine umfangreiche Literaturstudie [19] stützt, stellen die Autoren einige Beispiele geschweisster Verbindungen vor, bei denen Lamellenrisse beobachtet worden sind. Sie beschreiben anschliessend den Mechanismus der Entwicklung solcher Terrassenbrüche und folgern daraus die für deren Eintreten nötigen Bedingungen. Man erörtert die vorbeugenden Massnahmen und beschreibt die zur Bestimmung der Neigung zum lamellaren Aufreissen verwendeten Prüfverfahren (zerstörungsfreie und andere) sowie die üblichen Reparaturmassnahmen. Festgestellte Werte der Bruch einschnürung in Dickenrichtung erlauben eine Schätzung der entsprechenden Minimalwerte, bei denen Terrassenbrüche nicht mehr auftreten.



0. INTRODUCTION

"Lamellar tearing is a cracking phenomenon occurring in rolled products stressed normally to the plane of rolling. Though welding is not a necessary condition for its occurrence in practice it is found almost exclusively in welded constructions where the welding is heavy, requiring a number of runs for its placement, where the plates are thick and there is considerable restraint within the joint giving rise to high stress and localized strains across the weld. It is this high stress and localized strains which causes the parent plate material to tear. The type of cracking which can be found in several welded constructions usually, but not exclusively, just beneath the heat affected zone within the parent material is shown in Fig. 1. Clearly to avoid this phenomenon it is necessary to keep shrinkage stresses within the weld to a minimum and the use of a filler material for the electrode which results in a lower yield high ductile deposit is beneficial, especially if the yield point of the deposit is below that of the transverse ultimate strength of the parent material. It is for this reason that in very special circumstances austenitic electrodes may have to be used.

Having become aware of the problem every effort should be made in the detail design of structures to avoid the use of such details for primary load-paths whenever possible".

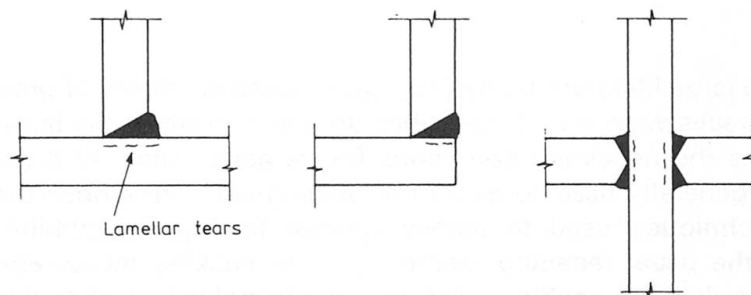


Figure 1. Welded joints susceptible to lamellar tearing.

Figure 2 gives some examples of practical welded joints where lamellar cracking was found [9].

Case	1	2a	2b	3	4a	4b	5
through thickness réduction in area tensile strenght $\frac{R_m th}{R_m}$ ratio	1 1 2 3 5 0,33	5,3 9,9 14,4 0,70 0,90	17 22 27 0,93 0,97	0 0,67	15,8 17,4 0,86 0,89	15,8 17,4 0,86 0,89	0,2 2,3 5
thickness tension	8mm $\sigma_{sh}$	50mm $\sigma_{sh}$	50mm $\sigma_{sh}$	10mm $\sigma_{sh}$	88 112 $\sigma_{sh}$	88 112 $\sigma_{sh}$	20mm $\sigma_{sh}$
steel type	A 42	A 52 BS 4360 grade 50 b	A 52 BS 4360 grade 50 b	A 283 C A 283 C	A 283 C A 283 C	A 283 C A 283 C	W St E 47 Normal
steel strength analysis	Re = 280 310 Rm = 420 430 not told	Re = 352 377 Rm = 521 532 not told	Re = 352 377 Rm = 521 532 not told	Re = 210 Rm = 385 455 not told	Re = 210 Rm = 385 455 not told	Re = 210 Rm = 385 455 not told	C Si Mn P S 0,14 .39 1,21 .12 .25
consumables discovery restraint	in service on repairing normal	E 344 B 39 6-7 pas...preh 80°C on fabrication	E 344 B 39 6-7 pas...preh 80°C on fabrication	CO <sub>2</sub> welding on fabrication	CO <sub>2</sub> welding on fabrication	MMA	Cr Ni V Cu Nb .21 .69 .06 .51 .016 during fabrication



Case through thickness reduction in area tensile strenght $\frac{R_m th}{R_m}$ ratio thickness tension	6 teared 23 23 17 26 23 10 92 50mm ∩ sh	7 teared 0 (specimens) 48 71 11,5 - 32,5 ∩ sh	8 teared 36mm ∩ sh	9 teared 70 or 65 or 50	10 teared 55mm	11 teared 80mm
		Longitudinal stiffeners 				
steel type steel strength analysis consumables discovery restraint	SIS 142106 Normaliz. Re = 380 Rm = 530 C Si Mn P S .16 .47 1.33 .30 .013 Nb N .026 .005 on fabrication very high restraint	DnV grade spécial Re=390 Rm 490 590 C Si Mn .17.22 24.43 12.17 P .026 S 0.45 OK 48 00 on fabrication	D 36 Normalized Re= 390 Rm = 520 C Si Mn P .15 .25 1.26 .020 S Nb .026 .045 on fabrication	MR St 37 2N MMA basic elec trodes	A St 41 MMA	A 37 S C C S P .11 .020 .025 CO2 in root run others MMA in fabrication rut

Case short transverse réduction in area tensile strenght $\frac{R_m th}{R_m}$ ratio thickness tension	12 teared 18 mm 18mm ∩ sh	13 teared 40mm	14 teared 50mm	15 teared 50mm	16 teared 17 120mm
steel type steel strength analysis consumables discovery restraint	HT 50 normalized MMA interpass 110°C eye on fabrication	HT 50 Re=420 Rm = 550N/mm <sup>2</sup> C Si Mn P S Nb .17 .39 1.36 .021 .020 .030 1.MMA 2.3.CO <sub>2</sub> 4 SAW naked eye on fabrication	MS as rolled MMA interpass 100 C E7016 naked eye on fabrication	HT 50 as rolled MMA 100 C ASTM 7016 dried naked eye on fabrication 25000kg/mm <sup>2</sup> mm	HT 50 normalized Re= 360 Rm = 530 C Si Mn P S .17 .46 1.41 .021 .012 V: .07 eye during gas heating



Case	17	18	19	20	21	22
short transverse réduction in area tensile strenght $\frac{R_m \cdot th}{R_m}$ ratio thickness tension	not teared $> 20$	teared	teared	teared 0 0 89	teared 16 83	teared 25 15 25 20 11 15 56 81 74
	32mm $\sigma_{sh}$	30mm $\sigma_{sh}$	25mm $\sigma_{sh}$	14mm $\sigma_{sh} + M_d$ dynamic	70mm $\sigma_{sh}$	20mm 30mm
steel type steel strength analysis consumables discovery restraint	HT 50 normalized S .006 Ew 44 interpass temp. 150 MMA E 7016	AE 36 D au Nb interp. basic dried eye after stress relief stress relief crack?	AE 36 D au Nb preheat 150 basic elect. on fabrication by ult	R St 37 2 D N 17100 Re = 260 Rm = 420 C Si Mn P S N .12 .31 .39 .018 .31 .007	Re = 270 Rm 440	Re = 330 400 Rm = 513 515 C P .11 .14 .025 .029 S .019 .021

The mechanism of the lamellar cracking phenomenon is described on figure 3 in the general case of initiation and propagation in the parent metal [1].


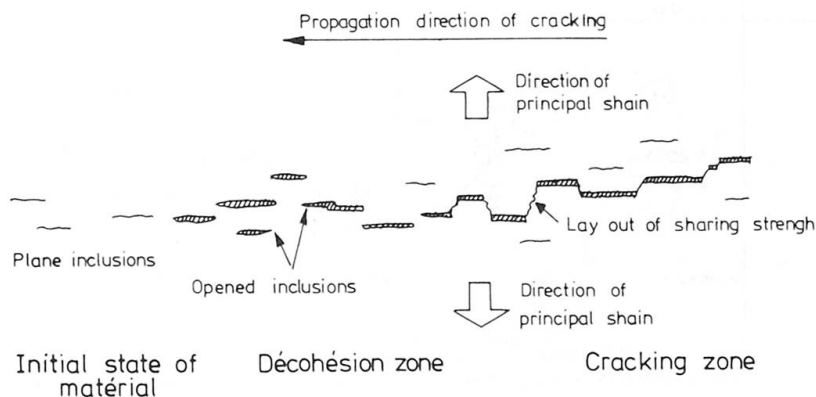


Figure 3. Mechanism of initiation and propagation of lamellar cracking.

The base metal, susceptible to the phenomenon, contains generally plane inclusions whose main plane is parallel to the rolling plane. In highly restrained welded joints, the shrinkage during cooling involved not only high residual stresses but also very important localized strains as shown on figure 4. This figure, taken from [2], shows the strain repartition under a K butt joint

symmetrically welded. In spite of the precautions used to limit the value of

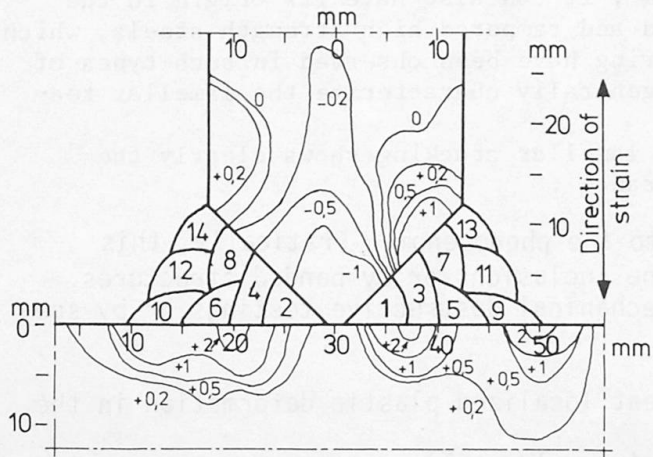

Strain distribution in a T-butt weld measured by a Moiré fringe technique. Strains in (%)

Figure 4

the strains, these reach a measured maximum of 2 % very near to the weld, considerable strains, up to 0,5 %, from 7 to 10 mm. deep where also found in the plate susceptible to lamellar tearing. The effect of this strain accumulation is to open the plane inclusions and, if the parent metal does not possess a sufficiently good short transverse ductility to permit strain concentrations at the end notches of the opened inclusions a characteristic strains line crack propagation occurs. Typically lamellar cracks are given in the nexts photos |3, 4|.


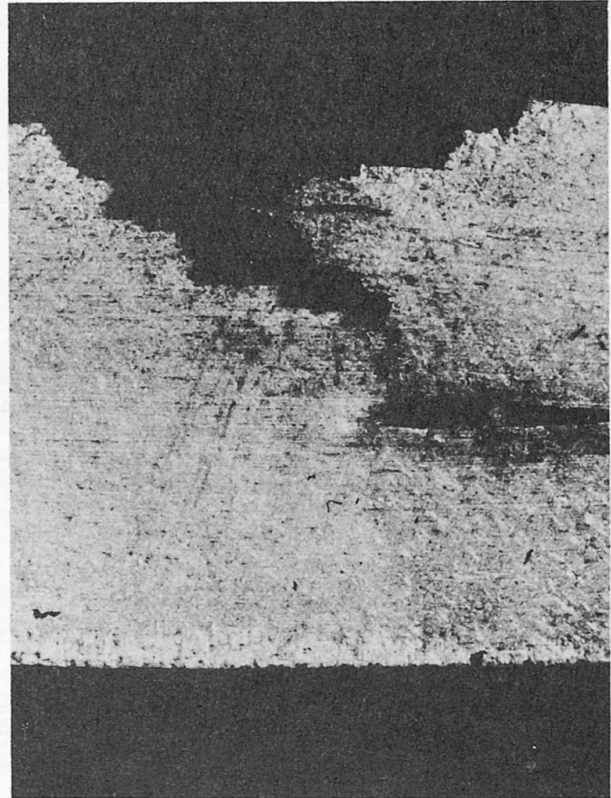


Figure 5. Examples of typical lamellar cracks and ruptures.

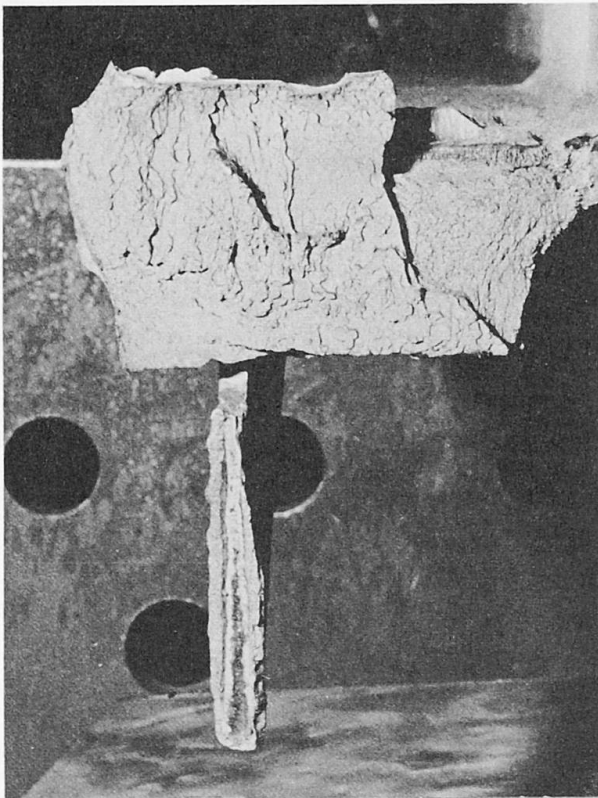

In exceptional cases, cracking by lamellar tearing can also be initiated in the heat affected zone by a preliminary cold crack ; it can also have its origin in the banded structures of low alloyed quenched and tempered high strength steels, which explains that some cases of lamellar tearing have been observed in such types of plates having no plane inclusions which generally characterize the lamellar tearing susceptibility [5].

The described mechanism of initiation of lamellar cracking shows clearly the three necessary conditions for its appearance :

1. The parent metal must be susceptible to the phenomenon. Practically, this susceptibility is revealed either by plane inclusions or by banded structures. This susceptibility can be detected by mechanical destructive testings or by special ultrasonic scanning techniques.
2. A highly restrained joint leads to great localized plastic deformation in the parent metal, close to welded joint. The strains result from the shrinkage during weld cooling ; they are the greater the restraint and weld metal volume are higher.
3. The susceptibility to lamellar cracking increase when the shape of the groove permit the development of the shrinkage strains normally to the rolling plane.

A shrinkage normal to the rolling plane is also normal to the main plane of the inclusions, this makes easier the inclusion opening and, in the same way, lamellar cracking initiation. Preventive measures used to limit the risk of lamellar tearing concern on the one hand the design and execution of the welded joints and, on the other hand, the use of non susceptible materials in the cases of T, L and cruciform joints.

## 1. PREVENTIVE MEASURES.

### 1.1. Joints design.

Joints design to limit lamellar cracks consists in the limitation of plastic strain which occurs near the highly restrained weld and in avoiding a weld shrinkage normally to the main plane of inclusions.

#### 1.1.1. Strain limitation

a) by reduction of the weld metal.

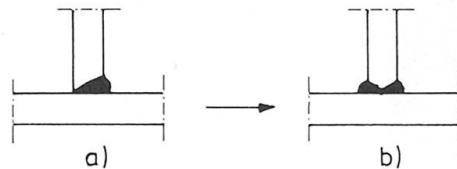


Figure 6

b) by reduction of the localization of the plastic strains.



Figure 7



The use of fillet weld in place of V groove weld assume, of course, that the volume of the weld metal is not greater in figure 7 b than in figure 7 a.

c) by the use of a shaped groove which limits the component of weld shrinkage normal to the rolling plane.

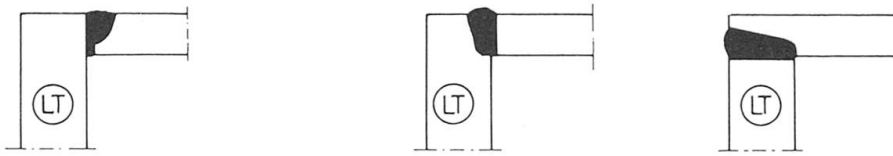


Figure 8

ⓁT plate susceptible to lamellar tearing.

#### 1.1.2. Local use of non susceptible material.


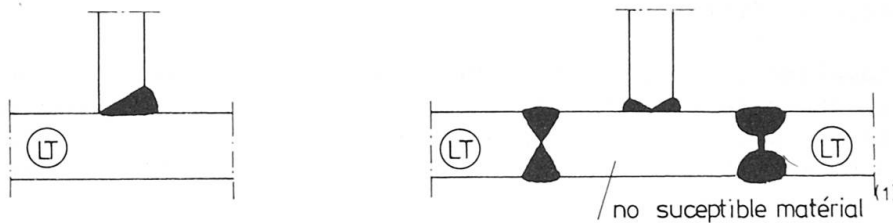


Figure 9

(1) Well known non susceptible steels are Z steels and forged steels.

As shown on figure 10, welded tube joints can also reveal lamellar cracks. The I.I.W. proposes in Doc. IIW XI-286-73 some examples of welded tube joints to avoid lamellar cracking. This figure represent a longitudinal section of the tube [6]. The symbol ● concerns the tubes for which lamellar cracks influences the joint behaviour, the symbol ○ represents the opposite behaviour.



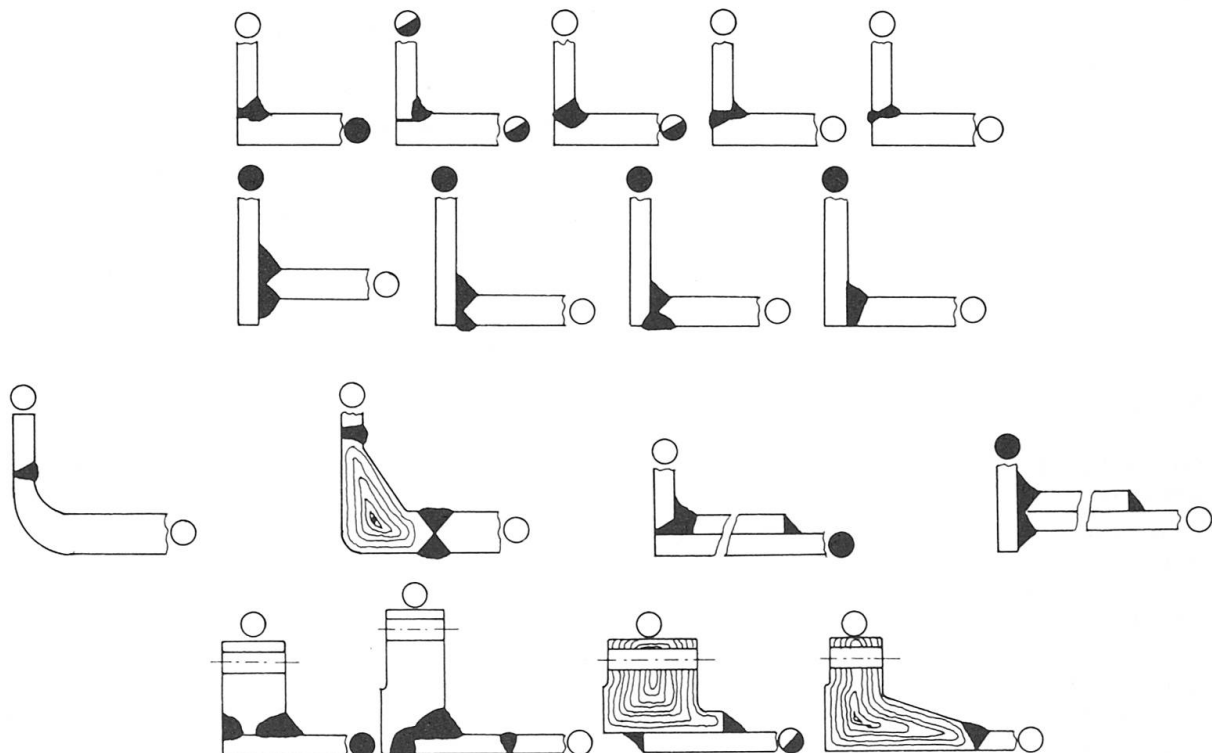

## 1.2. Procedure and Practical welding conditions.

The influence of the procedure and of the practical welding conditions on cracking by lamellar tearing is mentioned in almost all studies concerning this phenomenon [7], although it seems that no systematic investigation has already been made to date.

### 1.2.1. Influence of the welding process.

The influence of the welding process on the risk of lamellar tearing has not been proved; at the very most, it is reported in the specialized literature that the use of low hydrogen electrodes and fluxes can help to diminish the risk of lamellar cracking without eliminating it completely [7]. This can be explained on the one hand by the influence of hydrogen on the cold crack appearance which can initiate lamellar tearing and, on the other hand, by the diminution of the notch toughness in presence of hydrogen [8].

### 1.2.2. Influence of filler metal.

The risk of lamellar tearing can be limited by the use of a low yield and ductile filler metal. The effect of the use of such a filler metal permits to localize the strains in the weld metal and to avoid strains in the parent metal. The use of nickel and nickel alloys as filler metal is generally recommended for critical joint welding.

### 1.2.3. Influence of welding technology.

#### a) Surfaces "buttering".

The so called "buttering" technique consists to lay, before effective welding, a 5 to 10 mm. low yield and high ductile filler metal on the surface of the piece susceptible to lamellar cracking.

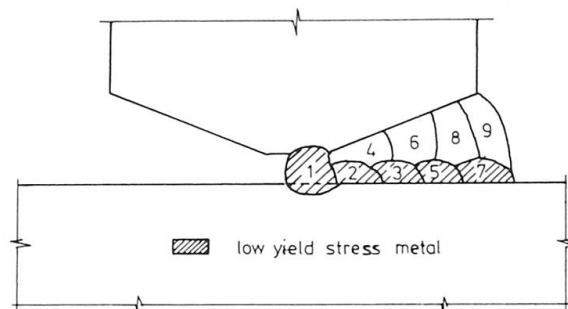


Figure 11 "Buttering" technique

#### b) Symmetrical welding.

In fact, this technique permits a certain uniformisation of the restraining strains under the welded joint. This limits the value of localized strains. Nevertheless, figure 4 shows that, in all cases the restraining strains remain very high.

#### c) Other methods.

Other methods like preheating, hammering or intermediate relaxing can be used to limit the risk of lamellar tearing but they do not permit its complete elimination [7].



## 2. ASSESSING THE LAMELLAR TEARING SUSCEPTIBILITY.

### 2.1. Non destructive methods |9|.

Ultrasonic testing of plates is widely used to reveal and localize lamination and large inclusions. The extension of destructive techniques to assess the risk of lamellar tearing has been done. The best results have been obtained by special techniques using high frequency probes : measurements of the fading out or attenuation of the signal at multiple backwall echos and defect area integrating test with water immersion seems to be given the best results |9|. Extensive conventionnal ultrasonic testing is not useless in this respect, the experience is that tearing incidents have been reduced by about 40 % applying such expensive techniques |7-10|. From a safety joint of view such extensive conventionnal ultrasonic scanning is not sufficient.

If high frequency improves the testing sensibility for attenuation measurements, the determination of acceptance levels, in relation to the risk of lamellar tearing seems somewhat difficult because the metallurgical grain dimensions becomes a signifiant parameter of this attenuation |11|. The ultrasonic testing with attenuation measurements can detect local variations of inclusion distribution and thus determine the most susceptible part of the plate where destructive testing can be made to assess safety the risk of lamellar tearing of the tested plate.

### 2.2. Destructive methods.

Generally the proposed destructive testing to characterize the risk of lamellar tearing measure the through thickness properties of the material, it seems that the deformation measures are the most adequate in this respect. Two types of tests can be distinguished : test with and without welding. Among the test without welding, which permits a classification of parent metals regarding the risk of lamellar cracking, the I.I.W. test |12|, the slice bend test |13|, the Brodeau test |14| and the bend test on notched test pieces |15| can be mentioned. Among the tests with welding, the most usual are the I.I.W. test on modified test piece, the CRANFIELD or NICHOLS-ELLIOT test |15|, the FARRAR test |14| and the LEHIGH test |18|.

### 2.3. Description of the destructive tests.

#### 2.3.1. Tests without welding.

Among the tests without welding, a special attention must be given to the I.I.W. test because it has obtained the agreement from international specialists.

The I.I.W. proposes two types of test according to the plate thickness : a test without welding and a test which use welding. Test pieces of the first type are recommended for plates having a thickness over 25 mm. This is a cylindrical tensile test piece machined in a throughthickness direction in the tested plate : figure 12 gives its geometry.

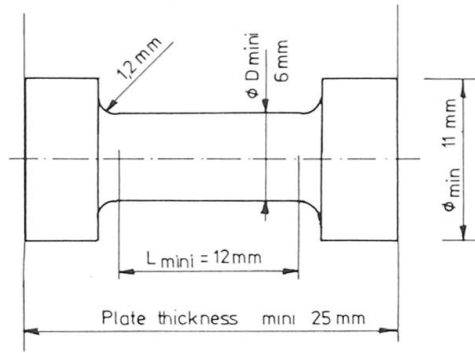


figure 12

The values represented on this figure are minimum values ; the condition  $L > 2 D$  must always be observed. In the case of the tested plate have a thickness up to 25 mm. the testpiece is machined out of the plate to which extensions have been welded by stud or friction welding (figure 13) or out of a cruciform-welded test (figure 14).

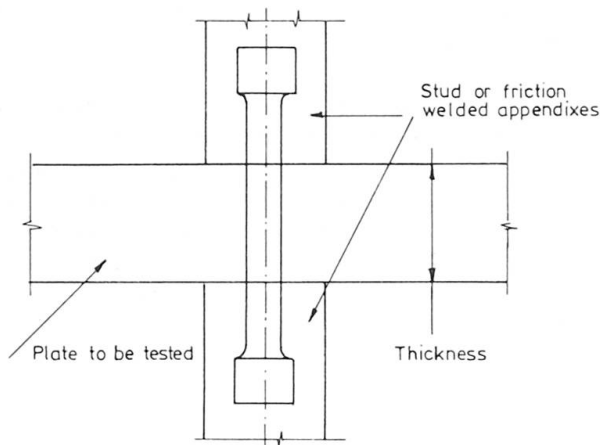


figure 13

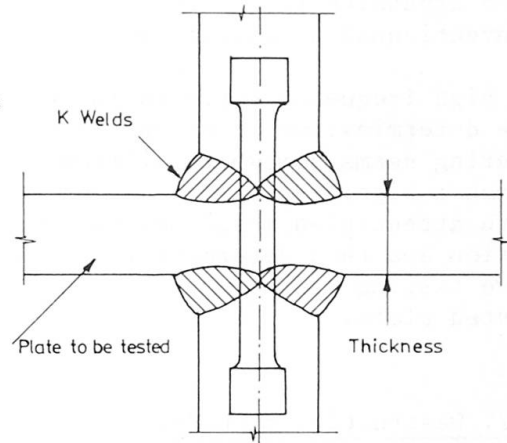


figure 14 a

Figure 14b represents the stages of machining when cruciform welded specimens are used. In this last case special precautions must be taken to avoid cold cracks. The technology of the I.I.W. test on welded joint try to minimize the effects of this welding on the lamellar cracking. The parameter measured to characterize the risk of lamellar tearing is the pourcentage reduction of area Z. This is the ratio between the ultimate variation  $S_o - S_u$  of a transversal cross-sectional area  $S_o$  expressed as a percentage :

$$Z = 100 \frac{S_o - S_u}{S_o} \%$$

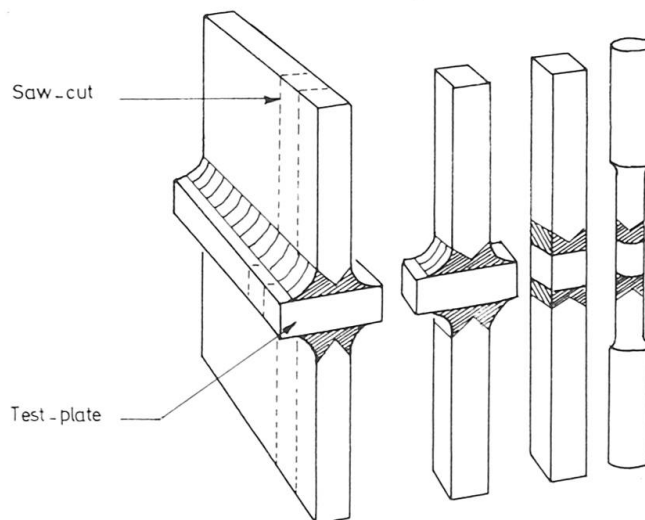


figure 14 b

### 2.3.2. Tests with welding.

The so called test with welding are tests which uses the restraining effect of welding to induces the stresses and strains in the plate susceptible to lamellar tearing. No one of these tests seems to have been generally accepted, anyway the most usual, in our opinion, are described afterwards.

#### 1. Cranfield or NICHOLS-ELIOTT test [15].

The test piece used is described on figure 15. The stress acting normally to rolling plane is essentially due to the weld shrinkage effect.

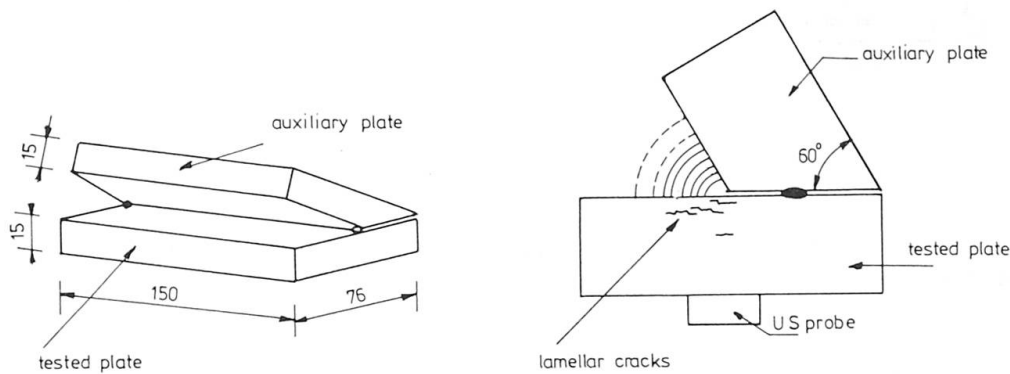


Figure 15

An auxiliary  $60^\circ$  beveled plate is used. The fillet weld is deposited horizontally with covered low hydrogen electrodes. The bevel angle chosen permits the initiation and propagation of lamellar tearing in the test plate. The electrode diameter and, of course, the welding current increase progressively when the welded joint is progressively filled. After any run, the complete cooling of the joint is necessary and a conventional ultrasonic scanning is performed to detect the lamellar cracks. If no cracks are discovered, a new run is welded, if cracks are found, the auxiliary plate is rocked to make the cracks visible.



2. Window test [16]

The test method used is briefly described on figure 16. A massive plate with a machined window is used, the test piece is put in this window and welded with massive plate to make a very highly restrained welded joint for which the shrinkage kage does normally to the rolling planes of the tested piece.

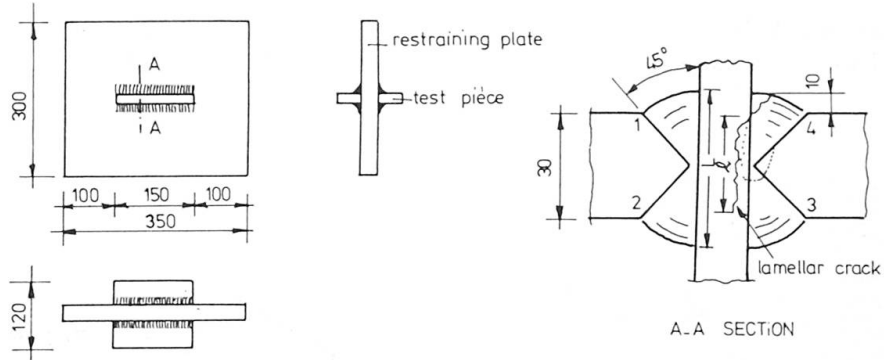


figure 16

The lamellar tearing susceptibility is characterized by  $\left(\frac{\sum \ell}{\Sigma L}\right) 100 \%$ , where  $\ell$  and  $L$  are defined on the figure.

3. FARRAR test [14].

The test piece used in the FARRAR test is machined out a half V (45°) groove weld as shown on figure 17

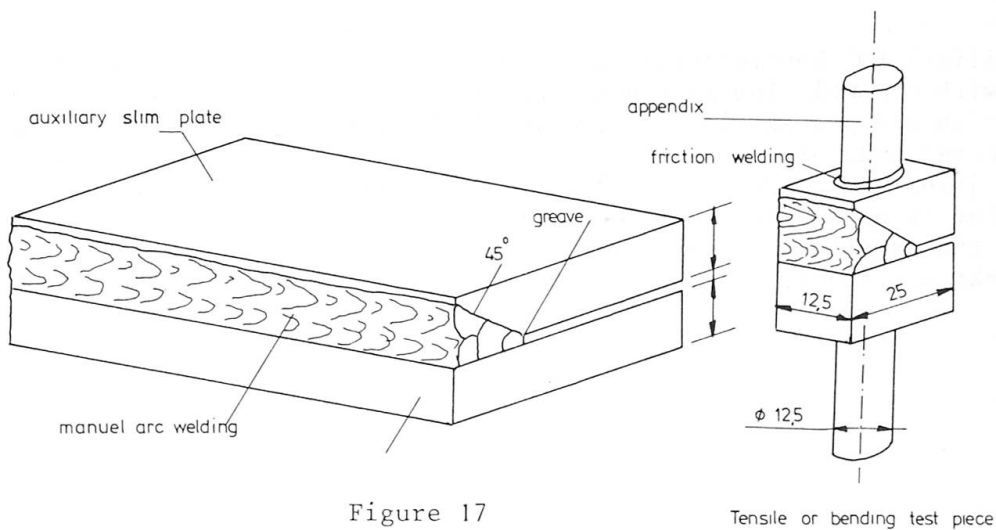


Figure 17

Tensile or bending test piece

This machined piece is finished by adding, generally by friction welding, a double appendix to complete the test piece for a tensile or bending test.

#### 4. LEHIGH test.

The test method used in the LEHIGH test is described on figure 17.

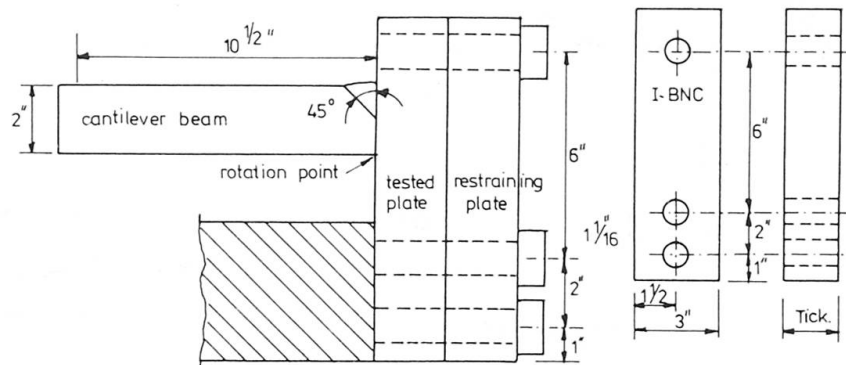


Figure 17

A cantilever beam is welded with a half Y ( $45^\circ$ ) groove weld on the test plate. A known external force is applied on the beam to initiate lamellar tearing. The lamellar cracks are detected by conventional ultrasonic scanning of the tested plate. The main advantage of this test is its very easy practical interpretation.

#### 2.3.2. Conclusions.

The main disadvantage of destructive testing is the obligation to measure the risk of lamellar tearing of a localized part of the piece that will not necessarily be used afterwards in the construction. From a safety point of view it is thus necessary to machine the test pieces in the most susceptible part of the structural element which can be localized by ultrasonic methods.

### 3. REPAIRING.

#### 3.1. Detection of lamellar cracking.

The lamellar cracks propagate parallel to the rolling plane ; the most appropriate non destructive techniques for its detection is conventional ultrasonic scanning ; angle probes ( $45^\circ$  ou  $70^\circ$ ) must be generally used. In certain cases straight beam transducers can also be used. Figures 18 a) an b) show the techniques in both cases. Only the straight beam transducer permits a good localisation of the lamellar cracks by using 20 dB probes. In certain cases, it can be useful for small defects to make calibration against small flat bottomed holes [9].

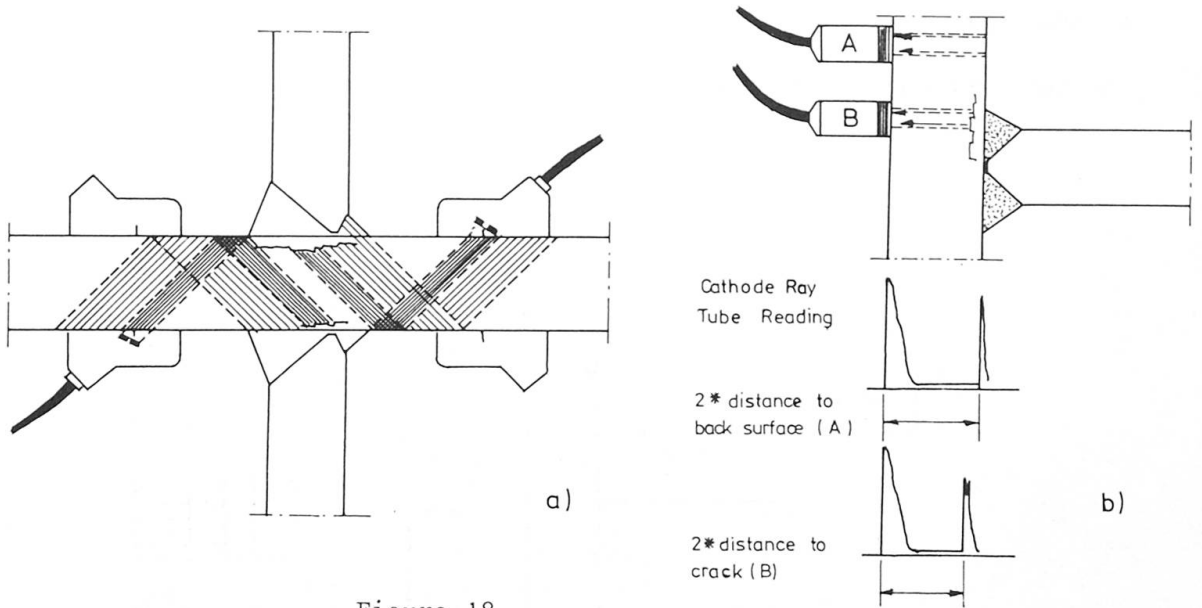


Figure 18.

Non destructive radiography or grammagraphy test do not permit a safe detection of such cracks because their orientation.

3.2. Repairing techniques.

The repairing techniques used begin, in all cases with the removal of the cracked zone of the lamellar teared piece. Afterwards, this removed part of the piece is filled with low yields weld metal, what is called "buttering", or a new piece, which does not risk lamellar tears, is butt welded in place of the removed piece. This two techniques are respectively represented on figure 19.

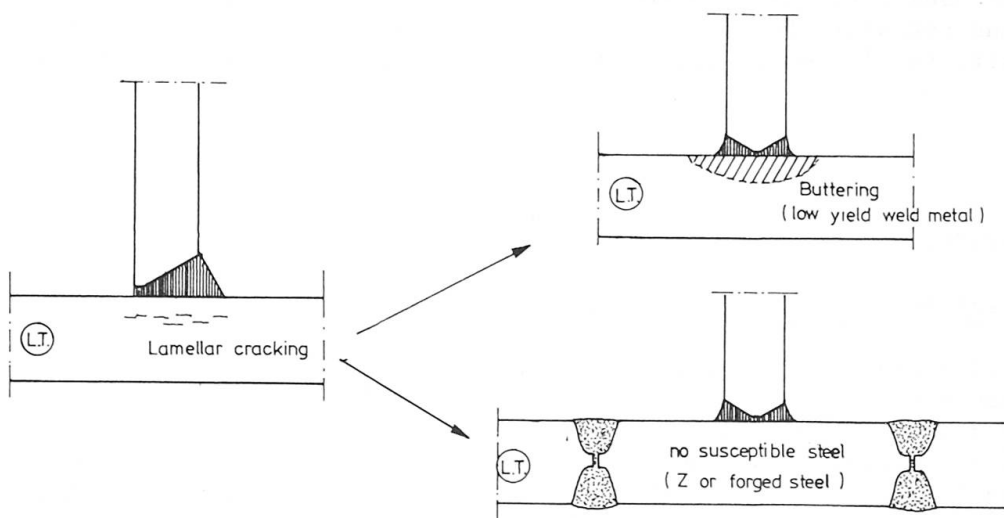


Figure 19

The high residual stresses that appear with the use of this methods require the relaxation of the repaired joint or, in case of buttering, intermediate relaxations during repairing.

#### 4. CONCLUSIONS.

The risk of cracking by lamellar tearing must always be considered by the designer of a welded structures, especially when this structures contains welded T, L or cruciform joints of elements whose thickness exceeds 25 mm. In general, for thickness up to 25 mm., the risk of lamellar tearing is very small, but special attention is necessar when quenched and tempered high strength steel is used. The banded structures, which are frequent in these type of steel, can initiate this cracking phenomom.

The prevention of this risk must be done :

1. At the level of the general design, which must be such as to reduce to a minimum the stressing of the rolled products normally to the rolling plane. The external stresses are not at the origin of the phenomom but they can help to propagate the cracking, especially in the case of fatigue.
2. At the level of the joint design, by adhering to the rules given in section 1.1., which concern mainly the strain limitation in the parent metal and the local use of no susceptible materials. In certain specific cases of tube joints the I.I.W. recommendation can be adopted [6].
3. At the level of joint welding, by choosing a welding procedure minimizing the strains caused by the restraining effects, by using systematically symmetrical welding, by depositing the minimum weld metal and by using filler metal whose mechanical characteristics although being ductile arc, nerverttheless, compatile with the service conditions of the structures.
4. At the level of the choice of the parent metal, by imposing a minimal value of the reduction in a measured in a short transverse tensile test. The literature survey, taken from [9] and summarized on figure 20, shows that this minimal value is a function of the type of welded joint. It seems that a safe valeur for T joint (figure 20 a, b) is 15 % of reduction in area and for cruciform joint (figure 20) this safe value is 30 %

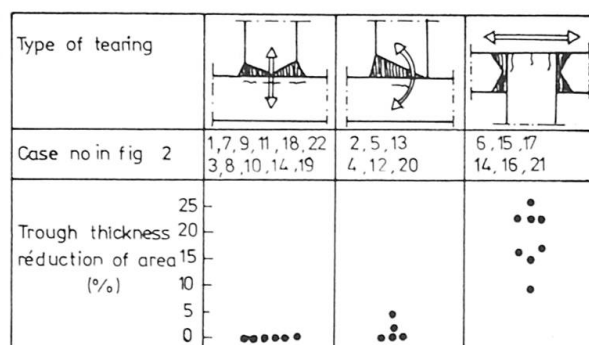


Figure 20

#### ACKNOWLEDGEMENT

This State of Art Report was written by Dr. W. Chapeau of the University of Liège, under the supervision of Professor Ch. Massonnet, Chairman of the Working Commission II of IABSE. We wish to extend our sincere thanks to those who have contribu-



ted actively to the elaboration of the present document and especially to Professor Ben Kato from the University of Tokyo and Dr. Schönherr, from the Bundesanstalt für Materialprüfung (BAM). We must also mention Ir. A. Granstöm and Dr. Alpsten the papers of which /9, 19/ were largely used in the elaboration of some paragraphs of this State of Art Report.

Thanks also due to Professor W. Soete, from the University of Gent, for its useful remarks.

#### REFERENCES

1. SAKLIN, R.: Les fissurations dans les soudures. Institut Belge de la Soudure D/1972/083/10 Bruxelles 1972.
2. CARGILL, J.: Measuring strains under welds using the Moire fringe technique. Naval Construction Research Establishment Report R. 551, 1968.
3. Institut Belge de la soudure - L'arrachement lamellaire. IBS-Doc. 9-10-146-76, 1976.
4. ECCS - Second International Colloquium "Stability of Steel Structures", Final Report, University of Liège, avril 1977.
5. CHAPEAU, W.: Suceptibility of lamellar tearing in quenched and tempered high strength steels. ECCS Second International Colloquium, Liège 1977.
6. International Institute of Welding - Weld Details - Suitability Grading. Doc. IIS/IIW - XI-286-73, 1973.
7. DEBIEZ, M., GERARD P. et GUICHARD: Etude concertée sur l'arrachement lamellaire et le cloquage dû à l'hydrogène. Institut de la Soudure (Paris) Rapport No. 5873.
8. CHAPEAU, W.E., PIRON, M.E.: A new test to measure the remanent ductility in are welded joints. Symposium Japan Welding Society, 1978.
9. GRANSTROEM, A.: Methods of Assessing the risk for lamellar tearing - the relevance of laboratory tests in assessing the strength of large structures. Swedish Institute of Steel Constructions. Publication 58, October 1977.
10. MEYER, H.J. and al: Report on Inquiry into the Failure of Structural Members Stressed in the Direction of the Plate thickness IIW-DOC-V-479-71, 1971.
11. WETTERFALL, S.E., NILSSON, G.: Kornstorleksmätning met ultrajud. ASEA investigation report V 1118-2224 Västeras 1969.
12. International Institute of Welding - Proposal of Sub-Commission IX-F for a complementary information test for lamellar tearing. Doc. IIS/IIW-455-74, 1974.
13. GRANSTROEM, A.: Tests on full scale structural connections compared with results from various test methods to detect the susceptibility for lamellar tearing. Swedish Inst. of Steel Construction. Progress Report, Report No. 15/6, 1973.
14. DE LEIRIS, H.: L'arrachement lamellaire et l'essai des tôles d'acier dans la direction travers court. Association Technique Maritime et Aéronautique. Session 1971. Doc. IIS/IIW V C 213-71 DF 1971.
15. NICHOLLS, D.M.: Lamellar Tearing in hot rolled steel. British Welding Journal J 15 1968.
16. International Institute of Welding - On the assesement of lamellar tearing suceptibility of Steel Plates. Doc IIS/IIW IX-840-73.
17. RE DOLBY and al: An ultrasonic method for assessing suceptibility to lamellar tearing - development of general techniques. The welding institute international Conference - Quality Control and Non Destructive testing in Welding. London 1974.
18. DATES, R.P., STOUT, R.D.: A quantitative weldability test for suceptibility to lamellar tearing. Welding Research Supplement 481-S, 1973.
19. GRANSTROEM, A., ALPSTEN, G.: Lamellar Tearing - A literature survey, Swedish Institute of Welding Publication no 22 (Jerkonrorets Annaler 1971).