

**Zeitschrift:** IABSE reports of the working commissions = Rapports des commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen

**Band:** 5 (1970)

**Artikel:** Effect of creep on the flexural strength and deformation of structural concrete

**Autor:** Ghosh, S.K. / Cohn, M.Z.

**DOI:** <https://doi.org/10.5169/seals-6925>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 20.08.2025

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## **Effect of Creep on the Flexural Strength and Deformation of Structural Concrete**

Influence du fluage sur la résistance et déformation en flexion des ossatures en béton armé

Der Einfluss des Kriechens auf die Biegefestigkeit und die Verformung von Stahlbetontragwerken

**S.K. GHOSH**

Research Assistant  
Civil Engr. Department  
University of Waterloo, Waterloo, Ont., Canada

**M.Z. COHN**

Professor and Chairman  
Solid Mechanics Division

### **1. INTRODUCTION**

A considerable amount of basic research on the creep laws and factors affecting it has been conducted to-date (1). Comparatively less work has been devoted to the effect of long-term loading on the strength and deformations of beams, columns and frames (2), (3), (4), (5).

Recently various aspects of the non-linear response of structural concrete, including creep, have been investigated both theoretically and experimentally at the University of Waterloo (6), (7), (8), (9), (10). The paper develops an approach to the non-linear analysis of structural concrete (6), (7), with particular reference to the strength and deformations of reinforced concrete beams and long columns under long-term loading. The study is based on a time-dependent stress-strain relation for concrete, in which the creep, lateral reinforcement and strain-gradient are some of the major factors considered. A computer program is used in order to develop a general time-dependent moment-curvature relation, which subsequently is used for the prediction of the long-term load, moments and deflections of beams and slender columns.

### **2. STRESS-STRAIN RELATIONS FOR CONCRETE AND STEEL**

#### **2.1 Time-Dependent Stress-Strain Relation for Concrete in Compression**

The main factors affecting the concrete behavior are the concrete strength, lateral reinforcement, creep, strain gradient, size of

specimens and type of loading. A stress-strain relation for concrete in compression, proposed by Sargin (6), takes all these factors into account by a proper choice of five governing parameters: the concrete cylinder strength  $f'_c$ , the initial Young modulus,  $E_c$ , the ratio of maximum stress to cylinder strength,  $k_3$ , the strain corresponding to maximum stress,  $\epsilon_0$ , and a parameter,  $D$ , that affects the descending branch of the stress-strain curve. By denoting  $A = E_c \epsilon_0 / k_3 f'_c$  and  $x = \epsilon / \epsilon_0$  Sargin's relation is expressed as:

$$\sigma_c = k_3 f'_c \frac{A x + (D - 1) x^2}{1 + (A - 2) x + D x^2} \quad (1)$$

In creep analysis the major factors are the rate of loading, loading duration and age of concrete at the time of loading. Because the control of the rate of loading is very difficult in actual structures, a conventional loading rate has to be adopted. A practical proposal, due to Rüsch (2), is to assume the load is applied in about 20 minutes at constant rates and sustained subsequently up to failure. The loading duration and the concrete age at the time of loading are reflected through parameters  $E_c$ ,  $k_3$  and  $\epsilon_0$ , whose expressions are detailed in (6) and are not reproduced here, for the sake of brevity.

Typical stress-strain relations of concrete cylinders loaded in compression at 28 days are shown in Fig. 1 for three loading durations. As Rüsch has shown (2), the changes in concrete under long-term loads consist of the continued cement hydration and the effects of sustained loads. While an advanced hydration results in a strength increase, sustained load effects result in a reduction of strength and an increase of deformation. Because the influence of  $f'_c$  on  $\epsilon_0$  is negligible, the values of  $\epsilon_0$  in Fig. 1 increase in time, due to the sustained load effects. However, the values of  $k_3$  decrease initially due to these effects, but increase subsequently, when the effect of the continued cement hydration is prevailing.

## 2.2 Time-Dependent Stress-Strain Relation for Concrete in Tension

The behavior of concrete in tension is represented by the following elastic-brittle relations:

$$\begin{aligned} \sigma_t &= E_c \epsilon \quad (\text{for } \epsilon < \epsilon_t) \\ \sigma_t &= 0 \quad (\text{for } \epsilon > \epsilon_t) \end{aligned} \quad (2)$$

where  $\epsilon_t = \sigma_{tr} / E_c$  is the cracking strain and  $\sigma_{tr}$  is the concrete modulus of rupture. The stress-strain relation (2) is time-dependent because  $E_c$  and  $\sigma_{tr}$  are defined in terms of the duration of loading and concrete age at the time of loading.

## 2.3 Stress-Strain Relations for Reinforcing Steels

The stress-strain relations of most reinforcing steels consist of three branches corresponding to the elastic, yield and strain-hardening

ranges, respectively. The following idealized relations, considered applicable to most American steel grades with a yield limit not in excess of 75 ksi, are adopted in this study:

$$\begin{aligned} \sigma_s &= E_s \epsilon & (\text{for } 0 \leq \epsilon \leq \epsilon_y) \\ \sigma_s &= f_y & (\text{for } \epsilon_y \leq \epsilon \leq \epsilon_h) \\ \sigma_s &= f_y + E_h (\epsilon - \epsilon_h) [1 - E_h (\epsilon - \epsilon_h) / 4(\sigma_{su} - f_y)] & (\text{for } \epsilon > \epsilon_h) \end{aligned} \quad (3)$$

where  $E_s$  is the Young modulus for steel,  $f_y$  is the yield limit,  $\epsilon_h$  is the strain at the onset of hardening,  $E_h$  is the strain-hardening modulus and  $\sigma_{su}$  is the ultimate stress. Typical stress-strain curves for steel, Eqs. (3), are illustrated in Fig. 2.

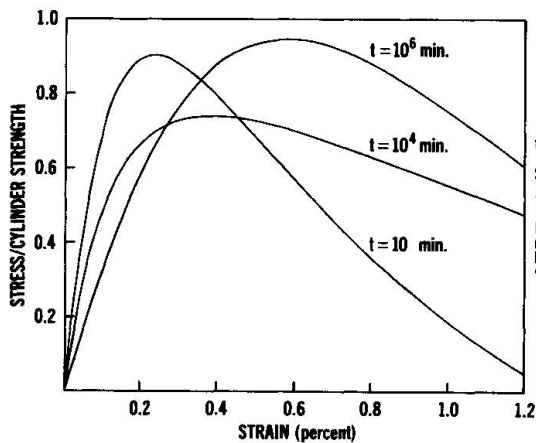


Fig. 1

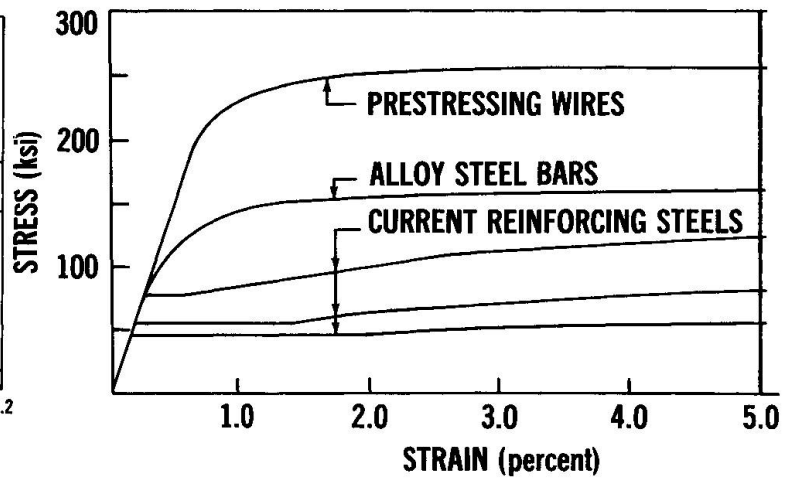


Fig. 2

For high strength steels (alloy steel bars, pre-stressing wires) other equations consisting of an initial linear range and a subsequent non-linear range, can be introduced, without any change in the analysis.

### 3. NON-LINEAR ANALYSIS OF REINFORCED CONCRETE SECTIONS AND MEMBERS

#### 3.1 Section Analysis

With the notations and assumptions in Fig. 3 the force and moment equations of equilibrium for a reinforced concrete section symmetrical about the vertical axis, can be written as follows:

$$\int_0^{kd} \sigma(\epsilon) b(y) dy + A'_s \sigma'_s - \int_0^{kd} \sigma_t(\epsilon) b(y) dy - A_s \sigma_s = P \quad (4)$$

$$\begin{aligned} & \int_0^{kd} \sigma(\epsilon) b(y) (d - kd + y) dy + A'_s \sigma'_s (d - d') - \\ & - \int_0^{kd} \sigma_t(\epsilon) b(y) (d - kd - y) dy = Pe + M \end{aligned} \quad (5)$$

where  $\sigma_s$  is the stress in the compression steel.

The assumption of linear strain distribution implies:

$$\frac{\epsilon_c}{kd} = \frac{\epsilon_s}{kd-d'} = \frac{\epsilon_s}{d-kd} = \frac{\epsilon}{y} = \frac{\epsilon_t}{y_t} \quad (6)$$

Eqs. (1), (2), (3) are used to eliminate  $\sigma_c$ ,  $\sigma_t$ ,  $\sigma_s$  and  $\sigma'_s$ , respectively, and Eqs. (6) to eliminate  $y$  and  $y_t$  from Eqs. (4) and (5). A numerical method is developed to solve Eqs. (4) and (5) simultaneously in the following steps (Fig. 4a.):

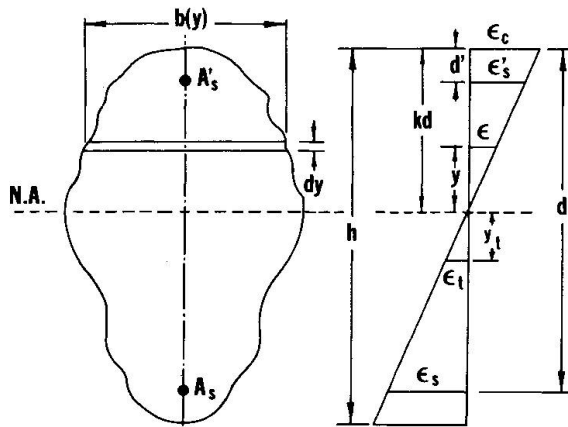


Fig. 3

- (a) Starting from zero increase  $\epsilon_c$  at some chosen interval.
- (b) For any given value of  $\epsilon_c$  find a value of  $k$  by successive approximations such that Eq. (4) be satisfied within a specified tolerance.
- (c) Solve Eq. (5) for  $M$  with the known

values of  $\epsilon_c$ ,  $k$  and the given  $P$ .

- (d) Calculate all other behavior parameters  $\phi$ ,  $EI$ , etc.
- (e) Continue to increase  $\epsilon_c$  up to the value  $\epsilon_{cu}$  at which the moment reaches a maximum. This is the ultimate of the section.

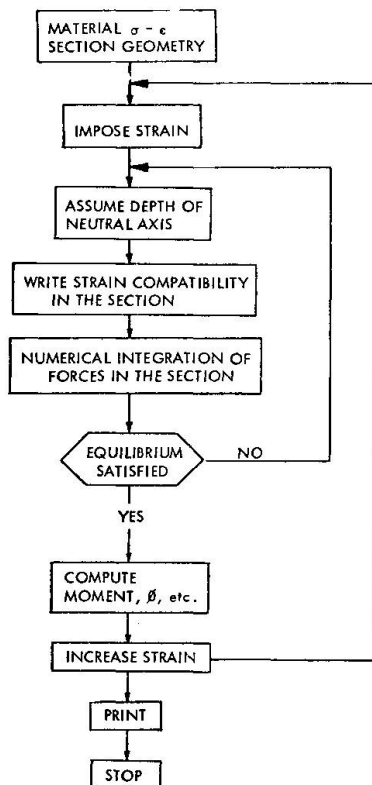


Fig. 4(a)

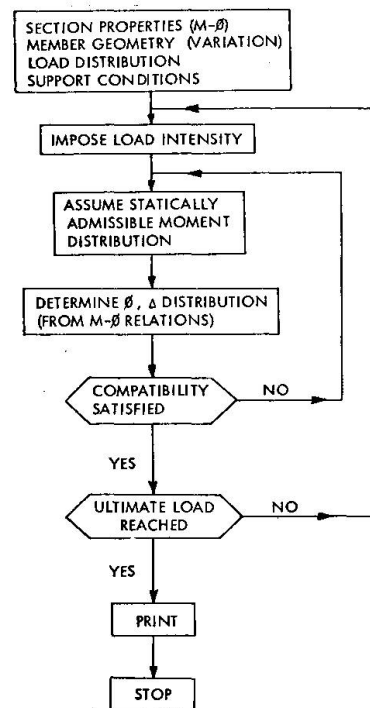


Fig. 4(b)

### 3.2 Member Analysis

The non-linear analysis of reinforced concrete members can be performed by following the steps outlined in the diagram, Fig. 4b. Loads of some known intensity are first imposed on the member and a statically admissible moment field is assumed. The associated curvature field is computed by using the moment-curvature relations derived as indicated in Section 3.1. Slopes and deflections along the member are calculated from the known curvature field and the boundary conditions are checked. A statically admissible moment field that satisfies all boundary conditions is found by trial and error. The intensity of imposed loads is increased at desired intervals and the above process is repeated until the ultimate moment capacity is reached in at least one section along the member.

## 4. TIME-DEPENDENT MOMENT-CURVATURE RELATIONS FOR REINFORCED CONCRETE SECTIONS

The moment-curvature relation of a rectangular singly reinforced concrete section in pure bending has been derived for six different loading durations by using the approach of section 3.1. The results, plotted in Fig. 5, show five sets of curves, each corresponding to a particular steel percentage. It is noted that larger durations of loading have a more favorable effect on the ductility than on the strength of reinforced concrete sections.

The maximum moment,  $M_u$ , and the associated curvature,  $\phi_u$ , are plotted against the time in Figs. 6 and 7, respectively, where each line corresponds to a set of curves in Fig. 5. These diagrams show that time has but a minor influence on the ultimate moments and curvatures. Fig. 6 illustrates the initial stress drop due to sustained load effects and the subsequent stress increase that occurs when the continued hydration of the cement paste becomes predominant. However, from Fig. 7, it is seen that the peak curvatures tend to increase in time because of the sustained load effects.

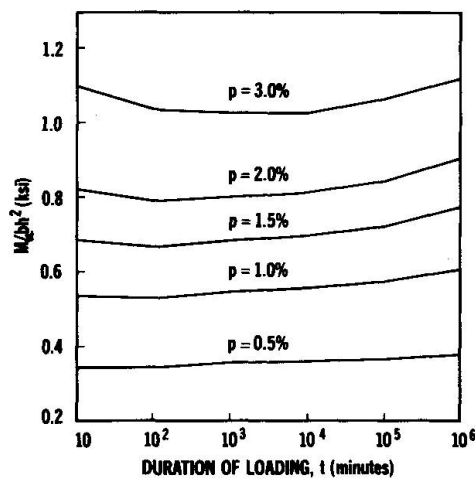


Fig. 6

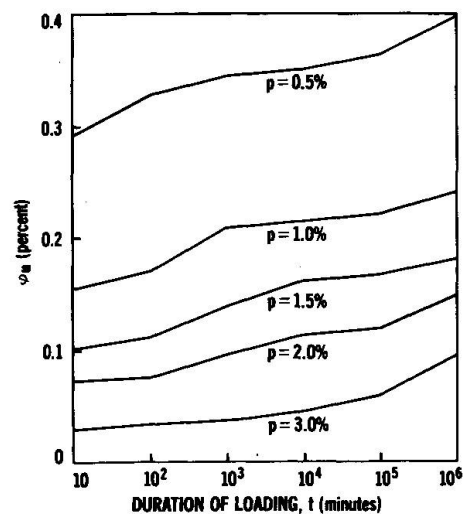


Fig. 7

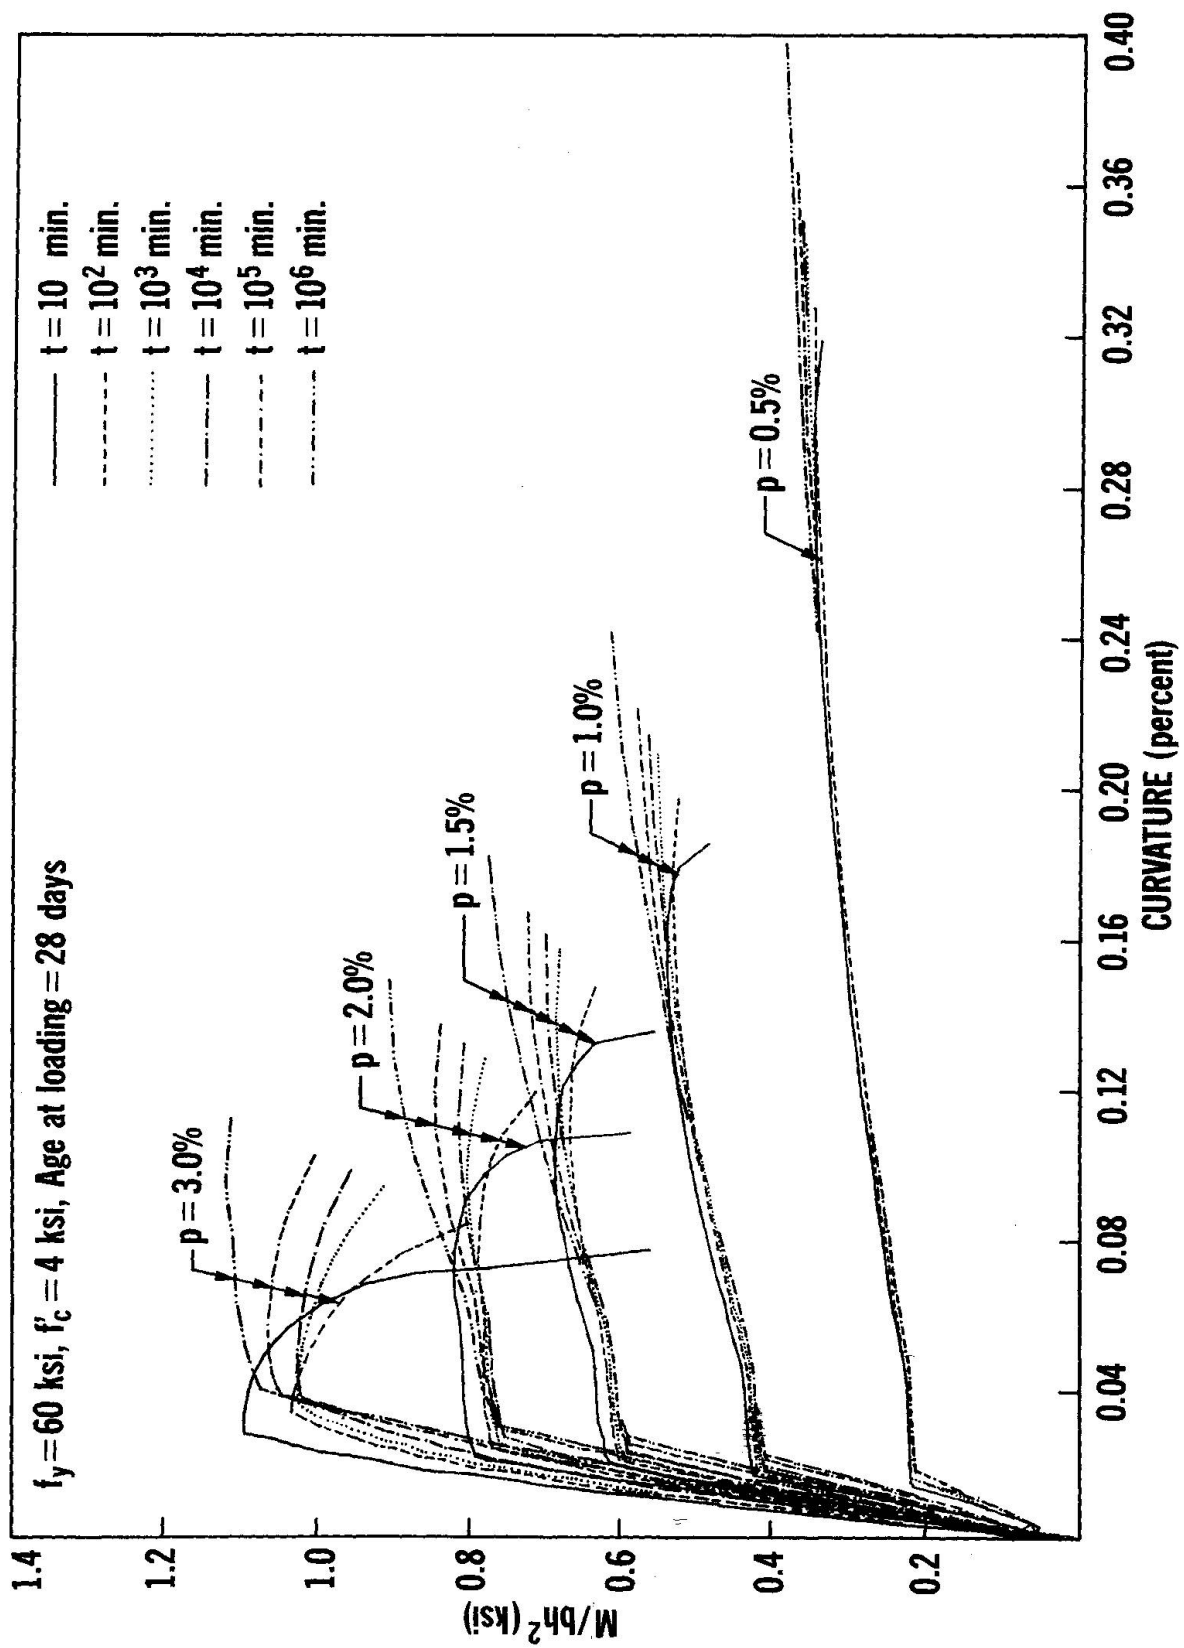


Fig. 5

## 5. TIME-DEPENDENT BEHAVIOR OF A REINFORCED CONCRETE CONTINUOUS BEAM

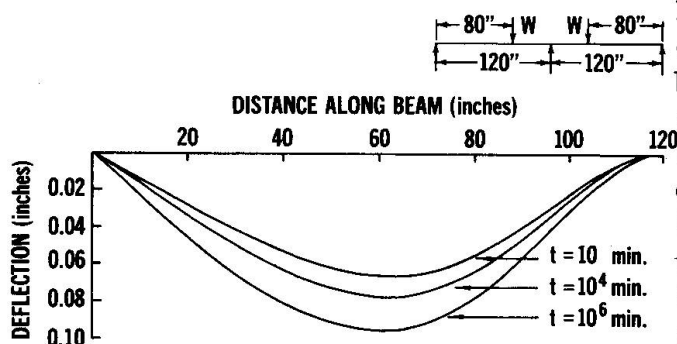


Fig. 8

The analysis described in Section 3 was applied to predict the long-term behavior of a two-span continuous beam previously studied both theoretically (7) and experimentally (9) for short-time loading. The section sizes, steel reinforcing and other details are the same as in Ref. (9). The deflected shape of the beam under service loads is shown in Fig. 8 for loading durations of 10 minutes, approximately one week and two years.

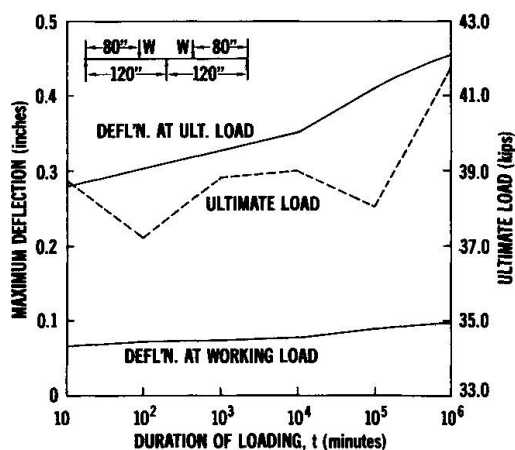


Fig. 9

Assuming the service load to correspond to about one third of the theoretical ultimate load, it is seen from Fig. 8 that the maximum deflection after two-years of loading is about 50% higher than the short-time maximum deflection.

The maximum deflections at service and ultimate loads as well as the ultimate load of the beam investigated are plotted against the load duration in Fig. 9. It is seen that whereas the ultimate load is negligibly affected by creep, the deflections at both service and ultimate loads increase considerably in time.

## 6. TIME-DEPENDENT BEHAVIOR OF A LONG REINFORCED CONCRETE COLUMN

Fig. 10 shows the deflected shapes of a long reinforced concrete column corresponding to loading durations of 40 minutes, 5 days and 70 days. The applied concentric load is 15% of the ultimate load computed by the ACI 318-63 code formula. The geometry, concrete sizes, steel reinforcement and detailing are the same as those used in Hellebrand's tests (10), the results of which are represented by dots in Fig. 10. It is seen that the agreement between theoretical and experimental data is very good.

A similar correlation is noted in the comparison of analytical and test data of mid-height deflections, illustrated in Fig. 11. The maximum deviation between predicted and measured deflections does not exceed 10%.



## 7. CONCLUSIONS

A general, non-linear analysis program, based on a realistic time-dependent stress-strain relation for concrete, was used to predict the behavior of reinforced concrete structures under long-term loading.

The study confirms that creep has little effect on the strength of flexural members and illustrates its major influence on the deflections and strength of slender columns.

Consideration of adequate bond characteristics, and extensions to structures with higher degrees of static indeterminacy, appear to be significant potential developments of the analytical approach presented in the paper.

## ACKNOWLEDGMENTS

The authors are indebted to Dr. M. Sargin, formerly a Post-Doctoral Fellow at the University of Waterloo, for his contribution in the early stages of this work. Also, thanks are offered to Mr. S. Srivastava and Dr. J. Hellesland, of the University of Waterloo, for providing some data of their M.A. Sc. and Ph.D. dissertations, which were used in Figs. 8-9 and 10-11, respectively.

The work reported in the paper is part of a comprehensive investigation on the "Inelastic Behavior of Reinforced Concrete Structures", in progress at the University of Waterloo with the financial support of the National Research Council of Canada, under Grant A-4789.

## REFERENCES

- (1) I. ALI and C. E. KESLER: "Rheology of Concrete: A Review of Research", Bull Eng. Exp. Sta. No. 476, Univ. of Illinois, Urbana, Illinois. March 1965.
- (2) H. RÜSCH: "Researches Toward a General Flexural Theory for Structural Concrete", Journal ACI, Vol. 57, No. 7, July 1960, pp. 1-28.

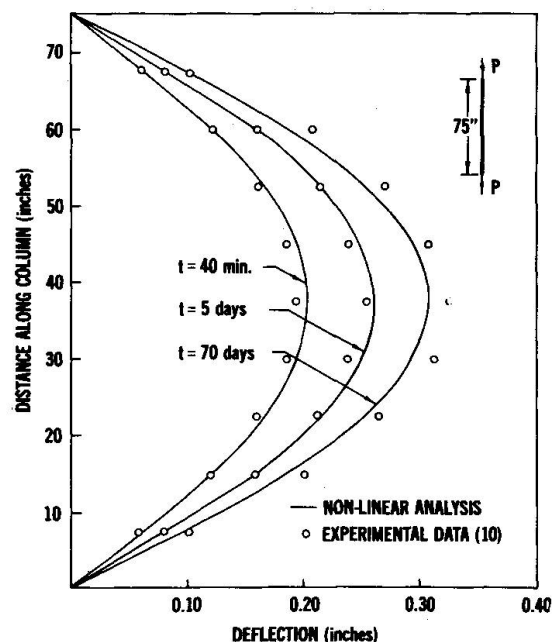


Fig. 10

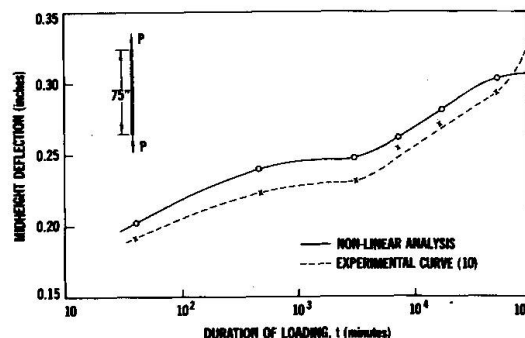


Fig. 11

- (3) H. GESUND: "Shrinkage and Creep Influence on Deflections and Moments of Reinforced Concrete Beams", Journal ACI, Vol. 59, No. 5, May 1962, pp. 687 - 704.
- (4) W.G. CORLEY and M.A. SOZEN: "Time-Dependent Deflections of Reinforced Concrete Beams", Journal ACI, Vol. 63, No. 3, March 1966, pp. 373 - 386.
- (5) L.G. SELNA: "Creep, Cracking and Shrinkage in Concrete Frame Structures", Proc. ASCE, Vol. 95, No. ST.11, Dec. 1969, pp. 2743 - 2761.
- (6) M. SARGIN: "Stress-Strain Relationship for Concrete and the Analysis of Structural Concrete Sections", Ph.D. Thesis, Univ. of Waterloo, Waterloo, Ont., March 1968.
- (7) M. SARGIN and M.Z. COHN: "Analysis of Structures Made of Non-Linear Composite Materials", Proc. Second Canadian Congr. Appl., Mech., University of Waterloo, Waterloo, Ont., April 1969.
- (8) S.K. GHOSH: "A Study on the Effectiveness of Cover and the Effects of Strain Gradient on Concrete Stress-Strain Relationships", M.A. Sc. Thesis, Univ. of Waterloo, Waterloo, Ont., May 1969.
- (9) S.K. SRIVASTAVA: "Moment Redistribution in Over-Reinforced Concrete Continuous Beams", M.A. Sc. Thesis, Univ. of Waterloo, Waterloo, Ont., Sept. 1969.
- (10) J. HELLESLAND: "Long-Term Behavior of Eccentrically Loaded Long Columns", Ph.D. Thesis, University of Waterloo, Waterloo, Ont. May 1970.

### SUMMARY

A non-linear analysis of structural concrete is developed on the basis of a time-dependent stress-strain relation of concrete, in which creep is a major factor, along with the lateral reinforcement, strain-gradient, etc.

A computer program enables the flexural strength and deformation of reinforced concrete sections and moment-curvature relationships under long-term loading to be predicted.

The analytical procedure is applied to the investigation of the creep effects on reinforced concrete beams and columns and corresponding results are compared with some recent experimental data.

## RESUME

En partant d'une relation contrainte-déformation dont les principaux facteurs sont: fluage, armature transversale, gradient de déformation etc., on présente une méthode d'étude du comportement non linéaire des ossatures en béton armé.

La résistance et la déformation à la flexion des sections en béton armé ainsi que les relations moment-courbure sous charge de longue durée sont obtenues à l'aide d'un programme d'ordinateur.

La méthode est appliquée à l'analyse du fluage sur les poutres et poteaux en béton armé et les résultats sont comparés avec quelques données expérimentales récentes.

## ZUSAMMENFASSUNG

Ein nichtlineares Berechnungsverfahren für Stahlbetonbauwerke ist entwickelt worden aufgrund einer zeitabhängigen Spannung-Dehnungs-Beziehung des Betons, in welcher das Kriechen die Hauptvariabel neben der Schubbewehrung, dem Dehnungsgradienten usw. darstellt.

Zur Ermittlung der Biegefestigkeit und -verformung der Stahlbetonquerschnitte sowie der Moment-Krümmungs-Beziehungen unter Langzeitbelastung ist ein elektronisches Rechenprogramm ausgearbeitet worden.

Das Berechnungsverfahren wird für die Untersuchung der Kriechwirkung von Stahlbetonbalken und -stützen angewendet, und die Ergebnisse sind mit vorliegenden Versuchsdaten verglichen worden.