

**Zeitschrift:** IABSE reports of the working commissions = Rapports des commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen

**Band:** 12 (1973)

**Artikel:** Experimental studies concerning steel structures, their elements and their connections

**Autor:** Fujimoto, Morihisa / Naka, Takeo

**DOI:** <https://doi.org/10.5169/seals-12954>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 31.03.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## Experimental Studies concerning Steel Structures, their Elements and their Connections

Etudes expérimentales concernant les structures en acier, leurs éléments et assemblages

Experimentelle Untersuchungen an Stahlbauten, ihren Elementen und Verbindungen

<p><b>MORIHISA FUJIMOTO</b> Professor Tokyo Institute of Technology</p>	<p><b>TAKEO NAKA</b> Prof., Emeritus Tokyo University Tokyo, Japan</p>
---	--

### 1. INTRODUCTION

The objectives of structural design and researches are to reappear the behaviors of a completed structure that may be subjected to dead loads, live loads, wind loads and seismic loads and, based on the above results, are to design and construct safe structures satisfying economical requirements. Although innumerable researches have been carried out in each country and enormous energy has been devoted to these objectives, all of the problems have not been necessarily solved to date, mainly because the natural phenomena such as earthquakes and natural winds have to be dealt with and eventually they include many indefinite factors. Recent researches, however, have been making a remarkable progress. Especially, well-developed technics of numerical analysis utilizing digital computers give us precise informations about deformations and stresses of detailed structures at the design stage\*<sup>1</sup>, and particularly they brought forth dynamical elasto-plastic design method which made possible to construct high-rise buildings in the cities in Circum-Pacific seismic zone\*<sup>2</sup>.

The behaviors of structures at a very disastrous earthquake are dynamical random ones; dynamical random elasto-plastic vibrations due to random earthquake motions. Therefore, the action of dynamical random repeated forces should be taken into consideration in order to obtain data such as low-stressed high-cycle fatigue or high-stressed low-cycle fatigue necessary in estimating the behaviors of structures. At present, however, quasistatic actions of well-defined repeated force are dealt with in most cases.\*<sup>3</sup>. In this paper, are reported the behaviors of steel structures, their elements and their connections subjected to such repeated forces.

For the structures which may be attacked by strong winds e.g., typhoon, cyclone and hurricane etc., aeroelastic phenomena such as buffeting, aeolian vibration, galloping and flutter should be taken into consideration. In these cases, the stresses will remain mostly in elastic range, and problems such as low-stress high-cycle fatigue or comfortability of occupants should be considered. Yet, the above problems are beyond the scope of this report.

From the above viewpoint, the behaviors and mechanical characteristics of;

- (1) Materials
- (2) Local buckling of plate elements

\*<sup>1</sup> For instance, see Ref. 1).

\*<sup>2</sup> See Ref. 2), 58), for instance.

\*<sup>3</sup> In Ref. 3), related to earthquake loading, dynamic test by force generator is compared with simulations in quasistatic manner and it is reported that both results show a good agreement.

- (3) Compression members
- (4) Beams and columns
- (5) Mechanical fasteners and welding
- (6) Connections
- (7) Unbraced frames
- (8) Braced frames

under well-defined repeated force are considered in this report.

## 2. MATERIALS

### a. Lowering of proportional limit

Fig. 1 shows stress-strain diagram under repeated tension and compression, of structural steel of which tensile strength is  $50 \text{ kg/mm}^2$ . In the virginal loading, the upper yield point, the lower yield point, the plateau and strain hardening appear clearly. On the other hand, in subsequent loadings, these properties disappear and the proportional limit markedly decreases due to well-known Bauschinger effect.<sup>4),5)</sup> At present on the mechanical treatment of steel structures, steels are usually treated that they possess such prominent properties as yield point, plateau and strain hardening. As far as the repeated loading beyond elastic range is concerned, however, the stress-strain diagram with no plateau should be applied instead. There should be paid more attentions to the possibilities that the lowering of proportional limit in each loading cycle may cause directly structural failure (for instance, buckling), increase of deformations and reduction of rigidity, of structural members, connections and cross section of members.

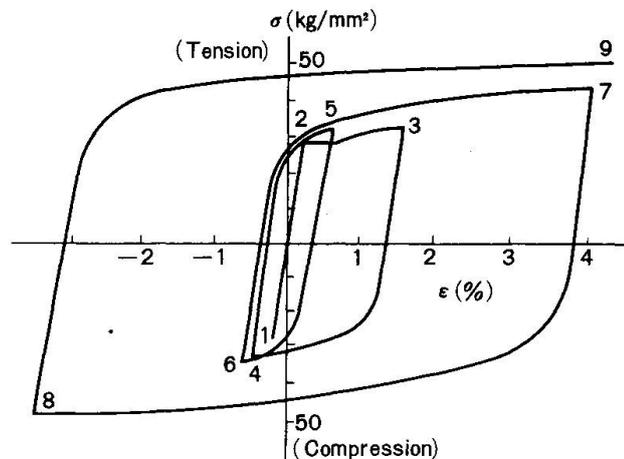


Fig. 1 Stress-Strain Relationship of a Structural Steel SM50 under Repeated Tension-Compression.

### b. low-cycle fatigue

Among the theories of failure of materials, well-known von Mises' criterion of yielding;

$$(\sigma_x - \sigma_y)^2 + (\sigma_y - \sigma_z)^2 + (\sigma_z - \sigma_x)^2 + 6(\tau_{xy}^2 + \tau_{yz}^2 + \tau_{zx}^2) = 2\sigma_Y^2$$

in which  $\sigma_Y$  denotes yielding stress in simple tension, are commonly used for steels. Here, from the viewpoint of plastic hysteresis, it becomes necessary to establish condition of failure of steel in the range of large strains beyond yielding. In other words, this is low-cycle fatigue, which has been remarkably concerned recently. Considering possibility of occurrence of brittle fracture due to applied-tension to the direction perpendicular to that of rolling (Fig. 2)<sup>7)</sup> and considering the influence of plastic strain on the notch toughness of steels\*<sup>1</sup>, it becomes necessary without delay to

\*1 For instance, see Ref. 8). It is reported that the transition temperature by impact test rises as much as  $20^\circ$  in case of 3% of pre-strain.

establish condition of failure of steels under various types of repeated loading.\*1.

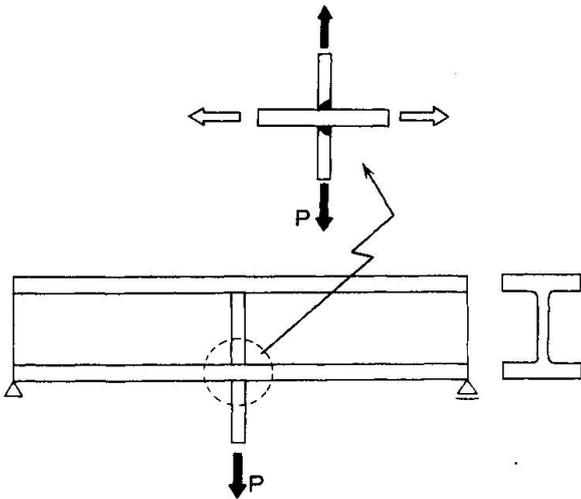


Fig. 2

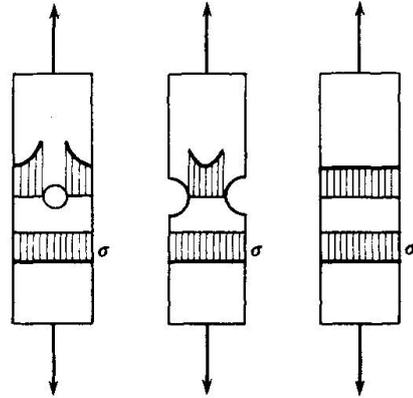


Fig. 3

**c) Elongation capacity**

When tension is applied to the steel members in which abrupt change of sectional area exists as shown in Fig. 3, yielding concentrates on the abruptly changed section and total elongation considerably decrease.<sup>9)</sup> This tendency is notable particularly in case of high-strength steels with high yielding-strength ratio, which has been used widely now. Such structural discontinuities are unavoidable in frames and members and thereby it is necessary to understand their properties including the influences of repeated force, taking account of relationship with section b) above.

**3. LOCAL BUCKLING OF PLATE ELEMENTS**

As for the buckling of the plate elements such as flanges and webs, many researches have been carried out in case of simply compressed loading, as one of the fundamental problems in relation to the rotational capacity of yield hinges in plastic design.\*2. For instance, in case of A-7 ( $\sigma_Y = 33\text{KSI}$ ,  $23 \text{ Kg/mm}^2$ ), the width-thickness ratio requirements of H-shaped section as illustrated in Fig. 4(a) are;

- i) under the condition not to allow for local buckling of flanges to occur until plastic strain reaches the end of the plateau i.e., the starting point of strain hardening,

$$b/t_f \leq 17$$

- ii) under the condition not to allow for local buckling of webs to occur until plastic strain reaches  $4 \cdot \epsilon_Y$  ( $\epsilon_Y = \sigma_Y/E$ ),

$$43 \leq \frac{d}{t_w} \leq 70 - 100 \frac{P}{P_Y}$$

in which,  $P_Y = \sigma_Y \cdot A$ , where A denotes sectional area of H-shaped section.

The local buckling behavior of plate elements subjected to plastic hysteresis due to repeated loads appears differently compared with that in case of monotonic loading due to the lowering of proportional limit in each loading cycle, as stated in section 2.a. This problem is dealt with incidentally in the experiments of members and connections under repeated loading. From the above viewpoint, in Ref. 14), 15), 16), 17) and 57), the local buckling are dealt with in cases of beams and

\*1 This kind of problems are vigorously investigated in ship-building engineering. For instance, see Ref. 29).

\*2 For instance, see Ref. 10), 11), 12), 13).

columns, particularly as to beam-to-column connections, and also in cases of cantilevered beams and simply supported beams. In those investigations are reported interesting results including plastic hysteresis in post local buckling. The local buckling of plate elements are accentuated by the action of repeated force, and large distortion in panel zone induces local buckling of flanges in beam-to-column connections as illustrated in Fig. 4(b). Nevertheless, it should be noted that local buckling of flanges does not lead to a significant drop in strength and rigidity.<sup>5,7)</sup>

Hereafter, it is expected that series of researches will be undertaken concerning on the local buckling of plate elements with different width-thickness ratios and concerning on post buckling behaviors under repeated loading.

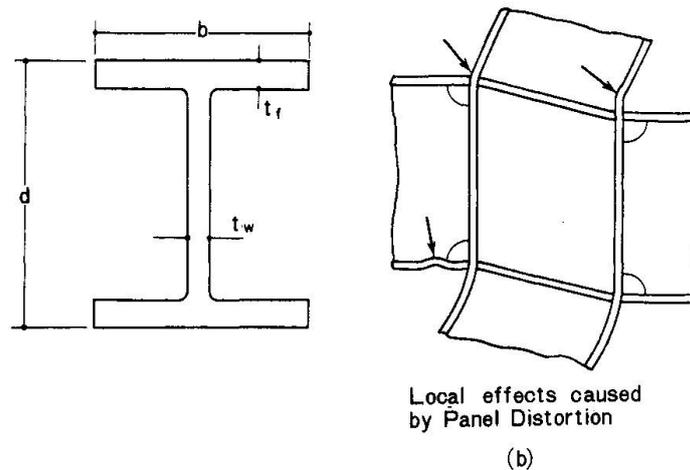


Fig. 4

#### 4. COMPRESSION MEMBERS

There are few experiments for compression members subjected to plastic hysteresis by repeated loading. Fig. 5 shows  $P-\delta$  curve obtained from experiment, in which a bar of rectangular cross section with slenderness ratio of 120 is subjected through pinned ends to repeated tension and compression, gradually increasing strain amplitude in each loading cycle.<sup>23)</sup> It should be noted that compression member loses its resistance considerably once it buckles. Fig. 6 shows theoretical  $P-\delta$  curve of a bar, in which yield hinge is assumed in mid-section in post buckling and furthermore plastic deformation of member is neglected. In this analysis, because it is assumed that a bar recover a perfectly straight form at E, the buckling load in the second compressive loading cycle is equal to the first buckling load, A.

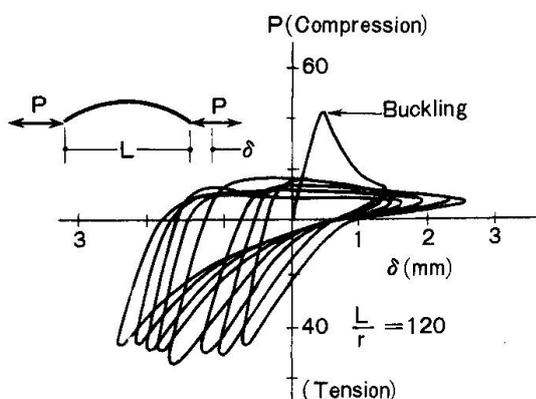


Fig. 5 Hysteresis Loops of a Bar under Repeated Tension-Compression.

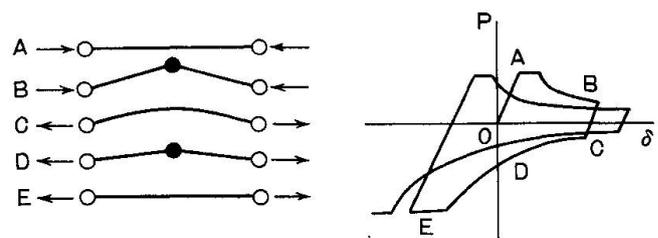


Fig. 6 Theoretical Hysteretic Behavior of a Bar under Repeated Tension-Compression.

As understood from Fig. 5, however, a bar does not recover a perfectly straight form at E, and consequently buckling load actually decreases. Therefore, in pursuing plastic hysteretic curve, it becomes necessary to establish more exact analytical method in which plastic deformations are taken into consideration.

Fig. 7 shows analytical results by non-linear analysis in which a bar is divided into discrete elements, and incremental displacements at arbitrary loading state are determined by numerical calculation based on the principle of stationality of potential energy.

It is seen that the reduction of resistance in post buckling appears differently depending on slenderness ratios and that buckling strength decreases in each loading cycle.

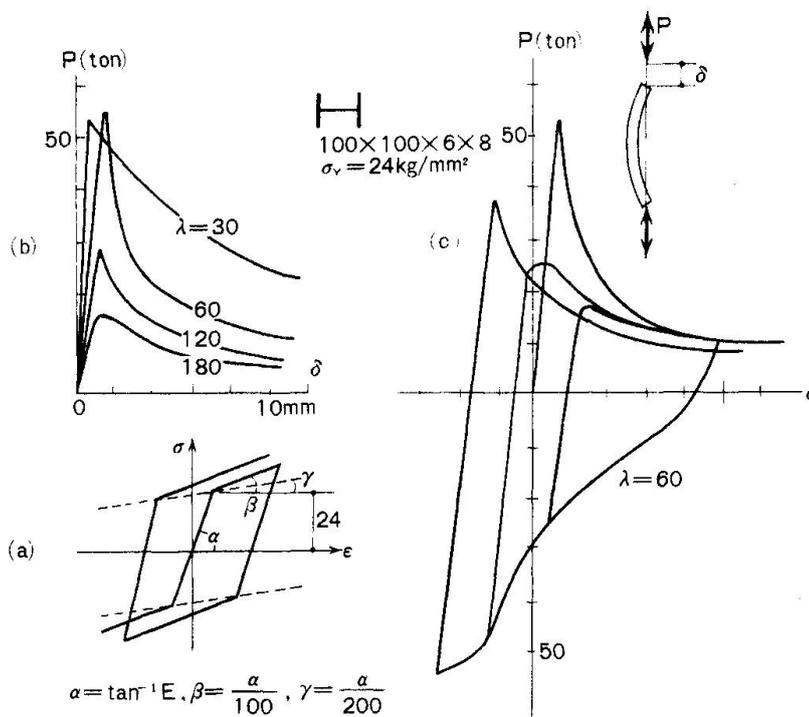


Fig. 7 Theoretical P- $\delta$  curves of a Bar under compression and Repeated Tension-Compression.

## 5. BEAMS AND COLUMNS

Fig. 8 shows load-deformation hysteretic curve of cantilevered beams subjected to repeated loading. The plateau exists in the virginal loading and in subsequent loadings the curves are quite stable. From the above results and as stated in Chapter 3, the local buckling of plate elements (in this case, flange) does not scarcely affect on the strength and the rigidity.<sup>(14),(15),(16),(17)</sup> A few experiments are undertaken for columns under repeated bending with constant axial force.<sup>(25), (26)</sup> Fig. 9 is an example of such experiment. From the above result, it is seen that in case large axial force exists, the height of the first curve is low and the gradients of the curves are negative after the attainment of maximum load in each loading cycle. This phenomenon is called P- $\Delta$  effect. It should be noted, however, that the load carrying capacity is increasing in each loading cycle because of the accumulated compressional strains and strain hardening under repeated bending and constant axial force. This can be analyzed by assuming bi-linear relationship between stresses and strains.<sup>(25),(26),(27)</sup>

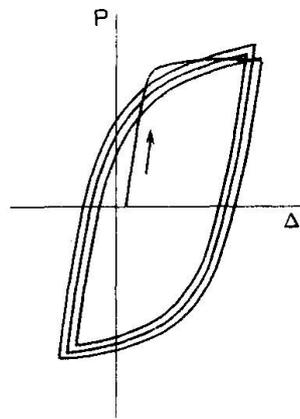


Fig. 8. Stability of Consecutive Hysteresis Loops

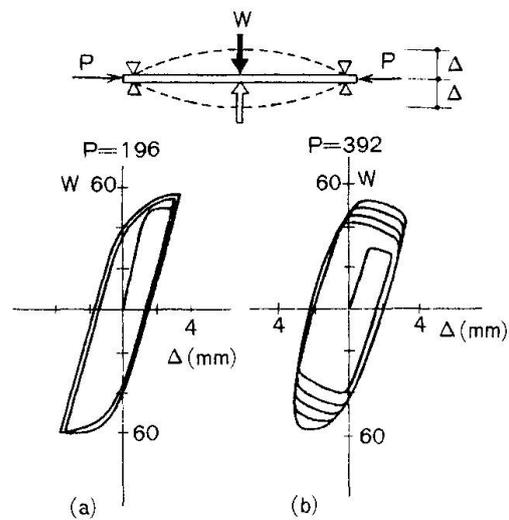


Fig. 9. Hysteresis Loops of Beam-Column under Repeated-Bending.

Fig. 10 shows one of the calculation results. Implied in the figure is that the system takes up more and more load under a constant amplitude of cyclic loading, and that the curves asymptotically approaches to the curve corresponding to that in no axial force.

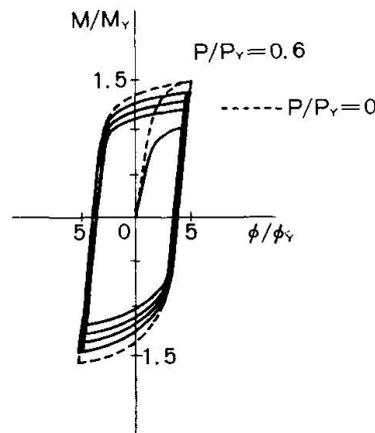


Fig. 10. Hysteresis Moment-Curvature Relationships of a Cross Section under Constant Axial Force.

Reference 28) presents the analytical moment-curvature hysteretic characteristic of a column under constant axial force and cyclic bending, by using stress-strain hysteretic characteristics of a simplified model which is subjected to one-sided repeated stressing. The analytical result is compared with experimental one of a column subjected to constant axial force and repeated pure bending.

Moreover, problems related to lateral buckling and lateral bracing of beams and columns under repeated plastic hysteresis are not systematically researched to date and are left for future investigations.

## 6. MECHANICAL FASTENERS AND WELDING

As the means of connections for steel structures, are used welding and mechanical fasteners, i.e. rivets, bolts and high-tensile bolts. The properties of fasteners and welded connections under repeated loading are in many cases verified indirectly through experiments in which these connections are used

in members and in frames. As for rivets and bolts under repeated plastic hysteresis, the need is for studies concerning on relationship between bearing stress and deformations, characteristics of shearing deformation of fasteners and deformations of steel plate with holes and furthermore conditions of their failures. The property of frictional force are to be clarified for high-tensile bolts, and the investigation from the same viewpoint upon the materials as stated in Chapter 2 are necessary for welding.\*1

## 7. CONNECTIONS

### a. Beam-joints

Fig. 11 is one of the example of H-shaped beams under repeated loading, in which high-tensile bolted friction joint are employed.<sup>14),30),31),32)</sup> It is found out from experiments that once slip occurs at beam joint, slip load consecutively decreases as the numbers of cycles increase, and that the reduction of rigidity due to repeated loading are not significant.

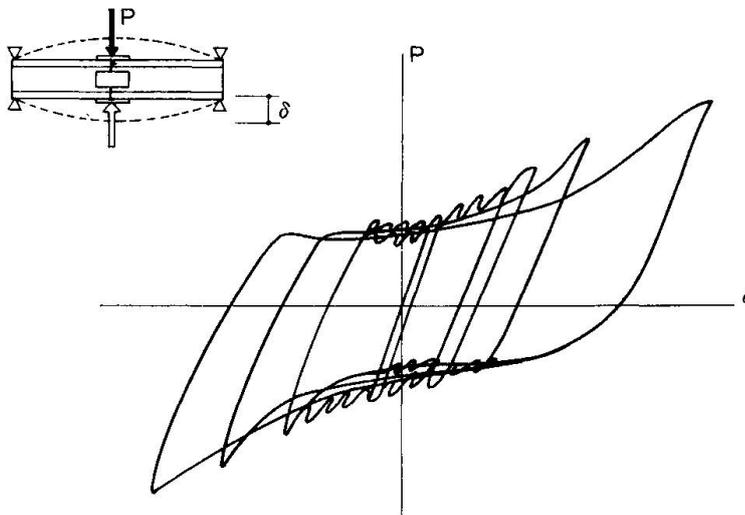


Fig. 11 P- $\delta$  curve of Wide-Flange Beam with High-Strength Bolted Joint.

### b. Beam-to-column connections

Experiments on beam-to-column connections subjected to repeated load have been extensively undertaken, particularly, in Japan for various specimens as illustrated in Fig. 12. Throughout the various types of test's models, the reduction in rigidity at comparatively lower load has been recognized and has been a matter of concern. Its reason is now explained as that the panel zone, i.e.

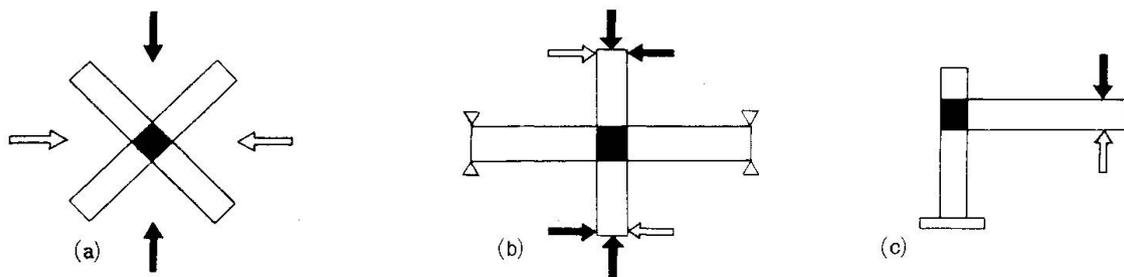


Fig. 12 Test Specimen of Beam-to-Column connection.

\*1 See Ref. 29), for instance

column webs at beam-to-column connections yields early due to the existing large shearing force,<sup>33),34),35),57)</sup> and at present it is recommended to stiffen panel zone if necessary.

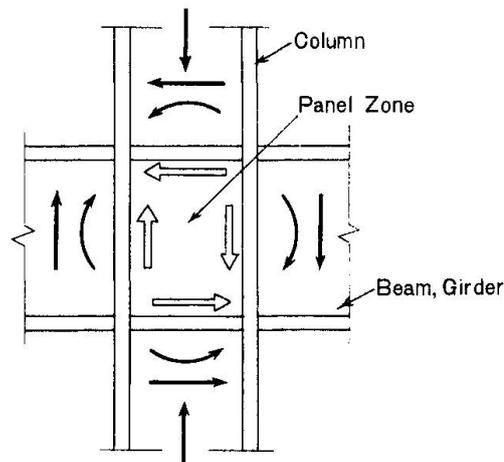


Fig. 13 Stress in the Panel zone.

#### c. Column bases

Although the column bases are important parts to transfer the stresses in the skeleton to foundation, there are few investigations for column bases taking consideration of the action of repeated force, and are expected to be undertaken in near future.<sup>55)</sup>

### 8. UNBRACED FRAMES

There're fewer studies, both experimental and theoretical, on the hysteretic characteristics of unbraced frames than those on monotonic loading case. Some result are available of experiments done in U.S.A. and in Japan.<sup>28),34) ~ 46),57)</sup>

In general, this kind of investigation is to research elasto-plastic behaviors of rigid frames under various types of repeated loadings. In many cases, however, it is done, particularly, to know the restoring force characteristic of each floor in order to apply for the dynamical elasto-plastic design of multi-storied buildings. Restoring force characteristic is, as illustrated in Fig. 14, so called spring constant between adjacent particles representing the masses of each floor. Restoring force characteristic is much influenced by shearing force and additional bending moments to the columns due to existing axial force  $P$  and horizontal displacement  $\Delta$ . The latter is called  $P$ - $\Delta$  effect, as already

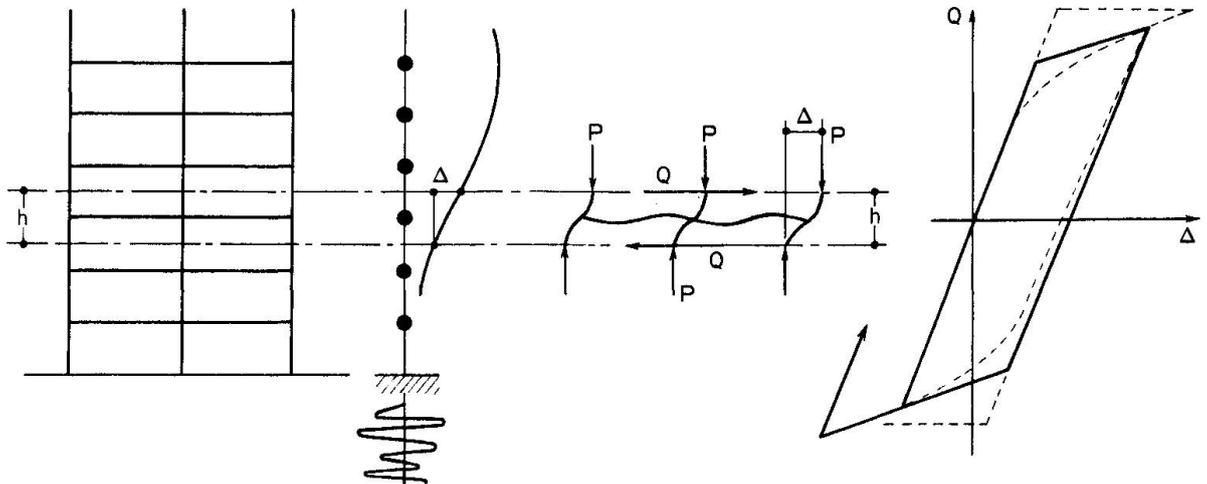


Fig. 14 Elastic-Plastic and Bilinear Type Restoring-Force Characteristics Used in the Seismic design.




Fig. 15 Multi-Story Frames and tested Components.




Fig. 16 Cycling Amplitude and Horizontal Displacement Program.

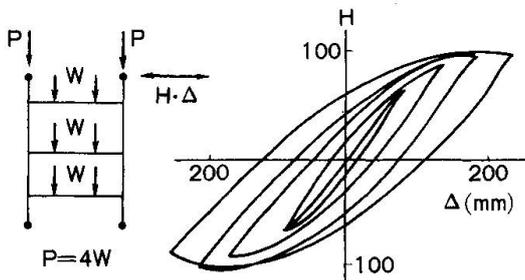


Fig. 17. Selected Load-Deflection Curves of a Frame under Repeated Horizontal Loading ( $P=4W$ ).

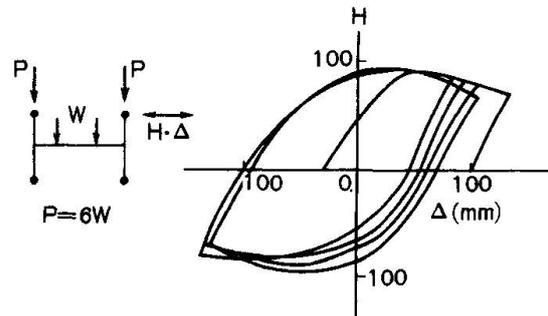


Fig. 18 Selected Load-Deflection Curve of a Frame under Repeated Horizontal Loading. ( $P=6W$ ).

mentioned in Chapter 5. The stability of hysteretic curve is much influenced depending on the magnitude of  $P$  and  $\Delta$ .

Reference 40) and 41) present full-scale test's results on three and one storied rigid subassemblages which are taken out of a multi-storied one-bay frame as shown in Fig. 15. Fig. 16 shows the test program of deflection amplitude which is gradually increased, and Fig. 17 and Fig. 18 are to show several cycles of hysteresis loops out of several ten of cycles. The conclusions deduced from the results are as follows:

- 1) Stability of loop is observed even at deflections after the maximum load is attained.
- 2) The maximum load that the frame can withstand is considerably greater than the theoretical prediction of the frame under monotonically increasing load.

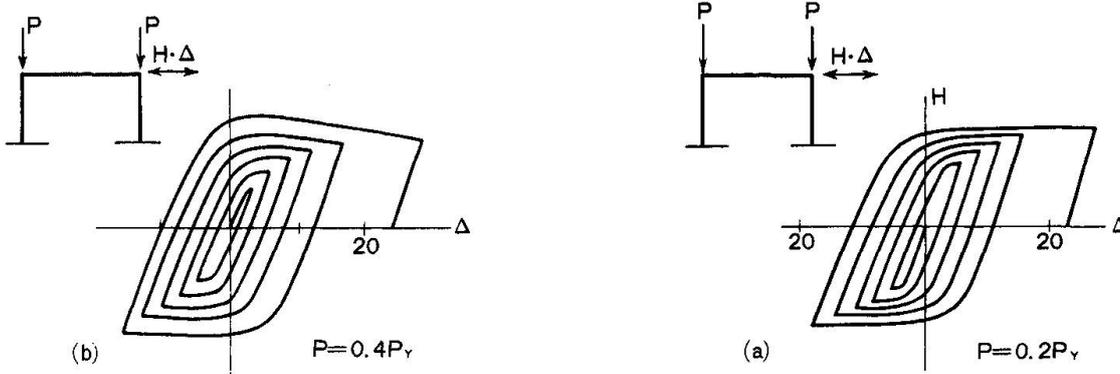


Fig. 19 Load Deflection Curve of Portal Frame under Repeated Horizontal Loading.

- 3) Strain hardening plays an important role after the attainment of the maximum load.
- 4) Hysteresis loops are influenced by yield zone at plastic hinges and the Bauschinger effect.

Shown in Fig. 19 are the results of small model tests with H-shaped cross section, indicating how the load carrying capacity increases with the increase in vertical load  $P$ .<sup>46),49)</sup> Fig. 20 shows hysteresis curve obtained from tests of knee frames consisting of H-shapes in which a plastic hinge is formed at the column top.<sup>47),48)</sup>

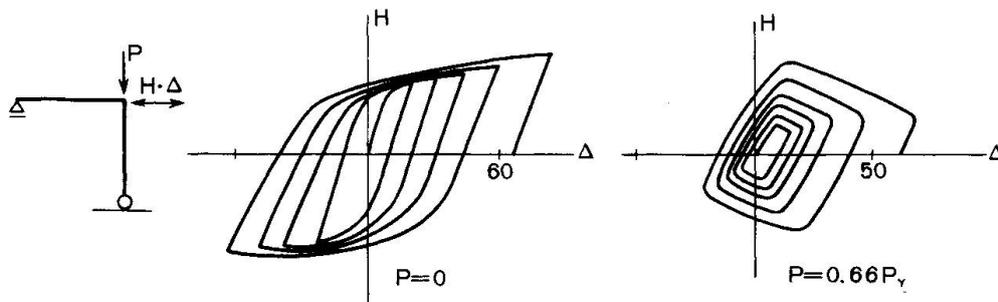


Fig. 20 Load Deflection Curve of Knee-Bents under Repeated Horizontal Loading.

From these results, plastic hysteretic curve of unbraced frames under the action of repeated horizontal loads is modeled as illustrated in Fig. 21, neglecting Bauschinger effect.<sup>48)</sup>

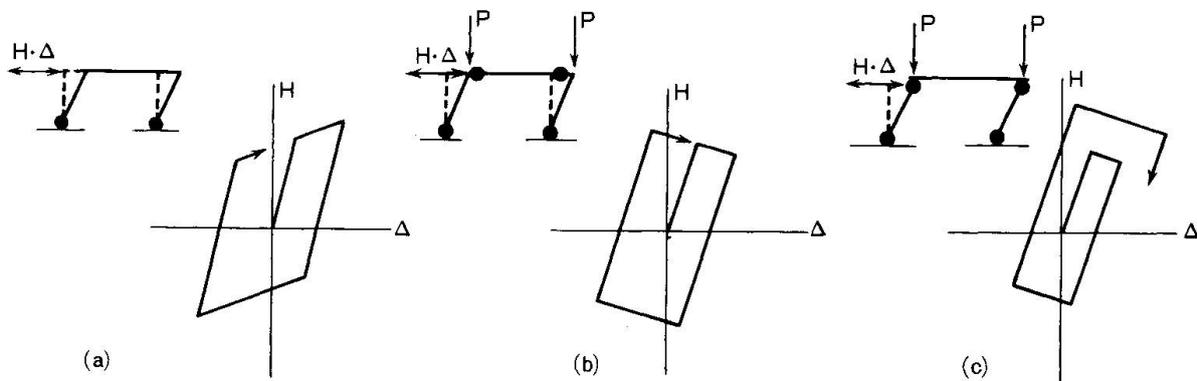


Fig. 21 Positive and Negative Bilinear Hysteresis Curves of Portal Frames under Repeated Horizontal Loading.

- a) In case that the vertical load  $P$  does not exist or are small, the plastic range of  $H-\Delta$  curve are parallel to  $\Delta$ -axis, neglecting strain hardening.
- b) In case that the vertical load  $P$  is large and the collapse occurs at beam ends,  $H-\Delta$  curve is modeled by closed loop with negative gradient in plastic range, due to  $P-\Delta$  effect.
- c) In case that the vertical load  $P$  is large and the collapse occurs in columns,  $H-\Delta$  curve is modeled by helically expanding loops due to the accumulated compressive strains and strain hardening as stated in Chapter 5, with negative gradient in plastic range, due to  $P-\Delta$  effect as in the case of b).

## 9. BRACED FRAMES

The restoring force of a braced frame is considered to be nearly equivalent to the summation of the restoring forces of both portal frame and bracing itself which is treated in Chapter 5. Therefore,

the hysteresis loops are directly affected by the behavior of bracings and are completely different from those of unbraced frame.

There have been undertaken very few investigations into the behavior of braced frames under large amplitudes of repeated loading. Experiments were done on small models of rectangular cross section and of H-section, on medium-sized models of H-section, and on full-scale model of H-section, all with two diagonal bracing members.<sup>36),37),38),46),48),49),52)</sup> Some others were done on K-truss type frames, and on braced frames with only one diagonal bracing.<sup>49),50),51),52),53),54)</sup>

Fig. 22 was obtained from a small model test,<sup>46),49)</sup> and some similarity is found between Fig. 22(a), which is obtained from a test on a braced frame with one diagonal bracing, and the one shown in Fig. 5, which presents the behavior of the bracing itself.

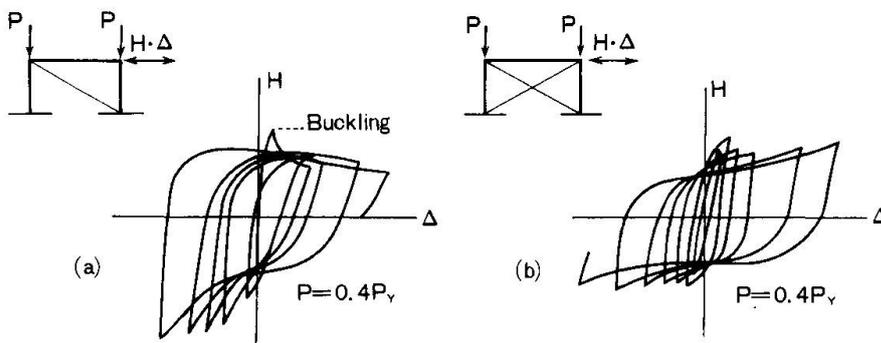


Fig. 22 Load Deflection Curves of Braced Portal Frames under Repeated Horizontal Loading

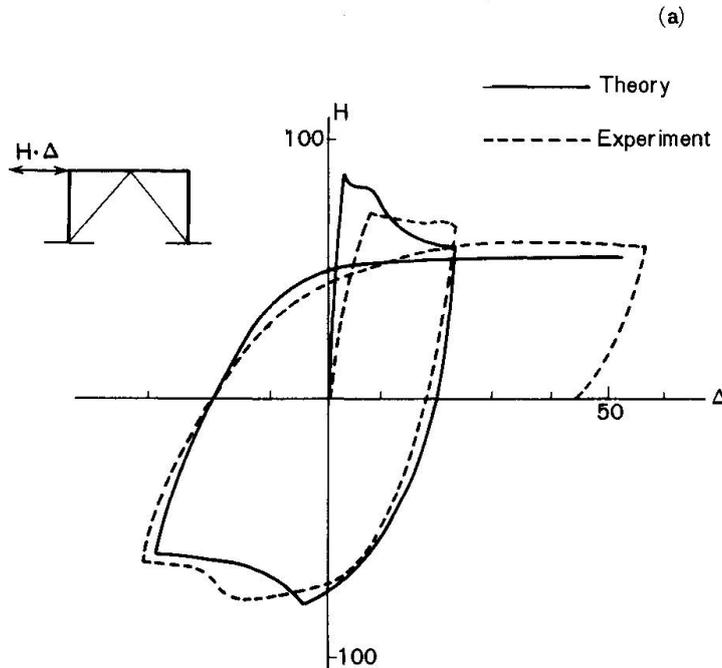


Fig. 23 Theoretical and Experimental Load Deflection Curves of a Braced Portal Frame under Repeated Horizontal Loading.

Fig. 23 shows comparison of experimental results,<sup>54)</sup> on one-half model of a braced frame composed of H-shaped members subjected to repeated horizontal force to the theoretical analysis by discrete element method<sup>24)</sup>, already referred in Chapter 4, and the both results seem to be in a good agreement.

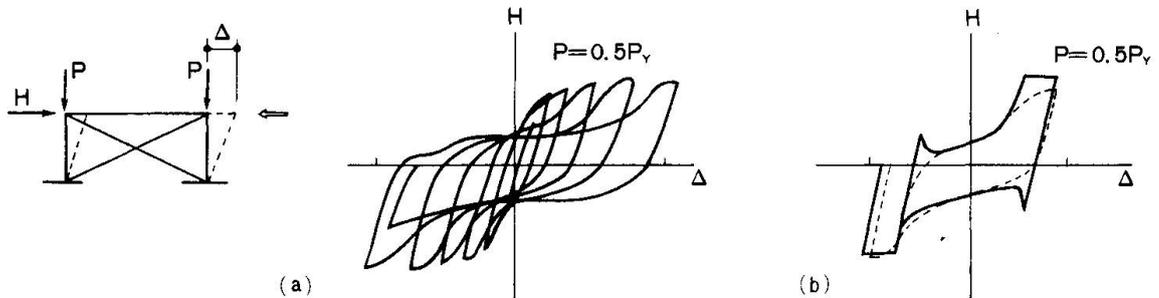


Fig. 24 Load-Deflection Curve of a Braced Full-Scale Portal Frame under Repeated Horizontal Loading

Fig. 24 is an example of the results obtained on a braced frame with two diagonal bracings.<sup>48)</sup> Fig. 24(a) is the results on full-scale tests, the bracing members of which are a little more slender than those shown in Fig. 22(b). In Fig. 24(b), one cycle of the result is plotted by dotted line, and the solid line is the corresponding curve that is theoretically obtained, making use of the hysteresis curves in Fig. 6. As was mentioned related to Fig. 5, once large deflections occur due to buckling, the bracing member does not recover its straightness even though plastic elongation is given to it. The loop is rather round in this case. The theoretical curve seems to be in good agreement with the test's result.

A model of hysteretic curve of braced frames can be the one as diagrammatically illustrated in Fig. 25.

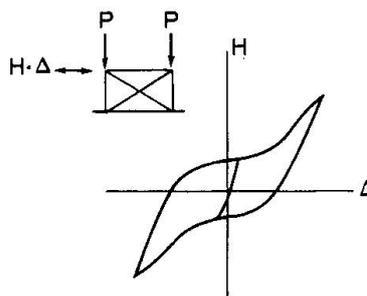


Fig. 25 S-Shaped Hysteresis Loop of a Braced Portal Frame under Horizontal Loading.

## 10. CONCLUSION

Concerning on the steel structures, their elements, their connections and their materials subjected to repeated force applied in quasistatic manner, are stated in this report various mechanical characteristics obtained mostly through experimental investigations. Here, are presented a brief summary for symposium discussion as reference items.

- (1) Mechanical properties of materials, steels and welding in particular – low-cycle fatigue
  - i) behavior of failure for steels and welded parts
    - a) necessity of criterion of failure for not only simply stressed states, but for combined stressed states

- b) conditions for deterioration of notch toughness due to plastic strains
- c) decrease in elongation capacity due to sectional discontinuity (influences of strain hardening and yielding-strength ratio)
- ii) quantitative treatment on stress-strain relationship\*1
  - a) lowering of proportional limit – Bauschinger effect
  - b) strain hardening
  - c) yielding-strength ratio
- iii) characteristic of bearing stress for riveted and bolted connections and of frictional force in high-tensile friction joint
- (2) Local buckling of plate elements
  - Influences of changes in material characteristics during loading cycles i.e., decrease of proportional limit and strain hardening
  - Necessity of establishment of width-thickness ratio on a basis of critical strain of buckling
- (3) Bucklings and P- $\Delta$  effect
  - Understanding of various characteristics under repeated loading; Euler buckling, lateral buckling, lateral bracing and P- $\Delta$  effect, or compression members, beams and columns, including post buckling behaviors and considering the influences of strain hardening
- (4) Connections
  - Establishment of various fastening systems and understanding of their mechanical characteristics under repeated loading in order to obtain rigid, ductile, tough connections
- (5) Frames
  - Understanding of characteristics of hysteresis loop considering P- $\Delta$  effect, reductions of maximum resistance and rigidity due to buckling of bracing and the influences of strain hardening
- (6) Miscellaneous problems
  - Problems such as influence of imperfections existing in plate elements, members and frames, influence of residual stress and bi-axial bending of members, which was not dealt with in this report, are also challenging problems. Though damping and energy absorption capacity have close relationships with hysteretic characteristics of structures subjected to repeated force, such problems are extensively discussed in Theme II and are not dealt in this report.

In order to confirm a design method of earthquake resistant structures, it is essential as stated in Introduction to understand behaviors of structures subjected to repeated force. In this purpose, we should treat seismic loads, not as quasistatically repeated forces as discussed herein, but as semi-impulsive\*2 and yet random dynamical ones.

Investigations on the basis of the aforementioned viewpoint, in fact, has just begun and many brains and efforts will be needed to secure a earthquake resistant construction of steel structures.

#### ACKNOWLEDGEMENTS

The writers are grateful to Prof. Toshie Okumura, Prof. Yukio Maeda and Prof. Minoru Wakabayashi for their adequate advices and encouragements. Some articles in this report are quoted from M. Wakabayashi's manuscript\*3 to ASCE-IABSE Joint Committee on Planing and Design of Tall Buildings.

\*1 See Ref 6), for instance

\*2 In Ref.56), influences of strain velocity and yielding-strength ratio of steels are discussed in case that sectional discontinuities such as holes and notch exist.

\*3 Wakabayashi, M., : FRAMES UNDER STRONG IMPULSIVE WIND OR SENSIMIC LOADING, State of Art Report No.5 Technical Committee, 5, 1972

**BIBLIOGRAPHIC REFERENCES**

- 1) **Cloughe, R. W.**  
THE FINITE ELEMENT METHOD IN PLANE STRESS ANALYSIS. ASCE, 2nd Conference on Electronic Computation, 1960.
- 2) **Seismology Committee Structural Engineers Association of California**  
RECOMMENDED LATERAL FORCE REQUIREMENTS AND COMMENTARY.
- 3) **Hanson, R. D.**  
COMPARISON OF STATIC AND DYNAMIC HYSTERESIS CURVES. Journal of Engineering Mechanics Division, ASCE, Vol. 92, No. EM5, Oct. 1966
- 4) **Chajes, A., Britvec, S. J., Winter, G.**  
EFFECTS OF COLD STRAINING ON STRUCTURAL SHEET STEELS. Journal of the Structural Division, ASCE, ST2, April 1963.
- 5) **Fujimoto, M., Moriya, K. and Wada, A.**  
STUDIES ON THE MECHANICAL PROPERTIES OF STRUCTURAL STEEL AND STEEL MEMBERS SUBJECTED TO THE PLASTIC HYSTERESIS (Part 1) Properties of Structural Steel for Tensile and Compressive Stress. Transactions of the Architectural Institute of Japan, No. 167, Jan. 1970 (in Japanese)
- 6) **Ramberg, W. and Osgood, W.R.**  
DESCRIPTION OF STRESS-STRAIN CURVES BY THREE PARAMETERS, NACA TN902, July, 1943.
- 7) **Naka, T.**  
ANISOTROPY OF ROLLED STEEL PLATES AND COMMENTS ON WELDED STRUCTURAL DESIGN. (Part 1) J. of the Japan Welding Society, No. 7, Vol. 24, 1957 (Part 2) J. of the Japan Welding Society, No. 11, Vol. 24, 1957 (in Japanese)
- 8) **Ikeda, K., Maenaka, H. and Sakuma, M.**  
THE EFFECT OF PLASTIC STRAIN INFLUENCING ON THE CHARACTERISTICS OF OCCURENCE OF BRITTLE FRACTURE IN VARIOUS STEEL PLATES. J. of the Welding Society, No. 8, Vol. 38, 1969 (in Japanese)
- 9) **Kato, B. and Aoki, H.**  
DEFORMATION CAPACITY OF THE TENSION MEMBER OF WHICH STRESS CONCENTRATION MUST BE CONSIDERED. Transactions of the Architectural Institute of Japan, No. 159, May 1969 (in Japanese)
- 10) **Beedle, L. S., Galambos, T. V. et al**  
STRUCTURAL STEEL DESIGN, Ronald Press, New York, 1964
- 11) **ASCE**  
PLASTIC DESIGN IN STEEL, American Institute of Steel Construction, New York, 1971.
- 12) **Driscoll, G. C., Jr. et al**  
PLASTIC DESIGN OF MULTI-STORY FRAMES-LECTURE NOTES AND DESIGN AIDS, Fritz Laboratory Report 273.20 and 273.24, Lehigh University, Bethlehem, Pa., 1965.

- 13) Galambos, T. V.  
STRUCTURAL MEMBERS AND FRAMES, Prentice-Hall, Englewood cliffs, N. J., 1968.
- 14) Popov, E. P.  
LOW-CYCLE FATIGUE OF STEEL BEAM-TO-COLUMN CONNECTIONS, RILEM International Symposium on the effects of Repeated Loading of Materials and Structural Elements, Mexico City, Vol. VI. Sept., 1966.
- 15) Popov, E. P.  
PERFORMANCE OF STEEL BEAMS AND THEIR CONNECTIONS TO COLUMNS DURING SEVERE CYCLIC LOADING, Contributions to the Expanded Discussion, 8th Congress of IABSE, Theme III, New York, Sept., 1968.
- 16) Popov, E. P.  
RELIABILITY OF STEEL BEAM-TO-COLUMN CONNECTION UNDER CYCLIC LOADING, Proc. 4th. World Conference on Earthquake Engineering, Santiago, Chile, Vol. I, B-3, Jan., 1969.
- 17) Nakamura, T., et al  
LOAD-DEFLECTION BEHAVIORS AND PLASTIC FATIGUE OF WIDE-FLANGE BEAMS' SUBJECTED TO ALTERNATING PLASTIC BENDING, Trans. Architectural Institute of Japan, No. 175, Sept., 1970, No. 176, Oct., 1970, and No. 177, Nov., 1970.
- 18) Baker, J. F., Horne, M. R., Heyman, J.  
THE STEEL SKELETON, Vol. 2, Cambridge University Press, Cambridge, England, 1956.
- 19) Heyman, J.  
PLASTIC DESIGN OF PORTAL FRAMES, Cambridge University Press, Cambridge, England, 1957.
- 20) Hodge, P. G., Jr.  
PLASTIC ANALYSIS OF STRUCTURES, McGraw-Hill Book Co., New York, 1959.
- 21) Neal, B. G.  
THE PLASTIC METHODS OF STRUCTURAL ANALYSIS, John Wiley and Sons, New York, 1956.
- 22) Prager, W.  
INTRODUCTION TO PLASTISITY, Addison-Wesley Publishing Co., Reading, Mass., 1959.
- 23) Wakabayashi, M., Nonaka, T., Koshiro, O., Yamamoto, N.  
AN EXPERIMENT ON THE BEHAVIOR OF A STEEL BAR UNDER REPEATED AXIAL LOADING, Annuals, Disaster Prevention Research Institute, No. 14A, Kyoto University, Apr., 1971. (in Japanese)
- 24) Fujimoto, M., Sudo, F. and Wada, A.  
THE NON-LINEAR STRESS ANALYSIS FOR THE ARBITRARY PLANE STEEL FRAMES. Transactions of the Architectural Institute of Japan, No. 189, Nov. 1971 (in Japanese)

- 25) **Tanabashi, R., Yokoo, Y., Wakabayashi, M., Nakamura, T., Kunieda, H.**  
DEFORMATION-HYSTORY DEPENDENT INELASTIC STABILITY OF COLUMNS  
SUBJECTED TO ALTERNATING LOADING, Preprint for RILEM Symposium on  
Experimental Analysis of Instability Problems on Reduced and Full-Scale Models,  
Buenos Aires, Sept., 1971.
- 26) **Yamada, M., et al**  
ELASTO-PLASTISCHE BIEGEFORMÄNDERUNGEN VON STAHLSTÜTZEN MIT  
IQUERSCHNITT, Der Stahlbau, Vol. 39, Ht 12, Dec., 1970, Vol. 40, Ht. 3, Mar.,  
1971, Vol. 40, Ht. 5, May, 1971
- 27) **Igarashi, S., et al**  
INELASTIC BEHAVIOR OF STRUCTURAL STEEL SECTIONS UNDER ALTERNATIVE  
LOADING, Trans. Architectural Institute of Japan, No. 169, Mar. 1970, No. 170, Apr.  
1970.
- 28) **Kato, B., Akiyama, H.**  
THE ULTIMATE STRENGTH OF THE STEEL STRUCTURE SUBJECTED TO  
EARTHQUAKE, Proc. 4th. World Conference on Earthquake Engineering, Santiago,  
Chile, Vol. II, A-4, Jan. 1969.
- 29) **Takahashi, Y., Yagi, J., Iida, K., Machida, S., Inoue, H.**  
LOW CYCLE FATIGUE STRENGTH OF SHIP STRUCTURAL STEELS. Yawata Technical  
Report, No. 257, Dec., 1966.
- 30) **Hokugo, H., Fujimoto, M. and Hashimoto, A.**  
THE CYCLIC LOAD TESTS OF HIGH-TENSILE-BOLTED FRICTION JOINT. (Part 1)  
Test of F11T High-Tensile-Bolted Friction Joint, (Part 2) Test of Beam Joint.  
Transaction of the Architectural Institute of Japan, No. 103, 1964 (in Japanese)
- 31) **Igarashi, S., Kawada, E.**  
ELASTO-PLASTIC BEHAVIORS OF H BEAM JOINT USING HIGH-STRENGTH BOLTS.  
Yawata Technical Report, No. 256, Sept., 1966.
- 32) **Yamada, M., Nakaza, I., Toide, K.**  
RESEARCHES ON LOW CYCLE FATIGUE OF RIVETED AND HIGH-STRENGTH  
BOLTED CONNECTIONS IN WIDE FLANGE BEAMS, Yawata Technical Report, No.  
256, Sept., 1966.
- 33) **Naka, T., Kato, B., Watanabe, M., et al**  
STATIC AND DYNAMIC BEHAVIOR OF STEEL BEAM-TO-COLUMN CONNECTIONS.  
Yawata Technical Report, No. 256. Sep. 1966.
- 34) **Bertero, V. V.**  
SEISMIC BEHAVIOR OF STEEL BEAM-TO-COLUMN CONNECTION  
SUBASSEMBLAGES. Proc. 4th World Conference on Earthquake Engineering.  
Santiago, Chile. Vol. II, B-3, Jan., 1969.
- 35) **Bertero, V. V., Popov, E. P. and Krawinkler, H.**  
HALF-SCALE TESTS OF SUBASSEMBLAGES OF MULTI UNBRACED STEEL

FRAMES UNDER CYCLIC LOADING, Proc. 3rd Japan Earthquake Symposium, Tokyo, Nov., 1970.

- 36) Wakabayashi, M.  
THE BEHAVIOR OF STEEL FRAMES WITH DIAGONAL BRACINGS UNDER REPEATED LOADING, Proc. of U.S.–Japan Seminar Earthquake Engineering with Emphasis on the Safety of School Buildings, Sendai, Japan, 1970.
- 37) Wakabayashi, M.  
THE RESTORING FORCE CHARACTERISTICS OF MULTI-STORY FRAMES, Bull. Disaster Prevention Research Institute, Vol. 14, Part 2, No. 78, Kyoto.
- 38) Wakabayashi, M., Matsui, C., Minami, K., Mitani, I.  
INELASTIC BEHAVIOR OF FULL SCALE STEEL FRAMES, Annuals, Disaster Prevention Research Institute, No. 13A, Kyoto University, Mar., 1970. (in Japanese).
- 39) Arnold, P., Adams, P. F., Lu, L. W.  
THE EFFECT OF INSTABILITY ON THE CYCLIC BEHAVIOR OF A FRAME, RILEM International Symposium on Effect of Repeated Loading on Materials and Structural Elements, Mexico City, Sept., 1966.
- 40) Carpenter, L. D., Lu, L. W.  
BEHAVIOR OF STEEL FRAMES SUBJECTED TO REPEATED AND REVERSED LOADS, Final Report on 8th Congress of IABSE at New York, Sept., 1968.
- 41) Carpenter, L.D., Lu, L.W.  
REPEATED AND REVERSED LOAD TESTS ON FULL-SCALE STEEL FRAMES, Proc. 4th World Conference on Earthquake Eng. Santiago, Chile, Vol. I, B-3, Jan., 1969.
- 42) Hanson, R. D., Almuti, A. M.  
POST-ELASTIC RESPONSE OF MILD STEEL STRUCTURES, Proc. 3rd Japan Earthquake Symposium, Tokyo, Nov., 1970.
- 43) Makino, M., Sato, T., Miyazaki, K.  
ELASTO-PLASTIC DEFORMATION OF MULTI-STORY FRAMES UNDER HORIZONTAL LOADING, Report of the Building Research Institute, Ministry of Construction. No. 46, Oct., 1965. (in Japanese)
- 44) Igarashi, S., Taga, N.  
HISTERETIC CHARACTERISTICS AND STRUCTURAL DAMPLING OF STEEL STRUCTURES UNDER ALTERNATE LATERAL LOADING, Trans. Architectural Institute of Japan, No. 120, Feb., 1966.
- 45) Igarashi, S., et al  
PLASTIC BEHAVIOR OF STEEL FRAMES UNDER CYCLIC LOADINGS. Trans. Architectural Institute of Japan, No. 130, Dec. 1966.
- 46) Fujimoto, M., Hakura, H., Matsumoto, Y.  
EXPERIMENTAL STUDY ON THE INELASTIC BEHAVIOR OF STEEL STRUCTURES UNDER REPEATED LOADING, Trans. of Annual Meeting of Architectural Institute of Japan, Oct.; 1968. (in Japanese)

- 47) **Wakabayashi, M., Matsui, C., et al**  
EXPERIMENTAL STUDY ON ELASTO-PLASTIC BEHAVIOR OF A STEEL FRAME  
SUBJECTED TO CONSTANT VERTICAL LOAD AND REPEATED HORIZONTAL  
LOAD. Trans. of Annual Meeting of Architectural Institute of Japan, Aug., 1968. (in  
Japanese)
- 48) **Wakabayashi, M., Matsui, C., et al**  
EXPERIMENTAL STUDY ON THE ELASTIC-PLASTIC STABILITY ON STEEL FRAMES  
AND RESTORING FORCE CHARACTERISTICS. JSSC, Vol. 6, No. 55, 1970,  
Society of Steel Construction of Japan. (in Japanese)
- 49) **Fujimoto, M., Hakura, H., Matsumoto, Y.**  
MODEL EXPERIMENT OF BRACED STEEL RAHMEN UNDER REPEATED LOADING,  
JSSC, Vol. 6, No. 55, 1970, Society of Steel Construction of Japan. (in Japanese)
- 50) **Wakabayashi, M., Tsuji, B.**  
EXPERIMENTAL INVESTIGATION ON THE BEHAVIOR OF FRAMES WITH AND  
WITHOUT BRACING UNDER HORIZONTAL LOADING, Bull. Disaster Prevention  
Research Institute, Vol. 16, Part 2, No. 112, Kyoto University, Jan., 1967.
- 51) **Onitake, N., Heki, K. et al**  
EXPERIMENT ON BRACED FRAMES UNDER REPEATED LOADING. Transactions of  
Annual Meeting of Architectural Institute of Japan, Kinki branch, Feb. 1964 (in  
Japanese)
- 52) **Takahashi, Y., Okada, H.**  
EXPERIMENTAL STUDY ON BRACED FRAMES. Transactions of Annual Meeting of  
Architectural Institute of Japan, Aug. 1969 (in Japanese)
- 53) **Fujimoto, M., Aoyagi, T., Ukai, K., Wada, A., Saito, K.**  
STRUCTURAL CHARACTERISTICS OF ECCENTRIC K-BRACED FRAMES.  
Transactions of the Architectural Institute of Japan, No. 195, May, 1972. (in Japanese)
- 54) **Fujimoto, M., Hashimoto, A., Hokugo, H., Kimura, A., Kosugi, R. and Kira, M.**  
STUDY ON ELASTO-PLASTIC BEHAVIOR OF BRACED RIGID STEEL FRAME  
SUBJECTED TO ALTERNATELY REPEATED HORIZONTAL LOAD. Transcation  
of Annual Meeting of Architectural Institute of Japan, Nov. 1971 (in Japanese)
- 55) **Masuda, K., et al**  
EXPERIMENTAL STUDY ON VARIOUS TYPE OF COLUMN-TO-BASE CONNECTION  
AND ITS RIGIDITY. Transactions of Annual Meeting of Architectural Institute of  
Japan, 1971 (in Japanese)
- 56) **Kato, B., Aoki, H. and Inamura, S.**  
EFFECT OF STRAIN VELOCITY ON MECHANICAL PROPERTIES OF STEEL.  
Transactions of Annual Meeting of Architectural Institute of Japan, Kantoh branch,  
1967 (in Japanese)
- 57) **Bertero, V. V., Popov, E. P., Krawinkler, H.**  
BEAM-COLUMN SUBASSEMBLAGES UNDER REPEATED LOADING. Proceedings of  
the ASCE, Vol. 98, No. ST5, May, 1972
- 58) **Architectural Institute of Japan**  
TECHNICAL RECOMMENDATION FOR HIGH-RISE BUILDINGS, (in Japanese)

## SUMMARY

This report refers to various mechanical characteristics of steel structures, their elements, their connections and their materials under the action of statically repeated force, mainly obtained through experimental investigations, and extensively considers lowering of proportional limit of materials, low-cycle fatigue, local and primary buckling, P- $\Delta$  effects, behaviors of connections and frames, and miscellaneous problems.

## RESUME

Ce rapport réfère à diverses propriétés mécaniques de constructions en acier, de leurs éléments, assemblages et matériaux sous l'action de charges statiques répétées. Les résultats obtenus proviennent essentiellement d'études expérimentales. Le rapport envisage la diminution de la limite élastique des matériaux, l'étude de la fatigue sous l'effet de cycles longs, du flambage local et primaire, des effets P- $\Delta$ , du comportement des assemblages et structures, ainsi que d'autres problèmes.

## ZUSAMMENFASSUNG

Der Bericht bezieht sich auf verschiedene mechanische Charakteristiken von Stahlbauten, auf ihre Elemente, ihre Verbindungen und Materialien unter Einwirkung statisch wiederholter Kräfte. Sie wurden in der Hauptsache durch experimentelle Untersuchungen gewonnen und berücksichtigen weitgehend das Absinken der Elastizitätsgrenze der Materialien, die in längeren Zyklen wiederholte Ermüdung, sowie die örtliche und primäre Knickung, die P- $\Delta$  Effekte, das Verhalten der Verbindungen und Tragwerke, nebst weiteren Problemen.

Leere Seite  
Blank page  
Page vide