

**Zeitschrift:** IABSE reports of the working commissions = Rapports des commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen

**Band:** 14 (1973)

**Artikel:** Effect of grouting on the fatigue strength of post-tensioned concrete beams

**Autor:** Brøndum-Nielsen, Troels

**DOI:** <https://doi.org/10.5169/seals-14480>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 29.03.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## IV

### Effect of Grouting on the Fatigue Strength of Post-Tensioned Concrete Beams

Influence de l'injection des câbles sur la résistance à la fatigue des structures en béton précontraint

Einfluss des Einpressmörtels auf die Ermüdungsfestigkeit von Spannbetonkonstruktionen

Troels BRØNDUM-NIELSEN  
Professor, Dr. techn.  
Structural Research Laboratory  
Technical University of Denmark

In the Structural Research Laboratory at the Technical University of Denmark tests have been carried out in order to investigate

The fatigue strength of prestressing wire.

The fatigue strength of anchorages for prestressing wire and tendons.

The influence of bond on the fatigue strength of post-tensioned concrete beams.

The research project was carried out under the supervision of S. Gravesen and E. Skettrup. N. J. Jørgensen and F. Petersen assisted in the beam tests.


For most prestressing systems the fatigue strength of the anchorages is much lower than the fatigue strength of the tendons. However, it should nevertheless be possible to utilize the fatigue strength of the tendons provided that the following three conditions are fulfilled:

The anchorages should be placed in zones where the stress variations are small, for instance, in the vicinity of simple supports.

The ducts for the tendons should be grouted after the tensioning.

The grout should be able to transfer stresses of a magnitude which is sufficient to ensure a reliable bond between tendon and concrete.

The test results have not yet been published. A brief description will be given in the following.

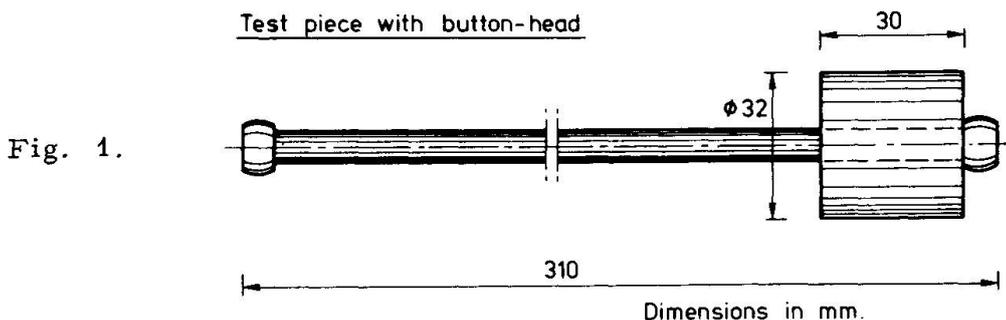

One prestressing system tested in our laboratory used button heads on the wires (see Fig. 1). These heads were made by pressing the ends

of the wires so that the diameter was locally increased. When the wire is threaded through holes in the anchor plates the button head will anchor the wire to the plate (see Fig. 2).

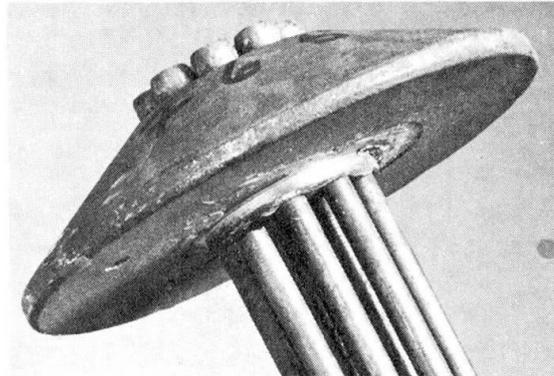


Fig. 2.

A stress-strain curve for the wire is shown in Fig. 3.

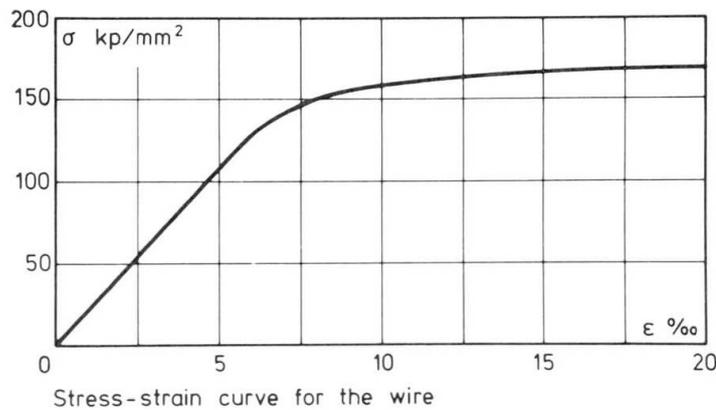


Fig. 3.

The fatigue strength of the wire proper is illustrated by the Wöhler diagram in Fig. 4.



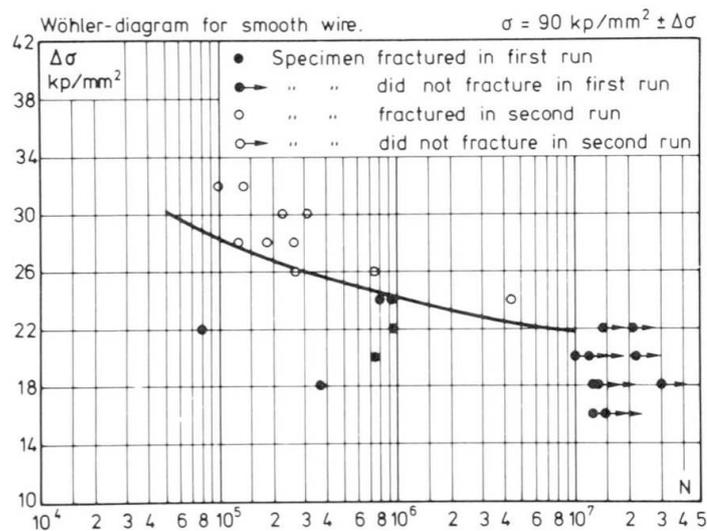


Fig. 4.

The corresponding diagram for wire anchored with button heads is illustrated in Fig. 5.

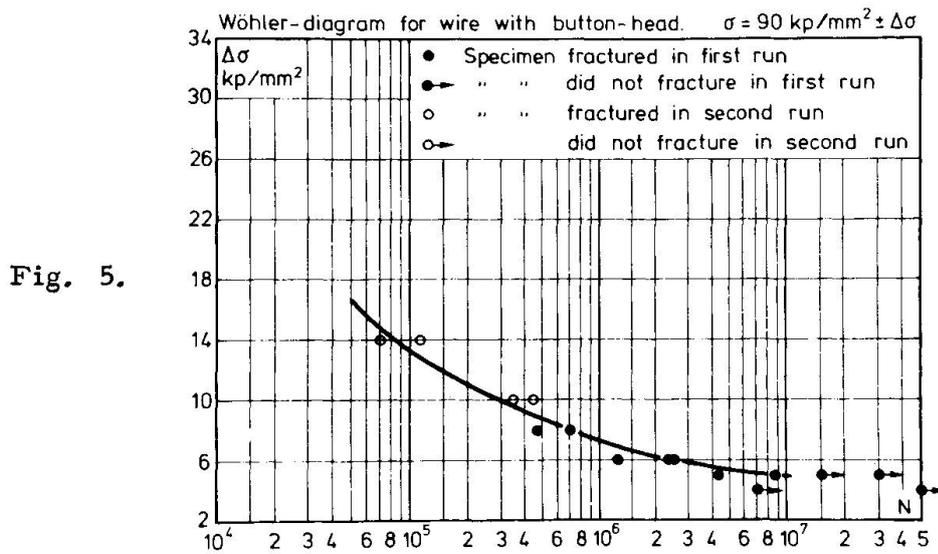


Static tensile tests were carried out with cables (see Fig. 6). The results of these tests are illustrated in Table 1.

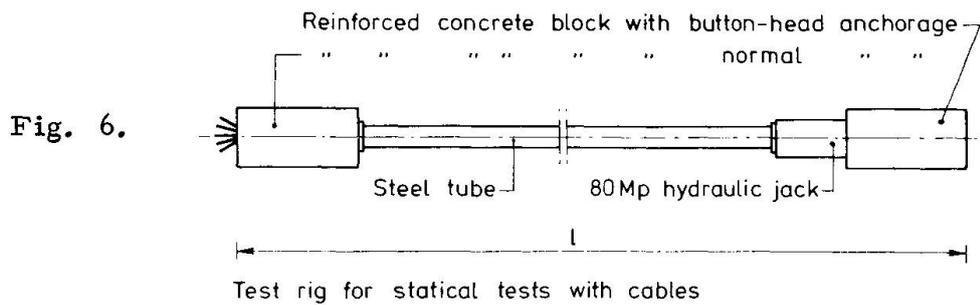

Test No.	Location of rupture	Character	Cable force Mp	Cable stress $\text{kp/mm}^2$
1	active anchorage	inclined	68	147
2	-	-	68	147
3	-	-	66	143
4	-	-	72	156
5	-	-	64	139
6	-	-	64	139
7	-	necking	78	169
8	passive anchorage	necking at button-head	76	165
9	active anchorage	necking	79	171

Table 1.


The fatigue strength of the cables were measured in the test rig illustrated in Fig. 7 and the results of the tests are given in Table 2.

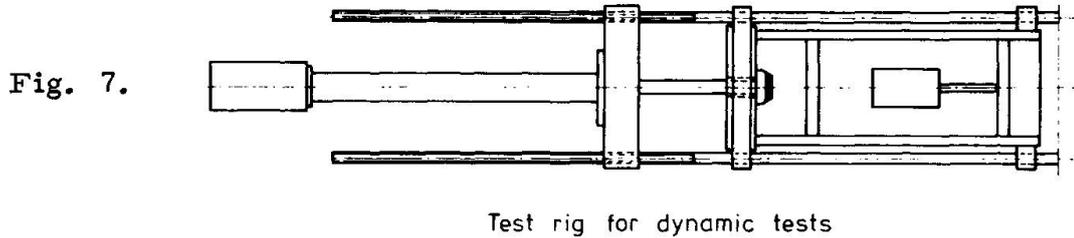

Test No.	Stress and force level		Number of load cycles in millions	
	kp/mm <sup>2</sup>	Mp		
1	90 ± 4	41.6 ± 1.85	0.829	First wire fracture Second - fracture
	90 ± 4	38.1 ± 1.70	0.986	
2	90 ± 4	41.6 ± 1.85	1.719	Fracture in two wires
3	90 ± 4	41.6 ± 1.85	0.828	First wire fracture Second - fracture No further fractures
	90 ± 4	38.1 ± 1.70	0.944	
	90 ± 4	34.6 ± 1.55	3.866	

Table 2.

Fatigue tests were carried out with 6 post-tensioned concrete beams (see Fig. 8). In order to simulate severe bond stress conditions, a shear span to depth ratio of about 3.0 was adopted.

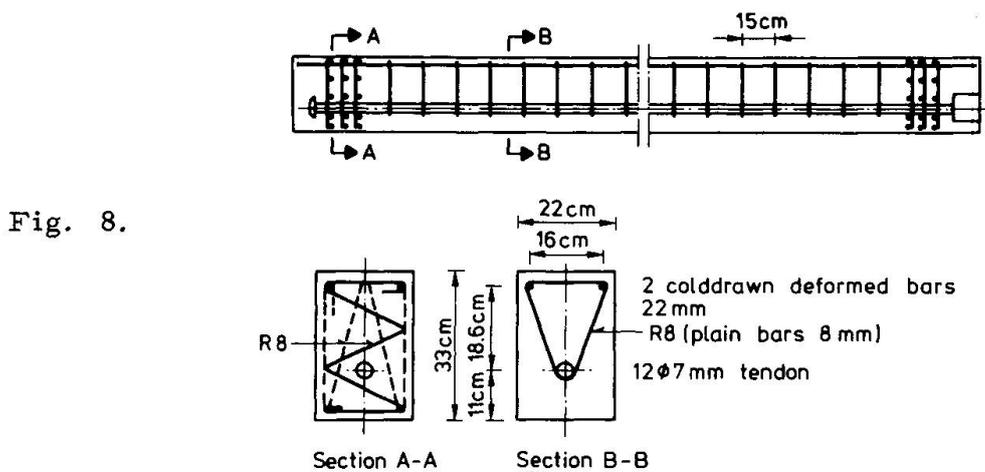


In three of the beams the cable duct was grouted whereas the duct was left ungrouted in the remaining three. The beams were subjected to a fatigue load in bending (see Fig. 9).

First a stress amplitude in the tendons of 5.5 kp/mm<sup>2</sup> in the un-

grouted beams and  $6 \text{ kp/mm}^2$  in the grouted beams was adopted. All six beams were subjected to about 2 million load cycles of this magnitude without rupture.

Fig. 9.

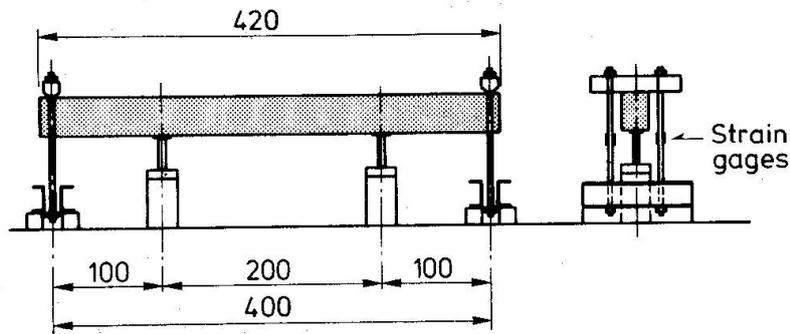

Afterwards the stress amplitude was increased to  $7,6 \text{ kp/mm}^2$  in the ungrouted tendons and  $7,8 \text{ kp/mm}^2$  in the grouted tendons, and the beams were subjected to this load until rupture. The number of cycles before rupture is indicated in Table 3.

Beam No.	Grouted			Ungouted		
	1	3	5	2	4	6
Number of load cycles before rupture in millions	2.02	3.18	2.09	0.26	0.23	0.09

Table 3.

### Conclusion.

According to the test results, the fatigue strength of post-tensioned concrete structures with unbonded tendons is low due to the low fatigue strength of the anchorages. If the anchorages are located in zones where the stress variations are small, the fatigue strength of the structure can be increased considerably by grouting the ducts.

## SUMMARY

The fatigue strength of post-tensioned concrete structures with unbonded tendons is low due to the low fatigue strength of the anchorages. Tests carried out at the Technical University of Denmark indicate that the fatigue strength can be increased considerably by grouting the ducts, provided that the anchorages are located in zones where the stress variations are small.

## RESUME

La résistance à la fatigue des structures en béton précontraint, utilisant des câbles gainés non injectés, est faible, due à la modeste résistance à la fatigue des ancrages. Des essais réalisés à l'Université Technique du Danemark montrent que cette résistance à la fatigue peut être augmentée considérablement par l'injection des câbles, pourvu que les ancrages soient placés dans des zones à faible variation de contrainte dans le béton.

## ZUSAMMENFASSUNG

Die Ermüdungsfestigkeit von Spannbeton ohne Verbund ist niedrig, weil die Ermüdungsfestigkeit der Verankerungen niedrig ist. Versuche an der Technischen Hochschule Dänemarks zeigen, dass die Ermüdungsfestigkeit durch Auspressen der Spannkanäle mit Zementmörtel vergrößert wird, vorausgesetzt dass die Verankerungen in Zonen mit niedrigen Betonspannungsvariationen angebracht sind.