

**Zeitschrift:** IABSE reports of the working commissions = Rapports des commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen

**Band:** 17 (1974)

**Artikel:** Ultimate load capacity of circular strongly reinforced concrete columns

**Autor:** Oberti, Guido

**DOI:** <https://doi.org/10.5169/seals-16500>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 13.12.2025

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## IV

### Ultimate Load Capacity of Circular Strongly Reinforced Concrete Columns

Résistance ultime de colonnes circulaires en béton fortement armé

Bruchbelastung sehr verstärkter, runder Betonsäulen

**Guido OBERTI**

Prof. Ing.

President of ISMES

Istituto Sperimentale Modelli e Strutture

Bergamo, Italy

## 1. INTRODUCTION

Special problems are involved about economy and safety of strongly reinforced concrete columns occurring in the design of tall buildings. Although circular-bound columns are not necessarily the most economical form of column construction, the extra cost is mostly offset by the advantages arising from the extra available floor space, especially in multi-story buildings.

Experimental investigations have been carried out several years ago at the ISMES (Bergamo, Italy) on 1 : 2.5 scale models. The scale ratio of supported loads was  $2.5^2 = 6.25$ . Some design considerations were examined and various types of reinforcement were compared.

The aim of the research was to establish a comparison between the maximum load which may be supported by differently reinforced circular columns, designed at the base of a multi-story building, having fixed diameter and established effective length. The slenderness of the columns was relatively small (5 to 7.5).

So many variants enter into the design of a column that is not easy to decide which combination gives the most economical member. For a column having a fixed diameter (as smaller as possible) and a very high load, exceeding 5,000 tons, the proportion of the concrete, the percentage of longitudinal reinforcement, independent or helical binders and steel pipes filled with concrete must be taken into consideration, and only an experimental comparison may suggest the best solution.

## 2. OUTLINE OF TESTED SERIES OF MODELS

Our tests concerned exceptional cases of reinforcement, beyond the rules established by the Italian Code for calculating the increase in bearing capacity due to the circular binding.

Two series of 1 : 2,5 models were tested. They were circular columns ( $\phi = 40$  cm) with different height Length, diameter, type of concrete, shape of web reinforcement (welded circular hoop), steel reinforcement of normal specified yield point ( $2,400 \text{ Kg/cm}^2$ ) were common factors for each series; whereas the percentage  $\mu$  of the longitudinal bars, of section  $A_f$ , and  $\mu_1$  of the circular binders ( $\wedge$ ), of equivalent section  $A_s$ , were different (Table 1).

1<sup>st</sup> SERIES

model N°	$\phi$ column cm	H cm	$A^\Omega$ cm <sup>2</sup>	$A_n$ core cm <sup>2</sup>	$A_f$ cm <sup>2</sup>	$\mu$ %	$A_s$ cm <sup>2</sup>	$\mu_1$ %	$A_{tot}$ cm <sup>2</sup>	$\mu_{tot}$ %	$P_r$ (tons) rupture		$\sigma_r = \frac{P_r}{\Omega}$ Kg cm <sup>2</sup>	$A_l$ (*) cm <sup>2</sup>	$\frac{\epsilon_d}{\epsilon_l}$	(P)
											( $\diamond$ )	( $\bullet$ )				
1	40	300	1250	-	0	0	0	0	0	0	-	306	245	1250	0,20	125
2	40	300	1250	706	12,5	1	25,0	2	37,5	3	187,5	350	280	2562	0,20	125
3	40	300	1250	633	25,0	2	12,5	1	37,5	3	282,0	350	280	2187	0,22	125
4	40	300	1250	633	62,5	5	125,0	10	187,5	15	560,0	1006	805	7812	0,18	250
5	40	300	1250	633	125,0	10	62,5	5	187,5	15	750,0	950	750	5937	0,14	250
6	40	300	1250	467	125,0	10	250,0	20	375,0	30	970,0	1525	1220	14375	0,09	250
7	40	300	1250	408	250,0	20	125,0	10	375,0	30	1060,0	1406	1125	10625	0,14	250

2<sup>nd</sup> SERIES

model N°	$\phi$ column cm	H cm	$A^\Omega$ cm <sup>2</sup>	$A_n$ core cm <sup>2</sup>	$A_f$ cm <sup>2</sup>	$\mu$ %	$A_s$ cm <sup>2</sup>	$\mu_1$ %	$A_{tot}$ cm <sup>2</sup>	$\mu_{tot}$ %	$P_r$ (tons) rupture	$\sigma_r = \frac{P_r}{\Omega}$ Kg cm <sup>2</sup>	$A_l$ (*) cm <sup>2</sup>	$\frac{\epsilon_d}{\epsilon_l}$	(P)
Protot.	100	500	7850	7235	209,0	2,7	105,0	1,35	314,0	4,0	NO FAILURE	-	-	0,26	1500
1	40	200	1250	907	33,9	2,7	17,6	1,35	51,5	4,1	675	540	2550	0,26	250
2	40	200	1250	-	22,6	1,8	50,2	4,0	72,8	5,8	825	660	4598	0,60	250
3	40	200	1250	-	22,6	1,8	100,4	8,0	123,0	9,8	1180	944	7620	0,60	250
1 a	40	200	1250	907	33,9	2,7	17,6	1,35	51,5	4,1	650	520	2550	0,27	250
2 a	40	200	1250	-	22,6	1,8	50,2	4,0	72,8	5,8	780	624	4598	-	-
3 a	40	200	1250	-	22,6	1,8	100,4	5,0	123,0	9,8	1130	904	7620	-	-

( $\diamond$ ) VALUE AT INTERRUPTION OF TEST (COLUMNS H=3 m)

( $\bullet$ ) FAILURE ON SPECIMEN OF 120 cm HEIGHT

(\*)  $A_l = A_n + 15 A_f + 45 A_s$

( $\wedge$ ) This percentage is related to the equivalent unit weight.

### 1st Series

Tests were carried out on 7 circular section models,  $\phi = 40$  cm and 300 cm high, corresponding to a prototype  $\phi = 1$  m and 7.5 m high.

The first column had no steel reinforcement; the others 6 were divided into three groups of two models, with total reinforcing percentage  $\mu_{\text{tot.}} = \mu + \mu_1$  of 3%, 15% and 30% respectively.

In each group the first model had double  $\mu$ , and  $\mu_1$  reduced by half, in relation to the second one.

The gradually increasing practically centered axial load tests were carried out in two separate stages. Stage one was interrupted when the radial displacements of the pillar became noticeable. In the second stage the height of the columns was reduced to  $h = 120$  cm; the columns were then subjected to gradually increasing axial load up to collapse.

The tests showed a better behaviour of axial reinforcement during the first tests stage, whereas at collapse the models with circular reinforcement behaved a little better.

During the first stage axial and diametral deformations were measured; in the second stage (column 120 cm high) only measurements of diametral deformations were taken (fig. 1).

The concrete was composed of crushed limestone, with a maximum grain size of 9 mm; the cement was normal (type 500), in the proportion of  $300 \text{ Kg/m}^3$ , with the ratio  $W/C = 0.6$ .

### 2nd Series

Here we had a prototype column  $\phi = 100$  cm and 5 m high with longitudinal reinforcement of steel ( $\phi = 32$  mm,  $\mu = 2.7\%$ ) and circular binders ( $\phi = 20$  mm) 9 cm spaced ( $\mu_1 = 1.35\%$ ). The column was tested with the eccentric load foreseen in design ( $e = 56$  mm) up to the maximum of the press-machine (2,000 tons), without reaching the collapse.

Moreover three 1 : 2.5 scale models ( $\phi = 40$  cm, 200 cm high) were tested: the first was exactly the model of the above mentioned prototype, while in the two others the reinforcing binders were composed of mild steel tubes, 4 and 8 mm thick respectively. These three models were tested with central load.

A second group of 3 models, equal to the previous ones, was tested with eccentric load as for the prototype ( $e_m = 56/2.5 = 22.4$  mm).

All these models were tested up to collapse. At the various load stages both horizontal and diametral deformations were measured (fig. 2).


The concrete used for models was composed of quarry aggregates, with maximum grain size of 30 mm, high resistance cement (type 680) (^) in the proportion of  $360 \text{ Kg/m}^3$ ; ratio  $W/C = 0.4$ .

Some photoes give an idea of the reinforcements and of the models after the collapse.

---

(^) Failure  $430 \text{ Kg/cm}^2$  at 28 days.

## CENTERED LOAD

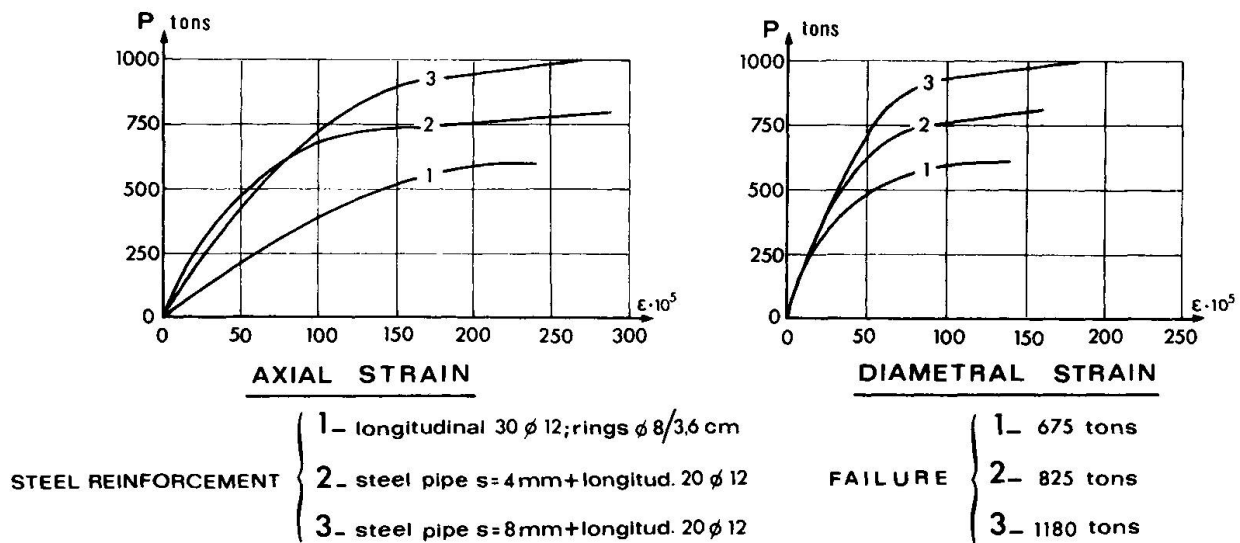

## ECCENTRIC LOAD ( $e=22,4$ mm)

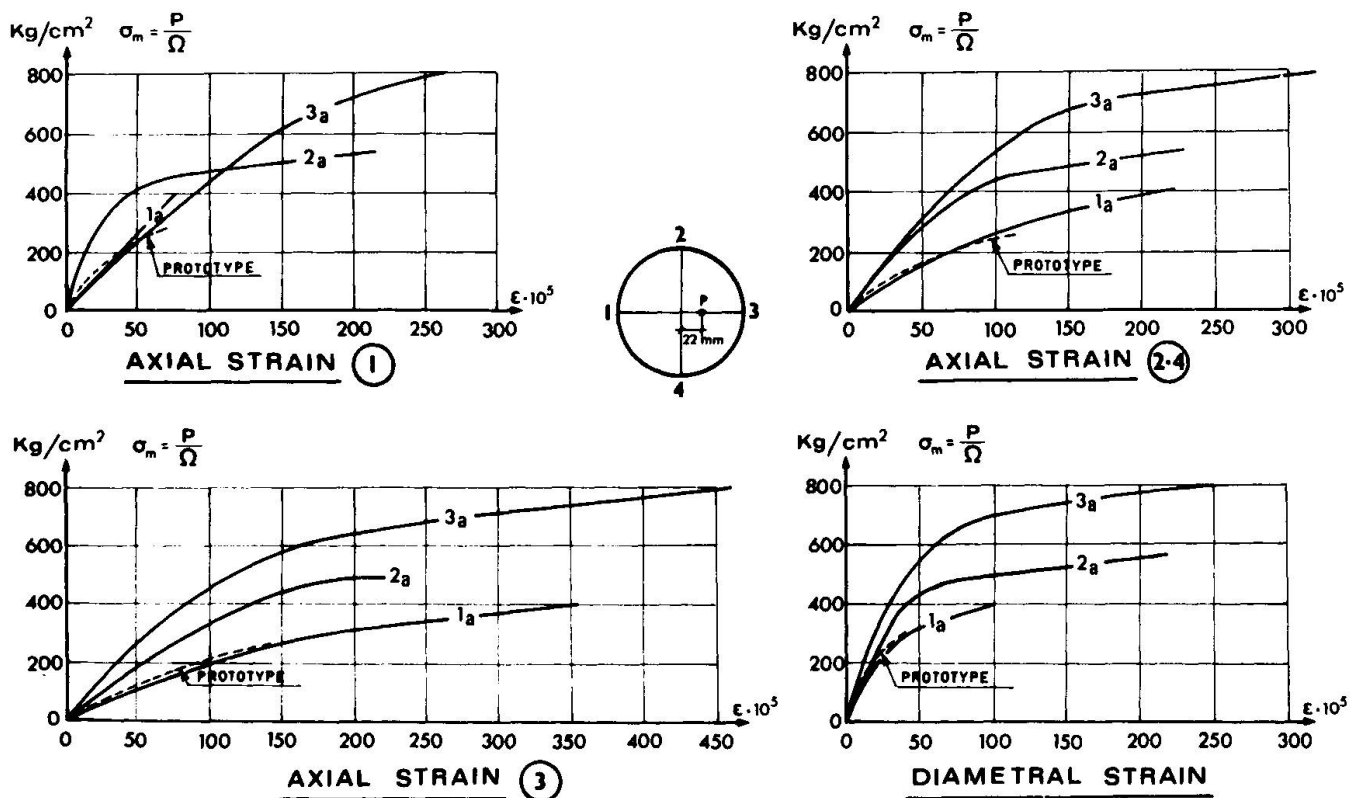


FIG. 2 - Second series

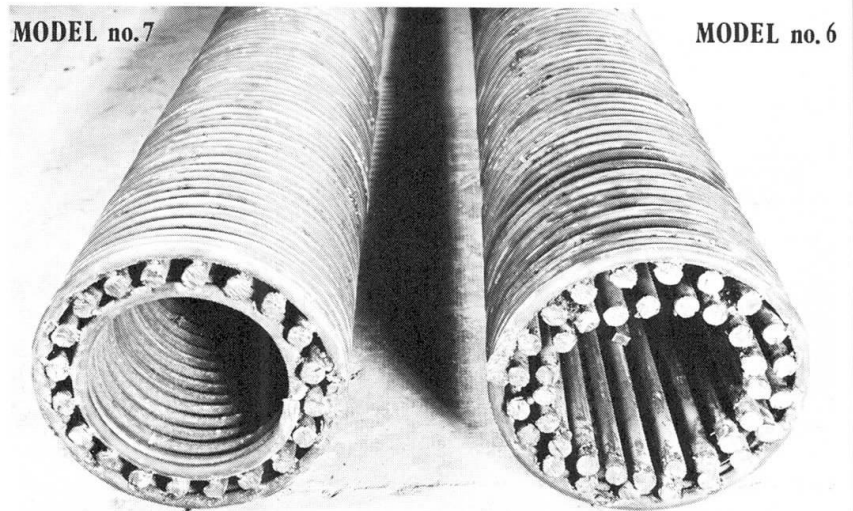
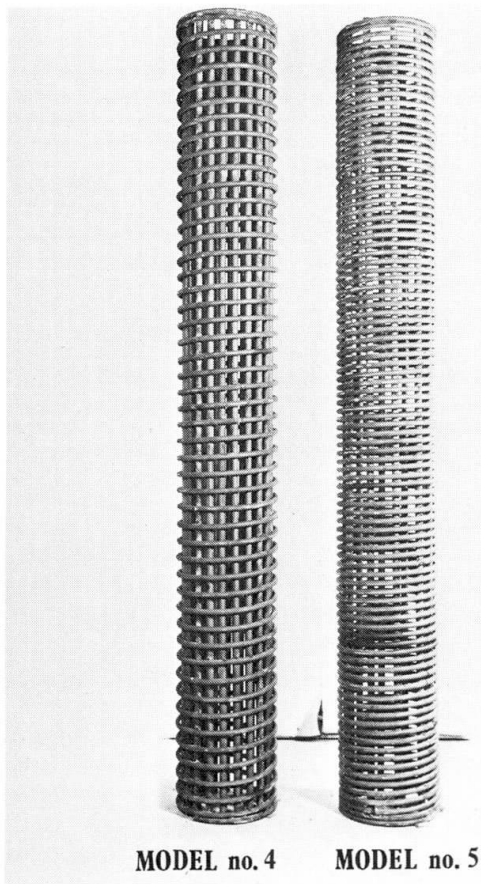


PHOTO 2      First Series:

Model no. 6 :	$\mu = 10\%$ ,	$\mu = 20\%$ .
Model no. 7 :	$\mu = 20\%$ ,	$\mu = 10\%$ .

PHOTO 1      First Series:

Model no. 4 :	$\mu = 5\%$ ,	$\mu = 10\%$ .
Model no. 5 :	$\mu = 10\%$ ,	$\mu = 5\%$ .

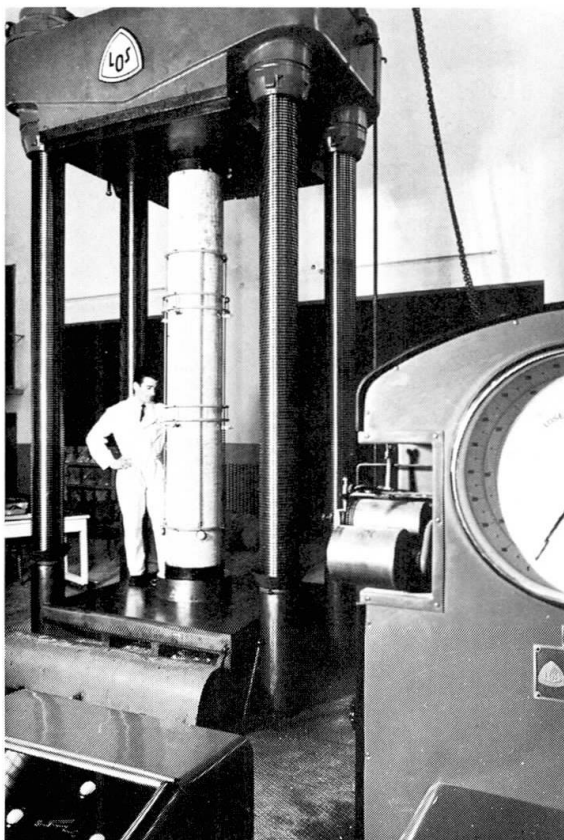


PHOTO 4      First Series:

1. 20 m height models after failure tests.

PHOTO 3

Model under test; view of the apparatus for measurement of axial and diametral deformations.



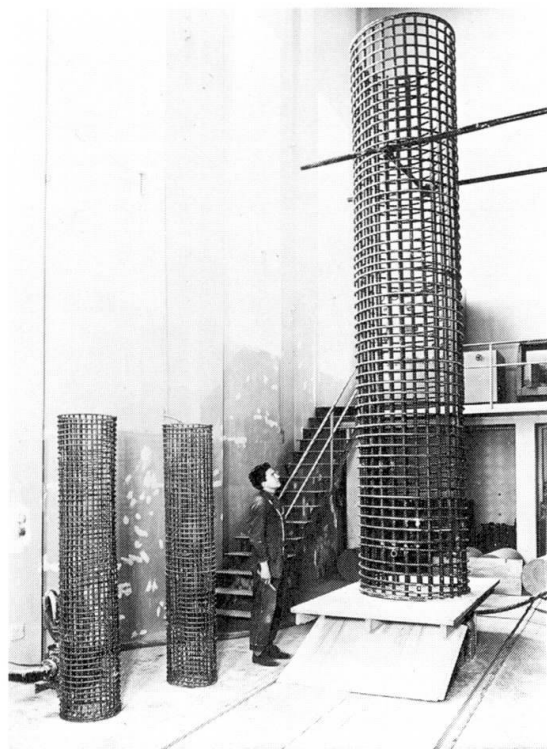


PHOTO 5 Second series:  
Reinforcement of prototype pillar.



PHOTO 6 Second series:  
Prototype pillar under test.

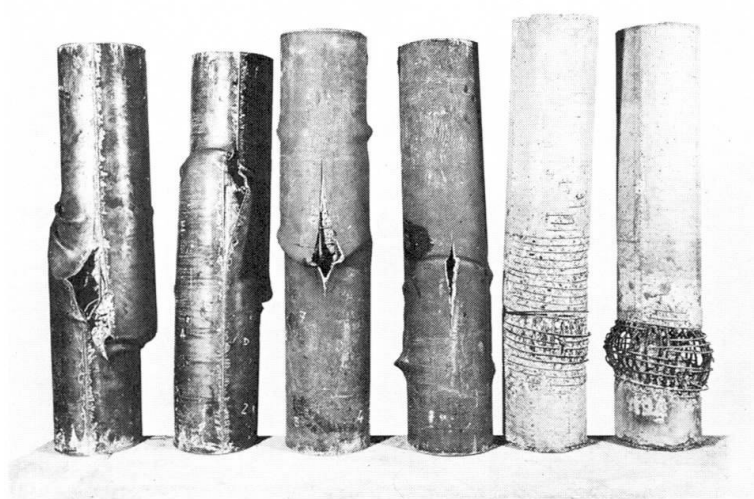


PHOTO 7 Second series: ( $H = 2\text{ m}$ ):  
Models after failure tests.

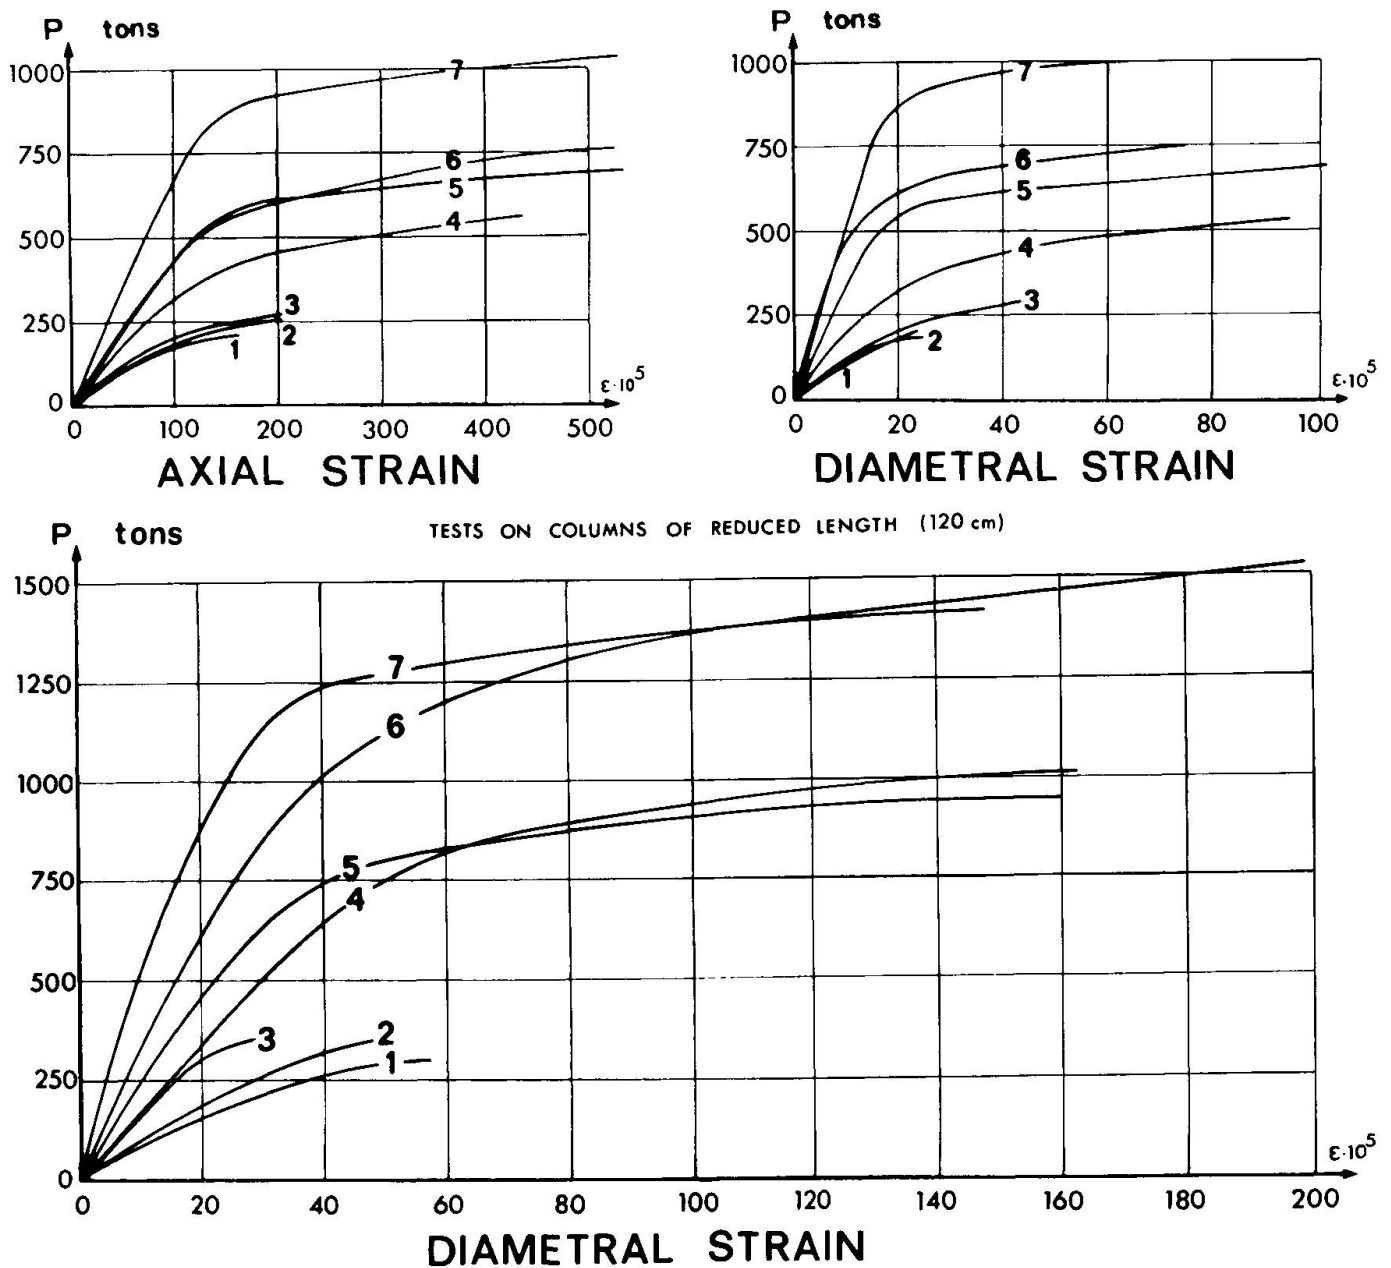


FIG.1 - First series

### 3. CONCLUSIONS

The tests on large scale models of strongly reinforced concrete circular columns, having limited slenderness, may give useful indications in design stage.

The first series of tests shows the elevate ultimate capacity of strongly reinforced concrete columns. Up to the yield point, the axial reinforcement appears more useful than the binder reinforcement; at collapse the binders show greater efficiency.

In the second series, the agreement of the deflections of one prototype and the corresponding model have been established. Moreover the remarkable influence of steel pipe reinforcement has been shown.



## SUMMARY

The paper deals with some tests on large scale models of strongly reinforced concrete columns having circular shape and limited slenderness. The usefulness of this type of tests in design stage is put in evidence.

## RESUME

Le rapport présente quelques essais sur de grands modèles de colonnes circulaires en béton fortement armé et d'élancement limité. On met en évidence l'utilité de ce type d'essai dans la phase du projet.

## ZUSAMMENFASSUNG

Der Artikel beschreibt Versuche an hochbewehrten Säulen mit kreisförmigem Querschnitt und begrenzter Schlankheit. Die Zweckmässigkeit dieser Art von Versuchen in der Entwurfsphase wird hervorgehoben.