Zeitschrift: IABSE reports of the working commissions = Rapports des

commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen

Band: 23 (1975)

Artikel: Column buckling curve of welded steel tube

Autor: Kato, Ben

DOI: https://doi.org/10.5169/seals-19815

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Mehr erfahren

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. En savoir plus

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. Find out more

Download PDF: 22.10.2025

ETH-Bibliothek Zürich, E-Periodica, https://www.e-periodica.ch

COLUMN BUCKLING CURVE OF WELDED STEEL TUBE

Ben Kato
Professor of Structural Engineering
Faculty of Engineering
University of Tokyo
Japon

ABSTRACT

This paper presents the results of experimental research regarding the buckling strength of centrally loaded welded steel tubular columns.

The specific contents of this paper are:

- (1) Effect of thermal residual stress and locked-in stress induced by cold forming on the tangent modulus in elasto-plastic range.
- (2) Effect of supporting fixtures.
- (3) Formulation of column buckling curve and comparison with test results.

1. INTRODUCTION

The column curve for steel tubular struts adopted by Commission 8 of the European Convention of Constructional Steelwork seems to be derived from the knowledge of the performance of seamless tube which is almost free from residual stress, and it was ranked with the superior class(a) of the eventually settled three curves. For the use of structural members, however, welded steel tubes produced by cold forming and high frequency induction welding are much more popular than seamless tubes because of their excellent productivity and of versatility of sizes. Mechanical properties of welded steel tube as a whole are somewhat different from that of seamless steel tube mainly by the influences of welding thermal residual stress and of locked in stress induced by cold forming. Hence the column buckling behavior of welded steel tube in inelastic region may also differ from that of seamless tube.

A series of buckling test of welded steel tubular columns were carried out under pin-ended centrally loaded condition. Test results are compared with the theoretical prediction based on the mechanical properties obtained from the stub-column tests. They are also compared with design loads allowed by the current Japanese specification.

2. TANGENT MODULUS AND CRITICAL STRESS OF WELDED STEEL TUBE

In a welded tube, three types of stress may be introduced during its producing process;

- 1) Elastic and plastic bending stress of tube wall along the circumferential direction as shown in Fig.1(a). Combined with the applied compressive axial load, this causes the biaxial state of stress and thus affects the yielding of a column. On this problem, a study on the basis of mathematical plasticity had been made (1).
- 2) When a steel strip is bent to tubular shape by cold forming, it will warp upward as shown in Fig.1(b). This is forced to straighten up in the course of cold rolling process. Thus bending stress of wall in longitudinal direction is induced. Several examples of measurement of the distribution of this bending stress(2) are shown in Fig.2(b).




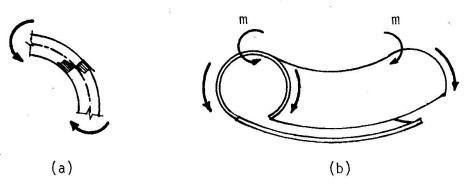


Fig.1 Cold Forming of Steel Tube

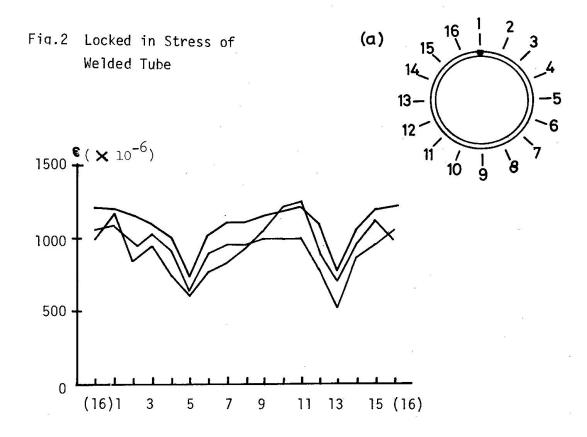



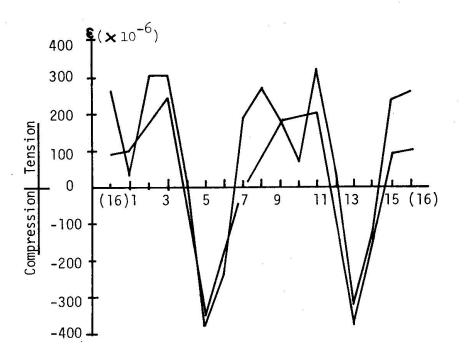

(c) Thermal Residual Stress due to Welding

3) Thermal residual stress due to welding. Examples of the distribution of this residual stress(2) are shown in Fig.2(c).

Yielding of the column subject to axial compression is affected by these locked in stresses, and the average stress-strain relationship obtained from stub-column test shows so called round house shape as is shown in Fig.3.

In case of seamless tube which is almost free from residual stress, it shows rather clear yield point(Fig. 3).

To obtain the general expression of stress-strain relationship of this round house type, stub-column tubes with different yield points and diameter-to-thickness ratios were tested. As shown in Fig.4, $\sigma_{\text{D}}/\sigma_{\text{y}}$ ratios can be roughly

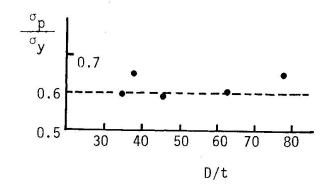


Fig.4 σ_p/σ_y ratios

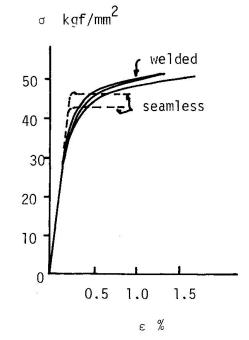


Fig.3 $\sigma - \varepsilon$ curve from stub-column tests

estimated as 0.6 through all tests, where σ_p is the proportional limit and σ_y is the yield strength defined by 0.2% offset basis. Assuming that σ_p = 0.6 σ_y , it was found that $\sigma\text{-}\epsilon$ relation could be well approximated as

$$\sigma = \alpha (80\alpha + 1.0)E - \frac{\alpha^2 (80\alpha + 0.4)^2 E}{\varepsilon + \alpha (80\alpha - 0.2)}$$
 (1)

where

$$\alpha = \sigma_y / E$$

E = Young's modulus

From eq.(1), tangent modulus E_t can be expressed as

$$E_{t} = \frac{d \sigma}{d \varepsilon} = \frac{\left[\alpha(80\alpha + 1.0)E - \sigma\right]^{2}}{\alpha^{2}(80\alpha + 0.4)^{2} E}$$
(2)

Then the critical stress in inelastic region is

$$\sigma_{cr} = \frac{\pi^2 E_t}{\lambda^2} = \frac{\pi^2 [\alpha(80\alpha + 1.0)E - \sigma_{cr}]^2}{\lambda^2 (80\alpha + 0.4)^2 E}$$
 (3)

Eq. (3) can be written in nondimensional form as

$$\frac{\sigma_{\rm cr}}{\sigma_{\rm v}} = \frac{1}{\overline{\lambda}^2} \left[\frac{80\alpha + (1.0 - \sigma_{\rm cr}/\sigma_{\rm y})}{80\alpha + 0.4} \right]^2$$

where

$$\overline{\lambda} = \lambda \sqrt{\frac{\sigma_y}{\pi^2}}$$

$$\lambda = l/r = slenderness$$

3. EFFECT OF SUPPORTING FIXTURES

It has been reported that it is very difficult to realize the ideal pin-end condition in column testing(3)(4). Knife edges and conventional spherical seats were reported to be unsatisfactory because of their inevitable friction. Shown in Fig.5 are hydraulically-supported spherically seated compression testing machine platens invented by R.L.Templin(5), which seems to be one of the best devices. Two series of test results of tubular columns are shown in Fig.6. Templin type platens were used in one

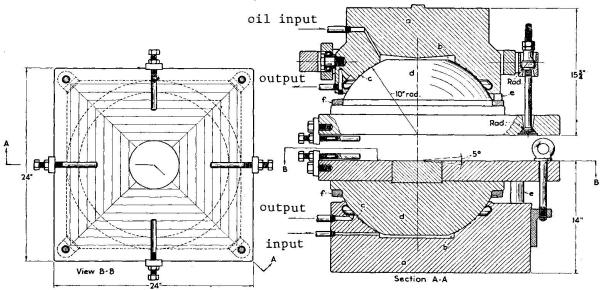


Fig. 5 Templin Type End Fixture

test, while conventional spherical seats were used in the other(6). The latter test resulted in higher values up to 40% than theoretical prediction. Hence, test results of tubular columns referred in this report are limited to those obtained by using Templin type platens.

4. TEST RESULTS

Available test results of welded tubular columns are shown in Fig.7 and in Table 1.(7)(8)(9). Test results are compared with eq.(4). Deviation from theoretical prediction becomes large in elastic-to-plastic transitive region. Many test results are higher than Eular value in elastic region, which means that even the Templin's device would be not ideal.

In Fig.7, test results of seamless tubes are also plotted by open circles(6)(8). The column curve after DIN4114 is shown by dashed line in the same figure, which is described as

$$\sigma_{cr} = \frac{\pi^2 E \tau}{\lambda^2}$$

$$\tau = 1 - \left(\frac{\sigma_{cr} - \sigma_{p}}{\sigma_{y} - \sigma_{p}}\right)^2, \quad \sigma_{p} = 0.6 \, \sigma_{y}$$
(5)

This can be written in nondimensional form as

$$\frac{\sigma_{cr}}{\sigma_{y}} = \frac{1}{\overline{\lambda}^{2}} \left[1 - \left(\frac{\sigma_{cr}/\sigma_{y} - 0.6}{0.4} \right)^{2} \right]$$

$$\overline{\lambda} = \lambda \sqrt{\frac{\sigma_{y}}{\pi^{2}}}$$
(6)

Test results on seamless tubes which are almost free from residual stress seem to show better correlation with eq.(6) than with eq.(4). Substantial difference can be seen between the buckling strength of welded tubes and of seamless tubes.

5. COMPARISON WITH JAPANESE COLUMN FORMULA

Column formulae specified by Japan Architectural Institute(A.I.J.)(10) are as follows;

$$f_{c} = \left[1 - 0.4 \left(\frac{\lambda}{\Lambda}\right)^{2}\right] \sigma_{y}/\nu \qquad \text{for } \lambda \leq \Lambda$$

$$f_{c} = \frac{0.6\sigma_{y}}{\nu(\frac{\lambda}{\Lambda})^{2}} \qquad \text{for } \lambda > \Lambda$$
(7)

where

 f_c = allowable compressive stress


$$\Lambda = \sqrt{\frac{\pi^2 E}{0.6\sigma_y}}$$

$$\nu = \frac{3}{2} + \frac{2}{3} \left(\frac{\lambda}{\Lambda}\right)^2 \qquad \text{for } \lambda \leq \Lambda$$

$$= 2.17 \qquad \text{for } \lambda \geq \Lambda$$
(8)

Above formulae can be written in nondimensional form as

$$\frac{f_c}{\sigma_y} = \frac{1 - 0.31 \lambda \sqrt{\frac{\sigma_y}{\pi^2 E}}}{1.5 + 0.4(\lambda \sqrt{\frac{\sigma_y}{\pi^2 E}})^2} \qquad \text{for } \lambda \sqrt{\frac{\sigma_y}{\pi^2 E}} \leq 1.29$$

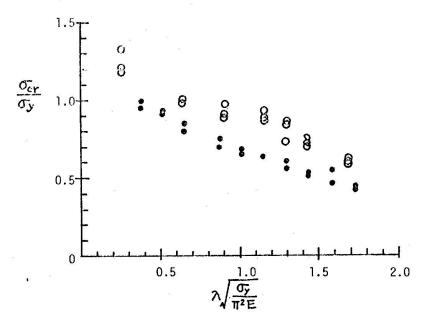

- ----Templin Type Platen(ref.7)
- O----Conventional Spherical Seat(ref.5)

Fig. 6 Effect of End Support Fixture

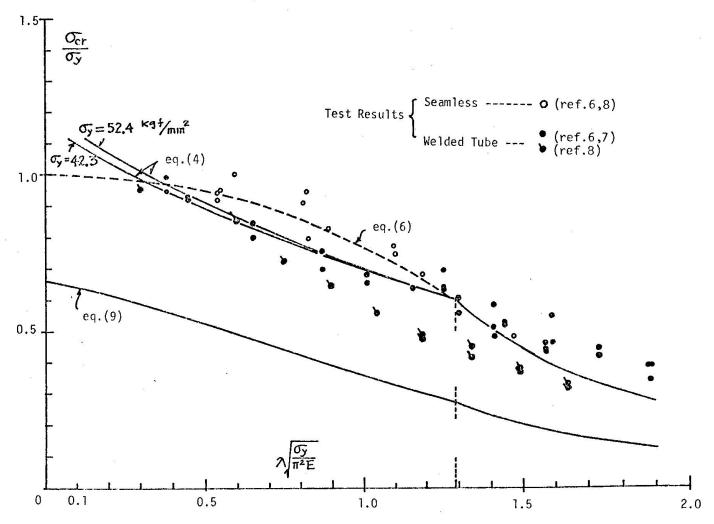


Fig.7 Test Results, Theoretical Curve & Design Formula

$$\frac{f_c}{\sigma_y} = \frac{1}{2.17} \frac{1}{\left(\lambda \sqrt{\frac{\sigma_y}{\pi^2 E}}\right)^2} \qquad \text{for} \qquad \lambda \sqrt{\frac{\sigma_y}{\pi^2 E}} > 1.29$$

The column curve expressed by eq.(9) is depicted in Fig.7 to compare with test results.

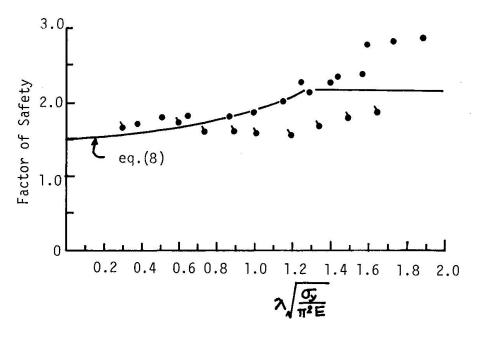


Fig.8 Factor of Safety

Each average of test results which have identical slenderness ratio are divided by corresponding nondimensional allowable stress comes from eq.(9), and is plotted in Fig.8. Nominal factor of safety specified by A.I.J. standard (eq.(8)) is also shown in the figure. In inelastic region, specified factor of safety increases paraborically starting from 1.5, while it is constantly designated as 2.17 throughout elastic region as seen in eq.(8). Safety factor of 1.5 is the one which is designated for the tension member. Test results of reference(8) show rather lower value. This might be caused by some imperfections (initial curvature, eccentricity) or unfavorable locked in stress for which no information is available from reference(8). Anyhow, as far as available test results are concerned, factor of safety of 1.5 is secured through the whole range.

Table 1. TEST RESULTS

Test A. Reference(6), Welded Tube, Grade of Steel:STK 50, σ_y =52.4 kgf/mm²

size $\phi \times t.mm$	length mm	slenderness $\lambda = \mathbf{l/r}$	σ _{max} (σ _{cr}) kgf/mm ²	σ _{max} /σ _y	$\lambda \sqrt{\frac{\sigma_y}{\pi^2 E}}$
	1,600	79.1 79.1 79.1	36.4 33.4 33.0	0.695 0.638 0.630	1.255 1.255 1.255
(0 Fv2 0	1,800	88.7 88.9	25.1 26.8 30.6	0.480 0.511 0.585	1.413 1.410 1.413
60.5×2.9	2,000	98.7 98.9 98.9	23.2 23.4 24.0	0.443 0.446 0.458	1.570 1.571 1.571
	2,400	118.5 118.7 118.4	18.1 20.1 20.2	0.346 0.384 0.386	1.885 1.890 1.885

Test B. Reference(7), Welded Tube, Grade of Steel:STK 50,

$\sigma_{y}=42.3$	kgf/mm ² fo	r 139.8φ×4.5mm	$\sigma_y = 43.8$	kgf/mm ²	for 60.5φ×3.2mm
	1,410	26.7	42.0	0.993	0.382
	1,409	26.7	40.0	0.945	0.382
139.8×4.5	$\frac{1}{1},910$	36.2	39.0	0.921	0.517
139.0×4.3	1,910	36.2	39.2	0.926	0.517
	$\frac{-2}{3}$, 412	45.6	33.8	0.799	0.651
	2,413	45.6	35.9	0.850	0.651
	1,210	59.7	33.2	0.758	0.871
	1,211	59.7	30.5	0.696	0.871
	$-\frac{1}{411}$	69.5	28.5	0.651	1.010
	1,411	69.5	29.7	0.678	1.010
	1,610	79.4		-	1.155
	1,612	79.4	27.8	0.635	1.155
60.5×3.2	1,812	89.2	24.6	0.561	1.299
60.3×3.2	1,812	89.2	26.7	0.610	1.299
	2,012	99.1	23.1	0.527	1.440
	2,013	99.1	22.9	0.523	1.440
	$\frac{-2}{2}, \frac{21}{3}$	109.1	20.3	0.464	1.590
	2,213	109.1	24.2	0.552	1.590
	$\frac{-2}{2},412$	118.9	18.6	0.425	1.730
V	2,412	118.9	19.5	0.445	1.730

Test C. Reference(8), Welded Tube, Grade of Steel:STK 50, σ_y =46.3 kgf/mm²

	a same a compact firm on an arrangement		care form no construct or a			
size ¢×t.mm	length mm	slenderness $\lambda = \mathbf{l}/r$	σ _{max} (σ _{cr}) kgf/mm ²	σ _{max} /σ _y	$\lambda \sqrt{\frac{\sigma_y}{\pi^2 E}}$	
	3,840	110.0	14.6	0.316	1.640	
	<u>3,840</u>	110.0	15.1	0.326	1.640	
	3,491	100.0	17.4	0.377	1.490	
	3,491	100.0	16.9	0.365	1.490	
	3,142	90.0	19.1	0.411	1,340	
2	3,142	90.0	20.8	0.448	1.340	
101.6×2.9	2,793	80.0	21.7	0.468	1.193	
	2,793	80.0	22.2	0.478	1.193	
	$\frac{-2}{3}, \frac{444}{4}$	70.0	25.6	0.552	1.043	
	2,095	60.0	29.7	0.643	0.895	
	1,746	50.0	33.5	0.725	0.745	
	1,396	40.0	39.5	0.852	0.597	
6 160 M M M M M	698	20.0	44.0	0.952	0.299	

Test D. Reference(6), Seamless Tube, σ_y =52.0 kgf/mm² for 60.5 ϕ ×2.9mm. σ_y =37.6 kgf/mm² for 89.1 ϕ ×3.5mm, 101.6 ϕ ×3.5mm, 114.3 ϕ ×4.5mm.

60.5×2.9	1,400	68.8	40.3	0.770	1.095
	1,400	69.0	39.2	0.749	1.100
89.1×3.5	1,200	39.9	35.4	0.940	0.535
	1,800	60.0	34.2	0.910	0.807
101.6×3.5	1,400	40.8	35.8	0.950	0.550
	2,100	60.8	35.6	0.945	0.818
114.3×4.5	1,550	39.9	34.7	0.920	0.537
	2,300	59.1	31.0	0.824	0.795

Test E. Reference(8), Seamless Tube, $\sigma_y = 46.1 \text{ kgf/mm}^2$

101.6×2.9	3,442	99.0	22.26	0.482	1.470
	2,793	80.0	31.31	0.680	1.192
	2,095	60.0	38.30	0.832	0.895
	1,396	40.0	46.45	1.020	0.596

REFERENCES

- (1) Ben Kato & H. Aoki, Effects of Cold Forming on the Mechanical Properties of Welded Steel Tube, Trans. Architectural Institute of Japan, extra issue, Aug. 1969.
- (2) Wakabayashi, M. et.al., Residual Stress in Welded Steel Tube, Proc. Annual Meeting of Kinki Branch of A.I.J., April, 1967.
- (3) Progress Report of the Special Committee on Steel Column Research, Trans. A.S.C.E., vol. 89.
- (4) Barlow, H.W., A Fixture for Obtaining Pin-end Conditions in Column Testing, Journal of Aeronautical Sciences, vol. 7, No.2, Dec. 1939.
- (5) Templin, R.L., Hydraulically-supported Spherically-seated Compression Testing Machine Platens, Proc. of the 45th Annual Meeting, vol. 1. 42, A.S.T.M., 1942.
- (6) Suzuki, T. & Fujimoto, M., NKK Design Manual of Tubular Structure, Nippon Kokan K.K.,
- (7) Kato Ben et.al., Column Buckling Test on High Tensile Steel Tubes, Trans. Architectural Institute of Japan, No.63, Oct. 1959.
- (8) Kato Ben et.al., Column Buckling Test on High Tensile Steel Tubes, Proc. Annual Meeting of Kanto Branch of A.I.J., No.35, June, 1965.
- (9) Wakabayashi, M. et.al., Column Buckling Test on Welded Steel Tubes, Trans. Architectural Institute of Japan, Oct. 1968.
- (10) Design Specification of Structural Steel for Buildings, Architectural Institute of Japan, 1968.