

Zeitschrift: IABSE reports of the working commissions = Rapports des commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen

Band: 29 (1979)

Artikel: Torsion-bending-shear in concrete beams: a kinematic model

Autor: Elfgren, L.

DOI: <https://doi.org/10.5169/seals-23541>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 23.02.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>



II

Torsion-Bending-Shear in Concrete Beams: A Kinematic Model

Poutres en béton armé soumises à la torsion, à la flexion et au cisaillement. Une solution cinématique

Torsion-Biegung-Schub in Stahlbetonbalken. Eine kinematische Lösung

L. ELFGREN

Associate Professor of Structural Engineering

University of Luleå

Luleå, Sweden

SUMMARY

A kinematic solution according to the theory of plasticity is presented for reinforced concrete beams loaded in combined torsion, bending and shear.

RESUME

La méthode cinématique de la théorie de la plasticité est appliquée pour déterminer la résistance des poutres soumises à la torsion, à la flexion et à l'effort tranchant.

ZUSAMMENFASSUNG

Für Stahlbetonbalken unter Torsion, Biegung und Querkraft wird eine Lösung nach der kinematischen Methode der Plastizitätstheorie dargestellt.



1. INTRODUCTION

A kinematic model for beams loaded in combined torsion and bending has recently been presented by Peter Müller and Bruno Thürlimann [1] - [3]. The model clarifies some contradictions in the theory for torsion which have earlier been discussed by the writer [4], [5].

In this paper the kinematic model of Müller-Thürlimann is extended to include the effect of vertical shear as well. The extension is based on the same principles as the writer has earlier used in a kinematic model for torsion-bending shear based on skew bending [4] - [9].

The presentation below follows the same outline as the one in Bruno Thürlimann's paper [1]. The same general assumptions are made i.e. the concrete and the reinforcement are rigid perfectly plastic materials. The concrete is governed by a square yield criterion. The reinforcement bars have a yield stress of $\pm f_y$ and carry forces in axial directions only. Local and bond failures are excluded.

2. KINEMATIC MODEL

A kinematic model for combined torsion, bending and shear is presented in Figs. 1 and 2. In Fig. 1 general notations are given and in Fig. 2 the kinematic model is presented. In the model, there are two cracks, ABC and DEF, see Fig. 2a. The right half of the beam rotates around the axis AD through the crack ends in the top of the beam. In the bottom of the beam a parallelogram, BCEF, is cut out. The rotation around the axis AD is notated $\dot{\omega}$. The rotation is possible if the axis AD is parallel to the diagonal CF in the parallelogram. This implies the condition that $l_{AD} = l_{CF}$, see Fig. 2b. Further, the angle β of the rotation axis AD follows from the following geometric conditions.

$$l_{CF} = b \cot \alpha_4 + h \cot \alpha_2 - l_{AD} + h \cot \alpha_6 + b \cot \alpha_4$$

With $l_{CF} = l_{AD}$ and $\cot \beta = l_{AD}/b$ we obtain

$$\cot \beta = \cot \alpha_4 + \frac{h}{2b} (\cot \alpha_2 + \cot \alpha_6) \quad (2.1)$$

In order to express the energy dissipation, the velocity components of point B (equal to point E) are needed, see Fig. 2c.

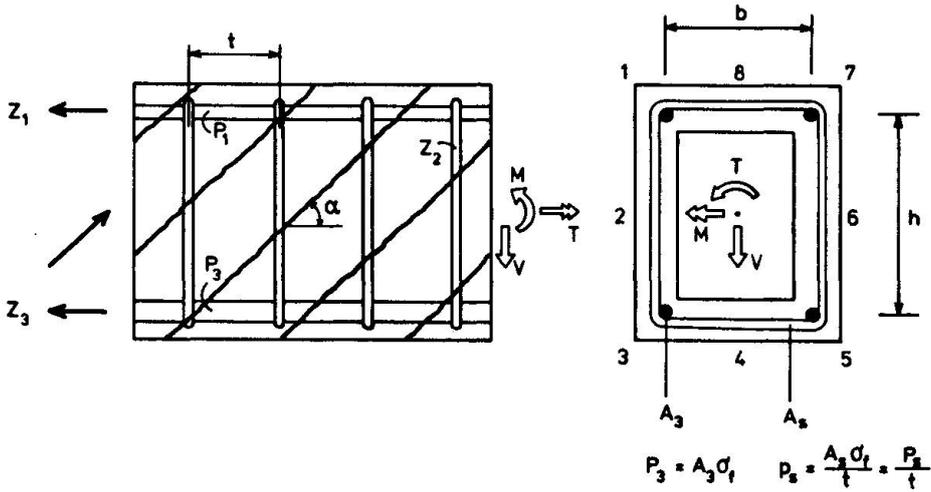


Fig. 1 Rectangular beam with box-section. Notations

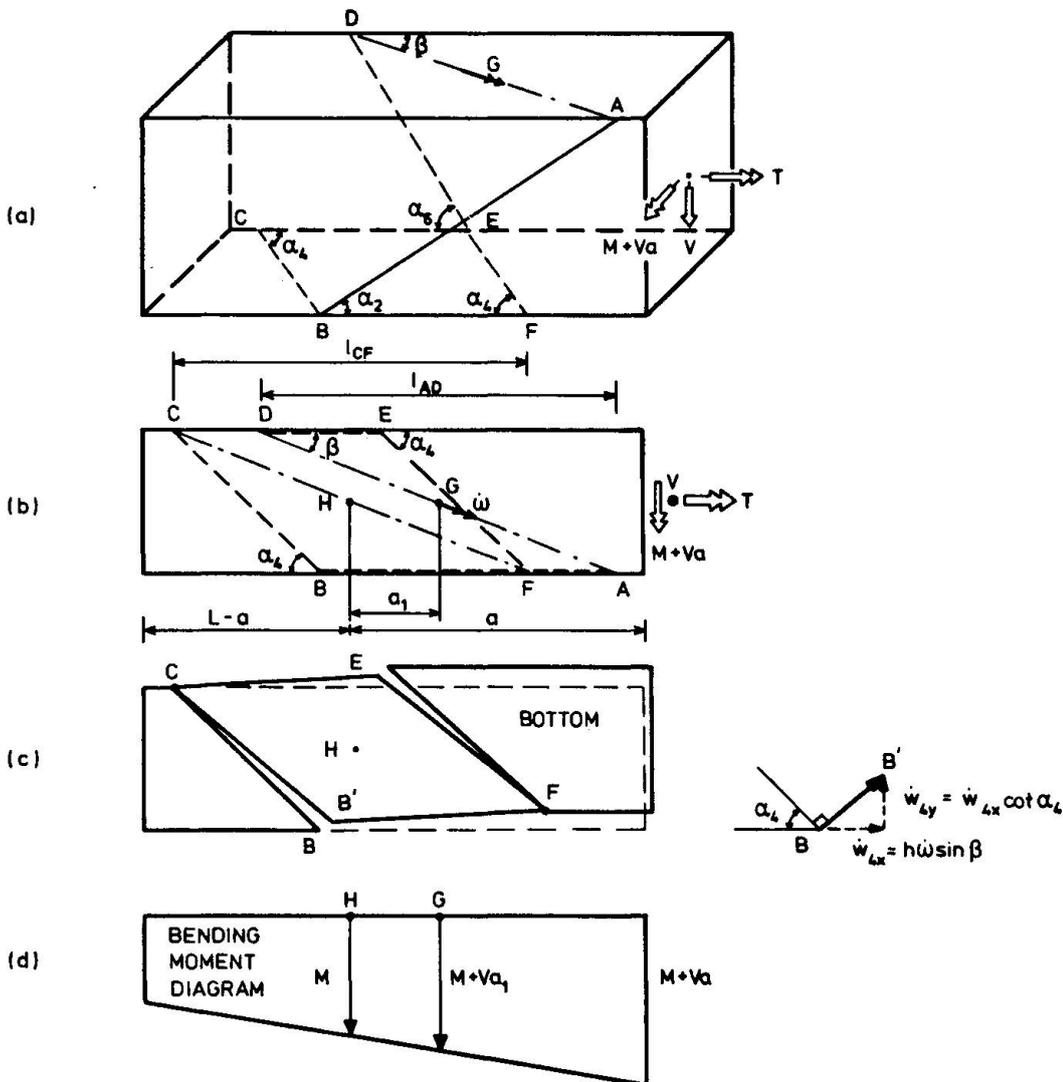


Fig. 2 Kinematic failure model: (a) General view; (b) Model seen from above; (c) Deformations in bottom; (d) Bending moment diagram.



$$\text{Wall 4: } \dot{w}_{4x} = h\dot{\omega} \sin \beta \quad \dot{w}_{4y} = \dot{w}_{4x} \cot \alpha_4 \quad (2.2)$$

$$\text{Wall 2: } \dot{w}_{2x} = h\dot{\omega} \sin \beta \quad \dot{w}_{2y} = \dot{w}_{2x} \cot \alpha_2$$

3. WORK EXPRESSIONS

Using the reinforcements shown in Fig. 1. the *internal work* in the cracks can be written as

$$L_{in} = \dot{w}_{4x}(P_3+P_5) + \frac{1}{2}p_s h\dot{w}_{2x} \cot^2 \alpha_2 + p_s b\dot{w}_{4x} \cot^2 \alpha_4 + \frac{1}{2}p_s h\dot{w}_{6x} \cot^2 \alpha_6 \quad (3.1)$$

The *external work* carried out when the beam rotates around the axis AD can be written in the following way. As a vertical shear force, V , is present, the bending moment is varying. It has the value M at the reference point H in the middle of the bottom parallelogram, BCEF, see Fig. 2b, where the longitudinal reinforcement bars Nos. 3 and 5 are crossed by cracks. The distance in the longitudinal direction of the beam between the point H and the midpoint G on the rotation axis is a_1 , and consequently the applied bending moment at point G will be $M + Va_1$. The external work equation then takes the form

$$L_{ex} = (M + Va_1) \dot{\omega} \sin \beta + T \dot{\omega} \cos \beta \quad (3.2)$$

where a_1 from Fig. 2b with $\cot \beta$ from Eq. (2.1) can be written as

$$a_1 = b \cot \alpha_4 + h \cot \alpha_2 - b \cot \beta = \frac{h}{2}(\cot \alpha_2 - \cot \alpha_6) \quad (3.3)$$

The failure mechanism is governed by the three inclinations α_2 , α_4 and α_6 . In the general case these three angles are independent of each other. This general case is lengthy to handle. In order to simplify the deductions, the following assumption will be made regarding the relationship between the angles

$$\left. \begin{aligned} \cot \alpha_2 &= \cot \alpha_T + \cot \alpha_V \\ \cot \alpha_4 &= \cot \alpha_T \\ \cot \alpha_6 &= \cot \alpha_T - \cot \alpha_V \end{aligned} \right\} \quad (3.4)$$

The angles α_T and α_V are here two independent variables.

The assumption is motivated by the fact that the failure mechanism will in this way correspond with a probable stress distribution in the beam.

The expression for the internal work L_{in} in Eq. (3.1) can now be rewritten as

$$\begin{aligned} L_{in} &= \dot{\omega} \sin \beta [h(P_3 + P_5) + \frac{1}{2} p_s h^2 (2 \cot^2 \alpha_T + 2 \cot^2 \alpha_V) + p_s b h \cot^2 \alpha_T] = \\ &= \dot{\omega} \sin \beta [h(P_3 + P_5) + p_s h(b+h) \cot^2 \alpha_T + p_s h^2 \cot^2 \alpha_V] \end{aligned} \quad (3.5)$$

In order to simplify the expression for the external work L_{ex} in Eq. (3.2), we first rewrite the expression for $\cot \beta$ in Eq. (2.1) and the expression for the distance a_1 in Eq. (3.3)

$$\cot \beta = \cot \alpha_T + \frac{h}{2b} 2 \cot \alpha_T = \frac{b+h}{b} \cot \alpha_T \quad (3.6)$$

$$a_1 = h \cot \alpha_V \quad (3.7)$$

The external work can now be written

$$L_{ex} = \dot{\omega} \sin \beta [M + T \frac{b+h}{b} \cot \alpha_T + Vh \cot \alpha_V] \quad (3.8)$$

The internal work in Eq. (3.5) shall be equal to the external work in Eq. (3.8)

$$M + T \frac{b+h}{b} \cot \alpha_T + Vh \cot \alpha_V = h(P_3 + P_5) + p_s h(b+h) \cot^2 \alpha_T + p_s h^2 \cot^2 \alpha_V \quad (3.9)$$

4. MINIMIZATION

If T and V are fixed, the minimum value of M with respect to the angles α_T and α_V follows from differentiations of Eq. (3.9) with respect to $\cot \alpha_T$ and $\cot \alpha_V$

$$\frac{\partial M}{\partial \cot \alpha_T} + T \frac{b+h}{b} = 2p_s h(b+h) \cot \alpha_T$$

$$\frac{\partial M}{\partial \cot \alpha_V} = 0 \text{ gives } \cot \alpha_T = \frac{T}{2bh} \cdot \frac{1}{p_s} \quad (4.1)$$

$$\frac{\partial M}{\partial \cot \alpha_T} + Vh = 2p_s h^2 \cot \alpha_V$$

$$\frac{\partial M}{\partial \cot \alpha_V} = 0 \text{ gives } \cot \alpha_V = \frac{V}{2h} \cdot \frac{1}{p_s} \quad (4.2)$$



For the case of pure bending ($T = V = 0$), pure torsion ($M = V = 0$) and pure shear ($M = T = 0$), Eq. (3.9) with Eqs. (4.1) and (4.2) gives

$$M_0 = h(P_3 + P_5) ; \quad T_0 = 2bh \sqrt{\frac{P_3+P_5}{b+h}} p_s ; \quad V_0 = 2h \sqrt{\frac{P_3+P_5}{h}} p_s \quad (4.3)$$

Using Eqs. (4.1) to (4.3), Eq. (3.9) can now be rewritten as

$$M/M_0 + (T/T_0)^2 + (V/V_0)^2 = 1 \quad (4.4)$$

This is the same solution as has earlier been obtained with a static approach [4], [6], [10]. Hence there is an identity between the kinematic model presented here and earlier presented static methods.

If the three inclinations α_2 , α_4 and α_6 are retained as independent variables in the work expressions, Eq. (3.9) can be written in the following way.

$$\begin{aligned} M + T\left(\frac{h}{2b}\cot\alpha_2 + \cot\alpha_4 + \frac{h}{2b}\cot\alpha_6\right) + \frac{h}{2}(\cot\alpha_2 - \cot\alpha_6) &= \\ = h(P_3+P_5) + \frac{1}{2}p_s h^2(\cot^2\alpha_2 + \cot^2\alpha_6) + p_s bh \cot\alpha_4 & \end{aligned} \quad (4.5)$$

A minimization of M with respect to the angles α_2 , α_4 and α_6 will then give

$$\left. \begin{aligned} \cot\alpha_2 &= \left(\frac{T}{2bh} + \frac{V}{2h}\right)\frac{1}{p_s} = \cot\alpha_T + \cot\alpha_V \\ \cot\alpha_4 &= \frac{T}{2bh} \cdot \frac{1}{p_s} = \cot\alpha_T \\ \cot\alpha_6 &= \left(\frac{T}{2bh} - \frac{V}{2h}\right)\frac{1}{p_s} = \cot\alpha_T - \cot\alpha_V \end{aligned} \right\} \quad (4.6)$$

Hence, the shear flow from torsion and shear are acting in the same direction in side 2, and in opposite directions in side 4. This is in agreement with the assumption in Eq. (3.4).

5. DISCUSSION

The inter-action equation presented, Eq. (4.4), is deduced for point H in Fig. 2c. As can be seen from the moment diagram in Fig. 2d, the bending moment is higher in point G and in every point to the right of point H in the figure. The failure mechanism presented for point H is for this reason not stable [3].

A failure mechanism will start to develop in the area with the highest loads, that is, in the right end of the beam element in Fig.2. However, in the right end of the beam a support or a concentrated load may be situated. This will influence and change the failure mechanism. High concrete stresses will occur and they may cause the failure. For this reason the failure model will be more complicated in the vicinity of a support or a concentrated load.

To be correct according to the theory of plasticity, the effect of warping should be considered [3]. However, Paul Lüchinger has shown that for a rectangular beam, as is studied here, the effect of warping may be neglected [10]. If the warping is considered, it will at worst give a slightly higher load-carrying capacity.

Although the presented kinematic model is not stable for mispan cross-sections, it does give a rather good prediction of the type of cracks and deformations that has been observed in tests see Fig. 3 [7], [8]. The model also gives an identical load-carrying capacity as earlier presented static methods [4], [6], [10]. For these reasons, the writer considers the presented kinematic model to be a step in the direction of a better understanding of the interaction between torsion, bending and shear. To be able to give a complete solution to the problem, the effects of supports and of loading conditions must be studied. Here the concrete compression strength must be entered as an essential parameter.

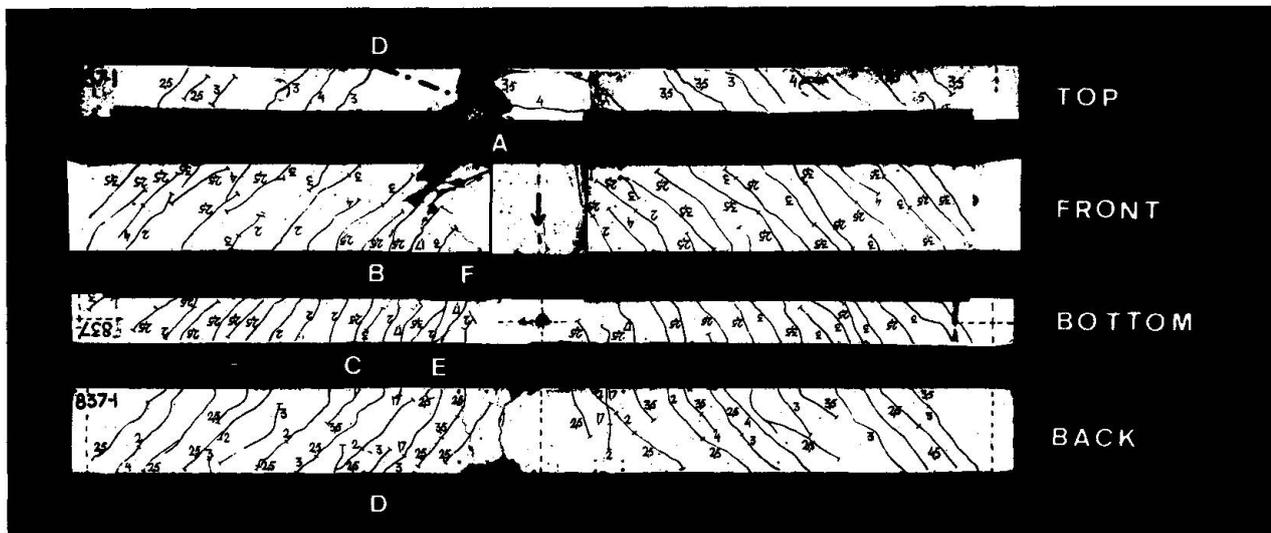


Fig. 3 Crack pattern and failure mechanism for a beam loaded in combined torsion, bending and shear. (Beam 1-1A in [4] and [7]). The beam is loaded in mid-span with an eccentric point-load acting downwards. The numerals along the cracks refer to the applied load when this part of the crack became visible (in $M_p = MN/100$). In the left part of the beam two failure cracks ABC and FED are indicated as well as a rotation hinge AD, compare with Fig. 2. (The beam is rectangular with $b \times h \times l = 100 \times 200 \times 3300$ mm. The stirrup capacity is $p_s = 0.236$ MN/m. The relation between the bending moment M , the torsional moment T and the vertical shear force V in the failure section is $M:T:Vh = 1:0.5:0.2$).



REFERENCES

- [1] BRUNO THÜRLIMANN: "Plastic Analysis of Reinforced Concrete Beams" IABSE Colloquium Copenhagen 1979, "Plasticity in Reinforced Concrete", Introductory Report. Reports of the Working Commissions, International Association for Bridges and Structural Engineering (IABSE), Vol. 28, Zürich 1978, pp. 71-90.
- [2] PETER MÜLLER: "Failure Mechanisms for Reinforced Concrete Beams in Torsion and Bending", Publications, International Association for Bridge and Structural Engineering (IABSE), Vol. 36-II, Zürich 1976, pp. 147-163
- [3] PETER MÜLLER: "Plastische Berechnung von Stahlbetonscheiben und -balken" (Plastic Analysis of Walls and Beams of Reinforced Concrete), Institut für Baustatik und Konstruktion, ETH Zürich, Bericht Nr. 83, Birkhäuser Verlag, Basel und Stuttgart, 1978, 160 pp.
- [4] LENNART ELFGREN: "Reinforced concrete beams loaded in combined torsion, bending and shear. A study of the ultimate load-carrying capacity". Dissertation, Chalmers University of Technology, Division of Concrete Structures, Publication 71:3, 1 Ed., Göteborg Nov. 1971, 204 pp, revised 2nd Ed., Göteborg Aug. 1972, 230 pp.
- [5] LENNART ELFGREN - INGE KARLSSON - ANDERS LOSBERG: "Nodal forces in the analysis of the ultimate torsional moment for rectangular beams". Magazine of Concrete Research (London), Vol 26, No 86, March 1974, pp 21-28.
- [6] LENNART ELFGREN - INGE KARLSSON - ANDERS LOSBERG: "Torsion - bending - shear interaction for reinforced concrete beams". Journal of the Structural Division, American Society of Civil Engineers (ASCE) (New York), Vol 100, No ST 8, Proc. Paper 10749, August 1974, pp 1657-1676.
- [7] LENNART ELFGREN - INGE KARLSSON: "Tests on rectangular beams in combined torsion, bending and shear". Chalmers University of Technology, Division of Concrete Structures. Report 71:1, Göteborg Nov 1971, 128 pp.
- [8] INGE KARLSSON - LENNART ELFGREN: "Förespända lådbalkar belastade med vridande och böjande moment samt tvärkraft" (Torsion, bending, and shear in Prestressed Concrete Box Girder Beams). Chalmers University of Technology, Division of Concrete Structures, Report 76:10, Göteborg, Sept 1976, 88 pp.
- [9] A A GVOZDEV - N N LESSIG - L K RULLE: "Research on Reinforced Concrete Beams under Combined Bending and Torsion in the Soviet Union". Paper SP 18-11 in "Torsion of Structural Concrete", American Concrete Institute (ACI), Publication SP-18, Detroit 1968, pp 307-336.
- [10] PAUL LÜCHINGER: "Bruchwiderstand von Kastenträgern aus Stahlbeton unter Torsion, Biegung und Querkraft" (Ultimate Strength of Box-Girders in Reinforced Concrete under Torsion, Bending and Shear), Institut für Baustatik und Konstruktion, ETH Zürich, Bericht Nr. 69, Birkhäuser Verlag, Basel und Stuttgart, 1977. 107 pp.