

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 37 (1982)

**Artikel:** New concepts for concrete fatigue design procedures in Japan  
**Autor:** Kakuta, Yoshio / Okamura, Hajime / Kohno, Michiyuki  
**DOI:** <https://doi.org/10.5169/seals-28894>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 06.12.2025

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**



## **New Concepts for Concrete Fatigue Design Procedures in Japan**

Nouveaux concepts pour le dimensionnement à la fatigue des structures en béton, au Japon

Neue Konzepte der Ermüdungsbemessung von Stahlbeton in Japan

### **YOSHIO KAKUTA**

Assoc. Professor  
Hokkaido University  
Sapporo, Japan

### **HAJIME OKAMURA**

Assoc. Professor  
University of Tokyo  
Tokyo, Japan

### **MICHIYUKI KOHNO**

Executive Director  
Nihon Kotsu Gijutsu KK  
Tokyo, Japan

## **SUMMARY**

The "Tentative Recommendations for the Limit State Design of Concrete Structures" were published by the Concrete Committee of the Japan Society of Civil Engineers in April 1981. The present report describes the fatigue design procedures introduced in the Recommendations. Fatigue strength of concrete in compression, reinforcing bars in tension and reinforced concrete in shear are dealt with.

## **RESUME**

Les Recommandations provisoires pour le calcul aux états-limites des structures en béton furent publiées par la commission "béton" de la Société japonaise des ingénieurs civils en avril 1981. Le présent rapport décrit les méthodes de calcul à l'état-limite de fatigue que la commission a recommandées. On traite de la résistance à la fatigue du béton en compression, des barres d'armature sous tension et du béton armé sous un effort tranchant.

## **ZUSAMMENFASSUNG**

Die vorläufigen Empfehlungen zur Bemessung von Betonbauwerken auf Grenzzustände wurden vom Betonkomitee der Japanischen Gesellschaft der Bauingenieure im April 1981 veröffentlicht. Der vorliegende Beitrag stellt das Bemessungsverfahren auf Ermüdung gemäss den Empfehlungen vor. Dabei werden die Ermüdungsfestigkeiten von Beton unter Druckbeanspruchung, Betonstahl unter Zugbeanspruchung, und Stahlbeton unter Schubbeanspruchung behandelt.



## 1. INTRODUCTION

In the 1967 Standards, the Japan Society of Civil Engineers (JSCE) introduced the fatigue provisions for design of reinforced concrete structures. Through the experiences of applying the provisions to the Shinkansen railroad structures, fatigue design procedures had been developed, and new procedures were introduced in the Tentative Recommendations for the Limit States Design of Concrete Structures in 1981 [1]. This report describes the fatigue design procedures introduced in the Recommendations and their background.

## 2. CONCEPTS OF FATIGUE DESIGN PROCEDURES

The concepts adopted in the Recommendations for the fatigue design procedures are summarized as follows:

(1) Fatigue limit states should be considered in the design of structures when the effects of variable loads are dominant.

(2) Design fatigue strength, which is obtained by dividing the characteristic strength by the appropriate partial safety factor for strength, should be larger than applied design variable stress.

(3) Characteristic fatigue strength shall be calculated from permanent stress and equivalent cycles,  $N$ , of the applied design variable stress. The equivalent cycles may be evaluated on the assumption of a linear cumulative damage theory, such as Miner's.

(4) Characteristic fatigue strength of concrete,  $f'_{rck}$ , may be calculated as follows:

$$f'_{rck} = (0.9k f'_{ck} - \sigma'_{cp}) (1 - \log N/15) \quad (1)$$

where  $f'_{ck}$  denotes the characteristic static strength of concrete,  $\sigma'_{cp}$  permanent compressive stress, and  $k(=0.85)$  coefficient considering the difference of the concrete strengths between cylinder specimens and the structural members. Principally, fatigue strength of reinforcing bars shall be determined on the basis of test results. The following values may be used for deformed bars with a diameter not larger than 32 mm:

$$\begin{aligned} f_{rsk} &= (160 \text{ MPa} - \sigma_{sp}/3) 10^{-0.2(\log N - 6)} && \text{for } \log N < 6 \\ &= (160 \text{ MPa} - \sigma_{sp}/3) 10^{-0.1(\log N - 6)} && \text{for } \log N > 6 \end{aligned} \quad (2)$$

where  $\sigma_{sp}$  is permanent tensile stress. However, fatigue strength of bars with bends or welding connections must not be taken greater than half of the values calculated from Eq.(2), unless determined by test results.

(5) Applied design stresses due to flexure may be calculated by the elastic theory of cracked section. However, the fatigue limit state for concrete in compression may be examined only for the stress at the location of compressive resultant. Applied design variable stress and permanent stress in shear reinforcement can be calculated as follows:

$$\begin{aligned} \sigma_{wrk} &= \{1.15(V_{md} - 0.5 V_{cd})s\} / \{A_w d(\sin \alpha + \cos \alpha)\} (V_{rd}/V_{md}) \\ \sigma_{wrp} &= \sigma_{wrk} (V_{pd}/V_{rd}) \end{aligned} \quad (3)$$

where  $V_{md}$  is the design maximum shear force,  $V_{cd}$  design ultimate shear force resisted by concrete,  $V_{pd}$  applied design permanent shear force,  $V_{rd}$  applied design variable shear force,  $A_w$  area of shear reinforcement within a distance  $s$ ,  $d$  effective depth and  $\alpha$  angle between shear reinforcement and longitudinal axis of the member.

(6) Fatigue limit states for reinforced concrete beams may generally be examined only for longitudinal tensile reinforcement and shear reinforcement. Fatigue limit states for reinforced concrete slabs may generally be examined only for tensile reinforcement. The examination of fatigue limit state for reinforced concrete columns may generally be omitted.

### 3. BACKGROUND OF THE CONCEPTS

#### 3.1 Methods for Checking of Safety

Limit states are generally placed in two categories, the ultimate and serviceability limit states. Fatigue limit states are considered as a kind of ultimate limit states since fatigue may result in a collapse of a part or whole structure.

The characteristic fatigue strength for a certain number of stress cycles corresponding to the specified life of a structure can be determined on the basis of the same concepts as the characteristic static strength which substantially corresponds to the strength for one stress cycle. The similar concepts may be applied to the partial safety factor for the strength of materials. Namely, the values of  $\gamma_m$  for fatigue limit states can be taken to be same as for the ultimate limit states. On the other hand the loadings associated with the fatigue limit states are essentially of the same nature as those with serviceability limit states. Therefore the values of  $\gamma_f$  for the fatigue limit states may be taken as much as for serviceability limit states, that is, in general  $\gamma_f = 1.0$ .

Criterion for fatigue failure of a material is generally expressed by a function of the permanent or the minimum cyclic stress, the range of stress or the maximum cyclic stress, and the number of stress cycles. The Recommendations define fatigue strength as the range of stress calculated from a fatigue criterion function for given permanent stress and a given number of cycles. Then the checking of safety against fatigue failure can be achieved to ensure that the design fatigue strength,  $f_{rd}$ , is larger than applied design variable stress,  $\sigma_{rd}$ .

$$f_{rd} > \sigma_{rd} \quad (4)$$

$$\text{where } f_{rd} > f_{rk} / \gamma_m, \quad \sigma_{rd} = \sigma_{rk} \quad (5)$$

$f_{rk}$  denotes the characteristic fatigue strength and  $\sigma_{rk}$  variable stress due to the characteristic loadings.

#### 3.2 Characteristic Fatigue Strengths

The characteristic fatigue strengths adopted in the Recommendations were determined on the basis of the investigations domestic as well as overseas'. The limitation of space, however, confined to enumerate only Japanese investigations, but a little overseas' ones.

##### (1) Fatigue Strength of Concrete



The statistical analysis of test data led to the following equation for probable fatigue life of concrete,

$$\log N = 17 [1 - S_r / (1 - S_p)] \quad (6)$$

in which  $S_r$  represents the range of stress level, defined as the ratio of variable stress to ultimate static strength, and  $S_p$  permanent stress level. Fig.1 shows a part of test data used in the analysis with the line obtained from Eq.(6). Fatigue strength calculated from Eq.(6) has an approximately 50 percent failure probability, and Eq.(1) was derived to provide characteristic fatigue strength of concrete with about 5 percent failure probability.

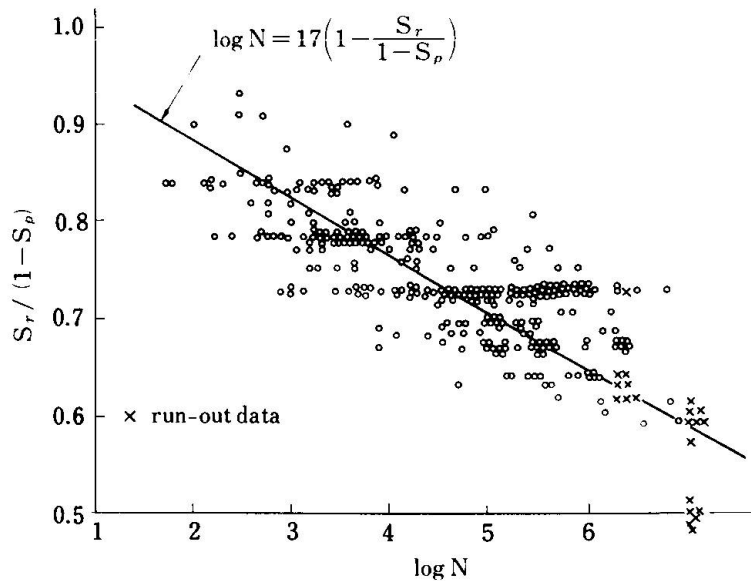


Fig.1 Fatigue strength of concrete in compression [4]-[8]

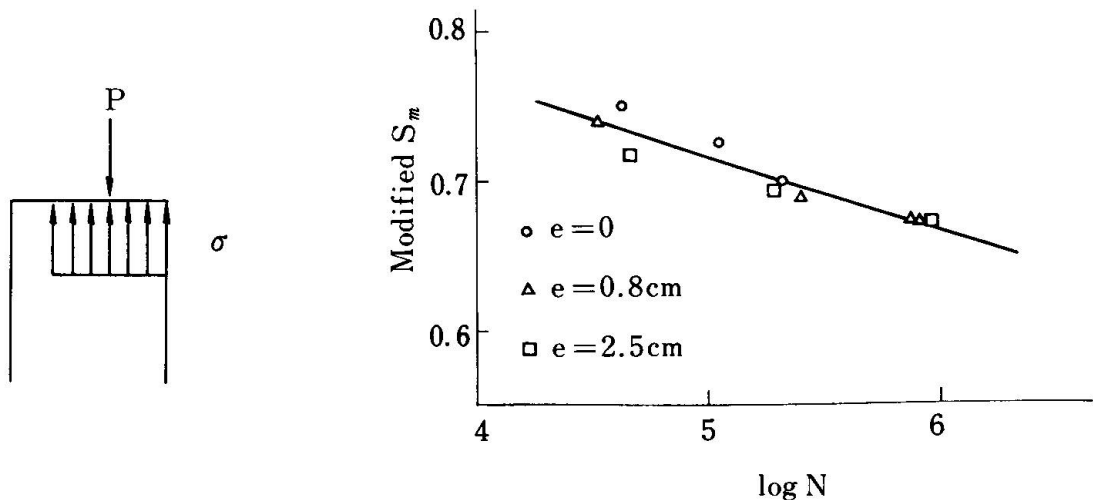


Fig.2 Stress calculation by rectangular stress distribution

Fig.3 Ople and Hulsbos' data with modified ordinate by [11]

It has been found that stress gradient has a significant effect on the fatigue strength of concrete in compression [8]–[10], in which the stress level is defined as the ratio of the extreme fiber stress to static strength in axial compression. On the other hand Matsushita and Makizumi [11] have pointed out that it is rather rational to define the stress level as the ratio of applied load to the ultimate load and proposed a method for calculating the stress of concrete by using a rectangular stress distribution, as seen in Fig.2, so that the effect of stress gradient diminishes as shown in Fig.3. The article in 2.(5) is based on their proposal.

The examination by numerical examples of the design of reinforced concrete members has shown that the checking of safety against fatigue failure of concrete can generally be omitted for the structures designed with  $\gamma_{mc} = 1.5$  and  $\gamma_f = 1.5$  for the ultimate limit states. However, it must be noted that the logarithm of fatigue life of lightweight aggregate concrete is about 70 percent of that of normal concrete, as seen in Fig.4 [5][9][10], and that logarithm of fatigue life of concrete in the water is only about two thirds or less of that in the air [15][16].

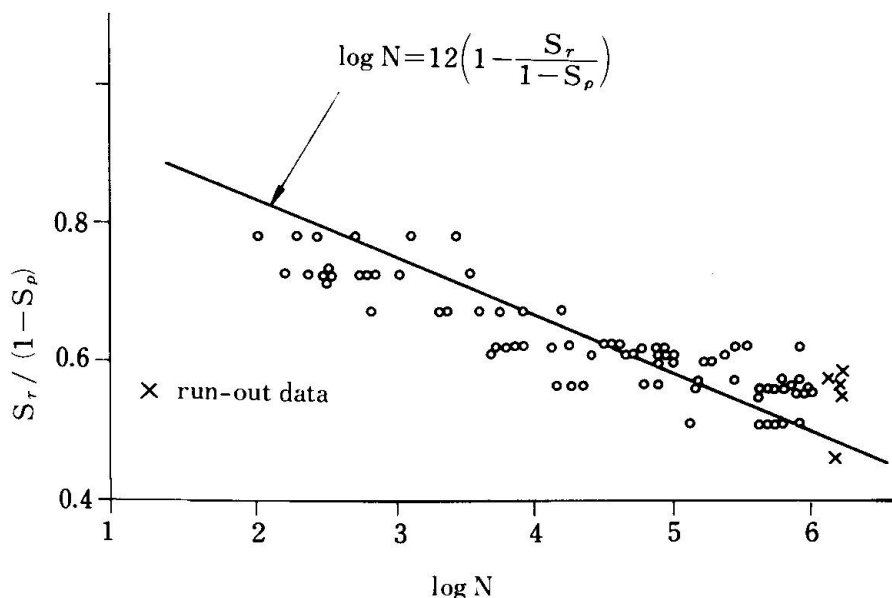


Fig.4 Fatigue strength of lightweight aggregate concrete in compression [5][9]

It has been found that the fatigue strengths of concrete in tension or flexure are about the same as that in compression when expressed by a percentage of the corresponding static strength [3][6]. Therefore, if necessary, Eq.(1) may be applied to determine characteristic fatigue strengths of concrete in tension or flexure.

Tests on concrete with compressive strength of 80 to 100 MPa [13][14] have shown that the fatigue strength of high strength concrete expressed by a percentage of its static strength is not less than that of normal concrete.

## (2) Fatigue Strength of Reinforcing Bars

It is known that the fatigue strength of reinforcing bars depends on many factors, such as geometry of surface deformations, bar diameter, yield and



tensile strength, bending, and welding [3][17][18]. However, the test results regarding the effect of these factors reported quantitatively differ considerably each other. Accordingly, it must be difficult to establish fatigue strength equation which can be applied widely. The Recommendations, therefore, state that principally, the characteristic fatigue strength of reinforcing bars,  $f_{sr}$ , shall be determined on the test results.

Many investigations have shown that  $f_{sr} - N$  curves exhibit transition of a steeper slope to a flatter one in the vicinity of one million cycles. This may imply that reinforcing bars have an endurance limit, however, the evidence is still insufficient because of the lack of data in the region of a sufficient number of cycles. As far as the tests conducted in Japan are concerned, the average slope of  $\log f_{sr} - \log N$  curves of the deformed bars is about  $-0.2$  in the finite life region as seen in Fig.5, and Eq.(2) was derived to cover all the data on the safe side.

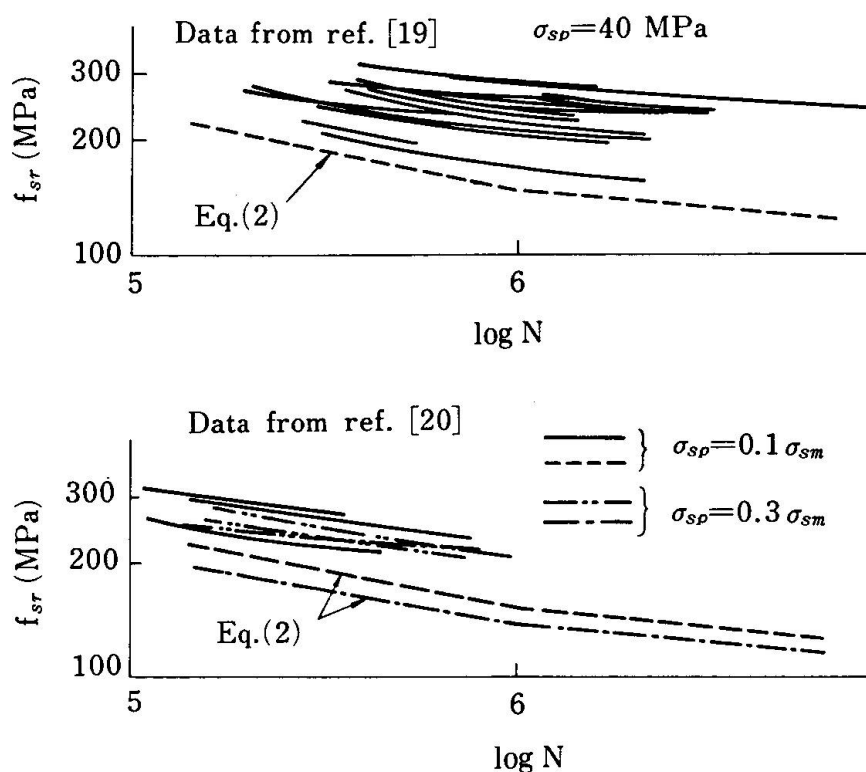


Fig.5 Fatigue strengths of reinforcing bars in tension

It is noted that most of the deformed bars made in Japan today have considerably higher fatigue strength than the value obtained from Eq.(2) owing to the efforts which have been made to improve the geometry of the deformed bars, particularly on the base radii of deformations [19]–[26]. It is, therefore, profitable to determine the characteristic fatigue strength of reinforcing bars by tests in most cases.

It has been found that the fatigue strength of bent bars, such as stirrups and bent-up bars, is considerably lower than that of straight bars [18][27]–[29].

The tests with bars bent around a pin radius conforming to the Japanese Code Requirements have shown that the fatigue strength of bent bars is  $1/2$  to  $2/3$  of that of the straight bars [28][29]. It has also been recognized that welding may considerably reduce the fatigue strength of reinforcing bars [30]–[32]. The tests [32] have shown that the fatigue strength of bars with stirrups attached by welding is about half of those attached by wire ties.

### (3) Fatigue Strength of Reinforced Concrete in Shear

The investigations [33]–[36] have handled the fatigue shear strength of reinforced concrete beams without web reinforcement. Most of the data reported in these references have the fatigue lives longer than those predicted by Eq.(1), which was originally derived for the fatigue strength of concrete in compression. Furthermore, most of the data in the reference [37], in which the fatigue strength of reinforced concrete slabs in punching shear is dealt with, have longer lives predicted by Eq.(1). Therefore, if necessary, Eq.(1) may be used to determine the characteristic fatigue strength in shear of reinforced concrete beams or slabs without shear reinforcement, unless more rational procedures are available.

It is important to establish rational fatigue design procedures for shear reinforcement because the fatigue strength of bent bars is very low. The investigation [38] has proposed that the applied stress range of stirrups may be calculated by truss theory and has compared it with the fatigue strength of bent bars. A more rational method has been proposed by the recent investigations [39][40], in which the behavior of stirrups in strain is examined in detail. Eq.(3) is based on these investigations.

### REFERENCES

- [1] Tentative Recommendations for the Limit States Design of Concrete Structures, Concrete Library No.48, Japan Society of Civil Engineers (JSCE), April 1981
- [2] Graf, O. and Brenner, E., Versuche zur Ermittlung der Widerstandsfähigkeit von Beton gegen oftmals Wiederholte Druckbelastung, Deutscher Ausschuss für Eisenbeton, Heft 76, 1934
- [3] ACI Committee 215, Considerations for Design of Concrete Structures Subjected to Fatigue Loading, Journal of ACI, Mar. 1974
- [4] Matsushita, H. and Tokumitsu, Y., A Study on Compressive Fatigue Strength of Concrete Considered Survival Probability, Proc. of JSCE, No.284, April 1979
- [5] Sakata, K., Kiyama, H., and Nishibayashi, S., A Study on the Fatigue Life of Concrete by the Statistic Treatment, Proc. of JSCE, No.198, Feb. 1972
- [6] Fujita, Y., and Kaiho, Y., Fatigue Behavior on Tension, Compression and Flexure of Plain Concrete, 21st General Meeting of the Cement Association of Japan (CAJ), 1968
- [7] Antrim, J. de C. and McLaughlin, J. F., Fatigue Study of Air-Entrained Concrete, Journal of ACI, May 1959
- [8] Ople, F. S. and Hulsbos, C. L., Probable Fatigue Life of Plain Concrete with Stress Gradient, Journal of ACI, Jan. 1966
- [9] Hamada, S. and Naruoka, M., An Experimental Study on Compressive Fatigue Strength of Lightweight Concrete, Proc. of JSCE, No.176, Apr. 1970
- [10] Tsuzuki, K. and Naruoka, M., Study on Compressive Fatigue Strength of Lightweight Concrete, 25th General Meeting of CAJ, 1971
- [11] Matsushita, H. and Makizumi, M., A Study on Fatigue of Pretensioned Prestressed Concrete Beams, 32nd General Meeting of CAJ, 1978
- [12] Gray, W. H., McLaughlin, J. F. and Antrim, J. D., Fatigue Properties of Lightweight Aggregate Concrete, Journal of ACI, Aug. 1961



- [13] Watanabe, A., Tsuruta, K. and Koga, J., Fatigue Characteristics of High Strength Concrete, 31st General Meeting of CAJ, 1977
- [14] Matsumoto, Y., Saito, T., Miura, I. and Mine, Y., Akkagawa Railway Bridge (Deck-type Prestressed Concrete Truss Bridge), Proc. of JSCE, No.264, Nov. 1977
- [15] Matsushita, H., A Study on Compressive Fatigue Strength of Concrete in the Water, Proc. of JSCE, No.296, Apr. 1980
- [16] Ozaki, S. and Shimura, M., Compressive Fatigue Strength of Concrete in Water, Proc. of 35th Annual Conference of JSCE, Oct. 1980
- [17] Hanson, J.M., Somes, M.F. and Helgason, T., Investigation of Design Factors Affecting Fatigue Strength of Reinforcing Bars, ACI SP-41, 1974
- [18] Soretz, S., Contribution to the Fatigue Strength of Reinforced Concrete, ACI SP-41, 1974
- [19] Kokubu, M., and Okamura, H., Fundamental Study on Fatigue Behavior of Reinforced Concrete Beams Using High Strength Deformed Bars, Proc. of JSCE, No.122, Oct. 1965
- [20] Yokomichi, H., Fujita, Y. and Nishihori, T., Fatigue Test of Reinforced Concrete Beams Using Deformed Bars, Concrete Library No.14, JSCE, Dec. 1965
- [21] Nakayama, N., Fatigue Test on T-shaped Beams Reinforced with Various Deformed Bars, Proc. of JSCE, No.122, Oct. 1965
- [22] Kokubu, M. et al., Fatigue Behavior of Reinforced Concrete Beams with High Strength Deformed bars, Proc. of JSCE, No.122, Oct. 1965
- [23] Kohno, M., Tomita, K., Komatsubara, M., Watanabe, S. and Kodera, J., The Fatigue Strength of the Deformed Bars, Concrete Library No.2, JSCE, Dec. 1962
- [24] Tomita, K. and Watanabe, S., Fatigue Strength of High Strength Deformed Bars, Concrete Library No.14, Dec. 1965
- [25] Kokubu, M. and Okamura, H., Use of Large-Sized Deformed Bars in Reinforced Concrete, Proc. of JSCE, No.202, June 1972
- [26] Yamazaki, T. et al., Studies on Fatigue Characteristics of Large-Diameter Deformed Bar D51 in Axial Load and RC Beam, Proc. of JSCE, No.278, Oct. 1978
- [27] Pfister, J.F. and Hognestad, E., High Strength Bars as Concrete Reinforcement Part 6, Fatigue Tests, Journal of PCA, V.6, No.1, Jan. 1964
- [28] Okamura, H., Sekijima, K. and Enomoto, M., Fatigue Strength of a Bent-up Bar, 29th General Meeting of CAJ, 1975
- [29] Okamura, H., Fatigue Properties of Beams Having 51mm Diameter Bars With Bends, Concrete Library No.40, JSCE, June 1975
- [30] Burton, K.T. and Hognestad, E., Fatigue Tests of Reinforcing Bars - Tack Welding of Stirrups, Journal of ACI, May 1967
- [31] Maruyasu, T., Kobayashi, K., Ito, T. and Kudo, Y., Fatigue Failure of Reinforced Concrete Beams, Concrete Library No.14, Dec. 1965
- [32] Okamura, H., Fatigue Characteristic of Concrete Structures, 22nd Symposium on Structural Engineering, JSCE, Jan. 1976
- [33] Chang, T.S. and Kesler, C.E., Fatigue Behavior of Reinforced Concrete Beams, Journal of ACI, Aug. 1958
- [34] Stelson, T.E. and Cernica, J.N., Fatigue Properties of Concrete Beams, Journal of ACI, Aug. 1958
- [35] Higai, T., Fundamental Study on Shear Failure of Reinforced Concrete Beams, Proc. of JSCE, No.279, Nov. 1978
- [36] Ueda, T., Enomoto, M. and Farghaly, S.A., Fatigue Strength of Reinforced Concrete Beams Without Web Reinforcement, JCI 3rd conference, 1981
- [37] Kakuta, Y. and Fujita, Y., Fatigue Strength of Reinforced Concrete Slabs Failing by Punching Shear, Faculty of Engineering, Hokkaido University, 1980
- [38] Hawkins, N.M., Fatigue Characteristics in Bond and Shear of Reinforced Concrete Beams, ACI SP-41, 1974
- [39] Okamura, H., Farghaly, S.A. and Ueda, T., Behavior of Reinforced Concrete Beams with Stirrups Failing in Shear under Fatigue Loading, Proc. of JSCE, No.308, Apr. 1981
- [40] Ueda, T. and Okamura, H., Behaviors of Stirrups under Fatigue Loading, Concrete Journal, V.19, No.5, Japan Concrete Institute, May 1981