

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 37 (1982)

Artikel: Fatigue treshhold concept applied to metal structures
Autor: Blom, A.F.
DOI: <https://doi.org/10.5169/seals-28912>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 05.12.2025

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Fatigue Threshold Concept Applied to Metal Structures

Concept de la limite de propagation des fissures due à la fatigue appliqué aux structures métalliques

Konzept des Grenzwertes für Ermüdungsrisswachstum angewendet auf Stahlkonstruktionen

A.F. BLOM

Research Engineer
Aeronautical Research Laboratory
Bromma, Sweden

SUMMARY

The concept of the fatigue threshold stress intensity factor as a design criterion is presented. This concept is of particular importance for structures having to sustain very many load cycles. The experimental evaluation and the influence of various parameters of this factor are examined.

RESUME

L'application du concept de la limite inférieure à la propagation des fissures par la différence du facteur d'intensité de contrainte comme critère de dimensionnement est présenté. Ce concept est d'une importance particulière pour les structures subissant de très grands nombres de cycles de charges. L'évaluation expérimentale de ce facteur et l'influence de divers paramètres sur ce facteur sont examinées.

ZUSAMMENFASSUNG

Die Anwendung des unteren Grenzwertes für das stabile Risswachstum der Spannungsintensitätsdifferenz als Dimensionierungsgrundlage wird vorgestellt. Dieses Konzept ist für Bauteile, welche sehr vielen Lastwechsel unterworfen sind, von grosser Bedeutung. Die experimentelle Bestimmung und der Einfluss verschiedener Parameter auf diesen Grenzwert wird untersucht.



1. INTRODUCTION

Traditionally, metal structures that must sustain a very large number of load cycles N have been designed from ordinary SN-curves (Wöhler-diagrams) where it for most metals appear to exist a fatigue limit $\Delta\sigma_e$, see Fig. 1. To avoid fatigue failures of such structures they have been designed so that the applied stress range S always should be below the fatigue limit.

The experimental procedure for determining the fatigue limit of a material is very tedious and will be quite expensive if it is properly accounted for all those variables that influence the value of the fatigue limit.

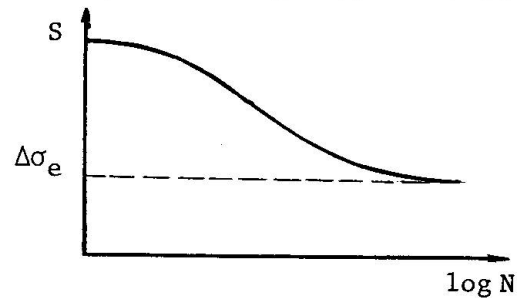


Fig. 1 SN-diagram

This paper presents an alternative approach to the "fatigue limit" problem. This approach which is based on fracture mechanics was originally developed in the aircraft industry, but has recently come to an extensive utilization in the design also of structures such as wind turbine blades, diesel engines, steam turbines and electric generators [1].

The design concept to be discussed here is the fatigue threshold concept which simply states that for a given load there exist cracks of a certain length that will not propagate. Inversely, we can for a given crack length calculate which load magnitude that will not cause crack growth [2].

2. FRACTURE MECHANICS AND FATIGUE

Various empirical crack-growth laws have been proposed over the past decades. Most of the early expressions were of the form given in Eq. (1). However, no real success with the difficult task of correlating the crack-growth rate da/dN to applied stress, crack length etc. was obtained before 1961 when Paris [3] proposed that the stress intensity range $\Delta K = K_{\max} - K_{\min}$ should be incorporated in a crack propagation law as shown in Eq. (2).

$$\frac{da}{dN} = C \sigma^m a^n \quad (1)$$

$$\frac{da}{dN} = C (\Delta K)^m \quad (2)$$

Paris came to this conclusion based on the results from experiments with aluminium. He also gave the value 4 of the exponent m for his test results. Further experiments have shown that for most metals the value of m varies between 2.3 and 6.7 [4]. The very large number of experiments that have been performed since Paris proposed his power relationship clearly indicate that Eq. (2) is not entirely valid over the whole range of ΔK . This means that a log-log plot of da/dN against ΔK is not linear but sigmoidal, see Fig. 2. In this figure we can distinguish between three distinct regions. At low ΔK the fatigue crack growth rate decreases progressively faster until the threshold, ΔK_{th} , for a non-propagating crack is reached. This region is our major concern and will be further dealt with in the following chapters.

Next region is composed of a straight line and constitutes the part of the curve where Eq. (2) can be utilized. A third region exists at high ΔK where the slope of the curve increases rapidly as the maximum stress intensity approaches the fracture toughness K_c .

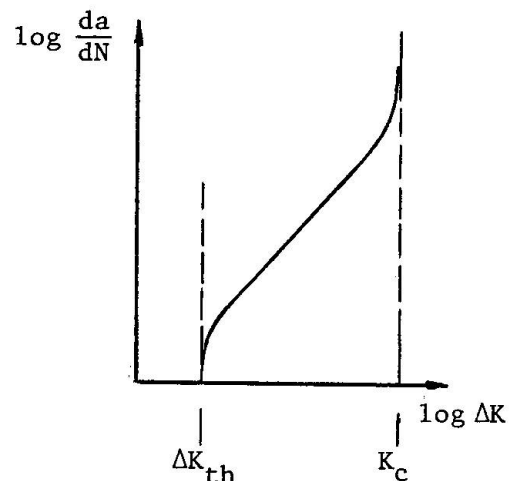


Fig. 2 Schematic shape of fatigue crack growth versus stress intensity variations.

3. THE THRESHOLD STRESS INTENSITY FACTOR ΔK_{th}

3.1 Utilization of ΔK_{th}

In the preceding chapter it was shown that the fatigue crack growth rate is a function of ΔK , the variation in stress intensity. Below a certain threshold value ΔK_{th} the fatigue crack growth rate equalizes zero as indicated in Fig. 2.

The existence of a threshold value means that specimens subjected to certain loads will not fail in fatigue if all existing flaws are smaller than a critical crack length. The reversed situation may also be of interest, when the designer knows the sizes of the cracks from measurements he will be able to calculate which stresses are allowed if fatigue should be avoided.

The utilization of threshold values is particularly important for components which are subjected to very large numbers of cycles during service, e.g. engine parts such as crankshafts.

The threshold stress intensity factor is, however, not a genuine material constant but is dependent on some parameters such as R-value, temperature and environment. The influence of these parameters and some others will be scrutinized in the next chapter. This dependence on other parameters must be born in mind when the experimental evaluation of ΔK_{th} is performed so that the right service conditions are imposed. Caution also to an uncritical adoption of results presented in the literature: how were these values measured, under which conditions and is the metallurgical composition exactly the same for the tested material as for the actual one?

Another application of the threshold value concept is when a comparable judgement about the fatigue qualities of several materials should be performed. This can be the case when, for instance, an old material should be replaced by a new one.

3.2 Some numerical values of ΔK_{th}

Some values of ΔK_{th} are given in Table 1 merely to give an indication of their magnitude and to compare various materials. Note that the threshold stress intensity factor also is meaningful for polymers. All results in Table 1 were given in [5].

3.3 Definition of the threshold value

Before going into more detailed discussions in the following chapters, let us ponder about the definition of the threshold value ΔK_{th} . From Fig. 2 it follows that the existence of ΔK_{th} requires the crack growth rate to equalize zero. This would be the case when for an infinite number of cycles no crack growth occurs. However, to perform experiments with an infinite number of cycles would be not only tedious and discouraging but also quite impractical. Therefore it is fortunate that the threshold value is associated with a fatigue crack growth rate of around one lattice spacing per cycle. This value which corresponds to about 4×10^{-7} mm per cycle is the minimum crack growth rate possible on physical grounds, [6]. However, in a corrosive environment

Material	Conditions	R	ΔK_{th} [MPa \sqrt{m}]
mild steel SIS 1450-01	air	0.1	12.0
		0.5	7.1
		0.9	4.4
mild steel SIS 1450-01	salt water	0.1	7.0
		0.5	3.6
		0.9	2.5
A 533 B	base material	0.25	7.1
		0.5	5.5
	HAZ	0.25	6.8
A1 5083	HAZ	0.5	5.2
		0.1	2.0
Inconel		0.1	6.5
PVC		0.1	0.68
		0.5	0.32
		0.75	0.29

Table 1 Some threshold values ΔK_{th} for various materials [5]



lower average rates could be observed, due to that the crack growth in those cases only takes place on part of the crack front during each cycle, [6].

For practical purposes it seems appropriate to utilize a crack growth rate of the magnitude 10^{-7} – 10^{-6} mm per cycle as a definition of a valid threshold value. Recently though many workers including the present author perform tests down to a maximum crack growth of 10^{-8} mm to ensure that no further crack growth occurs.

4. PARAMETERS INFLUENCING ΔK_{th}

As was previously stated the threshold value ΔK_{th} is not a genuine independent material constant but is influenced by various parameters. The forthcoming chapter will deal with some of the more prominent ones.

4.1 Crack size

Most experiments that have been performed to evaluate thresholds ΔK_{th} or fatigue crack growth data are based upon linear elastic fracture mechanics. However, in the vicinity of a very small crack the plastic zone size is not neglectable compared to the crack length and we may thus expect some peculiarities to occur if we still use the concept of stress intensity factors. Short cracks generally exhibit higher fatigue crack growth rates and lower threshold stress intensities than do longer cracks [2, 7]. There is much confusion on which crack size that should be considered short. It appears that this is dependent on the actual material as indicated in Fig. 3 [8] where ΔK_{th} is plotted versus the crack length for three different materials at $R=0$. In the pertinent literature crack sizes below 0.5 mm are often referred to as short cracks [2].

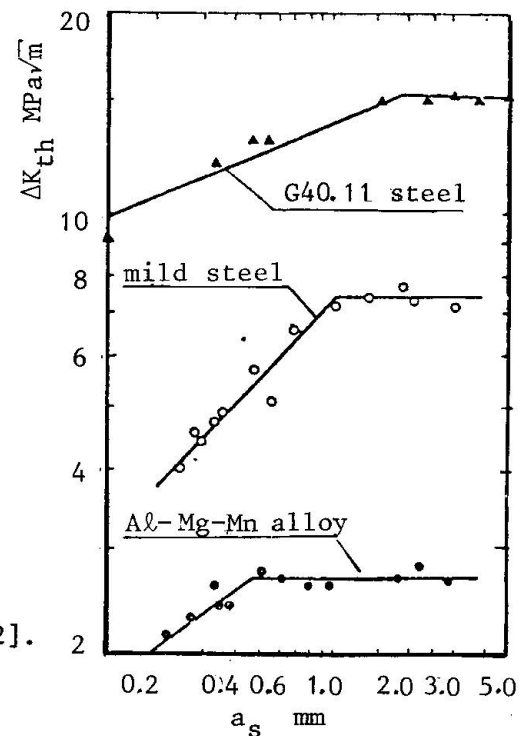


Fig. 3 Dependence of ΔK_{th} on crack length [8]

An approach to account for the behaviour of short cracks was proposed by El Haddad [9] where a constant length ℓ_o , see Eq. (3) is added to the physical crack size. The term ℓ_o which is assumed to be a material constant can be determined from the ordinary threshold stress intensity factor ΔK_{th} and fatigue limit $\Delta \sigma_e$ as

$$\ell_o = \frac{1}{\pi} \left(\frac{\Delta K_{th}}{\Delta \sigma_e} \right)^2 \quad (3)$$

In the following we will restrict ourselves to situations with "normal" crack sizes when discussing how different parameters influence the threshold stress intensity factor.

4.2 Loading modes

Almost all performed experimental evaluations of ΔK_{th} have been restricted to pure mode I loading. Recently, however, interest has been shown in the establishment of threshold stress intensity factors also for other modes, particularly mode II and mixed-modes [10, 11]. It was found that the mode II and the mixed mode I and II thresholds for mild steel can be lower than the pure mode I threshold [10, 11]. Experimental results from [10] are shown in Fig. 4 together with a lower bound derived in [11]. It was proposed in [10] that the reason for the very low values shown in Fig. 4 might partially be due to that crack initiation

rather than crack extension was monitored. In the following only pure mode I thresholds are to be discussed. For more information on other loading modes it is referred to [2, 10 and 11].

4.3 R-dependence

It is nowadays well established that the stress ratio $R = \sigma_{\min} / \sigma_{\max}$ greatly influences both the fatigue crack growth and the threshold stress intensity factor. The general conclusion from studies on the effect of stress ratio R on the threshold value ΔK_{th} is that an increasing R tends to decrease the threshold value. This behaviour is confirmed for various materials by a great number of authors, e.g. [2, 12].

There is, however, some confusion about the varying influence of R on different materials and also how environmental conditions influence the R -dependence. One might ponder about why the stress ratio influences the rate of fatigue crack growth. At very high propagation rates when K_{IC} , the fracture toughness, is approached, the influence is attributed to different fracture mechanisms such as intergranular cracking, cleavage and void coalescence. In the intermediate region relatively little effect is observed. This results in a schematic curve as in Fig. 5 when the influence of R is considered. The effect of R on region I in Fig. 5 can, however, not be clarified by means of different fracture mechanisms as accounted for above for the case of very high crack propagation rates.

Some different theories have been proposed to account for R effects on the threshold value ΔK_{th} .

A crack closure concept originally proposed by Elber is often utilized. Elber [13] stated that, as a result of permanent tensile plastic deformation left in the wake of a propagating fatigue crack, the cracks are partially closed, even though loading may be tension-tension. Crack extension takes place only during those portions of the cycle where the crack is open. It follows that for a given maximum load, the crack will remain open longer during each cycle for higher values of the mean load, i.e. higher minimum loads and thus higher R -values. This will explain the trend shown in Fig. 5.

Crack closure can, however, not entirely explain the effect of R on the threshold behaviour. It is shown, e.g. in [14], that the threshold value in vacuum is independent of the stress ratio R . This independence of ΔK_{th} on R should according to [15] indicate that there is no crack closure in vacuum. Recent work, however, closely shows that crack closure indeed occurs in vacuum. In [16] it is stated that crack closure is more pronounced in vacuum than in air. Thus, it is obvious that crack closure alone cannot adequately be used to explain the effects of stress ratio R .

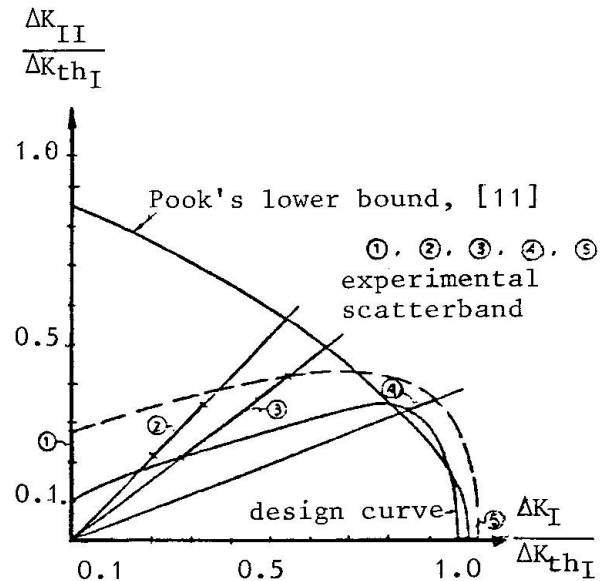


Fig. 4 Mixed mode thresholds for $R = 0.1$ [10]

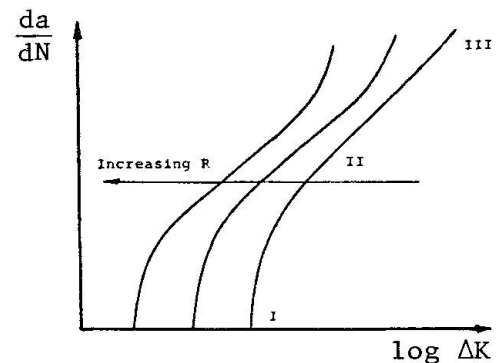


Fig. 5 R-dependence on fatigue crack-growth rate
I Threshold region
II Intermediate region
III Fracture toughness region



Several researchers, e.g. [14, 17 and 18], have proposed that the R-dependence could be explained by environmental effects. In [17] it is stated that environmental effects due to hydrogen embrittlement explains the stress-ratio effect while crack closure is assumed to be of only secondary importance. In [14] a two-component mechanism is introduced. This two-fold mechanism is proposed to take account for environmental actions such as intergranular corrosion. One of the two components involves the creation of damage ahead of the crack tip in the form of intergranular facets and the other component can be viewed as a linking of these facets to the main crack by a tensile tearing process. Ritchie, [18], agrees with Beevers et al, [14] about the R-dependence being due primarily to environmental effects. However, he claims that the above mentioned mechanism does not correctly describe the affection by environment.

The most recent opinions [1] seem to be that both crack closure and environmental effects should be accounted for, e.g. [19, 20], when the R-dependence on ΔK_{th} is discussed.

4.4 Thickness

The threshold stress intensity factor ΔK_{th} is generally not supposed to be affected by the thickness of the test specimen. Radon [21] has, however, recently found an influence of thickness at low stress ratios. It was found that ΔK_{th} decreased with thickness for a low alloy steel. It remains to be seen whether this will be shown also for other materials.

4.5 Frequency

At threshold conditions it seems that the influence of frequency is almost negligible [2]. Slight variations in the threshold value due to influence of the frequency can, however, be found in the literature. In [15] a lowering of the threshold value with increasing frequency from 342 to 1000 Hz was found. It was suggested that this behaviour might be due to a localized heating of the crack tip. In [22] the opposite behaviour was observed, i.e. an increased threshold value with increasing frequency from 30 to 1000 Hz. It therefore seems that no general statement can be done about the influence on ΔK_{th} of the frequency. When exposure to various detrimental environments occurs the situation is entirely different. Increasing frequencies then generally yield higher threshold values due to less time for environmental interaction. This is especially noticeable at very low frequencies.

4.6 Temperature and environment

Results on the effect of temperature and environment on ΔK_{th} are unfortunately somewhat contradictory why it is difficult to draw any general conclusions. Recent work by Ritchie [20] and Stewart [23] indicate that a concept of oxide-induced crack closure satisfactorily explains the influence of environment on ΔK_{th} . It is found that ΔK_{th} often is lower in dry environment, hydrogen or air, than in moist air and water at low stress ratios. This is explained [20, 23] with corrosion/fretting debris building up at the crack tip and thus reducing the effective cyclic stress intensity range.

The effect of temperature on ΔK_{th} is quite unclear and apparently varies for different materials. As example it was found in [24] that the threshold value for a mild steel plate was lower and higher, respectively, at 200°C and 360°C than at 20°C. For weld metal [24] ΔK_{th} was similarly shown to be lower between 20°C and 200°C, but higher at 360°C, than at 20°C.

It is concluded that all experimental evaluations of ΔK_{th} should necessarily be performed in an environment and at temperatures closely simulating the operational conditions.

4.7 Microstructure

Mostly it appears that the threshold value increases with increasing grain size [19, 25-27]. This has been found for many metals such as aluminium, various steels and titanium. Some materials though, for instance copper [28], do not show any variation in ΔK_{th} with grain size changes. Metallographic observations in [25] showed that at threshold the crack often arrests at grain boundaries and inclusions which may clarify the relatively large scatter in test results for materials with coarse grain sizes and inclusions. The structure sensitivity of ΔK_{th} is primarily considered to be associated with the closure process [19, 26]. The closure level is highest in the threshold region due to changes in the transgranular crack mode from the opening mode at higher ΔK -values to a combination of shear mode and opening mode.

It has been found that the threshold stress intensity factor is a function of yield strength and Young's modulus [19, 26]. A nearly linear plot of ΔK_{th} versus the square root of $E\sigma_y$ for several metals is considered [19] to be indicative of ΔK_{th} being related to a critical crack tip opening displacement.

4.8 Amplitude

All discussions so far have been presented assuming a constant load amplitude. It is, however, well known that both single overloads and random loading greatly affect the threshold value. When a specimen is subjected to overloads a plastic zone forms at the crack tip. This plastic zone can be of sufficient magnitude to prevent further crack growth which results in that a too high threshold value is registered.

To account for the load history, Klesnil and Lukáš [29] proposed the following relationship

$$\Delta K_{th} = \Delta K_{th,0} \left(\frac{\Delta K_{Ip}}{\Delta K_{th,0}} \right)^\alpha \quad (4)$$

where $\Delta K_{th,0}$ is the threshold value without prior loading, ΔK_{Ip} is the just preceding stress intensity factor and α is an exponent strongly dependent on the tensile strength of the steel.

In [30] the fatigue strength of cracked mild steel plate specimens was studied. It was found that a narrow-band random loading produced significantly greater fatigue strength than did estimates based on linear summation of constant amplitude fatigue crack growth data. More accurate results were obtained when the effect of prior loading on the threshold value, utilizing Eq. (4), was accounted for.

Experiments performed on a commercial nickel-base and titanium-base alloy, [22], disclosed various interesting effects of single and multiple cycle overloads on the threshold value. It was found that the overload modified threshold value, ΔK_{th}^* , increased exponentially with the magnitude of the prior overload. Further, it was shown that the effect of relative overload on relative threshold value is independent of the stress ratio R , but that overloads produce much larger absolute magnitude increases in the threshold value at low R than at high R . Also, it was shown that the number of overloads, overload rate, cycle shape, temperature and frequency can affect the threshold value but that these variables are much less important than the magnitude of the overload.

5. EXPERIMENTAL METHODS

It is obvious from the preceding chapter that all experimental evaluations of ΔK_{th} should account for such parameters as temperature, environment, stress ratio etc. simulating the operational conditions as closely as possible. Also, in order to avoid load history interactions, the load must be decreased very carefully.



Concerning test equipment and test specimens most workers use servo-hydraulic testing machines and standardized fracture mechanics specimens such as the Center-Cracked-Tension and the Compact Tension specimen. It has recently been proposed that a modified wider Compact Tension specimen would be more suitable [5].

The conventional test method is the load shedding technique where the load is manually decreased at selected crack length intervals. This method is thoroughly investigated by Bucci and his co-workers, [31, 32], who have developed a tentative ASTM standard based on their results. Stringent requirements are proposed for the load shedding procedure to avoid load history effects. It is stated that the reduction in P_{\max} for adjacent load steps must be lower than 10 per cent of the previous P_{\max} and further must the crack extension within each adjustment of the maximum load be at least 0.5 mm. This method has, however, some drawbacks, such as being rather time consuming with respect both to test equipment and personnel. This is due to that the crack length has to be monitored during the test and that the load must be reduced very slowly in order to eliminate any load history effects from prior overloads. Further there will be cusps on the ΔK versus time curve which are not very appealing from a physical point of view.

These disadvantages are substantially reduced when the load shedding is performed in a continuous manner utilizing a computer controlled test system [33, 34]. In Ref. [33] a stress intensity gradient technique is used and in Ref. [34] a technique is described which utilizes crack opening displacement as controlling parameter. The main objection against these methods is the relatively high cost of computerized test systems and even if such systems are available they ought to be saved for more sophisticated tests such as spectrum or random fatigue testing.

A simple method to measure ΔK_{th} was proposed by Jerram and Priddle, [35]. Their method which operates automatically seems to be rather cost effective as computer control is avoided. One serious disadvantage is, however, the inability of the method to keep the load ratio, R , constant throughout the test. As it is well established that R significantly influences the threshold stress intensity ΔK_{th} , the usefulness of the method seems rather limited.

If it would be possible to combine the advantage with a control unit as in [35], with the possibility of keeping R constant throughout the test, as in [33, 34], then a quite efficient method would be available. How this is accomplished is described in [5].

6. APPLICATIONS

It is evident from many recent papers that the threshold stress intensity factor ΔK_{th} is a parameter of great technical importance. Applications where ΔK_{th} has been used include different structural components such as: boiler feed pump shafts [36], low pressure turbine rotor shafts [36], turbo generator rotor [36], nuclear reactor gas circuitry [37], pipes [38], cylinder cover of diesel engines [39], engine shafts [39], connecting rods [39] and turbine blades [40].

7 CONCLUSIONS

The fatigue threshold concept as a design criterion has been discussed. This concept which simply states that the applied stress intensity range ΔK should be below the threshold stress intensity factor ΔK_{th} is of particular importance for structures sustaining very many load cycles, i.e. where no crack growth can be allowed.

It has been discussed how the threshold stress intensity factor is experimentally evaluated. The influence of various parameters was scrutinized and it is concluded that all experiments should necessarily simulate the operational conditions as closely as possible.



8. REFERENCES

- 1 BÄCKLUND, J., BLOM, A.F. and BEEVERS, C.J.: Fatigue Thresholds, Proceedings from the first International Conference on Fatigue Thresholds, Stockholm. Sweden, 1-3 June 1981, Vol. 1 and 2, Engineering Materials Advisory Services Ltd., United Kingdom 1981/82.
- 2 BLOM, A.F.: The Threshold Stress Intensity Factor in Fatigue, Report No. LiTH-IKP-S-136, Linköping University, Institute of Technology, Dept. of Mech. Eng., 1980, Also ICAF Doc. 1180, International Committee on Aeronautical Fatigue.
- 3 PARIS, P.C., GOMEZ, M.P. and ANDERSON, W.E.: A Rational Analytic Theory of Fatigue, The Trend in Engineering, Vol. 13, 1961, pp. 9-14.
- 4 NELSON, D.V.: Review of Fatigue-Crack-Growth Prediction Methods, Experimental Mechanics, Vol. 17, 1977, pp. 41-49.
- 5 BLOM, A.F., BÄCKLUND, J. and JILKEN, L.: Specimens and Test Equipment for Economical Fatigue Threshold Testing, in Ref. [1].
- 6 POOK, L.P.: Analysis and Application of Fatigue Crack Growth Data, Journal of Strain Analysis, Vol. 10, No. 4, 1975, pp. 242-250.
- 7 SCHIJVE, J.: Differences Between the Growth of Small and Large Fatigue Cracks. The Relation to Threshold K-values, in Ref. [1].
- 8 ROMANIV, O.N., SIMINKOVICH, V.N. and TKACH, A.N.: Near-Threshold Short Fatigue Crack Growth, in Ref. [1].
- 9 EL HADDAD, M.H., TOPPER, T.H. and SMITH, K.N.: Prediction of Non-Propagating Cracks, Engineering Fracture Mechanics, Vol. 11, 1979, pp. 573-584.
- 10 BLOM, A.F., BÄCKLUND, J. and JILKEN, L.: An Engineering Approach to Mixed Mode Thresholds, in Ref. [1].
- 11 POOK, L.P.: Mixed Mode Threshold Behaviour of Mild Steel, in Ref. [1].
- 12 PARIS, P.C. and HERMAN, L.: Twenty Years of Reflection on Questions Involving Fatigue Crack Growth, Part II - Some Observations of Crack Closure, in Ref. [1].
- 13 ELBER, W.: The Significance of Crack Closure, ASTM STP 486, Damage Tolerance in Aircraft Structures, American Society for Testing and Materials, 1971, pp. 230-242.
- 14 COOKE, R.J., IRVING, P.E., BOOTH, G.S. and BEEVERS, C.J.: The Slow Fatigue Crack Growth and Threshold Behaviour of a Medium-Carbon Alloy Steel in Air and Vacuum, Engineering Fracture Mechanics, Vol. 7, 1975, pp. 69-77.
- 15 SCHMIDT, R.A. and PARIS, P.C.: Threshold for Fatigue Crack Propagation and the Effects of Load Ratio and Frequency, ASTM STP 536, Progress in Flaw Growth and Fracture, American Society for Testing and Materials, pp. 79-93.
- 16 LAFAIRE-FRENOT, M.C., PETIT, J. and GASC, C.: A Contribution to the Study of Fatigue Crack Closure in Vacuum, Fatigue of Engineering Materials and Structures, Vol. 1, 1979, pp. 431-438.
- 17 MUSUVA, J.K. and RADON, J.C.: The Effect of Stress Ratio and Frequency on Fatigue Crack Growth, Fatigue of Engineering Materials and Structures, Vol. 1, 1979, pp. 457-470.
- 18 RITCHIE, R.O.: Contribution on "Slow Fatigue Crack Growth and Threshold Behaviour of a Medium Carbon Steel in Air and Vacuum" by R.J. Cooke, P.E. Irving, G.S. Booth and C.J. Beevers, Engineering Fracture Mechanics, Vol. 7, 1975, pp. 187-189.
- 19 BEEVERS, C.J.: Some Aspects of the Influence of Microstructure and Environment on ΔK Thresholds, in Ref. [1].
- 20 RITCHIE, R.O.: Environmental Effects on Near-Threshold Fatigue Crack Propagation in Steels: A Re-Assessment, in Ref. [1].
- 21 RADON, J.C.: Fatigue Crack Growth in the Threshold Region, in Ref. [1].
- 22 HOPKINS, S.W., RAU, C.A., LEVERANT, G.R. and YUEN, A.: Effect of Various Programmed Overloads on the Threshold for High-Frequency Fatigue Crack Growth, ASTM STP 595, Fatigue Crack Growth Under Spectrum Loads, American Society for Testing and Materials, 1976.



- 23 FREEMAN, B.L., SMITH, P. and STEWART, A.T.: The Influence of Corrosion Debris on Crack Closure at Near-Threshold Fatigue Crack Growth Rates, in Ref. [1].
- 24 PRIDDLE, E.K.: The Threshold Stress Intensity Factor for Fatigue Crack Growth in Mild Steel Plate and Weld Metal: Some Effects of Temperature and Environment, in Ref. [1].
- 25 PRIDDLE, E.K.: The Influence of Grain Size on Threshold Stress Intensity for Fatigue Crack Growth in AISI 316 Stainless Steel, Scripta Metallurgica, Vol. 12, No. 1, 1978, pp. 49-56.
- 26 MINAKAWA, K. and McEVILY, A.J.: On Near-Threshold Fatigue Crack Growth in Steels and Aluminum Alloys, in Ref. [1].
- 27 GERBERICH, W.W. and MOODY, N.R.: A Review of Fatigue Fracture Topology Effects on Threshold and Growth Mechanisms, ASTM STP 675, Fatigue Mechanisms, Ed. J.T. Fong, American Society for Testing and Materials, 1979, pp. 292-341.
- 28 MULLNER, H., WEISS, B. and STICKLER, R.: The Effect of Microstructure on the Fatigue Threshold in Copper, in Ref. [1].
- 29 KLESNIL, M. and LUKÁŠ, P.: Influence of Strength and Stress History on Growth and Stabilisation of Fatigue Cracks, Engineering Fracture Mechanics, Vol. 4, 1972, pp. 77-92.
- 30 POOK, L.P. and GREENAN, A.F.: The Effect of Narrow-Band Random Loading on the High Cycle Fatigue Strength of Edge-Cracked Mild Steel Plates, International Journal of Fatigue, January 1979, pp. 17-22.
- 31 HUDAK, Jr. S.J., SAXENA, A., BUCCI, R.J. and MALCOLM, R.C.: Development of Standardized Methods of Testing and Analyzing Fatigue Crack Growth Rate Data, AFML TR-78-40, Air Force Materials Laboratory, 1978.
- 32 BUCCI, R.J.: Development of a Proposed Standard Practice for Near-Threshold Fatigue Crack Growth Rate Measurement, ALCOA Report No. 57-79-14, Aluminum Company of America, 1979.
- 33 SAXENA, A., HUDAK, Jr. S.J., DONALD, J.K. and SCHMIDT, D.W.: Computer-Controlled Decreasing Stress Intensity Technique for Low Rate Fatigue Crack Growth Testing, Journal of Testing and Evaluation, Vol. 6, No. 3, 1978, pp. 167-174.
- 34 KAISAND, L.R. and LeFORT, P.: Digital Computer Controlled Threshold Stress Intensity Factor Fatigue Testing, in ASTM STP 613, Use of computers in the fatigue laboratory, Eds. H. Mindlin and R.W. Landgraf, American Society for Testing and Materials, 1976, pp. 142-159.
- 35 JERRAM, K. and PRIDDLE, E.K.: System for Determining the Critical Range of Stress-Intensity Factor Necessary for Fatigue-Crack Propagation, Journal Mechanical Engineering Science, Vol. 15, No. 4, 1973, pp. 271-273.
- 36 LINDLEY, T.C. and STEWART, A.T.: Fatigue Crack Growth Threshold Applications, in Ref. [1].
- 37 PRIDDLE, E.K.: High Cycle Fatigue Crack Propagation Under Random and Constant Amplitude Loading, International Journal of Pressure Vessels and Piping 4, 1976, pp. 89-117.
- 38 MUKHERJEE, B. and VANDERGLAS, M.L.: Fatigue Threshold Stress Intensity and Life Estimation of ASTM-A106B Piping Steel, Journal of Pressure Vessel Technology, Vol. 102, 1980, pp. 294-302.
- 39 STENVALL, P.: The Adopting of the Threshold Philosophy - A Modern and useful Tool for Designing and Controlling, in Ref. [1].
- 40 WANHILL, R.J.H.: Some Case Studies and the Significance of Fatigue Thresholds, in Ref. [1].