

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 49 (1986)

**Artikel:** Behaviour of thin-walled corrugated sheets and restrained beams  
**Autor:** Melcher, Jindich  
**DOI:** <https://doi.org/10.5169/seals-38300>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 06.01.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## Behaviour of Thin-Walled Corrugated Sheets and Restrained Beams

Comportement des tôles ondulées à paroi mince et des poutres

Verhalten von wellenförmigen Dünnwandblechen  
und ausgesteiften Trägern

### Jindřich MELCHER

Prof. Dr. Ing.  
Technical University  
Brno, Czechoslovakia



Jindřich Melcher, born 1939, received his civil engineering degree at the Technical University of Brno, Czechoslovakia. He is involved mainly in the stability of steel structures and limit states design problems. He is Professor in the Department of Steel Structures and Bridges and Dean of the Civil Engineering Faculty.

### SUMMARY

The paper provides information on the experimental research programme directed to the problem of local buckling of metal thin-walled corrugated wave-formed sheets under bending moment and to the problem of local and general buckling of beams restrained by sheeting and sag rods. The procedure referred to as the vacuum test (Cornell) method was utilized for the experiments.

### RÉSUMÉ

Cet article concerne un programme de recherche expérimentale orienté vers les problèmes de voilement local de tôles profilées en acier à paroi mince sous l'effet d'un moment de flexion; et de voilement local et global de poutres stabilisées par la tôle et des tirants. La procédure expérimentale utilisée est la méthode d'essais sous vide développée à l'Université Cornell.

### ZUSAMMENFASSUNG

Der Beitrag berichtet über ein Versuchsprogramm, das auf das Problem der lokalen Stabilität von wellenförmigen Metallblechen unter Biegemomenten und auf das Problem der lokalen Stabilität und der Gesamtstabilität von Trägern abzielt, die durch profilierte Bleche und Zugstangen gehalten sind. Für die Versuche wurde die von Cornell entwickelte Vakuumprüfungsmethode angewandt.



## 1. LOCAL BUCKLING OF CORRUGATED SHEETS UNDER BENDING

In the problem of local buckling of thin-walled metal sheets subjected to bending moment much attention has been given to the trapezoidal (ribbed) profiles. One of our research projects was concerned with corrugated (wave-formed) panels because of a little amount of the information about both the theoretical and experimental results in this field.

### 1.1 An Experimental Investigation

The experimental research programme was conducted on single-span and two-span steel panels with the nominal cross section geometry and actual characteristics for one wave (i.e. for the width of 95 mm) shown in Fig. 1.

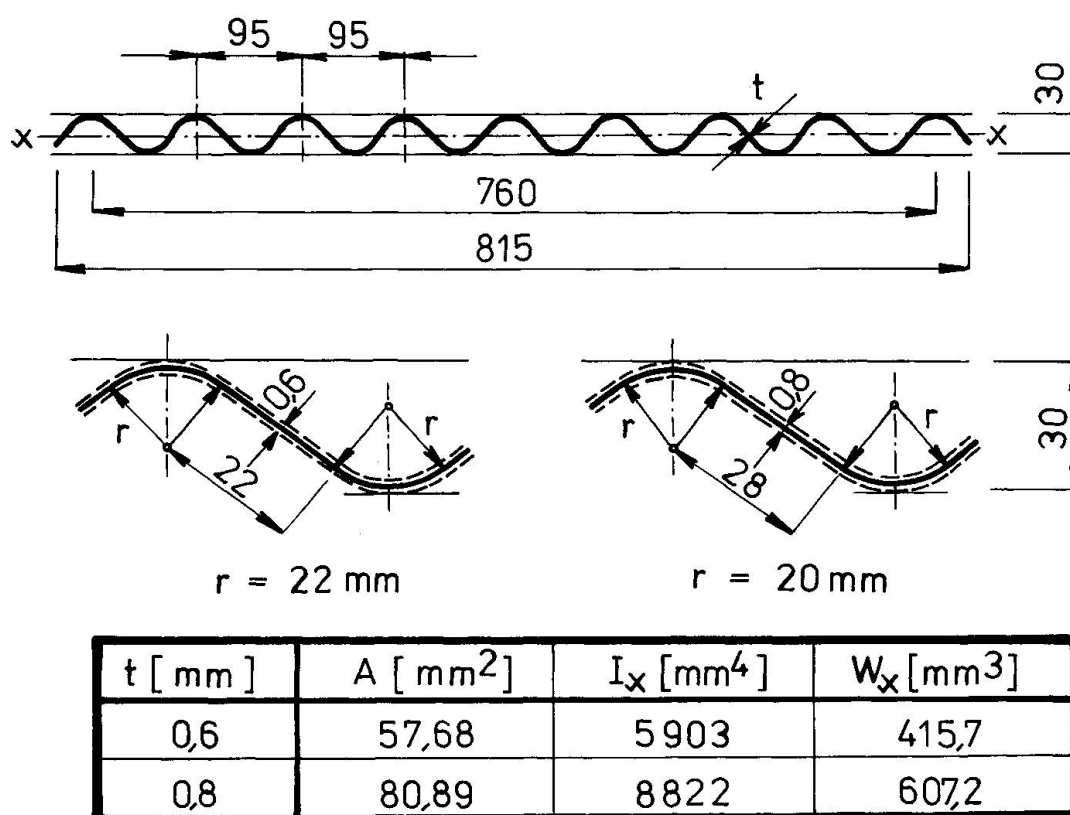


Fig. 1 Cross section and characteristics of the specimens


The steel panels are zinc coated. The actual thickness of the steel sheet was  $t = 0,52$  mm (nominal  $t = 0,6$  mm) and  $t = 0,72$  mm (nominal  $t = 0,8$  mm) respectively.

Totally 12 specimens were tested, namely 6 simple supported panels with a span of  $L_1 = 1440$  mm and 6 continuous panels of two equal spans of  $L_2 = 1480$  mm. The overall width of wave sheets was 815 mm. The breadth of the transverse support elements was  $b = 40$  mm.

The actual material characteristics were measured in 6 tensile test specimens for sheets of nominal thickness  $t = 0,6$  mm and in 3 specimens for  $t = 0,8$  mm. The mean values of the yield stress and the ultimate tensile strength were  $R_y = 237$  MPa (minimal  $R_y = 225$  MPa; maximal  $R_y =$

$= 259$  MPa) and  $R_u = 284$  MPa (minimal  $R_u = 272$  MPa; maximal  $R_u =$   
 $= 304$  MPa) for the nominal sheet thickness of  $t = 0,6$  mm and  $R_y =$   
 $264$  MPa (minimal  $R_y = 248$  MPa; maximal  $R_y = 281$  MPa) and  $R_u =$   
 $314$  MPa (minimal  $R_u = 298$  MPa; maximal  $R_u = 327$  MPa) for the nominal sheet thickness of  $t = 0,8$  mm, respectively.

To simulate the behaviour of thin-walled corrugated sheets under uniformly distributed load, an experimental procedure referred to as the vacuum test method was utilized (author learned the application of this method in the field of steel stability research problems during the study stay by

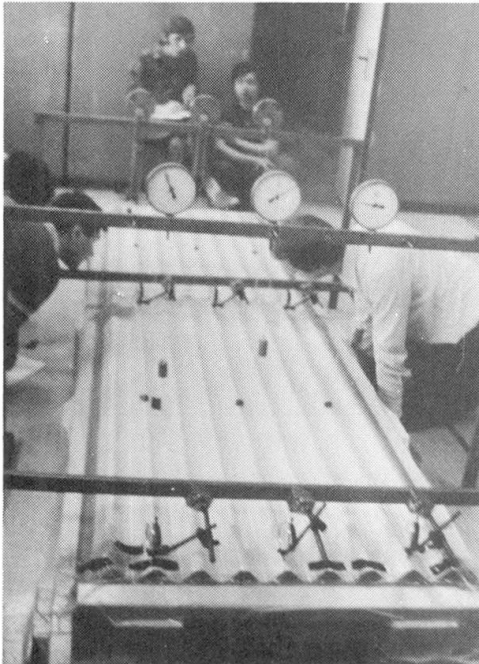

**Fig. 2** Test Arrangement

SPECIMEN	t [ mm ]	TEST ARRANGEMENT	LOAD BY BUCKLING $p_{max}$ [ $kN \cdot m^{-2}$ ]	
			AT CENTRAL SUPPORT	IN THE SPAN
D 1	0,6	TWO - SPAN PANEL 2 x 1480 mm (width 815 mm)	4,0	7,0
D 3	0,6		4,0	7,0
D 4	0,6		4,0	7,0
D 2	0,8		7,0	11,3
D 5	0,8		7,0	11,5
D 6	0,8		7,2	11,0

**Table 1** Two-span Test Results



R.N. White and T. Peköz, Cornell Univ., Ithaca, N.Y.). The method involves producing a vacuum under the test specimen covered by clear plastic, and then measuring the difference in pressure

SPECIMEN	$t$ [ mm ]	TEST ARRANGEMENT	$p_{max}$ [ $kN \cdot m^{-2}$ ] LOAD BY BUCKLING IN THE SPAN
X 1 (D 2)	0,8	SINGLE-SPAN PANEL $1 \times 1440$ mm (width 815 mm)	9,5 (10,2)
X 2 (D 5)	0,8		9,4 (9,6)
X 3 (D 6)	0,8		9,5 (9,6)
X 4 (D 1)	0,6		6,0 (6,2)
X 5 (D 3)	0,6		6,0 (5,1)
X 6 (D 4)	0,6		5,8 (5,9)

Table 2 Single-span Test Results

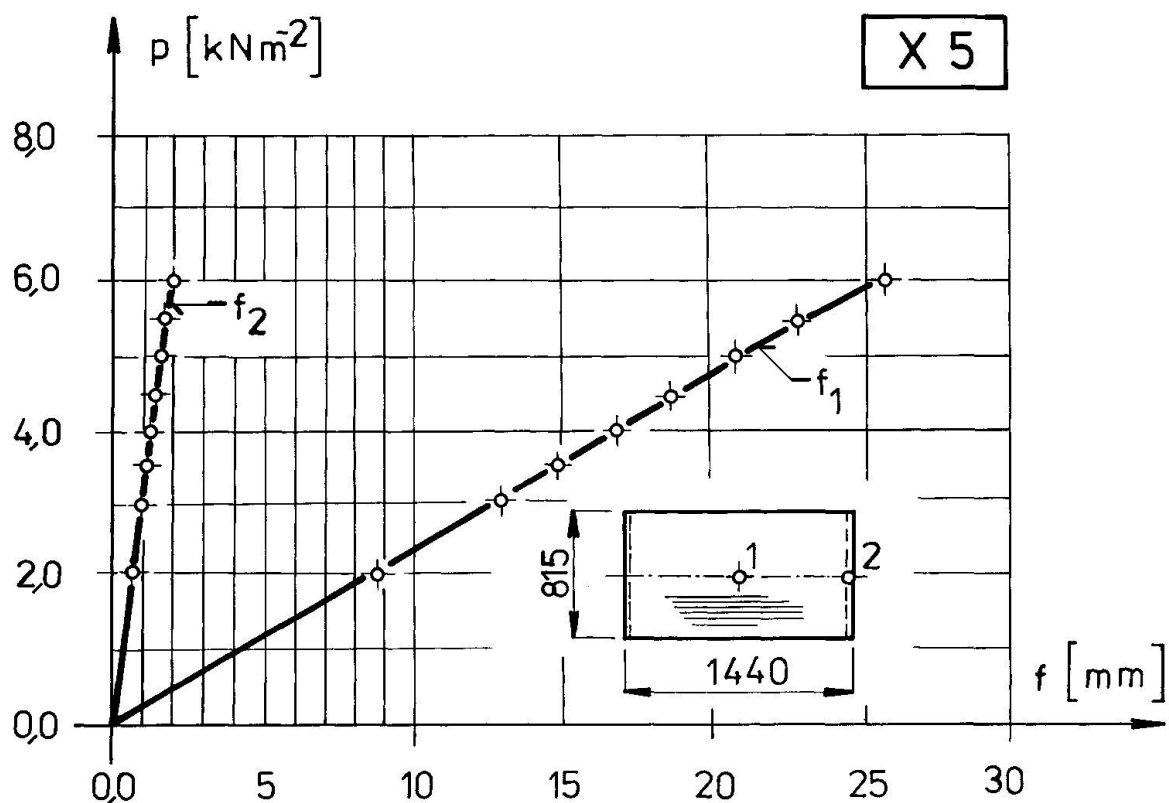


Fig. 3 Load - Deflection Relationship for Single-span Panel between the outside atmospheric pressure and inside the test frame. The test setup and instrumentation are shown in Fig. 2. The support settlements and maximum span deflections were measured using a stroke dial gages.

The description of specimens and the experimental results are summarized in Table 1 and Table 2.

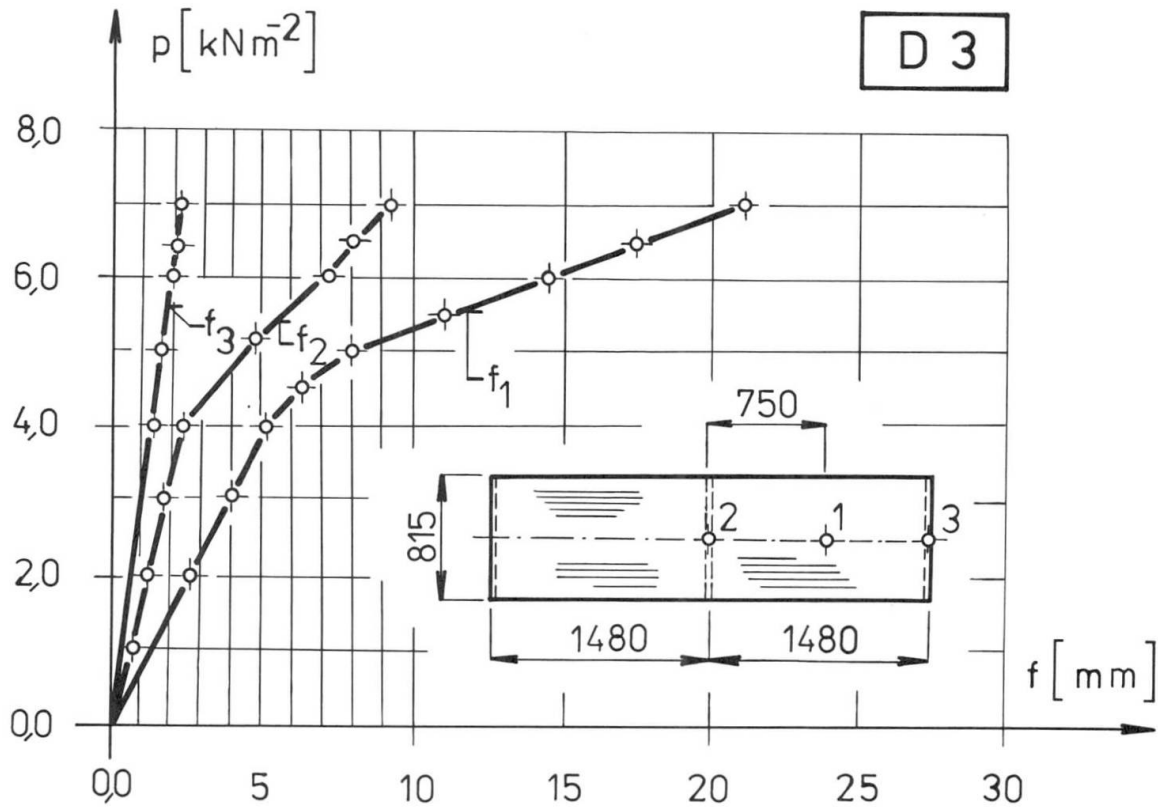


Fig. 4 Load - Deflection Relationship for Two-span Panel

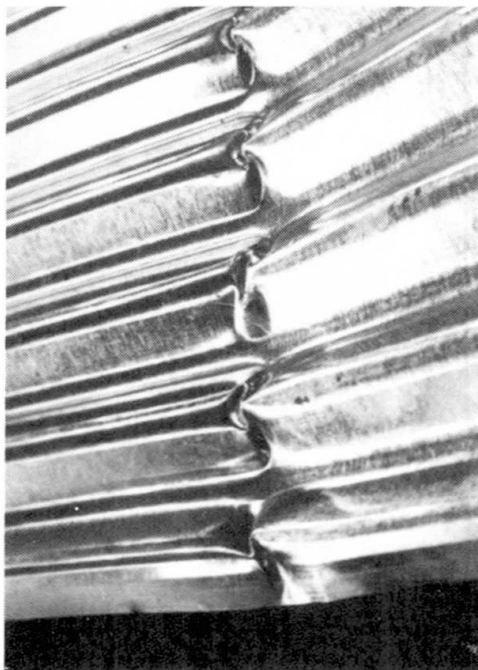


Fig. 5 Span Buckling

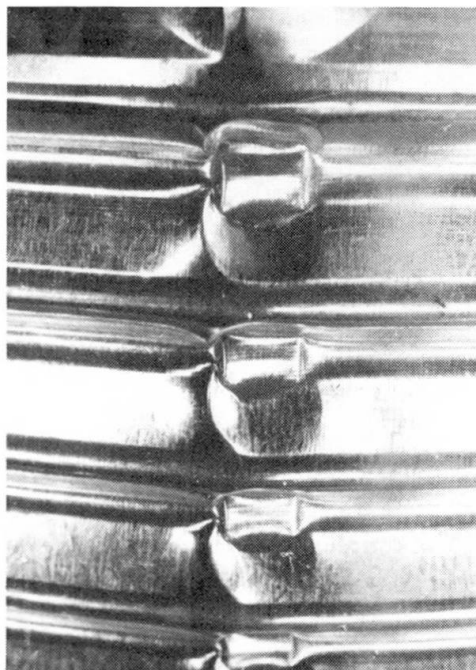


Fig. 6 Support Crippling

The typical example of applied uniform load "p" plotted against the maximum span and support deflections "f" is for the single-span specimen X5 in Fig. 3 and for the two-span specimen D3 in Fig. 4.



The influence of the plastic hinge arising, combined with web crippling at central support of two-span specimen can be clearly seen from Fig. 4. None of significant effect of the sheet support deformation upon the ultimate load carrying capacity of single span specimens was observed.

The behaviour of the corrugated sheets at ultimate load was characterized by outright and abrupt local buckling of the compression cross-section part in the span (see Fig. 5). After sheet waves deformation and bearing on the central support (see Fig. 6) the process of load increasing had been stabilized again until local buckling occurred in the span.

## 1.2 Analysis of the Test Results

This part of the paper is aimed to the problem of local buckling strength in the span of the wave-formed sheets. The critical moment and corresponding buckling stress follows directly from the ultimate load of single-span specimens. In the case of two-span panels the critical moment in the span is influenced by actual value of negative moment at central support. This moment obviously depends on cross section deformation cau-

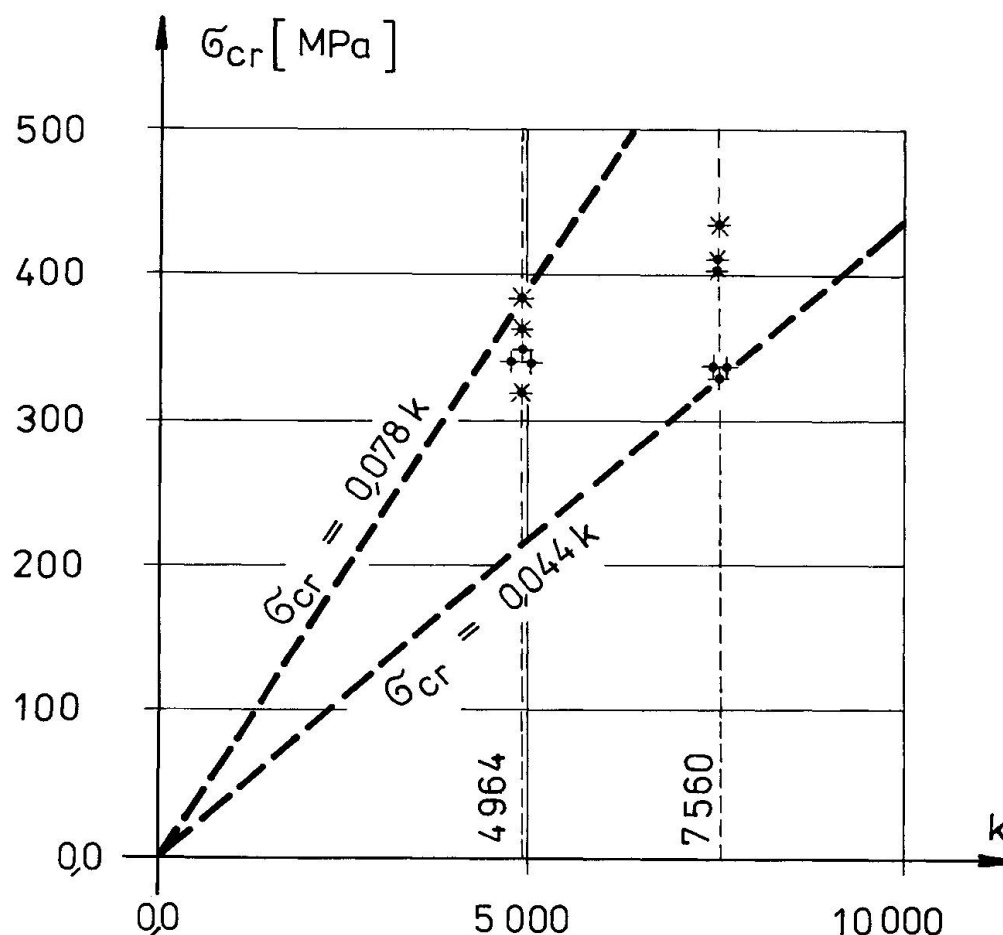


Fig. 7 Test Results Evaluation

sed by web crippling and can be easily determined using the measured values of maximum deflection in the span. Thus the ultimate buckling load for a conventional single span panel can be derived from the tests of two-span specimens. The corresponding specimen descriptions and conventional buckling loads are summa-



rized in parentheses, Table 2.

Based upon the theory of local buckling of unstiffened cylindrical shells [ 1 ] , [ 2 ] , [ 3 ] , the buckling stress of undulated plates is given by the following general equation:

$$\sigma_{cr} = \alpha \frac{E t}{r} = \alpha \cdot k \quad . \quad (1)$$

The buckling coefficient  $\alpha$  for the range of parameters  $k$  considered in this study varies from  $\alpha = 0,044$  to  $\alpha = 0,078$  (see Fig. 7, where the star-symbols indicate the test results for the two-span specimens). The value of measured ultimate buckling load includes the influence of both the imperfections and material non-linearity. The experimental results are in a good agreement with [ 4 ] where  $\alpha = 0,06$  for undulated plates is proposed.

## 2. LOCAL AND GENERAL BUCKLING OF RESTRAINED BEAMS

The contemporary trend in the development of structural design procedures is characterized by a successive transition from the analysis of the "ideal member incorporated into the ideal structure" to the problem of "actual member incorporated into the actual structure". In the theory of beams braced by discrete and

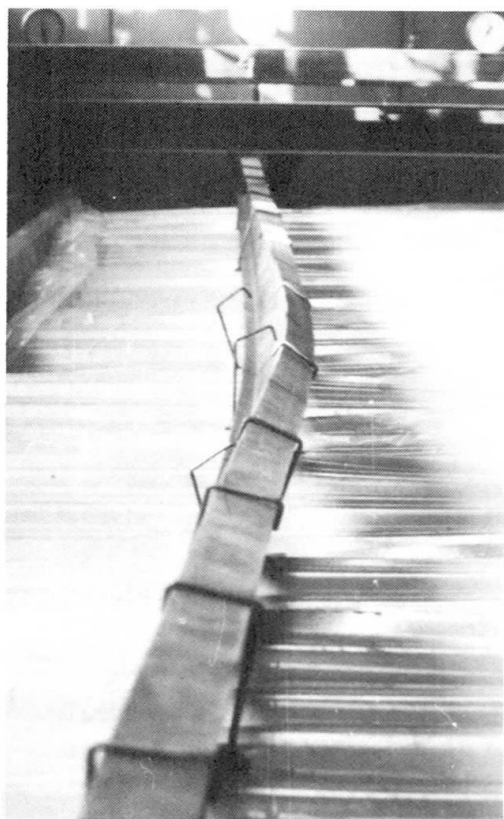


Fig. 9 Restrained Buckling

experimental programme directed to the behaviour of restrained beams is presently being conducted. The full-scale specimens arrangement is typical of those used in the metal building industry. The procedure referred to as vacuum test method is used, as well. The span of the beams tested is 6 m and the total loading breadth of the two parallel members is 3 m (Fig. 8).

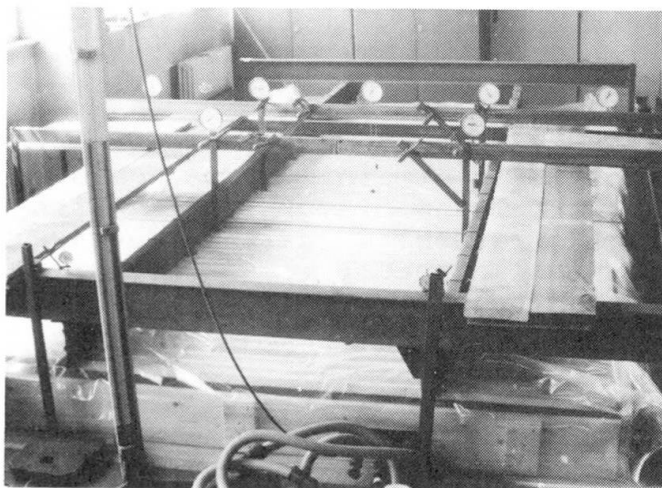


Fig. 8 Test Setup

continuous restraints (H. Nylander, T. Peköz, T. Höglund, N.S. Trahair, D.A. Nethercot, G.J. Hancock and others) a fair progress was made in the last period. But more attention to check the validity of the several assumptions and simplifications by experiments is needed. Interesting results of research in this field are for example in [ 5 ] , [ 6 ] .

At Technical University of Brno the



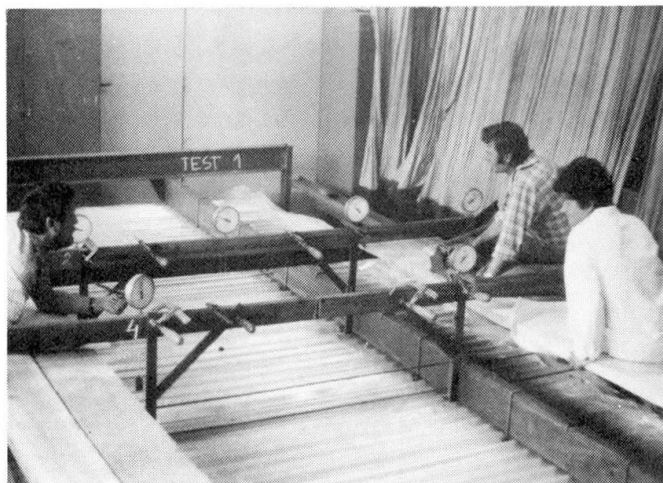


Fig. 10 Shot of Testing

The influence of sheeting and sag roads upon the behavior of restrained beams is studied under the conditions corresponding to the effect of wind uplift loading upon the secondary roof or wall structures.

Typical example of restrained general buckling of hot-rolled I - section is presented in Fig. 9. Also the general and local buckling tests of thin-walled cold-formed steel channel flexural members are being conducted (see examples in Fig. 10 and Fig. 11). From the test results follows that the ultimate buckling strength of restrained beams could be associated with considerable lateral and distortional deflections, their limitation should be respected deriving the design (specified) limit state. In thin-walled beams restrained by sag rods at third-point along the span the local buckling of compression flange can govern the ultimate strength in bending.



Fig. 11 Local Buckling

#### REFERENCES

1. FUNG Y.C., SECHLER E.E., Instability of Thin Elastic Shells. Proc. of the 1st Symposium on Naval Struct. Mechanics, Stanford Univ., August 11-14, 1958.
2. POGORELOV A.V., Cilindriczeskie oboloczki pri zakriticheskih deformaciyakh (Cylindrical Shells under postcritical deformations). Kharkov State Univ., 1963.
3. TIMASHEV S.A., Ustoychivost podkreplennykh oboloczok (Stability of Stiffened Shells). Stroyizdat, Moscow, 1974.
4. STABILITY OF METAL STRUCTURES - A World View, Chapter 10 - Cold-formed Steel. Engineering Journal, AISC, Vol. 19, No. 2, 1982.
5. PEKÖZ T., Diaphragm-Braced Thin-Walled Channel and Z-section Beams; Beams and Beam Columns. Applied Science Pub., London - New York, 1983.
6. LA BOUBE R.A., Purlin Braces: Measured Forces. Proc. of the Third Colloquium on Stability of Steel Structures, Toronto, 1983.