

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 54 (1987)

**Artikel:** Simulation and evaluation of deterioration of reinforced concrete structures  
**Autor:** Sakurai, Hiroshi / Aoki, Toshihiko / Momozaki, Kazuhiro  
**DOI:** <https://doi.org/10.5169/seals-41940>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 01.04.2026


**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## Simulation and Evaluation of Deterioration of Reinforced Concrete Structures

Simulation et évaluation de la détérioration des structures en béton armé


Simulation und Auswertung der Schädigung von Stahlbetonkonstruktionen

**Hiroshi SAKURAI**  
Lecturer Concrete Eng.  
Kitami Inst. of Techn.  
Kitami, Japan




Hiroshi Sakurai is a lecturer in concrete engineering at the Developmental Engineering Dept., Faculty of Engineering, Kitami Institute of Technology. He is a member of the Japan Society of Civil Engineers and a member of the Japan Concrete Institute.

**Toshihiko AOKI**  
Engineer  
Taisei Corp.  
Yokohama, Japan




Toshihiko Aoki is an engineer in the Osaka Branch of Taisei Corporation. He is a member of the Japan Society of Civil Engineering.

**Kazuhiro MOMOZAKI**  
Senior Res. Eng.  
Taisei Corp.  
Yokohama, Japan



Kazuhiro Momozaki is a senior research engineer at the Technical Research Institute of Taisei Corporation.

**Aketo SUZUKI**  
Chief Res. Eng.  
Taisei Corp.  
Yokohama, Japan



Aketo Suzuki is a Doctor of Engineering and chief research engineer of the Technical Research Institute of Taisei Corporation. He is a member of the Japan Society of Civil Engineering.

### SUMMARY

The purpose of this study is to evaluate the deterioration of reinforced concrete structures at the planning and design stages. This paper examines the basis for quantifying the durability of structures. In addition, reinforced concrete structure (kaleidoscopic change) deterioration predictions were analyzed.

### RÉSUMÉ

Le but de cette étude est d'évaluer la détérioration des structures en béton armé dans la phase du projet. L'article examine les bases permettant d'évaluer la durabilité des structures. Des prévisions sont faites pour l'évaluation de la détérioration des structures en béton armé.

### ZUSAMMENFASSUNG

Das Ziel dieser Studie ist es, die Schädigung von Stahlbetonkonstruktionen im Planungs- und Entwurfsstadium zu bewerten. Der Beitrag befasst sich mit möglichen quantitativen Erfassungsmethoden.



1. INTRODUCTION

Recently, calculation of life cycle cost and quantifying of service life for concrete structures have been of concern, and establishment of rational and objective techniques for quantifying the durability of new structures at planning are in demand. The technique for quantifying durability of concrete structures are distinguished between evaluating the degree of health for existing structures and the techniques of quantifying for planning structures by purpose. This paper examines the basis of quantifying for structures at planning at the design stage and the prediction of concrete deterioration change in time by analyzing and choosing of concrete durability data. One of the latest studies are the projects of synthetic developing techniques of the Building Research Institute of the Ministry of Construction. Some of the purposes are development of synthetic techniques for research and improvement of durability, and preparing of criterion for judgment of structures. At the present, the techniques for judging the degree of deterioration of existing structures for maintenance and the technical skill has been given in the project. On the other hand, the test method or construction materials and quantifying durability and the prediction of service life are given at ASTM E-632. The development of the technique of quantifying for planning structures at the design stage would be an advance.

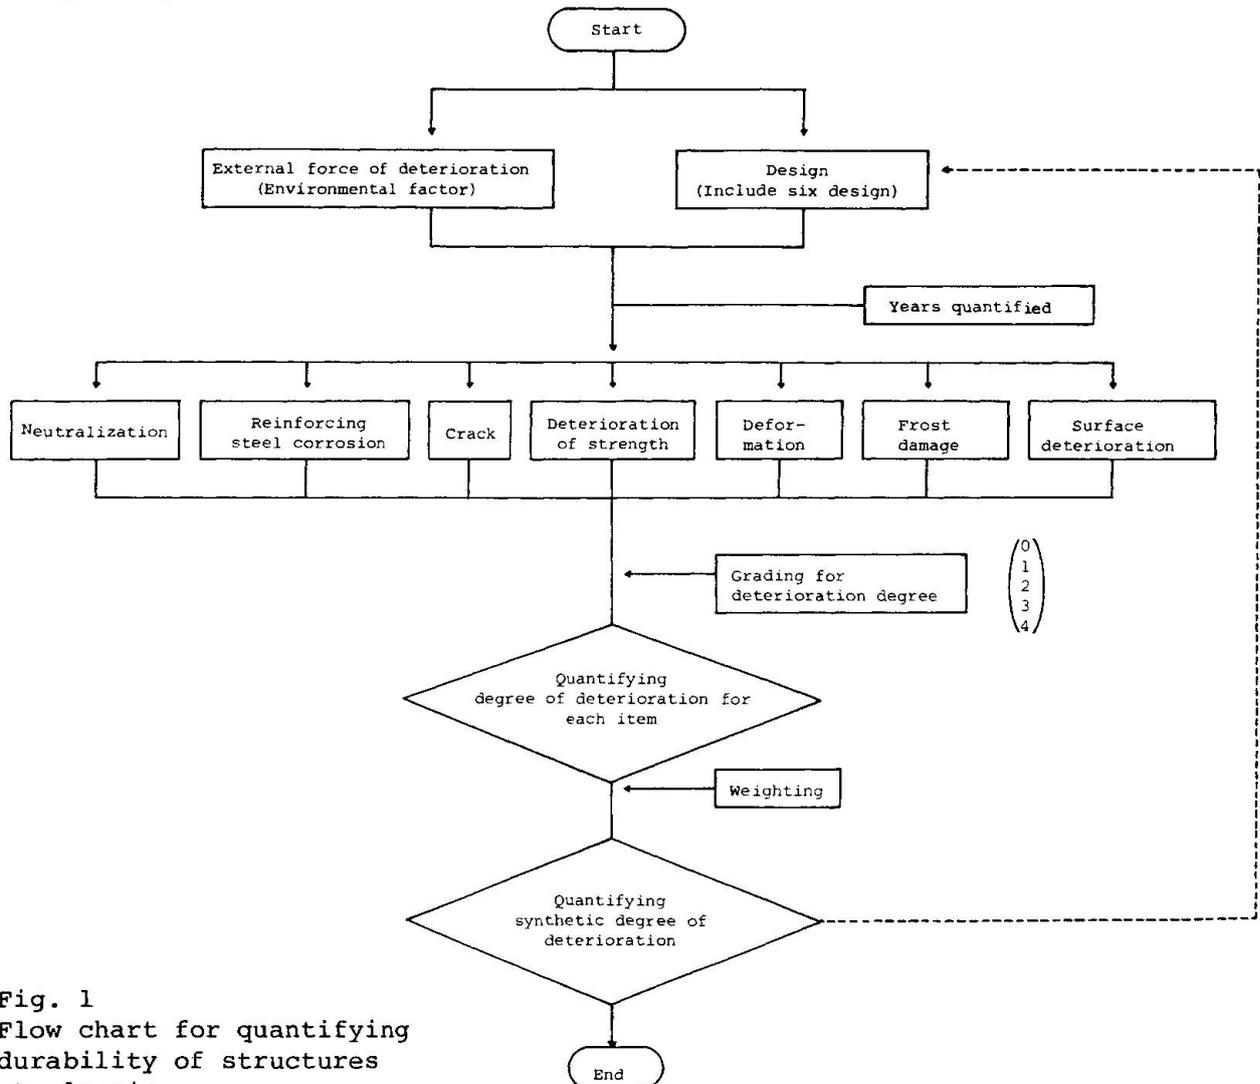


Fig. 1  
Flow chart for quantifying durability of structures at planning



## 2. INVESTIGATION OF TECHNIQUE FOR QUANTIFYING DURABILITY

### 2.1 Investigation of Flow for Quantifying Durability of Structure at Planning

The Flow chart for quantifying durability of structures at planning is shown in Fig. 1. In this flow chart, the initial data of temperature, humidity, the distance from the sea, the result of water analysis and so on, which are external forces of degradation of external factors, and environmental factors around the structure, are imputed. The strength of concrete, its stress, the strength of its reinforcing steel, mix proportion of concrete (w/c, type of cement, water amount, content of air, material and so on), which are the value of design and inner factors, are imputed too. Further, years of quantifying are imputed. Next, the degree of deterioration for year for each item are calculated, graded, and weighted with capability demanded in each item. Lastly, the synthetic degree of deterioration are quantified with calculation results.

### 2.2 Choice of Items for Quantifying Durability

Seven items for quantifying civil structures were chosen which are neutralization, reinforcing steel corrosion, crack, deterioration of strength deformation, frost damage and surface deterioration. The definition of these are shown in Table 1. The reason why surface deterioration is chosen is that good siting and adequate cover of reinforcing steel are demanded for bridges and so on in civil structures. However, the deterioration phenomenon of each item's quantified durability are regarded as independent against their dependence of each other.

### 2.3 Choice of Deterioration Indicator

In choosing a deterioration indicator, the possibility of quantifying deterioration change in time and much existing data supported with enough experiments are to be taken into account. As the indicator, neutralization depth, ratio of corrosion, change rate in relative dynamic modulus of elasticity and average depth of damage are selected for each item to be quantified, as shown in Table 2.



Table 1. Definition of deterioration for each item quantified

Item of quantifying	Definition
a Neutralization	Deterioration due to declining alkalinity of concrete with carbonic acid gas in air and sodium carbonate in water (pH < 10)
b Reinforcing steel corrosion	Deterioration due to corroding reinforcing steel by oxidation and deoxidation with neutralization of concrete around it, water from cracks and corrosion ( $cl^-$ , $SO_4^{2-}$ )
c Crack	Deterioration due to growing macro and scopic failure of concrete by over permi stress (major stress over tensile strength) of concrete
d Deterioration of strength	Deterioration due to decreasing strength of concrete with material, environment in service, thermal action and chemical action
e Deflection	Deterioration due to deflecting horizontal members by structural external force action and dry shrinkage (excepting short term load)
f Frost damage	Deterioration due to decreasing strength proper ties of concrete by freezing and thawing water in concrete
g Surface deterioration	Deterioration lossing concrete surface by scaling and popout

Table 2(a) Deterioration indicator, factor, calculation and grading for each item quantified

Quantifying Item	Selected Indicator		Factor (1): valuable		Calculation of Deterioration Indicator (durability) at Lapse of Year	Grading
	Indicator	Phenomenon	External Factor	Inner Factor		
a. Neutralization	Depth of neutralization X (mm)	① Neutralization	[t: Service life (year)]	W/C: Water cement ratio (%) R: Type of cement Type of AE agent Type of aggregate	W/C≥60%: $x=10x\sqrt{\frac{R^2(0.01W/C-0.25)^2}{0.3(1.15+0.01W/C)t}}$ 4) W/C<60%: $x=10x\sqrt{\frac{R^2(0.046W/C-1.76)^2}{7.2t}}$	1: 20≤X<40 2: 40≤X<80 3: 80≤X<100 4: 100≤X Depth of neutralization X: Depth of cover
b. Reinforcing steel corrosion	Ratio of corrosion surface P (%)	① Corrosion of penetrating chloride	[t: Service life (year)] L: Distance from sea (m) Co: Amount of chloride from sea (wt%)	Dc: Diffusivities of concrete (cm <sup>2</sup> ) D: Depth of cover (mm) UC: Unit weight of cement (kg/m <sup>3</sup> ) W/C: Water cement ratio (%) γ: Index of workability: γ=1	Co=0.48-0.07ln L (Pacific side) Co=0.45-0.06ln L (Japan sea side) C=Co(1-erf $\frac{D/10}{2\sqrt{Dc \cdot t \cdot 3.1536 \times 10^7}}$ ) 5) erfx= $\int_0^1 \exp(-u^2) du = 0.094t+0.245-0.029D$ 6) P=γ $\frac{2000}{UC} \cdot \frac{C}{2} \cdot (0.01W/C-0.3) \cdot 10^n$ 7)	0: P<10 1: 10≤P<20 2: 20≤P<30 3: 30≤P<50 4: 50≤P
		② Corrosion of neutralization		D: Depth of cover (mm) X: Depth of neutralization (mm)	P=(1-φ(d-X/0.41X))x100 where; φ(a): Normal distribution function 8)	
		③ Corrosion of crack		D: Depth of cover (mm) Wmax.: Maximum width of crack (mm)	Wmean= $\frac{Wmax+0.03}{1.91}$ where; Wmean: Average width of crack P=0.167(Wmean/D <sup>2</sup> x10 <sup>6</sup> -20) 10)	
c. Crack	Maximum width of crack (mm)	① Crack of steel stress		fs: Stress of reinforcing steel (kgf/cm <sup>2</sup> ) D: Depth of cover (mm) β: Note 1) A: Note 2)	Wmax=0.0108 β·fs <sup>3</sup> $\sqrt{D/10xA} \times 10^{-3}$ 11)	0: Wmax<0.05 1: 0.05≤Wmax<0.2 2: 0.2 ≤Wmax<0.3 3: 0.3 ≤Wmax<0.5 4: 0.5 ≤Wmax
		② Crack of dry and temperature shrinkage	TC: Change of temperature (°C)	b: (m) h: (m) NH: fct: (kgf/cm ) fb: (kgf/cm ) φ: (m) cs: te: Show in Table 4	Wmax= $\frac{2b \cdot h \cdot fct}{\pi \cdot NH \cdot \phi \cdot lb} (\epsilon cs + \epsilon te - 100 \times 10^{-6}) \times 1000$ 12)	
		③ Crack of alkali silica reaction		RG: Content of reactionable aggregate (%) Ru: Amount of Na <sup>2</sup> O in aggregate by cement (%)	The expansion (EX) is estimated by RG and RU 13)	

Table 2(b)

Quantifying Item	Selected Indicator		Factor (1): valuable		Calculation of Deterioration Indicator (durability) at Lapse of Year	Grading
	Indicator	Phenomenon	External Factor	Inner Factor		
d. Deterioration of strength	Notes 2) Ratio of compressive strength SN(%)	① Deterioration of penetrating sulfate	[t: Service life (year)]	W/C: Water/cement ratio	Linear Regression of experimental data W/C=55% {H <sub>2</sub> SO <sub>4</sub> : 0.3%, SN=-40.15t+100 H <sub>2</sub> SO <sub>4</sub> : 2.0%, SN=-233.6t+100 H <sub>2</sub> SO <sub>4</sub> : 5.0%, SN=-244.55t+100	14) 0: 95<SN 1: 90<SN≤95 2: 80<SN≤90 3: 70<SN≤80 4: SN≤70
		② Deterioration of frost damage	[t: Service life (year)] M: Cycles of freeze-thaw a year	W/C: Water/cement ratio AE or NonAE: Whether there is AE agent	DN of f ① is converted to by the equation $SN = \frac{DN-25}{0.75}$ AE {W/C=40% SN=-0.04 N·t+100 W/C=50% SN=-0.07 N·t+100 W/C=55% SN=-0.11 N·t+100 W/C=60% SN=-0.12 N·t+100 NonAE {W/C=40% SN=-0.49 N·t+100 W/C=60% SN=-0.69 N·t+100	15) 16)
		③ Deterioration of alkali silica reaction aggregate		RG: Content of reaction-able aggregate RU: Amount of Na <sub>2</sub> O in aggregate (%)	SN(f(EX)) is estimated with the expansion EX of c ③	17)
e. Deformation	Strain ε (%)	① Deformation of creep strain	σ: Stress of concrete loading (kgf/cm <sup>2</sup> )	Ec: Youngs modulus φ: Coefficient of creep	$\epsilon = \frac{\sigma}{Ec} \cdot \phi$ (outdoor φ=2.0)	18) 0: ε< 420 1: 420≤ε< 670 2: 670≤ε<1033 3: 1033≤ε<2290 4: 2290≤ε
		② Deformation of dry and temperature	Tc: Change of temperature (°C)	Uc: Unit weight of cement W/C: Water cement ratio	$\epsilon_{cs} = 0.00148W/C + 0.000301UC - 0.131$ $\epsilon_{te} = 10 \times 10^{-6} \times IC$	19)
f. Frost damage	Change rate in relative dynamic modulus of elasticity DN (%)	① Frost damage	[t: Service life (year)] N: Cycles of freeze-thaw a year	W/C: Water cement ratio (%) AE or NonAE: Whether there is AE agent	Linear Regression of experimental data AE {W/C=40% DN=-0.026N·t+100 W/C=50% DN=-0.053N·t+100 W/C=55% DN=-0.080N·t+100 W/C=60% DN=-0.085N·t+100 NonAE {W/C=40% DN=-0.36 N·t+100 W/C=60% DN=-0.51 N·t+100	15) 0: 96<DN 1: 93<DN≤96 2: 85<DN≤93 3: 78<DN≤85 4: DN≤78
g. Surface deterioration	Average depth of damage H(mm)	① Surface deterioration of frost damage	[t: Service life (year)] N: Cycles of freeze-thaw year W: Coefficient of supplying seawater	W/C: Water cement ratio (%) α: Coefficient of type of cement and curing condition fc: Compressive strength of concrete K: Construction	$H = W \cdot \alpha \left( \frac{W/C}{55} \right)^3 - (0.001195k^2 \cdot fc^2) \left( \frac{W/C}{55} \right)^3$ 20) W=0.5 where; α=0.0129 21)	0: H<1 1: 1≤H<2 2: 2≤H<3 3: 3≤H<4 4: 4≤H

Note 1) β: The ratio of distance from axial of neutrality to center of reinforcing steel to distance from axial of neutrality to tensile side in the case of beam 1.2

A: The area of tensile side concrete of symmetry with steel number of reinforcing steel

Note 2) Superpose the development strength at the age {SN=-55.32+16.60ln(365t)}  
{DN=-41.49+12.45ln(365t)}

## 2.4 Quantifying Change of Deterioration in Time by Deterioration Indicator

In the case that the deterioration indicators are varied by plural deterioration phenomenon, the progress of deterioration is distinguished by the assumptions which are shown in Table 3. The equation and data to quantify the change of indicator in time correspond to the deterioration phenomenon distinguished. In the case that the progress of deterioration is not described with an equation in general, the data was analyzed and adjusted by regression analysis statistically. The increase of the indicator of each deterioration phenomenon are calculated by the equation and they are added by the relation as shown in Table 3. The indicators of each quantifying item are made with the sum. However, crack and deformation are assumed that they occur at the early stage because the setting up of the condition to calculate the occurrence and the change in time are complex.

Table 3. Relation between quantifying item (deterioration indicator) and deterioration phenomenon

Item	Deterioration Phenomenon												
	Neutralization	Reinforcing Steel Corrosion	Crack	Deterioration of Strength	Deformation	Frost Damage	Surface Deterioration	Dry Shrinkage and Thermal Shrinkage	Alkali-Aggregate Damage	Strain of Creep	Diffusion of Chloride	Crack of Steel Stress	Diffusion of Sulfate
Neutralization (Neutralization depth: mm)	●												
Reinforcing steel corrosion (Ratio of corrosion surface: %)	■	○	■					△	△		●	△	
Crack (Width of crack: mm)			○					●	●			●	
Deterioration of strength (Ratio of compressive strength: %)				○		■			●				●
Deformation (Strain: %)					○			●		●			
Frost damage (Change rate in relative dynamic modulus of elasticity: %)						●							
Surface deterioration (Average depth of damage: mm)						■	○						

Table 3 Note 1) ●: Deterioration phenomenon which vary deterioration indicator and are converted to the indicator.  
 ○: Deterioration phenomenon which subordinate other deterioration phenomenon and are not converted to deterioration indicator.  
 ■: Deterioration phenomenon which subordinate other quantifying item and are converted to deterioration indicator.  
 △: Deterioration phenomenon which are subordinated the Case (3) and are not converted to deterioration indicator.

## 2.5 Investigation of Grading for Degree of Deterioration

The maximum values of the varying indicators are assumed. They are divided with proportion and so on, and made to grade from 0 to 4. The grading is shown in Table 2.

## 2.6 Calculation of Synthetic Degree of Deterioration

The synthetic degree of deterioration are calculated by equation (1). The number of items quantifying are seven.



$$\text{SYNTHETIC DEGREE OF DETERIORATION} = \sqrt{\sum_{i=1}^7 (A_i^2 \cdot \frac{\alpha_i}{100})} \dots\dots\dots (1)$$

Where  $A_i$  is the average degree of deterioration and  $\alpha_i$  is weight of deterioration at the each item ( $\sum_{i=1}^7 \alpha_i = 100$ ).

**3. APPLICABLE INVESTIGATION FOR EXISTING STRUCTURES**

The external forces of deterioration of existing structures, the value of design and the number of years at the investigation were inputted and calculated. The results were compared to the actual deterioration, and those applicable for existing structures were examined. The conditions of the existing structure, which was a wharf, and shown in Table 4 were inputted. The change in time of the item quantifying were calculated and shown in Fig. 2 from 1 to 7, but the calculation was done without considering crack because cracks occurred at the early stage and was maintained at the beginning. The rate of the depth of neutralization and the corrosion of reinforcing steel of the actual data were very much faster than the calculation showed. The reason seemed to be the effect of crack which occurred at an early stage. The structural safety and fire proof capability were assumed to be the capability of the structures, and the weight of capability were assumed to be shown in Table 5. The synthetic degree of deterioration was calculated and shown in Fig. 2.


Table 4. Data of actual structures for examination

Factor	Mark: Parameter (unit)	Actual Structure		Factor	Mark: Parameter (unit)	Actual Structure			
		Wharf (A)	Wharf (B)			Wharf (A)	Wharf (B)		
External factor	External factor of deterioration	t: Service life (year)	18	24	Material	Ec: Youngs modulus (kgf/cm <sup>2</sup> )	2.58x10 <sup>5</sup>	3.29x10 <sup>5</sup>	
		L: Distance from sea (m)	1	1		ϕ: Coefficient of creep	2.0	2.0	
		Co: Amount of chloride from sea (Wt%)	1.3	0.33		W/C: Water cement ratio (%)	49.1	62.0	
		Ic: Change of temperature (°C)	30.3	33.3		Uc: Unit weight of cement (kg/m <sup>3</sup> )	320	282	
		S: Concentration of sulfate of water contacted surface (Wt%)				Uw: Unit weight of water (kg/m <sup>3</sup> )	157	174	
		M: Cycles of freeze-thaw a year	5	5		Type of cement			
		W: Coefficient of supplying seawater	0.5	0.5		R: Type of AE agent	0.6	0.6	
Inner factor	Design	D: Depth of cover (mm)	75	50		Type of aggregate			
		fs: Stress of reinforcing steel (kgf/cm <sup>2</sup> )	816	1,400		RU: Amount of Na <sub>2</sub> O in aggregate by cement (%)			
		σ: Stress of concrete (kgf/cm <sup>2</sup> )	17.4	50.0		RG: Content of reactionable aggregate (%)			
		B: Note 1	1.2	1.2		AE or Non AE: Whether there is AE agent	AE	AE	
		A: Note 2 (cm)	260	62.5		Dc: Diffusivities of concrete (cm <sup>2</sup> )	1.6x10 <sup>-8</sup>	0.44x10 <sup>-8</sup>	
		b: Width of the section (m)	0.80	0.50		Construction	α: Coefficient of type of cement and curing condition	0.0129	0.0129
		h: Depth of the member (m)	1.30	0.60			K: Ratio of decreasing surface strength		
	WB: Number of steel members	4	4	γ: Index of workability: γ=1	1.0		1.0		
	Material	Material	ϕ: Diameter of the steel (m)	0.029	0.019	Result of investigation	x: Depth of neutralization (mm)	19.0	15.1
			fc: Compressive strength of concrete (kgf/cm <sup>2</sup> )	271	344		D: Corrosion surface	70	65
			fct: Tensile strength of concrete (kgf/cm <sup>2</sup> )	*	*	Crack etc.	Loss of cover	Loss of cover	
			fb: Average bond strength of concrete and steel (kgf/cm <sup>2</sup> )	54.0	68.9	Note (1) E: The ratio of distance from axial of neutrality to center of reinforcing steel to distance from axial of neutrality to tensile side in the case of beam 1.2			
				Note (2) A: The area of tensile side concrete of symmetry with steel number of reinforcing steel					

Table 5. Assumption of weight for capability demanded in each item quantified

Capability of structure	Structure safety	Fire proof capability	Factor of weight (%)
Weight of capability	80%	20%	
Neutralization	4%	7%	5%
Reinforcing steel corrosion	58%	20%	50%
Crack	8%	20%	10%
Deterioration of strength	20%	20%	20%
Deformation	4%	7%	5%
Frost damage	3%	13%	5%
Surface deterioration	3%	13%	5%
Total	100%	100%	100%

Fig. 2. Example of calculation for actual structure

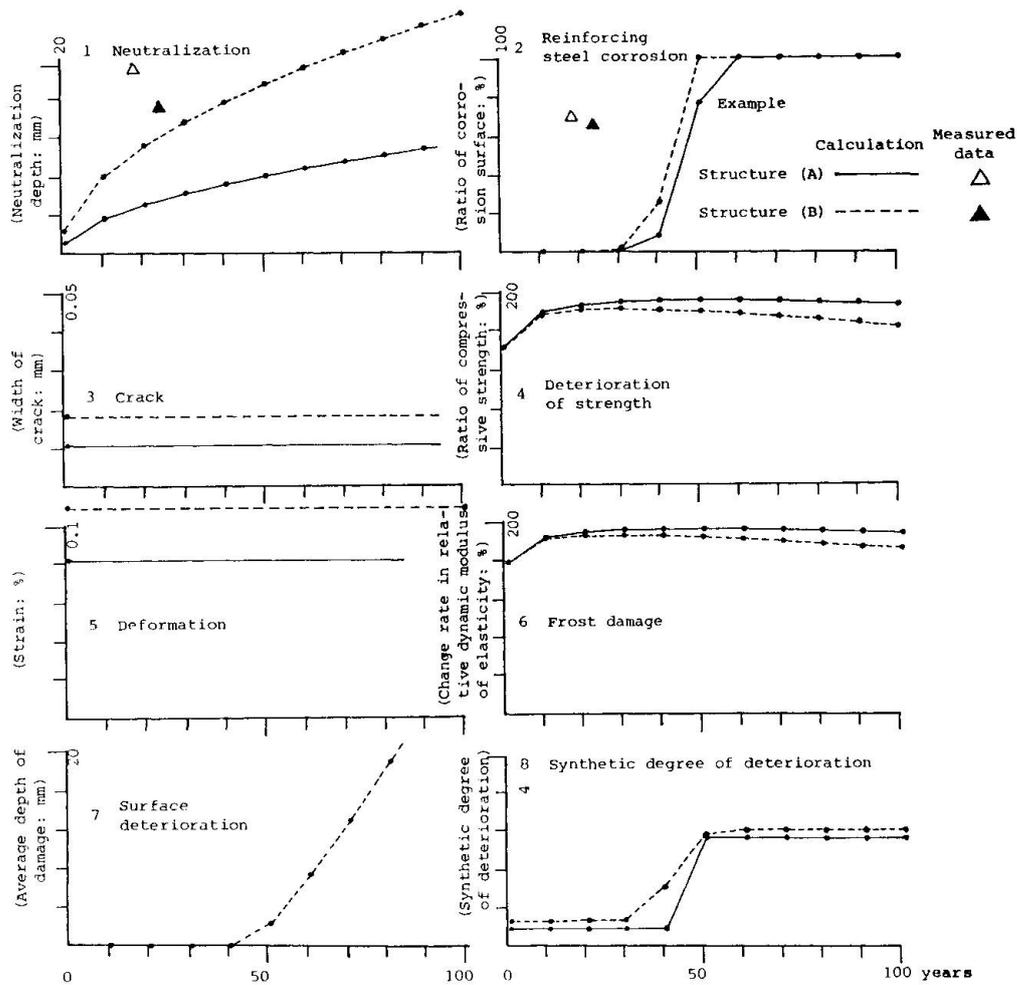



#### 4. FUTURE PROBLEMS

For developing the technique for quantifying durability of reinforced concrete structures, the following studies are needed for further application of the technique.

- 1) The mechanisms and the factors of deterioration must be understood and readjusted. F.T.A. (Fault Tree Analysis) and so on must be put into practice.
- 2) The measuring and understanding of the rate of damage occurrence, and the grading must be studied.
- 3) The capability and the weight of capability must be examined using many cases of deterioration in existing structures and items of quantified deterioration should be weighted to each of them.
- 4) Many detailed experiments combined with accelerated tests and exposed tests of items quantifying deterioration must be put into practice.
- 5) The pursuit of investigation into existing structures which are calculated with synthetic degrees of deterioration, must be put in practice for many years.

Thus what is demanded now is a systematic study for the development of the technique for quantifying durability of reinforced concrete structures.

#### REFERENCES

- 1) Building Research Institute: Development in maintenance of existing structure and improvement of durability of new building, report of committee of Ministry of Building, 1984
- 2) Building Research Institute: Report of the second department of Building Research Institute at spring lecture, 1985
- 3) ANSI/ASTM: "Standard Recommended Practice for Developing Short Term Accelerate Tests"
- 4) K. Kishitani: "Durability of Reinforced Concrete", Kajima Shuppankai
- 5) K. Kashino: "Investigation of effect of chloride from sea for building", The third edition of ARAKA, 1985
- 6) H. Nagano: "Application of Diffusion Theory for Chloride Penetration into Concrete Located at Splashing Zone", JCI 7th Conference, 1985
- 7) K. Takewaka, "Estimation of Steel Corrosion in Concrete Structure by Autoclave Process", JCI 4th Conference, 1982
- 8) Y. Tomozawa: "The problem in neutralization", Seko No. 229, 1985
- 9) M. Yachida: "Research for Cracks of Concrete Bridges and Corrosion of Reinforcement", JCI 6th Conference, 1984
- 10) H. Kamiyama: "Crack of Concrete and Corrosion of Steel", CAJ REVIEW of The 31 GENERAL MEETING, 1977
- 11) ACI 224 Committee: "ACI standard of structural design (ACI 318-77)", ACI, 1977
- 12) BSI: BS5337 "The Structural use of concrete for retaining aqueous liquids", 1976
- 13) The Society of Material Science Japan: "Symposium about Alkali-Silica Reaction, 1985
- 14) H. Ikenaga: "The deterioration of concrete soaked in water which are different kind and concentration of acid and chloride", 1976
- 15) K. Ayuta: "The Effect of Aggregate in durability of freeze and thaw", Hokkaido branch of JSCE Conference, 1976
- 16) S. Ito: "New edition of Concrete Engineering", Morikita Shuppan
- 17) H. Yamashita: "Basic Experiment of reaction aggregate (NO. 1)", JSCE Conference
- 18) JSCE: "Specification of Reinforced Concrete", 1980
- 19) JCI: "Point of Concrete technique'82", JCI, 1982
- 20) H. SAKURAI: "Progress Degree of Scaling on Concrete Surface", Hokkaido branch of JSCE Conference, 1980
- 21) H. SAKURAI: "Some Experiments of Progress Degree of Scaling on Concrete Surface", JSCE Conference, 1980