

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 60 (1990)

**Artikel:** Degree of safety in mixed structural systems  
**Autor:** Androic, Boris / Milcic, Vuk / Mujkanovic, Nijaz  
**DOI:** <https://doi.org/10.5169/seals-46556>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 01.04.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**


## Degree of Safety in Mixed Structural Systems

Degré de sécurité dans les systèmes à structures mixtes

Sicherheitsgrad im Mischbauwerkssystem

### **Boris ANDROIC**


Senior Lecturer  
University of Zagreb  
Zagreb, Yugoslavia

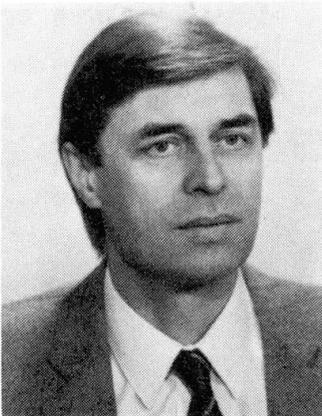

Boris Androic, born 1944, received Ph.D. from Zagreb University. Since 1986 Senior Lecturer at Civil Engineering Faculty, Zagreb Univ.

### **Vuk MILCIC**

Professor  
University of Zagreb  
Zagreb, Yugoslavia

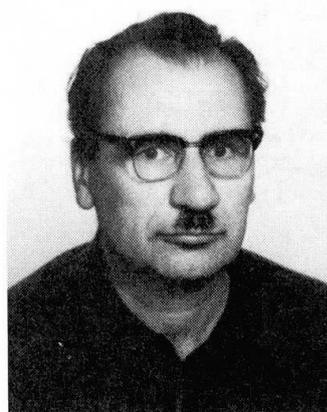

Vuk Milcic, born 1921, At present he is Professor at Civil Engineering Faculty, Department of Steel Structures, Zagreb University.

### **N. MUJKANOVIC**

Res. Assistant  
University of Zagreb  
Zagreb, Yugoslavia



Nijaz Mujkanovic, born 1961. Since 1987 has been working at Civil Engineering Institute. At present he is Assistant Lecturer in Steel Structures, Zagreb University.

### **SUMMARY**

A probabilistic analysis of mixed structural elements can be used to equalize the degree of safety of several layers in various limit states. The method has been illustrated by means of a practical example for the manufacturer of these elements.

### **RÉSUMÉ**

L'analyse probabilistique des éléments de structures mixtes peut être utilisée pour égaliser le degré de sécurité de plusieurs couches dans les divers états limites. La méthode est présentée à l'aide d'un exemple pratique par les fabricants de ces éléments.

### **ZUSAMMENFASSUNG**

Mit der probabilistischen Analyse von Verbundkonstruktionselementen ist es möglich, die Sicherheitsgrade verschiedener Schichten in den Grenzzuständen auszugleichen. Die Methode wird an einem praktischen Beispiel dargestellt.



## 1. INTRODUCTION

The calculation of internal forces in elements composed of several layers of different materials is based on the theory elaborated in [1]. The appearance of new materials has greatly increased the choice of mixed layered elements used in civil engineering.

In this, the materials in the various layers have very different mechanical properties and modes of bearing capacity loss. This points to the fact that safety verification based on present methods cannot include the problems of equalizing the safety of individual layers.

Since the standards are inadequate, it is not possible to prescribe the bearing capacity of equalized safety degree according to the chosen safety indices. As a result, the composite elements are not safe enough or economical.

The problem of practical application is analyses for the manufacturer and safety equalization of different layers in composite elements, bringing the damage or failure risk in individual layers to the levels prescribed by the society and required by the regulations.

## 2. LIMIT STATES EQUATIONS

The differential equation of the deflection line caused by flexural and shear deformations in a multi-layered element loaded with a transversal action is presented in [1]. The solution consists of the homogeneous part  $w_h$  and the particular part  $w_p$ :

$$w_h = C_1 + C_2 \cdot x + C_3 \cdot e \exp \left[ (x-l) \sqrt{\frac{B \cdot A}{B_s \cdot B_d}} \right] + C_4 \cdot e \exp \left[ -x \sqrt{\frac{B \cdot A}{B_s \cdot B_d}} \right] + M_L \left( \frac{x^3}{6 \cdot B \cdot l} - \frac{x^2}{2} \right) - M_R \frac{x^3}{6 \cdot B \cdot l} \quad (1)$$

$$w_p = \frac{q}{2 \cdot B} \left[ \frac{x^4}{12} - \frac{x^3 \cdot l}{6} + \frac{x^2 \cdot B_s}{A} \left( \frac{B_d}{B} - 1 \right) \right] - \frac{x^2 \cdot B_s \cdot q}{2 \cdot B} \quad (2)$$

The symbols are taken from [1]. Equations (1) and (2) contain an indefinite vector  $k^T \{C_1, C_2, C_3, C_4, M_L, M_R\}$  for which the equations with six known border conditions have to be determined. If the element consisting of  $n$  continuous fields is observed, where the field is a part of an element with an uninterrupted function for continuous transversal loading,  $6 \cdot n$  border conditions or rather continuity conditions for internal characteristic points have to be defined. This yields a system consisting of  $6 \cdot n$  linear equations accompanied by vector  $k$  with  $6 \cdot n$  unknown constants. The system in the matrix form is:

$$\{w\} = [z] \cdot \{k\} + \{s\} \quad (3)$$

where:  $\{w\}$  - displacement vector,  $[z]$  - coefficients matrix,  
 $\{k\}$  - unknown coefficients vector,  $\{s\}$  - load vector.

Further analyses are made if the statical system of the element is a field with two supports. The cross-section of the element consists of three mixed layers. The element is used for the facade, and its resistance to wind was tested.

From the safety aspect, i.e. the probability of bearing capacity failure, there is a margin between the safety and non-safety zone in an n-dimensional vector space, and this margin is expressed with a limit state equation:

$$Z = G(X, K) = 0 \quad (4)$$

where:  $Z$  - safety margin,  $G$  - bearing capacity value function,  $X$  - basic variables vector,  $K$  - deterministic parameters vector.

In an element mixed of three layers, four limit state equation can be written:

1. Ultimate limit state of the compressive face:

$$Z_1 = X_6 \sqrt[3]{K_3 X_4 X_5} - \frac{X_8 K_1^2}{8 X_1 X_2} = 0 \quad (5)$$

2. Ultimate limit state of the tensile face:

$$Z_2 = X_3 - \frac{X_8 K_1^2}{8 X_1 X_2} = 0 \quad (6)$$

3. Ultimate limit state of the core:

$$Z_3 = X_7 - \frac{X_8 K_1}{2 X_2 K_2} = 0 \quad (7)$$

4. Serviceability limit state of the element:

$$Z_4 = \frac{K_1}{K_6} - \frac{5 X_8 K_1^4}{192 K_3 X_1 X_2^2} - \frac{X_8 K_1^2}{8 X_5 X_2 K_2} - \frac{K_4 K_5 K_1^2}{8 X_2} = 0 \quad (8)$$

The symbols and meanings of the basic variables and of the deterministic parameters are shown in Table 1.

### 3. TEST SPECIMENS AND STATISTICAL DATA

Statistical data of the mechanical properties of the layers and of geometrical characteristics of the element are obtained by tests and measurements on random samples from the manufacture, and the result can be considered to represent the real situation in the manufacture. The results are shown by histograms in Fig.1. Statistical values of the basic variables and deterministic parameter values are comprehensively presented in Table 1.

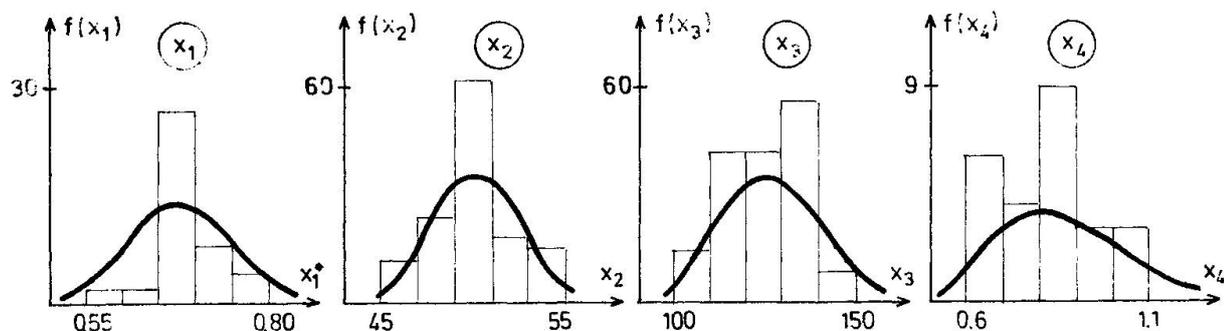


Fig.1a Histograms of basic variables  $X_1, X_2, X_3, X_4$

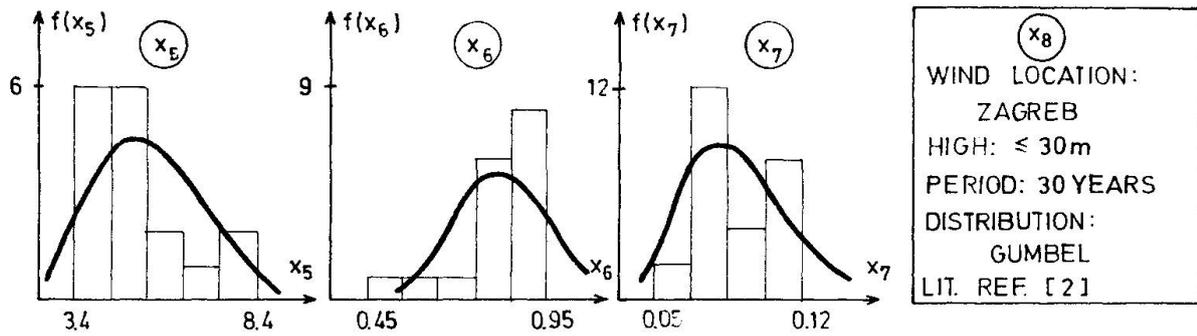


Fig.1b Histograms of basic variables  $X_5$ ,  $X_6$ ,  $X_7$ ,  $X_8$

BASIC VARIABLES [ $\bar{X}$ ]				
VARIABLES	MEAN VALUES	C.O.V.	DISTRIBUTION	
$X_1$	720 mm <sup>2</sup>	0.07	NORMAL	METAL FACE AREA ( $X_1 = X_1^* \cdot K_2^*$ )
$X_2$	51 mm	0.03	NORMAL	CENTROID DISTANCE THE FACES
$X_3$	126 N/mm <sup>2</sup>	0.08	NORMAL	YIELD STRENGTH
$X_4$	8.1 N/mm <sup>2</sup>	0.20	LOGNORMAL	ELASTICITY MODULUS OF THE CORE
$X_5$	5.0 N/mm <sup>2</sup>	0.24	LOGNORMAL	SHEAR MODULUS OF THE CORE
$X_6$	0.812	0.15	LOGNORMAL	FACE BUCKLING COEFFICIENT
$X_7$	0.085 N/mm <sup>2</sup>	0.24	LOGNORMAL	CORE SHEAR STRENGTH
$X_8$	850 N/m <sup>2</sup>	0.28	GUMBEL	UNIFORMLY DISTRIBUTED LOAD
DETERMINISTIC PARAMETERS [ $K$ ]				
$K_1 = l$ SPAN OF ELEMENT		$K_2 = b$ WIDTH OF ELEMENT		
$K_3 = 70\,000$ N/mm <sup>2</sup> FACE MODULUS OF ELASTICITY		$K_4 = \alpha_T$ TEMP. COEFFICIENT OF FACES		
$K_5 = \Delta T$ TEMP. DIFFERENCE OF FACES		$K_6 = k$ DEFLECTION LIMIT		

Table 1 Data for limit states equations

The value of  $k^*$  presents the element face length.

#### 4. EQUALIZATION OF SAFETY DEGREE

If statistical values of the basic variables and deterministic parameters from Table 1 are inserted in the limit states equations, safety indices for ultimate limit states and serviceability limit state for various displacement limits are obtained, as shown in Fig.4 and Fig.5.

If the required design value, i.e. safety index for the ultimate limit state  $\beta_f = 4.2$  and for the serviceability limit state  $\beta_s = 2.0$ , the safety equalization is achieved by looking for adequate spans and displacement limits satisfying the required criteria, according to Fig. 2 and 3:

a/ for the ultimate limit state :

$$\beta_1, \beta_2, \beta_3 \Rightarrow \beta_{\min} \geq \beta_f = 4.2 \quad (9)$$

b/ for the serviceability limit state :

$$\beta_4 \geq \beta_s = 2.0 \quad ; \quad \beta_4 = f(K_6) \quad (10)$$

For example, the chosen span  $l = 2.0$  m,  $\beta_{\min} = \beta_3 = 4.33 > \beta_f = 4.2$  and

the permissible displacement limit  $1/150$ , yield  $\beta_d = 3.61 > \beta_f = 2.0$ . Besides safety equalization to the safety index design values, the remaining two  $\beta_i$  in expression (9) can be equalized to the minimum one. This can be done by selecting the materials of lower qualities, by decreasing the cross-section of the layers, etc. Sensibility coefficients  $\alpha_i$  show immediately which changes of the basic variables will yield effective results.

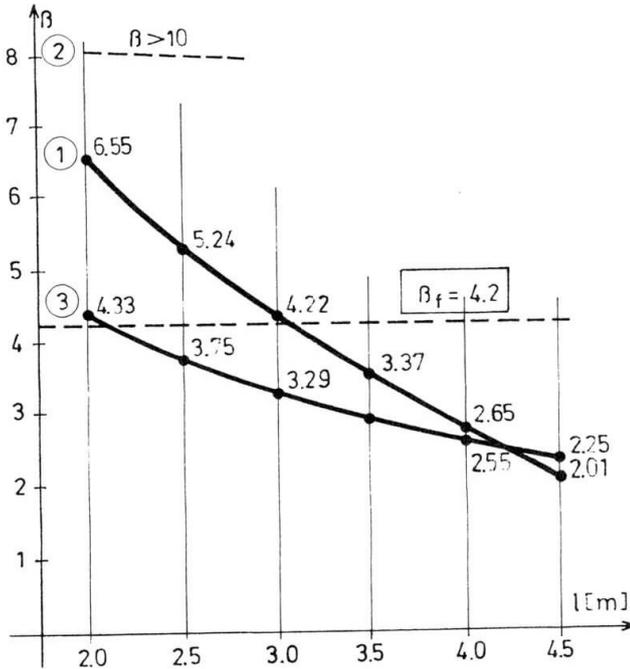


Fig.2 Safety index for ultimate limit states

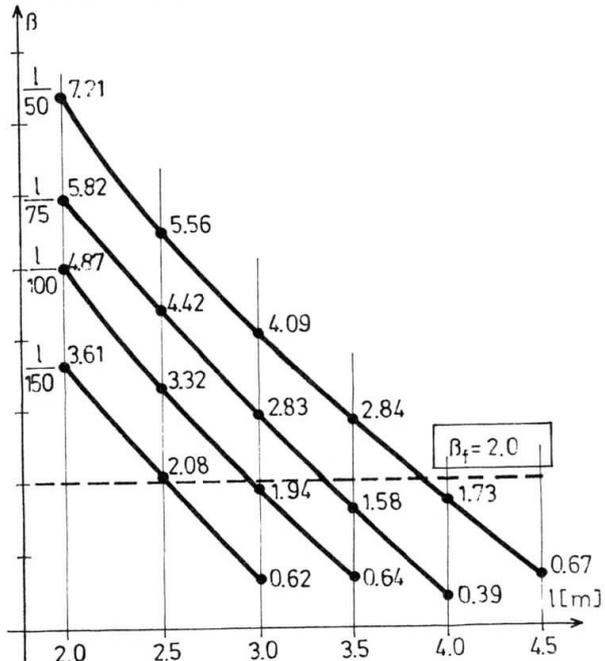


Fig.3 Safety index for serviceability limit state

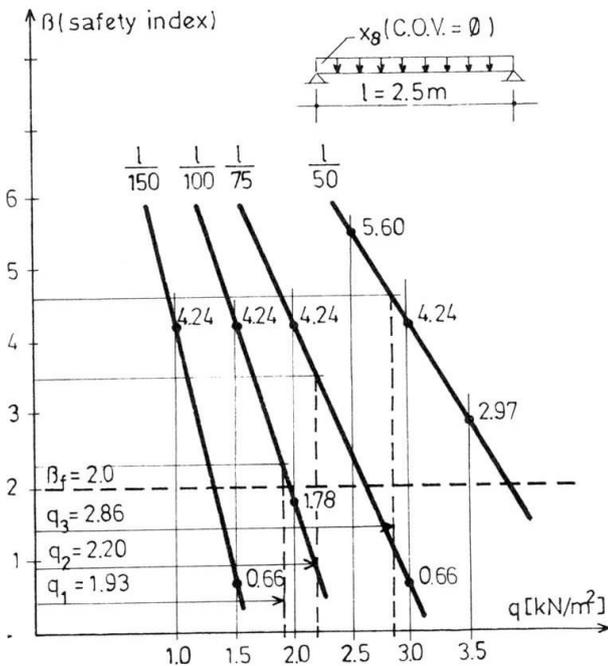


Fig.4 Serviceability limit state for displacement limit


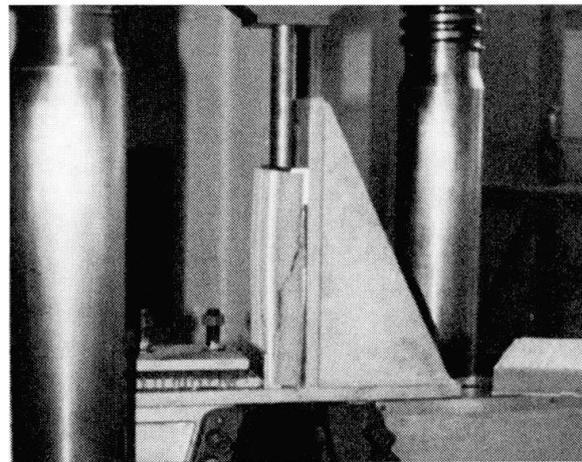


Fig.5 Laboratory testing for shear

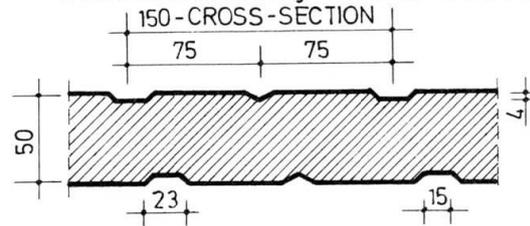

Tests on three elements with a span of 2.5 m have shown that, at failure, their loads were  $q_1$ ,  $q_2$  and  $q_3$ . They satisfied the displacement limits  $1/110$ ,  $1/90$  and  $1/70$  in relation to  $\beta_f = 2.0$  (Fig. 4). Fig. 5 shows laboratory testing of shear characteristic of the specimen.

## 5. DISCUSSION

The results obtained by laboratory testing and by numerical analyses can be discussed regarding the following statements:

The safety indices for tensile face  $\beta_2$  obtained from the limit state equation (6) are very high as expected.

Safety equalization of individual faces is done in two steps. The first step is with regard to the design values  $\beta_f$  and the second is by decreasing the required basic variable values.

Note: when equalizing the safety degree for all the three layers to the same safety index for the ultimate limit state, we should keep in mind that the probabilities of bearing capacity failure in all the layers should be added, and the common safety index could thus be below the required one. In this case, however, this is only theoretically significant because in only three composite materials the probability of failure does not essentially change.

If the bearing capacity is to be increased to a 4 m span considering the required  $\beta_f$  design value, a core with greater shear strength should be provided, and a span above 3 m should have greater face buckling values (Fig. 2).

An issue still open is adopting the design values  $\beta_f$ . Decision should also be made whether a definite safety index should be required for each of the four limit states, or the ultimate limit state and serviceability limit state should be distinguished as usual.

We consider that the control of composite elements during manufacture to ensure the guaranteed safety can be done by controlling small specimens with a statistical processing of the basic variables data.

## 6. CONCLUSIONS

This paper presents a probabilistic approach to the safety of composite elements. Since the safety verification of these elements is not yet definitely codified, it can still be discussed, but the results should serve as guidelines for the manufacturer. Equalization of safety is proposed for individual layers as well as for design values, based on probabilistic approach where the probability of failure is expressed with the safety index.

## REFERENCES

1. STAMM K., WITTE H., Sandwichkonstruktionen. Springer Verlag, Wien 1974. 337 p.
2. MILCIC V., PAUSE Z., TRUPCEVIC D., A probabilistic approach to defining a wind load, Gradevinar, Vol. 37, No.3., 1985, pp 101-107.