

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 60 (1990)

**Artikel:** Analysis of new types of composite beams  
**Autor:** Gramblicka, Stefan  
**DOI:** <https://doi.org/10.5169/seals-46481>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 01.04.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

# Analysis of New Types of Composite Beams

Etude de nouvelles poutres mixtes

Analyse von neuartigen Verbundträgern

**Stefan GRAMBLICKA**

Dr. Eng.  
Slovak Techn. Univ.  
Bratislava, Czechoslovakia

## 1. INTRODUCTION

Increasing use of composite steel-concrete structures in the construction of buildings has called for the development of a new type of composite steel-concrete beams. The first object of this paper is to present composite steel-concrete beams which have been developed at the VITKOVICE steelwork company and at the Slovak Technical University, Faculty of Civil Engineering, Bratislava. The second object is to present the experimental results obtained through the series of test programmes.

## 2. CHARACTERISTIC OF THE NEW COMPOSITE BEAMS

The proposed composite steel-concrete or steel-reinforced concrete beams consist of a steel member and of a concrete or reinforced concrete. The steel member is built with the two rolled  $\square$  profiles ( steel channels ) placed at the outside surface of the cross section. These beams can be mainly used as precast composite steel-concrete beams. The arrangement of steel part enables horizontally concreting without the need of special formwork. Beam joints can be solved as steel-steel. The basic idea is to build a composite steel-concrete beam without stud connectors. Theoretical analysis is based on the model of the trussed structure [1].

## 3. TEST SPECIMENS, APPARATUS AND MEASUREMENTS

Six beams ( three pairs UBO, UBA1, UBA2 ) were tested in the first series. The specimens, of total length 4,2 m were simply supported and subjected to the two point loads. Details of the specimens are summarized in Fig. 1, Fig. 2,

and Fig. 3. The cross section of the beam UBO was built only with two channels  $\square$  140 and concrete. The cross sections of the beams UBA1 and UBA2 were completed with the reinforced concrete. The arrangement of the reinforcement  $2 \text{ } \varnothing 25$  or  $\# 60.16$  show the Fig. 2 and Fig. 3. The overall design of each beam was made using simple plastic

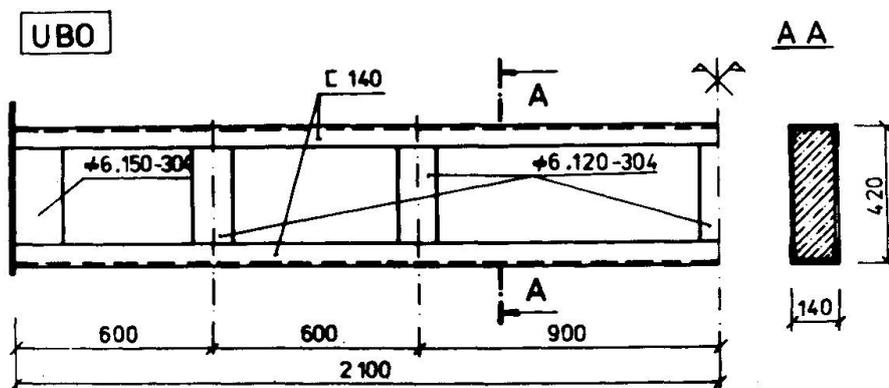


Fig. 1 Details of the beam UBO

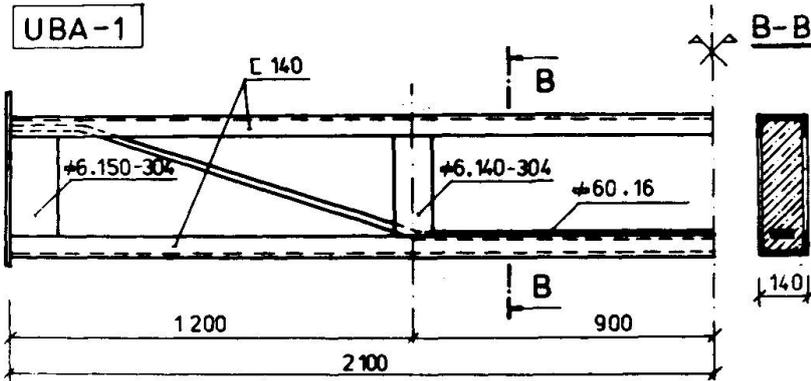


Fig. 2 Details of the beam UBA1

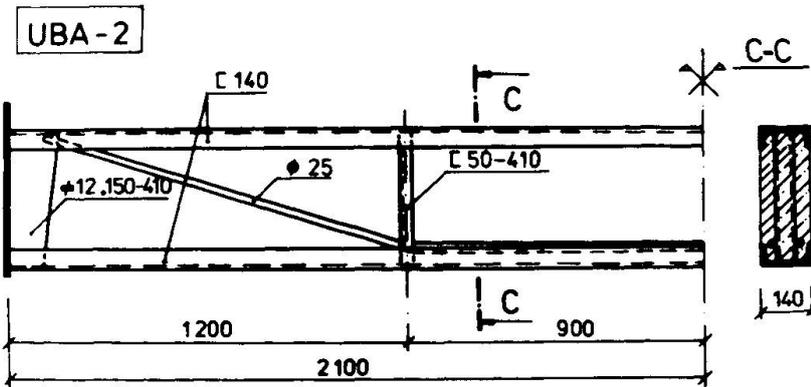


Fig. 3 Details of the beam UBA2

theory. The performance of the beams can be seen in Fig. 4 which shows the midspan deflexion and from the condition at ultimate load which is given in the Table 1.

Measurements of deflexion were taken at midspan by indicating gauges. Longitudinal strains on both steel channels and concrete were measured in three cross sections using mechanical strain gauges with a 200 mm gauge length and electrical resistance strain gauges, too. The test programme continues and we are testing another types and arrangements of the connectors between two steel channels.

Type of the beam	Ratio $M_t / M_d$
UBO - 1	1,38
UBO - 2	1,45
UBA1 - 1	1,40
UBA1 - 2	1,43
UBA2 - 1	1,21
UBA2 - 2	1,20

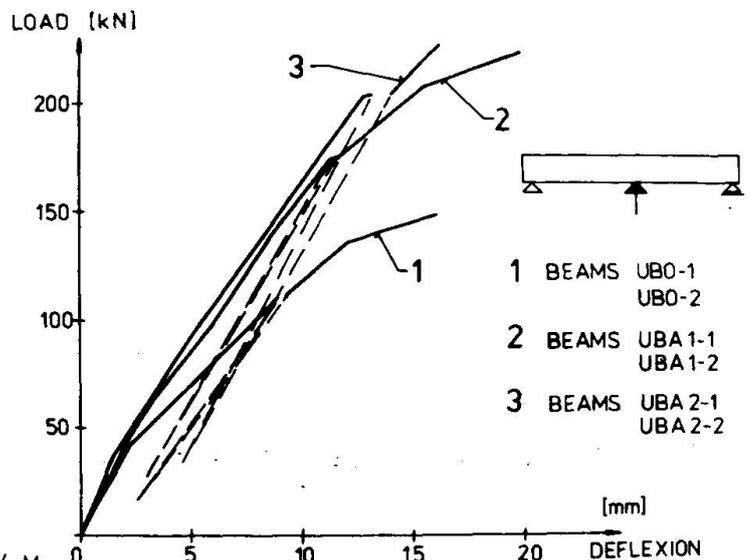


Fig. 4 Load-deflexion curves for centre spans

Table 1 Values of the ratio  $M_t / M_d$ .

$M_t$  is maximum bending moment in the test,  $M_d$  is design bending moment

REFERENCES

- SCHLEICH J.B., KLINGSCH W., Composite Steel Concrete Components, IABSE Symposium, Steel in Buildings, Luxemburg, 1985
- TAYLOR R., Composite reinforced concrete, Thomas Telford Limited, London, 1979.