

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 60 (1990)

Artikel: Reinforcement against shear failure of connection-panel
Autor: Matsui, Chiaki / Tsuda, Keigo / Nakatsui, H.
DOI: <https://doi.org/10.5169/seals-46490>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 01.04.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Reinforcement against Shear Failure of Connection-Panel

Armatures contre la rupture au cisaillement
de panneaux d'assemblage

Bewehrung gegen Schubversagen in Verbindungsscheiben

Chiaki MATSUI

Professor
Kyushu Univ.
Fukuoka, Japan

Keigo TSUDA

Research Assist.
Kyushu Univ.
Fukuoka, Japan

H. NAKATSUI

Graduate Student
Kyushu Univ.
Fukuoka, Japan

1. INTRODUCTION

Composite steel and reinforced concrete structures have been widely used in Japan. The arrangement of reinforcing bars is the same manner as that of a conventional reinforced-concrete structures. In a beam-to-column connection, therefore, the hoops are arranged as a reinforcement against shear failure. Arranging the hoops needs holes in the steel beam web so that the hoops can pass through. Moreover, because of existence of steel shapes and a lot of main reinforcing bars in the connection, the arrangement of hoops usually becomes troublesome. If a simpler method of the reinforcement against shear failure of the connection-panel is available, it seems that an economical and easy design is possible.


This paper presents the results of an experimental work carried out to study the strength and behavior of frames with a new type reinforcement against the shear failure of connection-panel.

2. TEST PROGRAM

Cruciform frame specimens are tested under a constant axial compressive load on the column and cyclic loads on the beam as shown in Fig.1. Total six specimens are tested. The detail of beam-to-column connection is shown in Fig. 2. All specimens are designed so that they fail in shear at beam-to-column connection. Three specimens with the conventional hoops (H0, H1, H2), and three specimens without them (W0, W1, W2) are tested. The specimens (H0, H1, H2) have different value of amount of the hoops p_w (H0;0%, H1;0.5%, H2;1%) in the connection-panel. The panel of steel portion of the specimens (W0, W1, W2) is strengthened by welding a doubler plate at a steel web in order to make the shear strength to be equal to that of specimen H1. Two specimens (W1, W2) have the bracing bars which is set so as to prevent the column reinforcing bars from buckling.

3. TEST RESULTS AND DISCUSSIONS

Figure 2 shows the load-deflection relation together with the detail of connection-panel. In each loading cycle, negative slope does not appear in the hysteresis loop. Even specimens without the hoops have equivalent maximum strength and deformation capacities to those of conventional connections (see H1 and W0). As to the effect of bracing to column reinforcing bars on the behavior, explicit difference is not observed (see W0, W1 and W2).

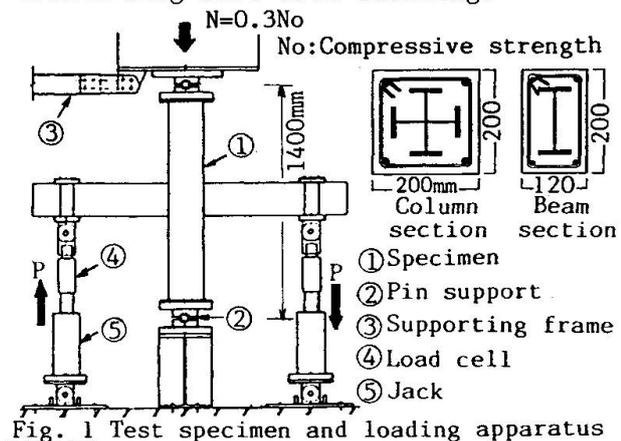

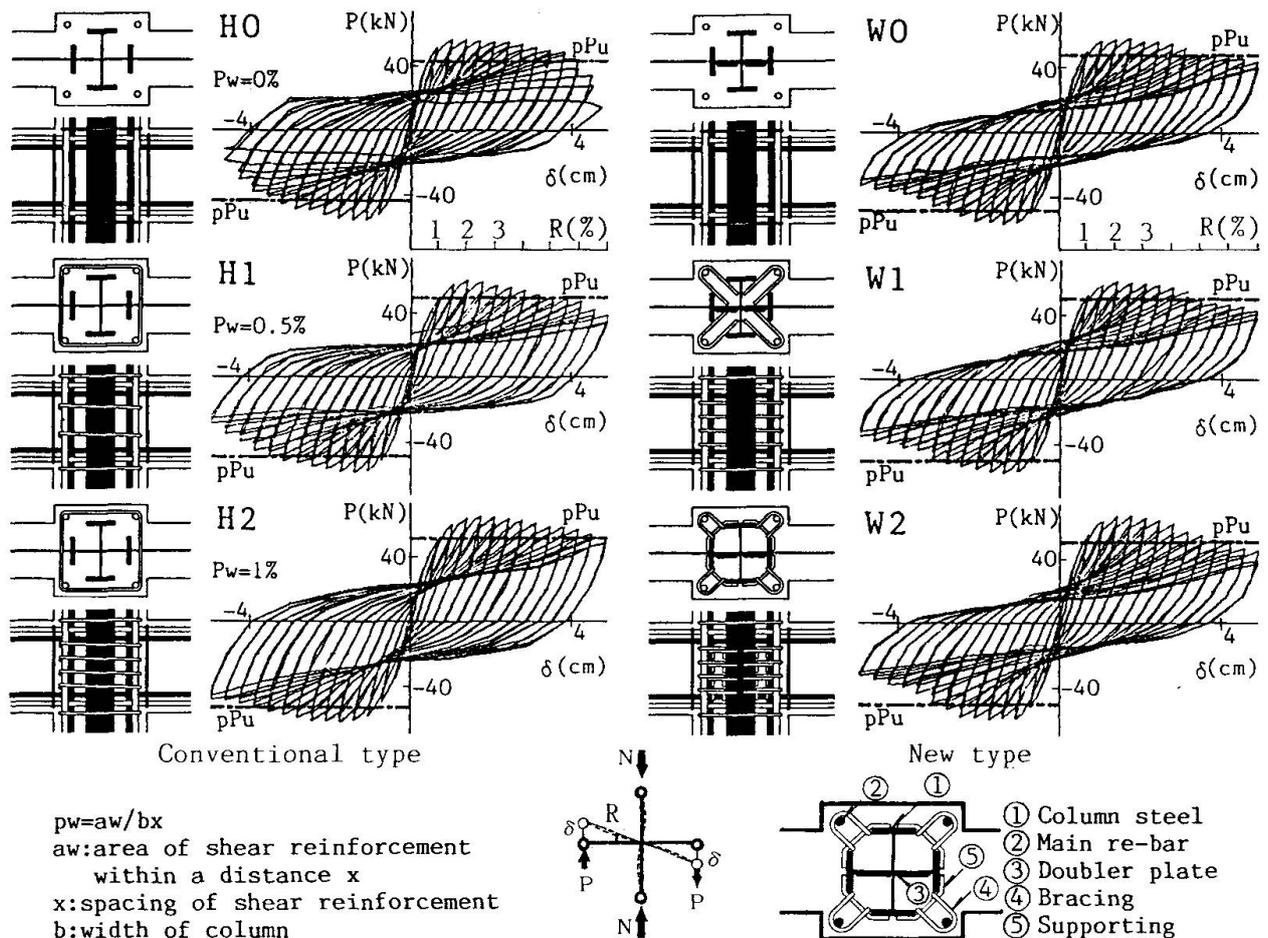


Fig. 2 Load-deflection relation

In Fig.2, dash-dot line indicates the ultimate shear strength of connection-panel obtained by using the strength formula specified by AIJ[1]. Table 1 shows the comparison of strength. The ratio of (experimental maximum strength) / (predicted strength) ranges from 1.2 to 1.3. Strength p_{Pu} is fairly well and conservatively predict the experimental strength of specimens.

Specimen	Experimental strength(1)	Predicted strength(2)	(1) (2)
H0	55.6	42.1	1.32
H1	59.4	48.5	1.22
H2	63.8	51.5	1.24
W0	57.5	47.7	1.21
W1	59.3	49.5	1.20
W2	65.6	50.1	1.29

Table 1 Comparison of strength (Unit:kN)

4. CONCLUSIONS

It has become clear from test results that :

- 1) Regarding the load carrying capacity and deformation capacity, a connection-panel without the hoops has the same performance as that with the conventional one if the panel of steel portion is strengthened by doubler plates. An economical design is possible by using this connection type which is easy to be manufactured.
- 2) Regarding the effect of the bracing to column reinforcing bars, there is no difference between with and without bracing.
- 3) The maximum strength of beam-to-column connections both with and without the hoops can be predicted fairly well by the AIJ strength formula.

REFERENCES

1. Architectural Institute of Japan, Standard for Structural Calculation of Steel Reinforced Concrete Structures, June 1987