

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 62 (1991)

**Rubrik:** Joints

#### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

#### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

#### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 16.01.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**


## Design of Vertical Joints in Precast Reinforced Concrete Shear Walls

Dimensionnement de joints à cisaillement vertical  
dans le cas de parois préfabriquées en béton

Bemessung von Fugen zwischen vorgefertigten Wänden

### Gheorghe CIUHANDU


Dr. Eng.  
INCERC  
Timisoara, Romania

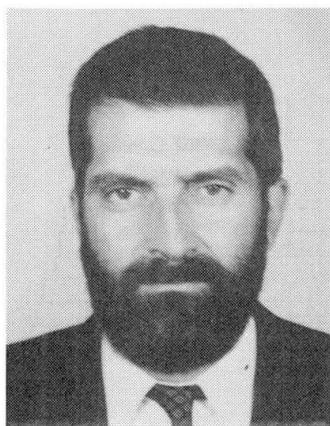

Gheorghe Ciuhandu, born 1947, received his civil engineering degree at the Polytechnical Institute of Timisoara, Romania, in 1970. For five years he worked in designing. From 1975, in Building Research Institute INCERC, Timisoara. He got his Ph.D. degree in 1986. Now as senior researcher at INCERC Timisoara, he is responsible for problems concerning structural concrete.

### Valeriu STOIAN

Dr. Eng.  
Polytechn. Inst.  
Timisoara, Romania

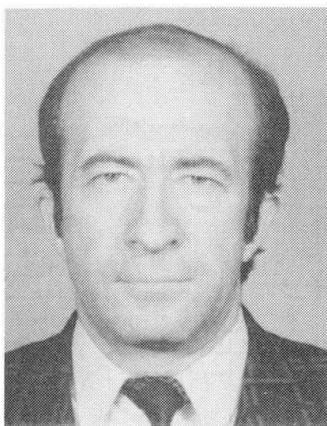

Valeriu Stoian, born 1949, received his civil engineering degrees at the Polytechnical of Timisoara, Romania, in 1972, and his Ph.D. degree in 1982. He is now professor of Civil Engineering at Building Construction Faculty, Polytechnical Institute of Timisoara, Romania.

### SUMMARY

For vertical shear joints, new design formulae are presented in order to establish the most appropriate design requirements describing the real behaviour of these structural elements. The theoretical values evaluated using different formulae, are compared with the experimental shear forces. Numerical analyses were performed in order to complete the experimental tests and to offer adequate numerical procedures vs, simpler hand calculations for the shear force resistance of the vertical joints.

### RÉSUMÉ

Pour ce type de joints, de nouvelles formules de dimensionnement sont présentées; les autres, déjà consacrées, sont rappelées en vue d'établir les meilleures recommandations possibles pour le projet de tels éléments de structure et d'en illustrer le comportement réel. Les valeurs théoriques calculées selon les différentes formules sont comparées avec des cisaillements expérimentaux. Des analyses numériques ont complété ces essais et permettent donc d'offrir les procédures numériques et manuelles les plus simples pour le calcul de la résistance au cisaillement des joints verticaux.

### ZUSAMMENFASSUNG

Es werden Formeln für die Bemessung der auf Schub beanspruchten Vertikalfugen von Wand- scheiben vorgestellt, die das reale Verhalten dieser Strukturelemente genauer veranschaulichen sollen. Die mit verschiedenen Formeln berechneten theoretischen Werte der Schubkräfte werden mit den Versuchsergebnissen verglichen. Diese Versuchsergebnisse wurden durch numerische Analysen ergänzt, um Berechnungsformeln für die auf Schub beanspruchten Vertikal- fugen aufzustellen.



### 1. FORCE DISTRIBUTION IN VERTICAL SHEAR JOINTS

Known the shear force distribution in the vertical shear joints of the reinforced concrete shear walls assembled from large precast panels is a major task in the designing of these structural elements. In a shear wall or a floor assembled from large precast panels the joints are, in general, the weakest link within the system. Therefore an elastic material behaviour can be assumed for the panels, since cracks and shear deformations only appear in the joints.

In accordance with the above mentioned facts, in structural systems composed of rectangular subunits the panels can be discretized with rectangular elastic finite elements in the plane state of stress. The reinforcement can be introduced approximately through modified modulus of elasticity for the concrete. As proposed in [1] the behaviour of the finite elements for the joints can be simulated by a pair of orthogonal springs at each end. Their characteristics diagram are coupled through an interaction diagram  $P_N - P_T$  as in fig.1. This characteristic and interaction diagram are based on a nonlinear incremental analysis or on results from suitable experiments. The latter procedure gives more realistic values, but is more expensive.

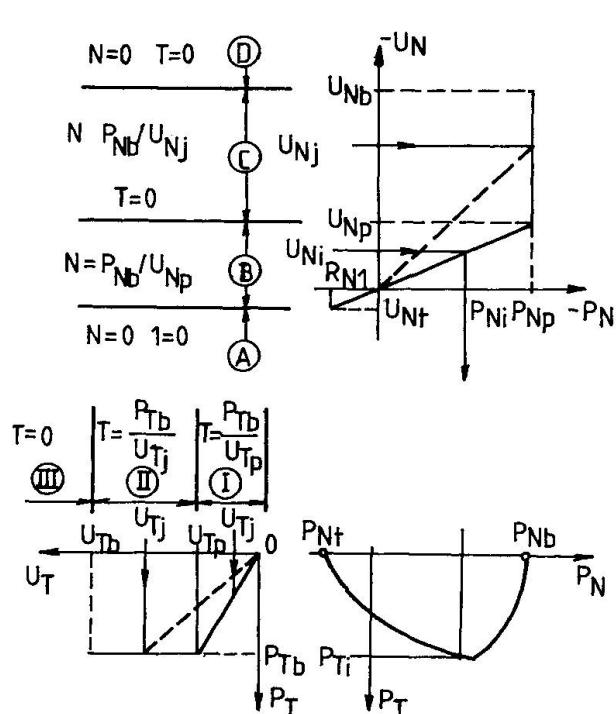


Fig. 1 Interaction diagram  $P_N - P_T$

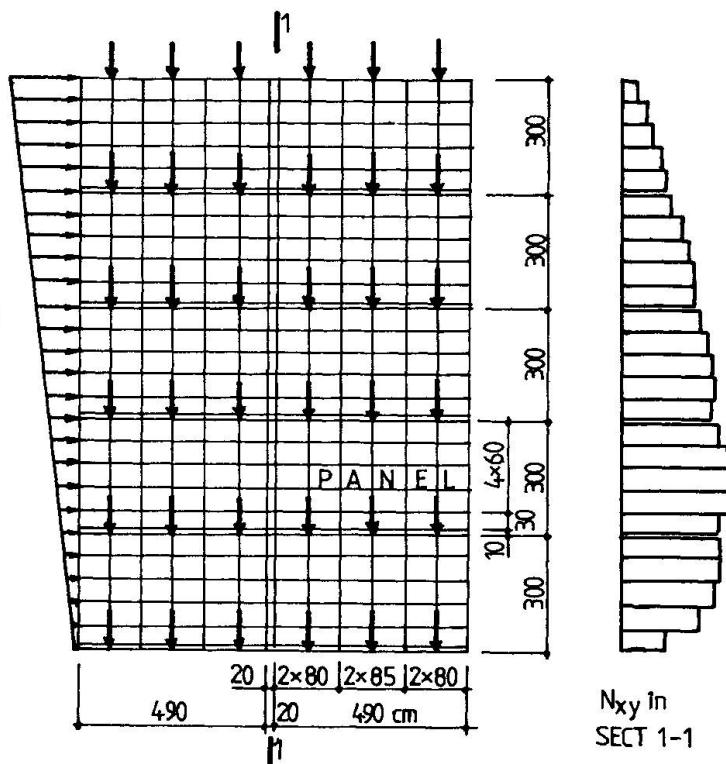


Fig. 2 Plane shear wall

The nonlinear analysis of the behaviour of the joints takes place iteratively, whereby within the successive iteration steps, each step is calculated linearly-elastic. For the mean value of the normal and tangential displacements in a joint finite element,  $U_{Nj}$  and  $U_{Tj}$ , Fig. 1 allows to obtain the updated rigidities  $N$  and  $T$  of the springs. It can be seen that the nonelastic behaviour is described by secant rigidities.

In order to establish the force distribution in the vertical shear joint, the plane shear wall in Fig. 2, composed from ten large precast panels was analysed under given vertical and horizontal loads. It was found that all joints remain in the elastic range for a given combination of the horizontal and vertical forces which are applied on the shear wall in an structure analysis. For this reason the results for the vertical joint are comparable with results obtained with the approximative method for the analysis of shear walls with holes. Yet, the latter method cannot be applied for a nonlinear analysis of the

coupling beams in shear walls. These conclusions are the basis for the new design formulae of the vertical shear joints.

## 2. NUMERICAL ANALYSIS OF THE SHEAR FRACTURE PROCESS

Experimental and numerical analysis of the shear fracture shows important features about the contribution of the tensile strength in this process. Therefore, the authors developed experimental and theoretical research programmes aimed to establish the contribution of the tensile strength to the total amount of the shear strength in the shear structural elements.

The numerical analysis is performed with anisotropic reinforced concrete elements [3]. This model was adopted because of his well known performances in modelling plain and reinforced concrete.

The nonlinear process which may be developed in the structure after reaching the elastic limit are: crack formation, crack closing, crack reopening, plasticity of uncracked or cracked concrete, crushing of the compressed concrete.

Element stiffness  $D_{rc}$  is formed for every physical state of the material by superposing concrete stiffness  $D_c$  and reinforcement stiffness  $D_R$ , taking into account the reinforcement ratio  $\mu$ :

$$D_{rc} = D_c + \mu D_R \quad (1)$$

Reinforcement is assumed to be uniformly distributed over the finite element, with perfect and continuously adherence to the concrete. Cracks are considered as smeared cracks. For the concrete a combined v. Mises-Maxwell behaviour criterion is considered, while for the reinforcement an elastic-plastic bilinear behaviour is assumed [2].

In [4] a set of 22 experimental models were analysed. The model is presented in Fig.3. A typical representation of the shear and tensile strength in the critical section of the element is illustrated in fig.4.

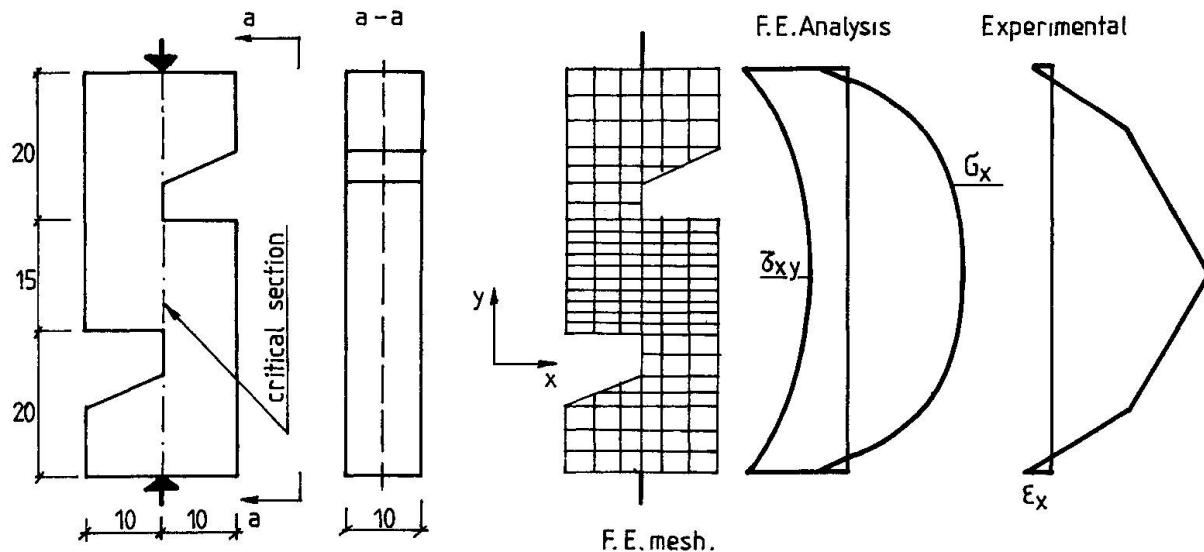


Fig.3 Shear modell

Fig.4 Strength in the critical section

The main conclusion of these analyses taking into account also the experimental results is that between the shear strength  $f_s$  and the tensile strength of the concrete  $f_{ct}$  there is the following relation:

$$f_s = 1.5 f_{ct} \quad (2)$$



The proposed value  $f_m = 1.5f_{ct}$  can be adopted for the design of plain or reinforced concrete structural elements in shear.

### 3. EXPERIMENTAL PROGRAMME

The accomplished researches were meant to observe the hysteretic behaviour of vertical joints under cyclic - alternating loads, their capacity to absorb and dissipate energy, the cracking and collapse mechanism. The experimental shear forces were compared to theoretical values calculated with various formulae, including the relation proposed in the new version of the Romanian technical instructions concerning the design of building with large, precast panel structures [5].

Four models of the same vertical joint were tested. The geometrical scale used was that of 1:1 (M1-M4). The experimental model shaped of two panel parts and the one-storey high vertical joint is given in fig.5.

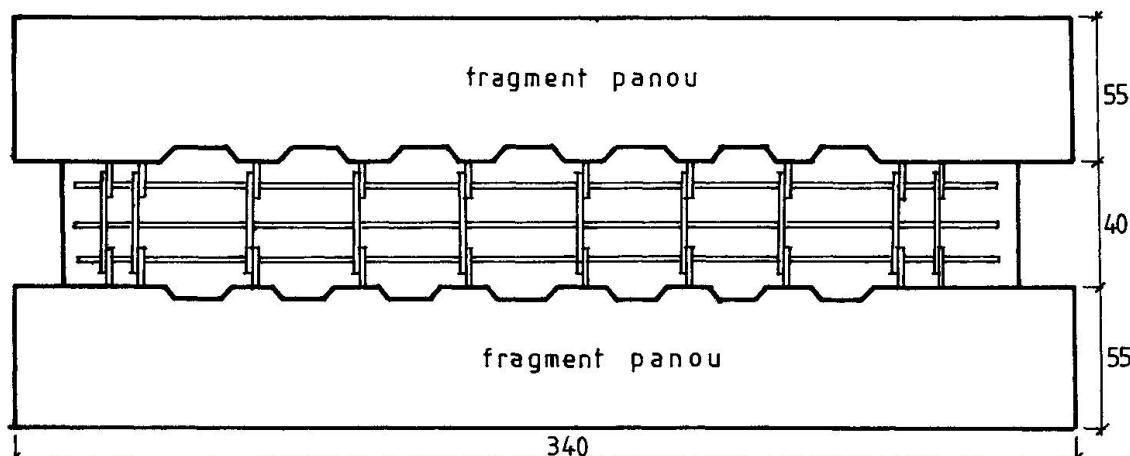


Fig. 5 Experimental model

The joint was tested in turned down position, on the narrow side, the model being inserted into the testing device schematically rendered in fig.6.

The testing methodology applied in the mentioned experiments was taken from the RILEM specifications concerning cyclic load testing. The monotonous M1 model testing served to establish the reference data required in the testing of the other three models under cyclic-alternating loads, according to the imposed deformation methodology [6].

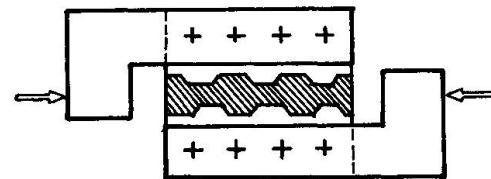


Fig. 6 Testing device

### 4. EXPERIMENTAL MODEL BEHAVIOUR

Generally, the behaviour of the experimental models points out cracks at the interfaces panels-joint, followed by the cracking of the joint in-situ concrete. The collapse results from shear failures of the keys in the joint. Consequently, the contribution of the in-situ concrete to the resistance of keyed joints is more dependent upon the resistance of concrete to tension than upon its resistance to compression.

At collapse, the cracking image typical for the tested models is that shown in fig. 7.

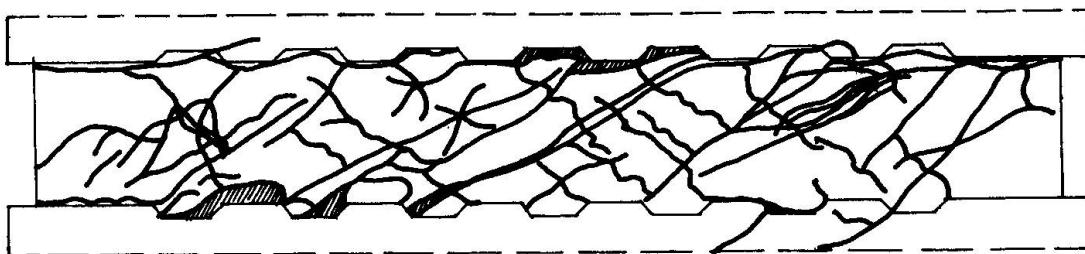


Fig. 7 Cracking at collapse

The ultimate loads (capable shears) of the experimental vertical joints were calculated in view of comparing them to the experimental results.

Characteristics of the materials used ( $f_c$ ,  $f_{ct}$ ,  $f_y$ ), the geometrical ( $A_{key}$ ,  $A_{crush}$ ) and reinforcement ( $A_s$ ) features have been considered in this respect.

Four estimating relations were used:

- the relation proposed by CEB [7]

$$R_{sv} = \beta_1 A_{key} f_c + \beta_2 A_s f_y \quad (3)$$

- the relation proposed by P101-78 [5]

$$R_{sv} = A_{crush} f_c + 0.8 A_s f_y \quad (4)$$

- the relations proposed by Tassios and Tsoukantas [8], [9]:

$$R_{sv} = A_s \tau_u = A_s (0.15 \lambda f_c + \mu \rho f_y + 1.8 \rho f_{ct} f_y) \quad (5)$$

- the relation proposed in the new version of P101, as a result of the experimental behaviour of the joints in conjunction with relation (2):

$$R_{sv} = \min \left\{ \frac{1.5 A_{key} f_{ct}}{A_{crush} f_c} \right\} + 0.8 A_s f_y \quad (6)$$

The estimated collapse force values compared to the experimental ones are given in Table 1:

Exp. mod.	$f_c$ (MPa)	$f_{ct}$ (MPa)	$f_y$ (MPa)	$A_{key}$ ( $\text{cm}^2$ )	$A_{crush}$ ( $\text{cm}^2$ )	$A_s$ ( $\text{cm}^2$ )	$R_{sv}$ [kN] rel. (3)	$R_{sv}$ [kN] calc. with rel. (4)	$R_{sv}$ [kN] rel. (5)	$R_{sv}$ [kN] rel. (6)	Exp. val. $R_{sv}$ [kN]
M1	23.54	2.17	360	1904	336	11.3	680	1116.5	1168.7	946	1150
M2	21.27	2.04	360	1904	336	11.3	650	1000	1103.7	905	1070
M3	30.53	2.58	360	1904	336	11.3	773	1351	1368.2	1064	1170
M4	29.96	2.55	360	1904	336	11.3	765.5	1332	1352	1054	1110

Table 1 Experimental and theoretical results.

The notations of the material characteristics used in Table 1 are those from the CEB Draft Guide [7].



## 5. CONCLUSIONS

As far as the possible shears in the joint are concerned, relations (5) and (6) offer values closer to the experiment. It is obviously that the relation (6) gives values under the experimental ones.

The experimental behaviour of the models shows that the contribution of the in-situ concrete to the resistance of keyed joints is more dependent upon the strength of concrete to tension than upon its strength to compression.

The joint behaves well with cyclic-alternating loads, since the joint resists without cracking to larger shear effort values as compared to the maximum shears that might occur in the joint in case of an earthquake.

The adequate joint behaviour to cyclic-alternating loads is confirmed by the curve position in fig.8 as well

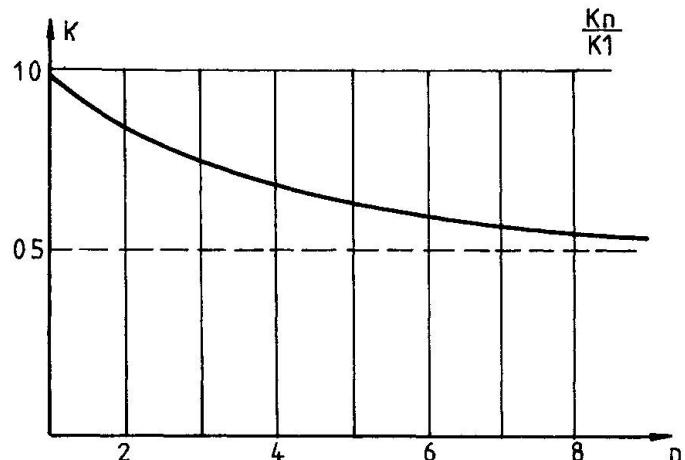


Fig.8 Stiffness decrease

## REFERENCES

1. MEHLHORN G., SCHWING H., *Tragverhalten von aus Fertigteilen zusammengesetzten Scheiben*, DAS, H.288, W. Ernst u. Sohn, Berlin, 1977.
2. CERVENKA V., GERSTLE K.H., *Inelastic Analysis of RC Panels Under In-Plane Loads, Inelasticity and Non-Linearity in Structural Concrete*, University of Waterloo Press, 1972.
3. AVRAM C., BOB C., FRIEDRICH R., STOIAN V., *Reinforced Concrete Structures. Finite Element Method. Theory of Equivalences*. (in Romanian), Editura Academiei, Bucuresti, 1984.
4. ABDUL R., *Shear Strength in Concrete Fracture* (in romanian), Dissertation, Polytechnical Institute Timisoara, 1990.
5. "Technical Instructions for Designing Building of Large Panel Structures P101-78" (in Romanian), Bucharest, 1978
6. TSOUKANTAS S., MACCHI G., *Proposals on Test-Procedures under Cyclic-Loading*, RILEM Committee 81-LCP, 1985
7. CEB, *Draft Guide for the Design of Precast Wall Connections*, Bulletin d'information, 169(1985)
8. TASSIOS T.P., TSOUKANTAS S.G., *Serviceability and Ultimate Limit States of Large Panels Connections under Static and Dynamic Loading*, Proceedings RILEM-CEB-CIB Symposium on Mechanical and Insulating Properties, Vol.1 Athens, 1978
9. TASSIOS T.P., TSOUKANTAS S.G., *Reinforced Concrete Precast Panel Connections under Cyclic Actions*. Proceedings of 7th European Conference on Earthquake Engineering, Vol.5, Athens, 1982


## Influence of Contact Surface Problems on Design Practice

Influence de problème des joints de contact sur le dimensionnement

Einfluss von Kontaktflächenproblemen auf die Bemessungspraxis

**Jürgen RUTH**

Civil Eng.  
Univ. of Stuttgart  
Stuttgart, Germany

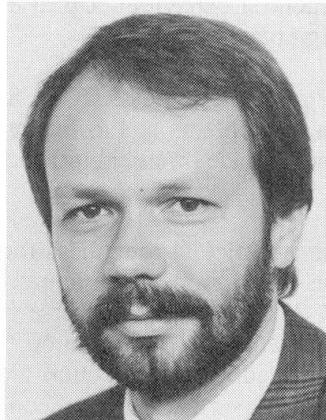

Jürgen Ruth, born 1957, obtained his civil engineering degree in 1983 at the Technical University Darmstadt, Germany. For three years he worked with a consultant, where he was especially involved in the design of railroad bridges. Since 1987 he is a Research Assistant.

### **SUMMARY**

Large buildings contain construction joints which may have a great influence on the loadbearing capacity of the structure. The design concepts of various standards for concrete structures will be presented and discussed briefly. Unfortunately, these design concepts treat the same problem in different ways. Based on a failure criteria of Mohr-Coulomb it will be shown how joints can be treated consistently in the design concept of strut-and-tie-models.

### **RÉSUMÉ**

Les grands bâtiments comportent des joints qui influencent beaucoup la capacité portante de la structure; des concepts divers de dimensionnement sont brièvement présentés puis discutés. Le critère de rupture de Mohr-Coulomb constitue la base d'une démonstration décrivant comment les joints sont considérés dans le cadre d'un dimensionnement utilisant le modèle des bielles (analogie du treillis).

### **ZUSAMMENFASSUNG**

Grössere Bauwerke beinhalten Fugen, die einen grossen Einfluss auf die Tragfähigkeit der Konstruktion ausüben können. Für Betonbauwerke werden Bemessungskonzepte verschiedener Normen vorgestellt und kurz diskutiert. Leider wird das gleiche Problem in diesen Bemessungskonzepten unterschiedlich behandelt. Auf der Grundlage eines Mohr'schen Versagenskriteriums wird aufgezeigt, wie Fugen in dem Bemessungskonzept der Stabwerkmodelle einheitlich behandelt werden.



## 1. DESCRIPTION OF THE PROBLEM

There are many structures where forces have to cross contact surfaces. In concrete structures this occurs for example at cracks or at construction joints between cast in situ or precast elements. The behaviour of the contact surfaces cannot solely be described by well-known material characteristics like the tensile and compressive strength, but also the surface condition (like smooth or rough) must be considered. Therefore an additional failure criterion for the contact surface must be defined.

In the following an attempt is made how the contact surface problems in connection with construction joints are treated in the consistent and translucent dimensioning concept of strut-and-tie-models according to Breen /B2/ and Schlaich /S1,S2/. This is desirable because contact surface problems may have an important effect on the structural behaviour. Up to now they are dealt with not systematically and partly unsufficiently in the design practice.

## 2. PRESENT DESIGN PRACTICE AND EXISTING CODES FOR CONCRETE STRUCTURES

In codes for concrete structures these problems are so far treated either as dimensioning problems for shear and normal stress in the contact surface or/and in terms of construction requirements.

### 2.1 German Standards

The German Standards /D2/ require a sufficient roughness for longitudinal joints between prefabricated parts and concrete cast in situ. The description of the appropriate surface condition is only given in a comment upon the Standards /E1/. An increased transverse reinforcement is needed, apart from a few exceptions, and the permissible shear stress is limited to 60 % of the regular value. The specialities of construction joints transverse to the loadbearing direction are specified only for prestressed structural members. Thereby a rough (or keyed) surface is a precondition, too. Additionally a value for the compression strength for the joint section is given.

### 2.2 ACI Standard 318-77

In the ACI Standard 318-77, section 11.7 /A1/ the dimensioning of construction joints is described on the basis of the shear-friction-theory which was originally developed by Birkeland /B2/ and Mast /M1/. An ultimate shear force  $V_u$  is defined for rough surfaces.

$$V_u = 1.0 A_s f_y < 0.2 f'_c A_c [N] \quad A_s : \text{total cross-sectional area of reinforcement across interface} \\ \text{or } 5.5 A_c [N] \quad f_y : \text{yield strength of reinforcement} < 420 \text{ N/mm}^2$$

Thereby rough means a clean interface which is free of laitance and roughened to a full amplitude of approximately 5 mm.

### 2.3 SIA-Standard 162

The SIA-Standard 162 /S3/ section 4 45 limits the concrete strength and steel strength of the prefabricated and connected parts.

$$\text{Concrete: } f_{c,red} = 0.35 f_{cw,min} \quad \text{Steel: } f_{y,red} = 0.80 f_y$$

According to section 6 06 2 only rough or keyed joints are permissible preferably perpendicular to the direction of the compression field. The rough joint should be realized by removing the cement-sand grout from the concrete surface.

## 3. A CONSISTENT DIMENSIONING-CONCEPT USING STRUT-AND-TIE-MODELS

### 3.1 Mathematical Description of the Loadbearing Capacity of Joints

The mathematical description of the loadbearing capacity of joints is based on the extended shear-friction-theory of Mattock /M1,M2/. It is drawn from a proposal by a FIP-Commission /F1/ supplemented by Walraven /W1/. The results are shown graphically in fig. 1.

$$\begin{aligned} \mu &: A_s/A_c \\ f_y &: \text{yield strength of} \\ &\quad \text{reinforcement} < 400 \text{ N/mm}^2 \\ \sigma_N &: \text{normal stress} \\ f_{ctk} &= 0.25 \sqrt{f_{ck}} \end{aligned}$$

$$\tau_u = K1 (f_y + \sigma_N) + K2 f_{ctk} \leq 0.25 f_{ck}$$

surf. cond.	K1	K2
very smooth	0.6	0.1
smooth	0.6	0.2
rough	0.9	0.4

Table I

The coefficient  $K_1$  is equivalent to a frictional coefficient and the term  $K_2 f_{ctk}$  corresponds to the so-called cohesion, which here is proportional to the tensile strength of the concrete. Both coefficients depend on exactly described surface conditions which are subdivided in three categories (Tab. I). By comparison with an extensive series of experiments carried out by Daschner /D1/ Walraven found out that the concept is on the safe side, if the steel strength is limited to  $f_y < 400 \text{ N/mm}^2$ . For comparison, the parabolic description of the joint behaviour according to Tassios /T1/ is shown in fig. 2.

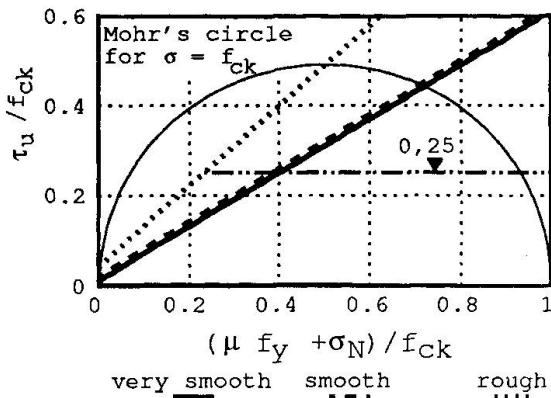


Fig. 1: acc. to FIP

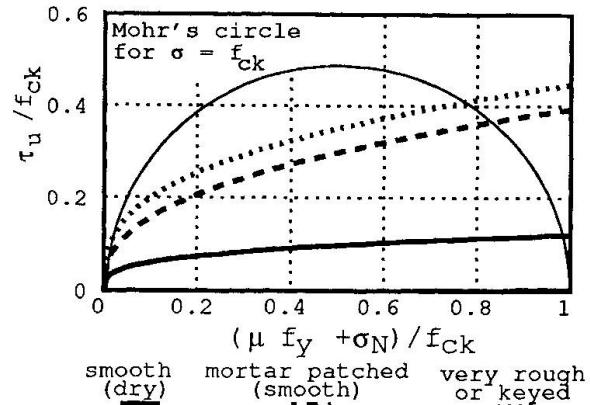


Fig. 2: acc. to Tassios

### 3.2 The Influence of a Joint on the effective Strength of a Prism

With the above given proposals the loadbearing capacity of a prism with a joint (fig. 3) is given according to Zelger and Rüsch /Z1/ and can be seen in fig. 4 and fig. 5. The diagrams clearly show that the capacity of the prism is only reduced by the joint, if the inclination of the joint exceeds a critical angle  $\alpha_{crit}$ . If the inclination is smaller than  $\alpha_{crit}$  the prism fails in concrete-compression. These dependencies can also be shown in a different way using Mohr's circle (see: Guckenberger /G1/ and Basler /B1/).

according to FIP /F1/:

$$\frac{\sigma_u}{f_c} = \frac{K_2 f_{ctk}}{f_c} \frac{1 + \tan^2 \alpha}{\tan \alpha - K_1} \leq 1$$

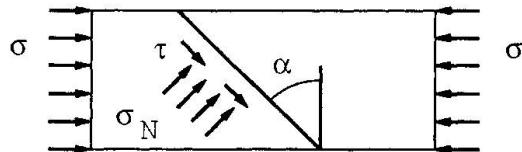


Fig. 3: prism with a joint

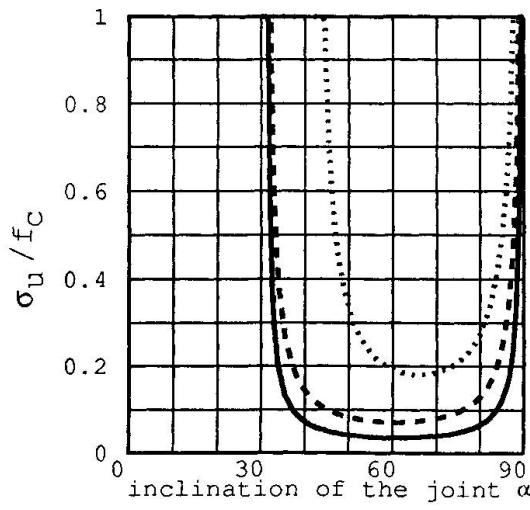


Fig. 4: acc. to FIP

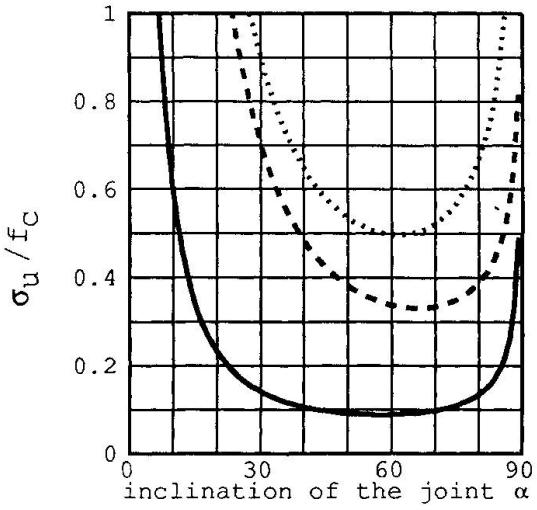


Fig. 5: acc. to Tassios



The following diagrams show in a different way some characteristics of the loadbearing behaviour of the prism. They are based on the FIP proposal, because it satisfies the demands of the structural engineer better than other proposals. Fig. 6 shows the dependence of the critical inclination on  $K_1$  and  $K_2 f_{ckt}$ . It is remarkable that the critical inclination of the joint is almost totally independent of the term  $K_2 f_{ckt}$  (cohesion). Fig. 7 shows the dependence of the minimal effective strength on  $K_1$  and  $K_2 f_{ckt}$ .

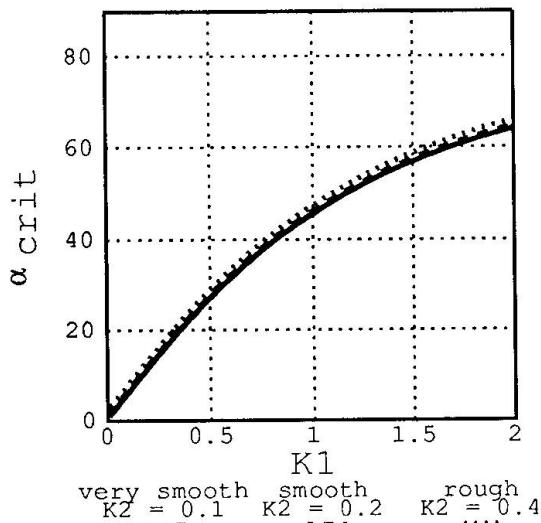


Fig. 6: crit. inclination

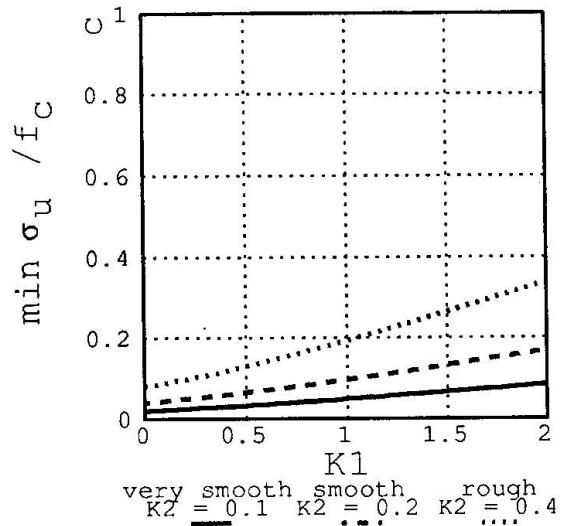


Fig. 7: minimal effective prism strength

With the above diagrams some problems of dimensioning structural members with joints can be solved directly, as e.g. for a joint in an arch bridge between the bottom edge of a column and the supporting arch.

### 3.3 Joints in the web of a Beam

In the following the influence of the joint on the ultimate shear force of a beam is explained. Two cases are considered either a longitudinal joint between a precast part and a layer of cast in situ concrete or a transverse construction joints between two stages of construction or precast elements (fig. 8). The loadbearing behaviour of the beam is described with a strut-and-tie-model. Thereby the joint influences essentially the effective strength of the compression strut. It is assumed that the effective strengths of the chords are not reduced. This leads to the conclusion that the reduction of the ultimate shear force depends mainly on the inclination of the strut - and accordingly on the transverse reinforcement - and the roughness of the joint.

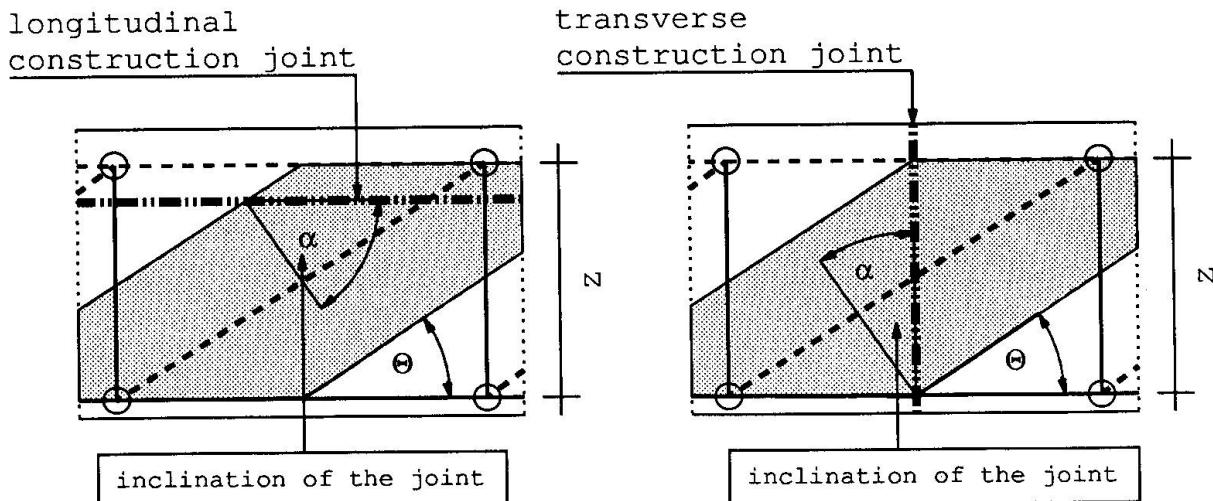


Fig. 8: strut-and-tie-model of a beam

The reduced ultimate shear force due to joint failure can be calculated as follows:

$$\frac{V_u}{b z \sigma_{cw,u}} = \frac{K2 \sin \Theta \cos \Theta (1 + \tan^2 \alpha)}{\tan \alpha - K1} \frac{f_{ctk}}{\sigma_{cw,u}} \leq 1 \quad \text{for } \alpha > \alpha_{crit}$$

Considering  $\alpha = 90^\circ - \Theta$  in case of a longitudinal joint and  $\alpha = \Theta$  in case of a transverse joint yields the curves shown in fig. 9 and fig. 10. In both cases the ultimate shear force of a beam without joints can be reached nearly if the surface is rough. However for a longitudinal joint an inclination  $45^\circ$  for the compression field and an accordingly increased tie reinforcement is required. For a transverse joint the inclination of the compression field varies between  $30^\circ$  and  $45^\circ$  as usually.

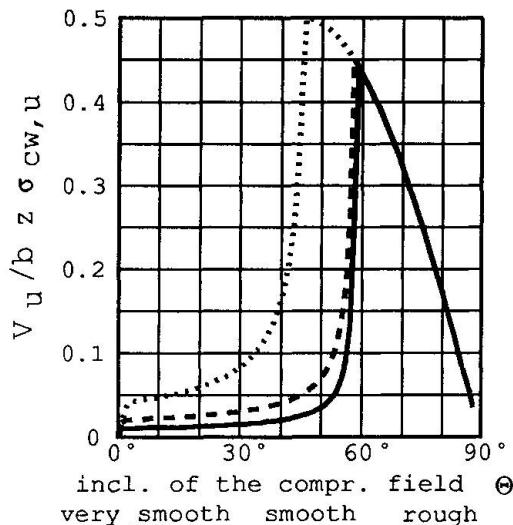


Fig. 9: Longitudinal joint

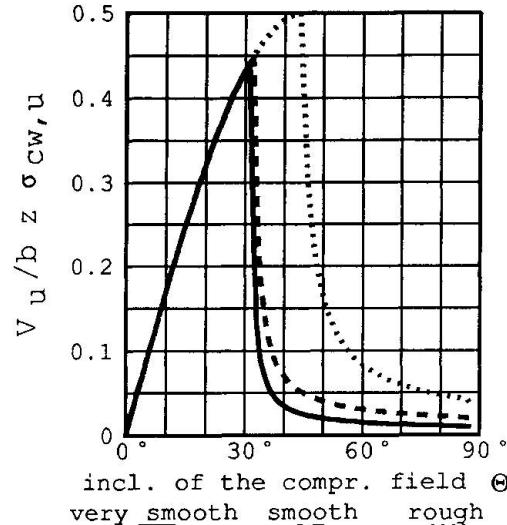


Fig. 10: Transverse joint

Fig. 12 and fig. 13 show diagrams for the necessary vertical shear reinforcement. For longitudinal joints highly increased reinforcement is required even if the joint is rough. For rough transverse joints only the maximum value for the ultimate shear force is reduced by the joint.

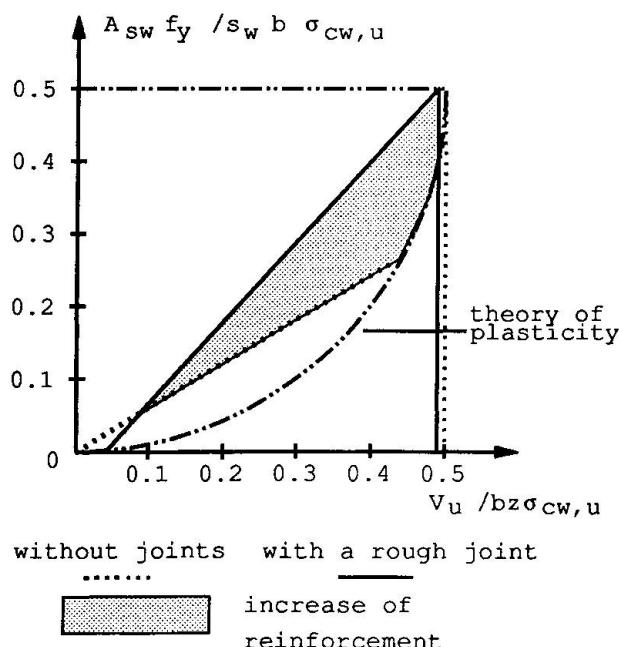


Fig. 11: Longitudinal joint

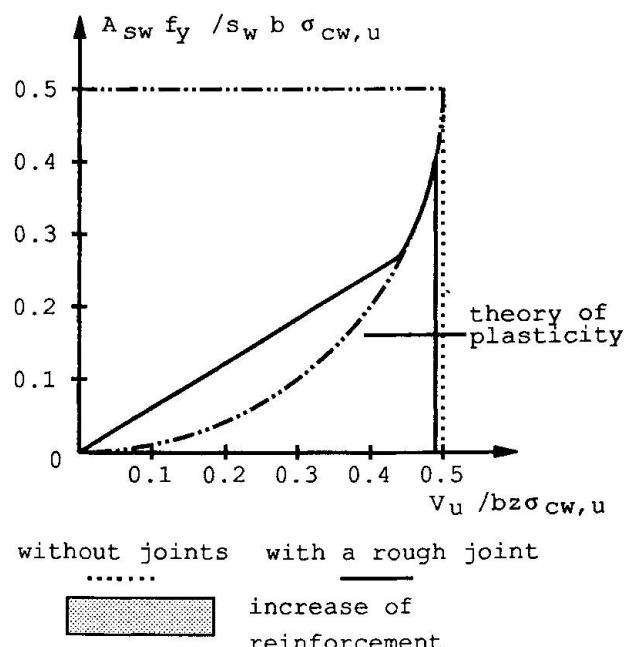


Fig. 12: Transverse joint



#### 4. SUMMARY AND PROSPECTS

It was shown that the influence of a joint on a structural concrete member can be expressed by an reduced effective strength of the struts in a strut-and-tie-model. Therefore the normally given relation between the normal stress and the ultimate shear stress of a joint must be transformed into a relation between the inclination of the joint in a strut and of its effective compressive strength. This relation depends on the roughness of the contact surface, which has to be described exactly. Reineck shows a similar approach in /R1/ concerning the influence of friction mechanisms in cracks on the ultimate strength of the web compression field. The advantage of these methods is that it becomes more obvious how a structural member with a joint or cracks works and which element will fail under ultimate load.

Prospective efforts should aim in the direction of integrating composite structures with contact surface problems between their different materials in a consistent dimensioning concept. At the moment this is unfortunately complicated by the splitting of codes according to materials which leads to different approaches for the same problem. Further types of contact surface problems will arise in future, when the advantages of combining new or unusual materials will be used to realize new kinds of structures with different and novel qualities.

#### REFERENCES:

- /A1/ ACI Standard 318-77: Building Code Requirements for Reinforced Concrete.
- /B1/ Basler, E., Witta, E.: Grundlagen für kraftschlüssige Verbindungen in der Vorfabrikation. Beton-Verlag GmbH, 2. Auflage, Düsseldorf 1967
- /B2/ Birkeland, P.W., Birkeland, H.W.: Connections in precast concrete constructions. ACI-Journal V.63, March 1966, pp.345-368
- /B3/ Breen, J.E.: Why Structural Concrete. Introductory Report, IABSE Colloquium "Structural Concrete", Stuttgart, April 1991
- /D1/ Daschner, F.: Versuche zur notwendigen Schubbewehrung zwischen Betonfertigteilen und Ortbeton. DafStb Heft 372, Berlin 1986
- /D2/ DIN-Normen 1045 und 4227 Teil1 und Teil3
- /E1/ Erläuterungen zu DIN 1045 Beton- und Stahlbeton Ausgabe Juli 1988, DafStb, Heft 400, Berlin 1989
- /F1/ FIP-Commission on Prefabrication: Shear at the interface of precast and in situ concrete. FIP-Report, Jan. 1982
- /G1/ Guckenberger, K., Daschner, F., Kupfer, H.: Segmentäre Spannbetonträger im Brückenbau. DAFStb, Heft 311, Berlin 1980
- /M1/ Mast, R.F.: Auxiliary reinforcement in concrete connections. Journal of the Structural Division, ASCE, V. 94, ST6, June 1968, p. 55-75
- /M2/ Mattock, A.H., Hawkins, N.M.: Research on shear transfer in reinforced concrete. PCI-Journal, V. 17, No.2, March-April 1972, pp. 55-75
- /M3/ Mattock, A.H.: Shear transfer in concrete having reinforcement at an angle to the shear plane. ACI-Special Publication 42, Detroit, Michigan, 1974, pp. 17-42
- /R1/ Reineck, K.H.: Consistent Modelling of Structural Concrete Members with Transverse Reinforcement Considering Strains and Cracks. IABSE Colloquium "Structural Concrete", Stuttgart, April 1991
- /S1/ Schlaich, J.: The need of consistent and translucent models. Introductory Report, IABSE Colloquium "Structural Concrete", Stuttgart, April 1991
- /S2/ Schlaich, J., Schäfer, K., Jennewein, M.: Toward a Consistent Design of Structural Concrete. PCI-Journal Vol.32, No.3, May/June 1987
- /S3/ SIA-Norm 162: Betonbauten. Ausgabe 1989
- /T1/ Tassios, T.P.: Physical and mathematical Models for RE-Design of repaired Structures
- /W1/ Walraven, J.: Über den kraftschlüssigen Verbund von Betonen unterschiedlichen Alters und unterschiedlicher Oberflächenbeschaffenheit der Verbundfuge. VDI Berichte Nr. 840, Oktober 1990
- /Z1/ Zelger, C., Rüsch, H.: Der Einfluß von Fugen auf die Festigkeit von Fertigteilschalen. Beton- und Stahlbetonbau (1961), Heft 10, S.234-237

## Reliance on Tensile Strength for Cast-in-Situ Wall-to-Wall Joints

Résistance à la traction des joints clavés de parois coulées sur place

Tragfähigkeit von Fugen in Ortbetonwänden

### Antanas KUDZYS

Prof. Dr.  
Lithuanian Academy  
Vilnius, USSR

Antanas Kudzys, Prof. Dr. Sc. Member of Lithuanian Academy, Head of Reinforced Concrete Department Vilnius Technical University. He is noted for his design projects and researches in the fields of reinforced concrete and reliability theories.

### Vytautas PAPINIGIS

Assoc. Prof.  
Vilnius Techn. Univ.  
Vilnius, USSR

Vytautas Papinigis, Associate Professor at Vilnius Technical University. He is involved in research problems of concrete strength under short-term and long-term tension. Probationer of Hannover Technical University.

### Vladimir POPOV

Assist. Prof.  
Vilnius Techn. Univ.  
Vilnius, USSR

Vladimir Popov, Assistant Professor at Vilnius Technical University. His research field belongs to problems of concrete and reinforced concrete joints and modelling in structural mechanics.

### SUMMARY

The paper considers theoretical and practical problems concerning an estimation of the complete concrete tensile deformation diagram in the analysis of the load bearing capacity of keyed joints of cast-in-situ exterior and interior walls.

### RÉSUMÉ

Cet article prend en considération les problèmes théoriques et pratiques d'une appréciation concernant le diagramme complet traction-déformation du béton, et ceci, dans le contexte de l'analyse de la capacité portante de joints clavés, appartenant à des parois intérieures et extérieures coulées sur place.

### ZUSAMMENFASSUNG

Im Aufsatz wird das theoretische und praktische Problem der Bewertung des vollständigen Dehnungsdiagramms des Betons in der Tragfähigkeitsberechnung der Monolithverzahnung der Aussen- und Innenwände besprochen.



The connections of intersection walls constructed both of cast-in-situ concrete of different nature and class (Fig. 1) and of precast concrete members can be provided by using keyed joints. The cross-shaped and wavy dividing closures of asbestos cement sheets provided a rational solution ensuring technologically simple connections between walls of buildings and constructions. A remarkable cohesion of these sheets with concrete is characteristic. Therefore it is expedient to use new types of joints for connections of cast-in-situ exterior lightweight and interior heavy concrete walls of buildings.

The experimental laboratory and site data indicate the necessity of new types joints with the division closures. The keyed joints of concrete walls lead to the economy and increase in both tolerable rigidity of the connections and stiffness of multi-storey buildings subjected to shear forces. Such forces are generated by horizontal wind or seismic actions, non-symmetrical vertical loading, shrinkage deformations, temperature gradient etc.

Shear carrying capacity of keyed joints depends on mechanical properties of wall concrete in tension. The shear strength of a key system belonging to one of wall connection members is closely related to the possibility of a redistribution of shear stresses both in a single key and among the connection keys.

Twenty four full-scale specimens of exterior and interior wall connections were tested to investigate the behavior of concrete keys and to establish a cracking resistance (a load rating) and a failure strength of keyed joints.

The shear capacity of keyed wall-to-wall joints can be determined by the following equation derived from a test analysis and modelling data

$$R = nR_1 (1 - \operatorname{tg}\alpha / \operatorname{tg}\beta) + A_s f_y \operatorname{tg}\alpha. \quad (1)$$

Here  $n$  - the number of keys in weaker wall member;  $R_1$  - shear strength of a single key;  $\operatorname{tg}\alpha$  - coefficient taking into account the shape of a crack surface and the position of a crack direction angle;  $\operatorname{tg}\beta$  - coefficient characterizing the key slope angle and the contract surface between asbestos cement sheet and concrete;  $A_s$  - cross-sectional area of horizontal reinforcing bars;  $f_y$  - steel yield strength.

The shear strength of a concrete key

$$R_1 = \alpha A_c f_v, \quad (2)$$

where  $\alpha$  - coefficient which helps to evaluate the influence of crack location on the cross-sectional area  $A_c$  of shear key;  $f_v$  - concrete shear strength.

The value of the strength  $f_v$  can be calculated on the basis of the empirical equation

$$f_v = \xi_v \sqrt{f_c f_{ct}}, \quad (3)$$

where  $\xi_v = 0,7$  for heavy and  $\xi_v = 0,5$  for lightweight concrete;

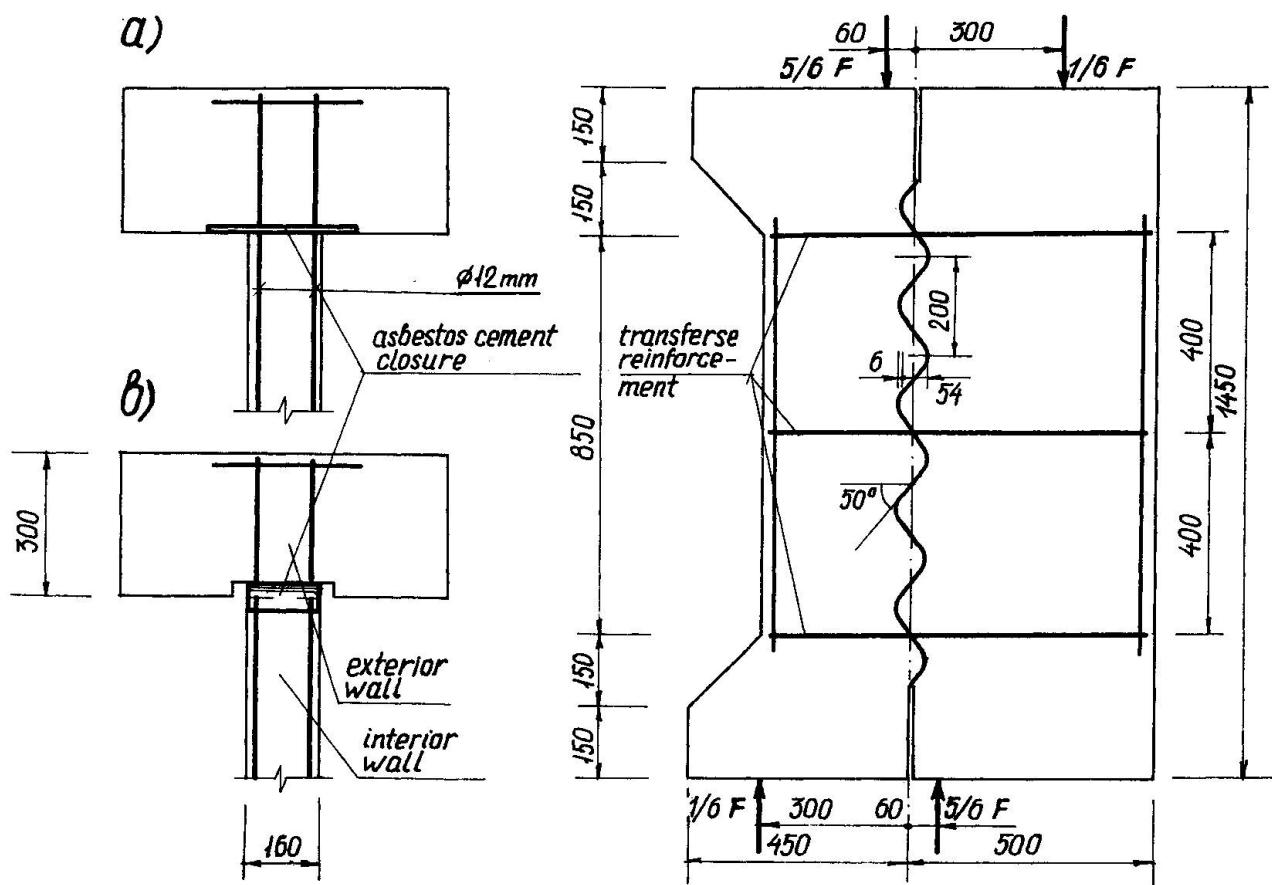


Fig. 1. Test specimens and test loading diagram of plain (a) and keyed (b) joints (dimensions in mm)

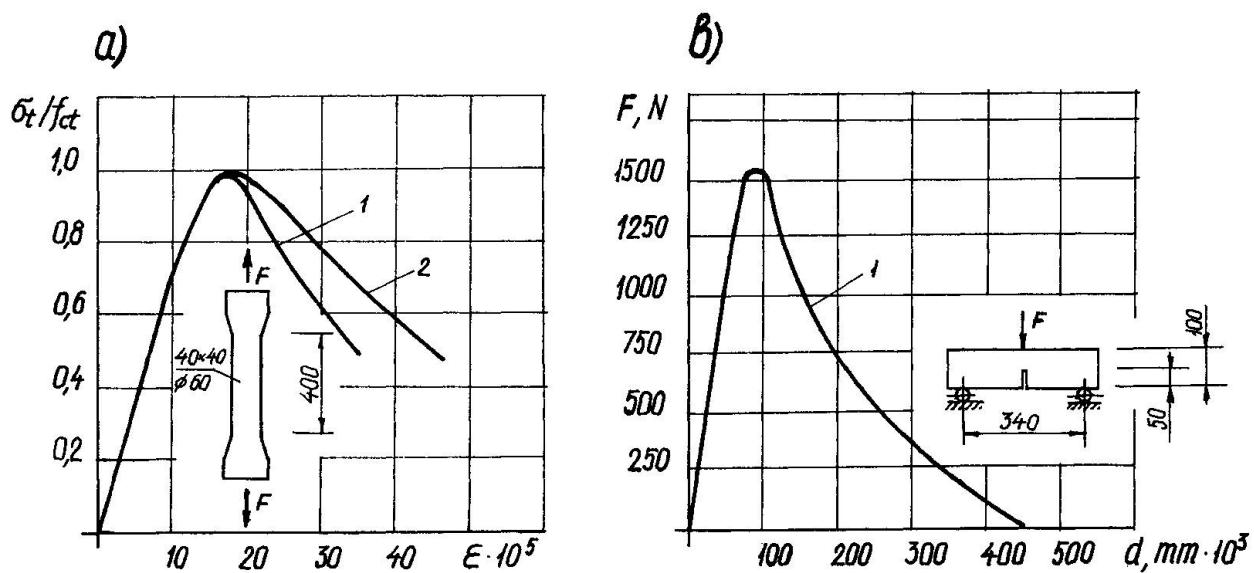


Fig. 2. A tensile (a) and a stable bending (b) tests of concrete (1) and reinforced concrete (2) specimens



$f_c$  and  $f_{ct}$  - concrete compressive and tensile strength, respectively.

According to the theory of plasticity [1] the shear strength of concrete can be assumed as

$$f_v = \sqrt{\frac{\nu_{ct}}{\nu_c} f_c f_{ct} (\nu_c - 4 \frac{\nu_{ct}}{\nu_c} \frac{f_{ct}}{f_c})} , \quad (4)$$

where  $\nu_{ct}$  and  $\nu_c$  - are the so called effectiveness factors for concrete in tension and compression, respectively.

The values of factors  $\nu_{ct}$  and  $\nu_c$  can be obtained by using the stress-deformation curves not only with ascending but also with descending branches, i.e. with the help of intensity of released energy of tensile concrete in fracture  $G_1$ .

A non-linearity of the post-peak curve contributes substantially to the toughness and ductility of tensile concrete. An investigation of fracture mechanism of tensile concrete gives a possibility to understand the behavior of keyed joints in shear. Moreover, it helps to conceive the indispensable conditions leading to instantaneous cracking and collapsing of the keyed joints.

A tensile stress concentration in concrete due to internal cracking is noticed. If concrete is a sufficiently tough material the stress concentration does not lead to a sudden brittle failure of a single key and to a decrease of carrying capacity of wall-to-wall joints. It may be explained by the fact that the toughness property helps to absorb the released energy of cracking concrete. Owing to it a distribution of load effects occurs in the key system.

Twenty test sets were used to investigate the main mechanical and energetical properties of tensile loaded concrete C15...C20. Both notched and un-notched tensile and bending specimens were tested to study the tension behavior of concrete (Fig. 2).

According to the recommendation [2] the failure mechanism of tensile concrete may be described by two parameters (Table 1). The critical coefficient of stress intensity

$$k_1 = \sqrt{\pi l} f(\zeta) , \quad (5)$$




where  $f(\zeta)$  - function, characterizing a specimen configuration and loading technique.

The intensity of released energy may be evaluated by the equation

$$G_1 = k_1^2 / E_c , \quad (6)$$

where  $k_1$  - coefficient by (5);  $E_c$  - modulus of elasticity of concrete. The intensity  $G_1$  by (6) allows to calculate the values of factors  $\nu_{ct}$ ,  $\nu_c$  and concrete shear strength  $f_v$  by (4) more accurately.

Table 1  
Parameters of fracture criterion of concrete in tension

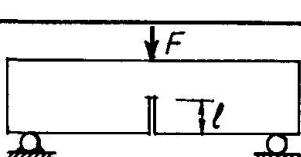Loading technique	Loading diagram	$k_1$ , MN/m <sup>3/2</sup>	$G_1$ , N/m
Centric tension		1,02	52
Centric tension		1,19	62,8
Three point bending		1,08	51,6

#### REFERENCES

1. Nielsen M.P. Limit Analysis and Concrete Plasticity. Prentice-Hall, Inc., Englewood Cliffs. New Jersey, 07632. 1982. 420 pp.
2. Siratory M., Miosy T., Macusita Ch., Vytchislitelnaia tekhnika razrushenia. Moskva. Mir. 1986. 336 pp.

Leere Seite  
Blank page  
Page vide