**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte

**Band:** 64 (1991)

**Artikel:** Railway bridges of corrosion resistant steel in Japan

Autor: Abe, Hidehiko / Sakamoto, Kenji

**DOI:** https://doi.org/10.5169/seals-49335

# Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Mehr erfahren

## **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. En savoir plus

#### Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. Find out more

**Download PDF: 22.11.2025** 

ETH-Bibliothek Zürich, E-Periodica, https://www.e-periodica.ch



# Railway Bridges of Corrosion Resistant Steel in Japan

Ponts ferroviaires en acier résistant à la corrosion au Japon Eisenbahnbrücken aus korrosionsbeständigem Stahl in Japan

#### Hidehiko ABE

Professor Univ. of Utsunomiya Utsunomiya, Japan

# Kenji SAKAMOTO

Senior Engineer Technical Inst. of Railways Tokyo, Japan

## 1. INTRODUCTION

A considerable number of railway bridges have been constructed of corrosion resistant steel, so-called "weathering steel", without painting in these ten years



Photo 1. Third Okawa Bridge

in Japan (say, 70 sets of span and 11.742 tons in total). Some of them were furnished with test specimens for future observation. type of bridge has been applied to only an open type bridge, where structural members are well exposed to rainfall and located in rural areas where air is not polluted. Such conditions are favorable to formation of the stable patina, an anticorrosive surface layer, which is essential to the protection of steel from corrosion. At present, all the brides are

generally in a very satisfactory condition and prove to be successful.

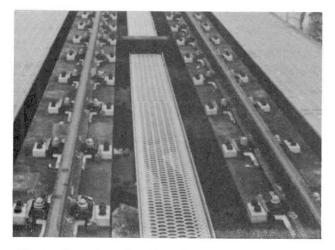


Photo 2. Track structure

# 2. STRUCTURAL DETAILS

The structural details of the weathering steel bridges for railways in Japan are so modified, as to fit the use of weathering steel without painting. They have been carefully designed, so that water and dust staying on the structural members should be minimized as shown in Fig. 1. Such considerations will be useful also to ordinary painted bridges for better durability. In Third Okawa Bridge (Photo 1), for instance, 1) The upper surfaces of horizontal mem-

bers, even the flanges of stringer and

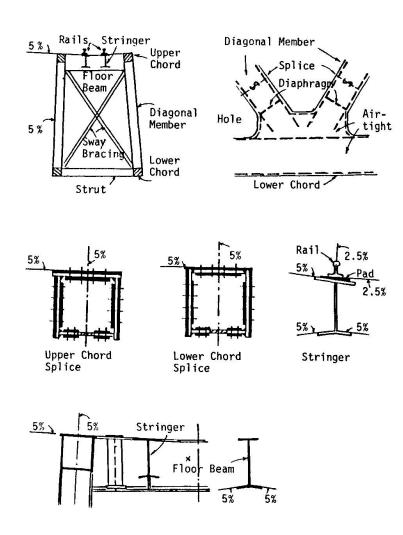


Fig.1. Examples of structural details

floor beam and chord members are inclined by 5%.

 Larger horizontal gusset plates are provided with large openings.

3) The chord members and the panel point portions are closed for air-tightness, except for their splice portions, the inside of which is coated with tar - epoxy

resin paint.

4) The rail track structure is different from an ordinary one with wood sleepers. Since the flange surface in contact with the sleepers is usually most severely damaged by corrosion, the rails are fastened to the flanges of the steel girders with a special device instead of wood ties as shown in Photo 2. It is drastically effective in reduction of maintenance work for the track as well as the bridge structure. And

5) The edge of the upper side of concrete pier is raised and water is gathered to the drain pipe, so that rainwater washing the bridge may not stain the flank of pier, as

seen in Photo 1.

## EXAMPLE OF OBSERVATION

Five years after Third Okawa Bridge was erected and opened to traffic, the bridge structure and the test specimens installed nearby were closely examined, by the visual inspection, X-ray test, Ferroxyl test, etc. In addition, some bolts used in the bridge were removed to see the state of bolts themselves and the inside of bolt holes. The summary of the results is as follows; 1) As a whole, the condition is so good, that reduction in the plate thickness can not be measured.2) According to Ferroxyl test on various parts of the bridge and X-ray test on the exposed specimens, the stable patina has been better formed on the surface has been directly exposed to rain-fall and dried immediately. From this of view, the upper surface is most favorable, if water does not stay, and followed by the vertical surface on a sunny side. In case water is apt to stay on horizontal surface, however, the patina is not easily formed. On the surface of underside, the patina is seldom formed and slight corrosion pits are recognized, the rate of corrsion is very slow if the environmental atmosphere is not humid, and 3) Some of the bolt holes were filled with water. Though it has resulted in no appreciable detrimental effect as yet, it may cause the corrosion of the bolts in the future. It will, therefore, be necessary to keep them water-tight.