

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 64 (1991)

Artikel: Influence of steel bars on structural behaviour of reinforced concrete
Autor: Bosco, Crescentino / Debernardi, Pier Giorgio
DOI: <https://doi.org/10.5169/seals-49337>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 10.08.2025

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>



Influence of Steel Bars on Structural Behaviour of Reinforced Concrete

Influence des barres d'armature sur le comportement du béton structural

Einfluss neuer Bewehrungsstäbe auf das Tragwerksverhalten

Crescentino BOSCO

Assist. Prof.
Politecnico di Torino
Torino, Italy

Pier Giorgio DEBERNARDI

Assoc. Prof.
Politecnico di Torino
Torino, Italy

1. INTRODUCTION

Due to the evolution of manufacturing processes, reinforcing steel bars possessing new mechanical characteristics, different from those of traditional ones, are now available on the market. Therefore Model Code 90 and Eurocode 2 take into account two classes of ductility, related to characteristic elongation at maximum load, and characteristic tensile strength to yield stress ratio (class A with $\epsilon_{uk} \geq 5\%$, $(f_t/f_y)_k \geq 1.08$ and class B with $\epsilon_{uk} \geq 2.5\%$, $(f_t/f_y)_k \geq 1.05$).

The different ductility characteristics, greatly affect the structural behaviour in the plastic range.

2. TESTS ON STEEL BARS.

Experimental tests have been carried out by strain controlled procedure on two types of high bond bars with 12mm diameter:

Measured charact.	Steel class A			Steel class B		
	Mean value	Stand dev.	Char. value	Mean value	Stand dev.	Char. value
$f_y(N/mm^2)$	587	24.14	540	596	6.22	583
$f_t(N/mm^2)$	672	19.94	633	641	4.12	633
f_t/f_y	1.150	0.021	1.108	1.076	0.008	1.061
$A_s (\%)$	17.85	1.58	14.74	15.10	1.08	12.97
$A_{10} (\%)$	12.58	1.27	10.08	10.03	0.91	8.24
$\epsilon_u(a)(\%)$	7.00	0.98	5.06	4.18	0.76	2.68
$\epsilon_u(b)(\%)$	6.29	0.81	4.69	4.47	0.85	2.80
$\epsilon_u(c)(\%)$	7.66	1.21	5.27	5.28	1.09	3.13

Table 1 Characteristics of steels

- hot rolled bars, which can be classified as class A (30 specimens);
- cold rolled bars, which can be classified as class B (50 specimens).

The determination of ϵ_u has been performed in three ways:
 (a) by means of extensometer;
 (b) by measuring the deformation after failure outside the necking zone and away from the grips (adding the elastic deformation f_t/E);
 (c) by measuring the deformation after failure of a 5 diameter (A_5) and a 10 diameter (A_{10}) base, including the necking zone, as follows:

$$\epsilon_u = 2A_{10} - A_5 + f_t/E.$$

3. TESTS ON REINFORCED CONCRETE BEAMS.

Plastic rotation capacity of the beams was taken as a parameter to evaluate the influence of steel type. Midspan deflection controlled tests were carried out on 28 simply supported r.c. beams with various steel percentages, loaded by one load applied at midspan or by three symmetrical loads (Fig. 1). Beam depth was 400mm for 13 specimens and 600mm for 15 specimens; depth to width ratio was two whereas the span was 4000mm and 6000mm, respectively.

Plastic rotation, θ_p , is obtained by integration, along the plastic zone, l_p , of the difference between mean curvature $1/r_m$ and that obtained at the yield limit of steel, $1/r_{my}$, according to:

$$\theta_p = \int_{l_p} (1/r_m - 1/r_{my}) dz$$

Bending moment versus plastic rotation curves, referred to the beams with 600mm of depth, are plotted in Fig. 2. Total plastic rotations, evaluated at 90% of the maximum bending moment in the descending branch of the moment-rotation diagram, are reported in Fig. 3 versus the x/d ratio, x being the compressive depth calculated at ultimate limit state assuming the design values for materials and d being the effective depth.

The existence of two branches, theoretically given, was confirmed by the tests performed so far. These branches, qualitatively shown in Fig. 3, depend on steel class, beam depth and form of bending moment diagram.

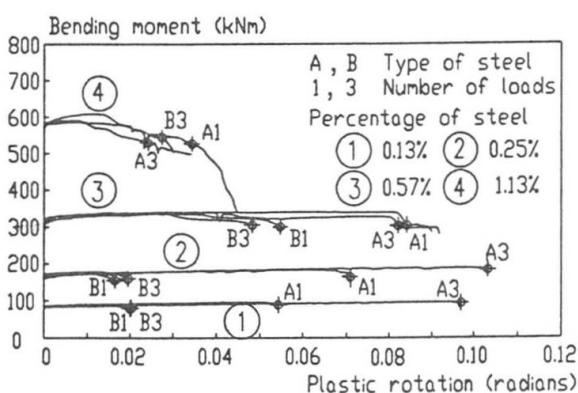


Fig. 2 Bending moment versus plastic rotation, varying the steel percentage, for beams with depth of 600mm

4. CONCLUSIONS

Compared to the traditional reinforcing steel bars the $(f_t/f_y)_k$ value requested by European Codes seems significantly reduced. As a consequence a reduced structural ductility can be observed, in particular when low percentages of class B steel are used. This behaviour may be significantly unfavorable in presence of imposed deformations (e.g. settlement of supports) and can reduce the possibilities of load effect redistribution.

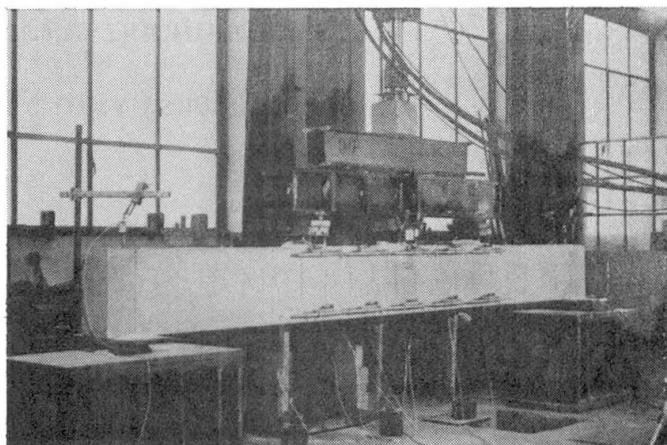


Fig. 1 Testing apparatus for three symmetrical loads

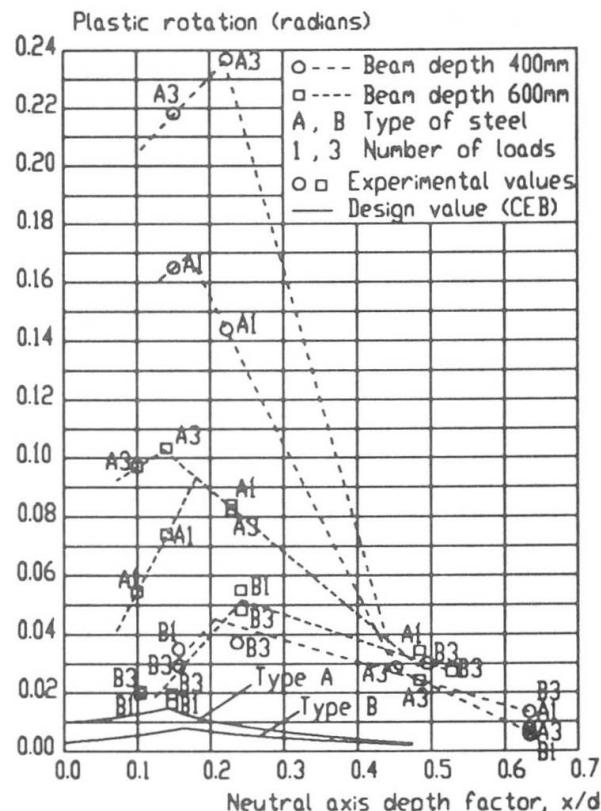


Fig. 3 Total rotation versus x/d ratio