

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 64 (1991)

Artikel: Shear strength of high strength concrete beams
Autor: Fang, I-Kuang / Horng, Muh-Tong / Pong, Sang-Chung
DOI: <https://doi.org/10.5169/seals-49339>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 12.03.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Shear Strength of High Strength Concrete Beams

Cisaillement de poutres en béton armé à hautes performances

Schubtragfähigkeit hochfester Betonbalken

I-Kuang FANG

Assoc. Professor
Nat. Cheng Kung Univ.
Taiwan, China

Muh-Tong HORNG

Former Grad. Assit.
Nat. Cheng Kung Univ.
Taiwan, China

Sang-Chung POUNG

Struct. Eng.
Pacific Eng. & Const. Ltd.
Taiwan, China

1. INTRODUCTION

The primary objective of this study is to investigate the shear strength of high strength concrete beams with and without stirrups. Thirty-three beams, of which twelve were without stirrups, having compressive strength in the range of 64 MPa to 90 MPa were tested. All specimens were 200 x 300 mm in cross section. The main variables considered were concrete strength, shear span to effective depth ratio (a/d), and the amount of stirrups ($\rho_v f_y$). The beams were tested by two point loadings symmetric about midspan as shown in Fig. 1. The a/d used were 2.0, 2.5, 3.0, and 3.5 respectively. The amount of stirrups designed were 0.5, 0.75, and 1.0 times the estimated V_{cr} . In the analytical study, the effectiveness factors of high strength concrete beams, according to the test results of authors and other investigators, were calculated based on the theory derived by M. P. Nielsen.

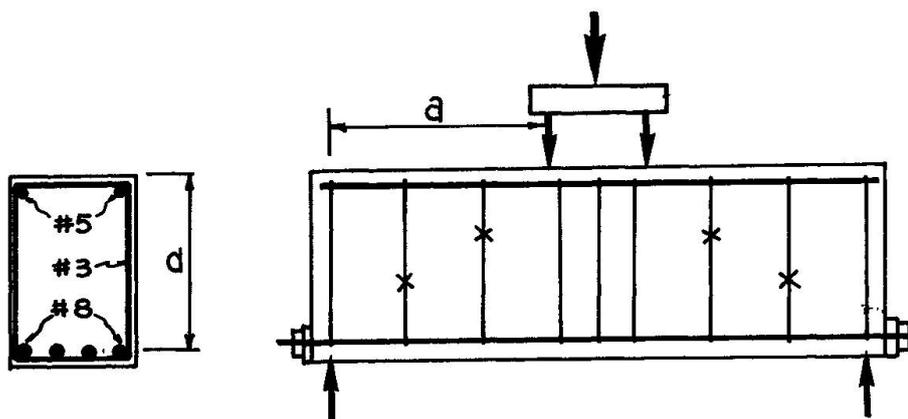


Fig. 1 Test specimen and loading arrangement

2. MATERIALS, SPECIMEN, AND MEASUREMENTS

The cement used was ordinary portland cement. River sand with F.M. of 3.0 and crushed stone with maximum size of 9 mm were used. Two mix proportions of high strength concrete, having water cement ratio of 0.26, were prepared in the laboratory. The first mix for those having compressive strength up to 70 MPa has a cement con-

tent of 600 Kg/m^3 . In the second mix, 5 per cent of cement by weight was replaced by silica fume to improve the strength. The volumetric ratio of fine to total aggregate (S/a) was 0.37. At least five $10 \times 20 \text{ cm}$ cylinders from the same batch of beam were cast to determine the compressive strength. The cylinders and beams were covered by wet burlap until test. The strains of stirrups and longitudinal steels, deflections at midspan and quarter span were monitored throughout the test. The load-strain relationship of concrete strut was measured using clip-on gage with both ends attached to the appropriate holes drilled prior to the start of test.

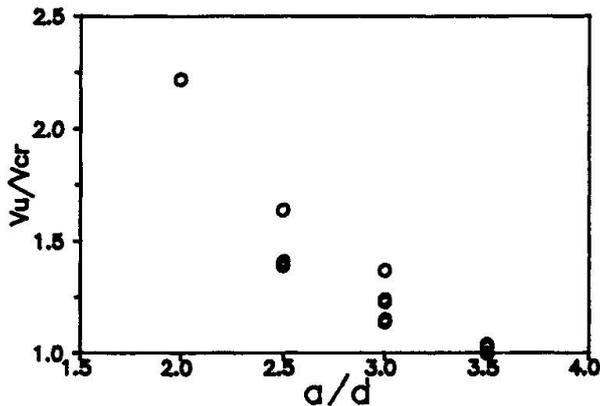


Fig. 2 Measured V_u/V_{cr} of beams without stirrups

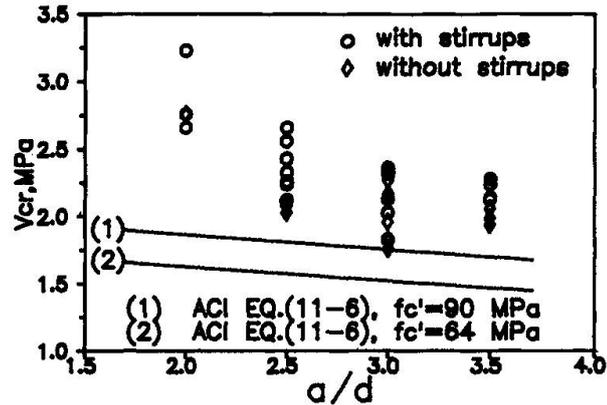


Fig. 3 Comparisons of V_{cr} measured vs. predicted

3. CONCLUSIONS

Some conclusions were drawn based on the test results:

1. Most of the beams without stirrups failed in shear - tension while those with stirrups failed in shear - compression.
2. The ratio of measured ultimated shear strength (V_u) to inclined shear strength (V_{cr}) for various a/d of beams without stirrups is shown in Fig. 2.
3. The inclined shear strength is slightly higher for beams with stirrups. The shear strength contribution of concrete predicted by current design provision (1989 AASHTO or ACI 318-89) is still conservative as shown in Fig. 3.
4. For the same a/d , the shear strength contribution of stirrups is more significant for beams with lower $p_v f_y$.
5. The effectiveness factors of high strength concrete beams without stirrups vary from 0.2 to 0.4, while those with stirrups vary from 0.4 to 0.6.