

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 67 (1993)  
  
**Artikel:** Remaining service life of a riveted railway bridge  
**Autor:** Brühwiler, Eugene / Kunz, Peter  
**DOI:** <https://doi.org/10.5169/seals-51397>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**


The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 05.09.2025

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**


# **Remaining Service Life of a Riveted Railway Bridge** **Durée de vie restante d'un pont-rail riveté** **Restnutzungsdauer einer genieteten Eisenbahnbrücke**

**Eugene BRÜHWILER**  
 Dr. Eng.  
 Swiss Federal Railways  
 Zurich, Switzerland

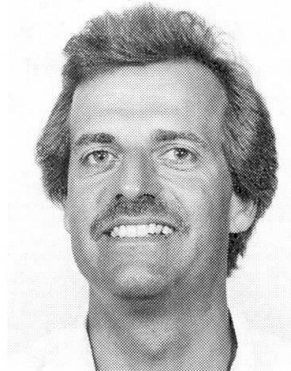

Eugene Brühwiler, born 1958, received his civil engineering and doctoral degree from the Federal Institute of Technology in Zurich and Lausanne. Since 1990, after a post-doctorate at the University of Colorado, Boulder (USA), he is involved in the evaluation of the remaining service life of bridges for the Swiss Federal Railways.

**Peter KUNZ**  
 Research Associate  
 Swiss Fed. Inst. of Technology  
 Lausanne, Switzerland

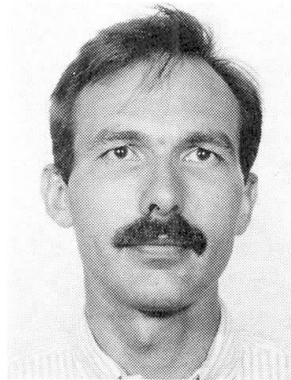

Peter Kunz, born 1959, graduated from the Federal Institute of Technology in Zurich and obtained his doctoral degree at the Federal Institute of Technology in Lausanne. He works in the fields of fatigue and evaluation of existing bridges at ICOM (Steel Structures).

## **SUMMARY**

The remaining service life of a riveted wrought-iron bridge from the last century is assessed. The case study concentrates on the application of probabilistic concepts for evaluating fatigue safety. The theoretical studies are complemented by strain measurements on the most fatigue critical members and by a thorough visual bridge inspection. Based on the results of this study, allowable rail traffic load and optimum inspection intervals are established.

## **RÉSUMÉ**

La durée de vie restante d'un pont-rail riveté en fer-puudlé du siècle passé est évaluée. L'étude se concentre sur l'application de méthodes probabilistes pour vérifier la sécurité à la fatigue. Ces études théoriques sont complétées par des mesures d'élongation sur des éléments de pont les plus critiques concernant la fatigue et par une inspection visuelle du pont. Sur la base des résultats de cette étude, la charge de trafic admissible et les intervalles d'inspection sont établis.

## **ZUSAMMENFASSUNG**

Die Restnutzungsdauer einer genieteten, schweisseisernen Eisenbahnbrücke aus dem letzten Jahrhundert wird untersucht. Die Fallstudie konzentriert sich auf die Anwendung probabilistischer Methoden für die Ermittlung der Ermüdungssicherheit. Die theoretischen Studien werden ergänzt mit Dehnungsmessungen an ermüdungskritischen Bauteilen und einer visuellen Inspektion. Basierend auf den Ergebnissen dieser Studie werden zulässige Bahnlasten und optimale Inspektionsintervalle festgelegt.



## 1 INTRODUCTION

Riveted bridges were built until the 1950s. There are thousands of riveted bridges around the world which are still in service. Most old bridges have been restricted to reduced permissible loads or repaired; critical elements have been reinforced or even replaced. Some bridges are subjected to more severe loading than was envisaged during their design due to increased traffic and higher axle loads. Economically, it is not possible nor justified to replace all bridges when they reach their "design lives". Often there is a considerable reserve and a remaining service life may be justified provided that inspection guidelines are followed.

This paper deals with the investigation of the reliability and remaining service life of a 118 year-old bridge on a branch railway line. Standard engineering methods revealed various bridge members to be fatigue critical. Since fracture of a chord member could result in collapse of the bridge, a severe load restriction was imposed on the bridge. This load restriction hampered the freight service on the line resulting in substantial financial loss. As a consequence, a thorough investigation of the structural reliability was conducted applying the method for evaluating the fatigue safety as developed in [1] and summarized in a companion paper [2].

## 2 DESCRIPTION OF THE BRIDGE

The investigated bridge crosses the Rhine river in Northern Switzerland near Lake Constance. It was built in 1875 and comprises riveted wrought iron members. The straight through truss bridge is a continuous girder bridge over four spans with a total length of 254 m (Fig. 1). The two main girders are of a truss-type construction with parallel chords and cross-wise diagonals. The single track is not ballasted; the timber sleepers are fixed directly to the stringers.

The bridge structure has been strengthened several times to allow for higher traffic loads. At the end of the last century, all major elements of the bridge were reinforced. In 1936, the stringers were strengthened for a second time, and in 1964 several truss nodes of the main girders were reinforced using high-strength bolts. Apart from some local corrosion, the present state of the bridge structure is satisfactory.

From 1875 until 1968, a mixed freight and passenger traffic of about 25 trains per day was crossing the bridge. Since 1969, this branch line has been exclusively in service for a daily traffic of 15 freight trains. To date, a total of 850'000 trains have crossed the bridge which is a moderate traffic compared to main lines with a daily traffic of about 120 trains.

## 3 LOAD CARRYING CAPACITY

A structural analysis is performed first to determine the load carrying capacity of the bridge. The action effect  $S$  is calculated using actions and load factors according to the Code SIA 160 [3] with the load model corresponding to UIC 702 [4]. The resistance  $R$  for wrought iron is chosen based on [5, 6, 7] which include test results for wrought iron

specimens from bridges built in Switzerland in the last century. The load carrying capacity is expressed by

$$\mu = \frac{R/\gamma_R}{S} \quad (1)$$

$\mu$  : load carrying capacity ratio  
 $R$  : resistance  
 $\gamma_R$  : resistance factor (=1.20)  
 $S$  : action effect

For  $\mu > 1$ , the investigated element fulfills the structural safety required by SIA Code. For  $\mu < 1$ , the load carrying capacity in terms of admissible rail traffic load is established. The structural analysis reveals that the main girders are the governing elements regarding load carrying capacity of the bridge. The minimum value for  $\mu$ , equal to 0.80, is obtained for the top chord members over the piers.

## 4 FATIGUE SAFETY

### 4.1 Proceeding in stages

The fatigue safety is verified using a method described in [1], proceeding in stages with increasing level of sophistication:

1. Simplified deterministic method (chap. 4.2)
2. Simplified probabilistic method (chap. 4.3)
3. Inspection intervals (chap. 4.4)
4. Detailed probabilistic method (chap. 4.5)

The aim of the first stage is to identify the fatigue critical members of the structure. The probability of failure  $p_f$  due to fatigue is calculated in stages 2 and 4. The probability of crack detection  $\bar{p}(cd)$  during inspection is evaluated in stage 3, and subsequently linked to  $p_f$  to obtain the probability of rupture  $p_{rupt}$ :

$$p_{rupt} = p_f \cdot [1 - \bar{p}(cd)] \quad (2)$$

$p_{rupt}$  : probability of rupture  
 $p_f$  : probability of failure  
 $\bar{p}(cd)$  : probability of crack detection in a construction detail

The probability of rupture can also be expressed by means of the reliability index  $\beta_{rupt}$  according to the standard normal distribution. Finally the reliability of a structural element is compared to the target value  $\beta_t$ :

$$\beta_{rupt} > \beta_t \quad (3)$$

$\beta_{rupt}$  : reliability index with respect to rupture  
 $\beta_t$  : target reliability index





The target value  $\beta_t$  for fatigue safety is adopted based on proved values assumed in the design of structures where a reliability index of 4.7 is often used; this corresponds to a probability of rupture of about  $10^{-6}$  per year. Assuming a design life of 100 years,  $p_t$  drops to  $10^{-4}$  or  $\beta_t = 3.7$  over the entire service life of the structure. The probability of rupture due to fatigue should not be larger than structural safety. Consequently, a target value  $\beta_t = 3.7$  is considered in this study for the total collapse of the structure resulting from fatigue failure of the detail being assessed.

## 4.2 Simplified deterministic method

The fatigue safety of all bridge members is checked by the following ratio:

$$v_{fat} = \frac{\Delta\sigma_C / \gamma_{fat}}{\Delta\sigma_e} \quad (4)$$

with 
$$\Delta\sigma_e = \alpha_{SIA} \cdot \alpha_N \cdot \Delta\sigma(\Phi \cdot Q_{fat}) \quad (5)$$

- $v_{fat}$  : fatigue safety ratio
- $\Delta\sigma_C$  : fatigue resistance to  $2 \cdot 10^6$  cycles (= 67 N/mm<sup>2</sup>) [5, 7, 8]
- $\Delta\sigma_e$  : fatigue load effect referred at  $2 \cdot 10^6$  cycles
- $\gamma_{fat}$  : fatigue resistance factor
- $\alpha_{SIA}$  : correction factor from the SIA Code 161
- $\alpha_N$  : correction factor taking into account the number of trains in the past [1]
- $\Delta\sigma(\Phi \cdot Q_{fat})$ : stress difference due to the fatigue load defined by UIC (International Union of Railways) multiplied by the dynamic factor

The resistance factor  $\gamma_{fat}$  is adopted to obtain a reliability index  $\beta_t$  of 3.7 [1]. For redundant details causing local failure,  $\gamma_{fat} = 1.20$  is chosen, and for elements leading to total collapse of the structure,  $\gamma_{fat} = 1.34$  is considered.

Based on this deterministic method, the bridge members are compared, and a ranked list identifying fatigue critical bridge details is established. Details with  $v_{fat} < 1$  require further investigation and inspection. Fatigue safety is verified if  $v_{fat} > 1$ .

The lowest  $v_{fat}$ -values are calculated for truss elements of the main girders. This is an uncommon result because frequently the stringers are the most fatigue critical elements of old bridges with non-ballasted track. This result is explained by the various strengthening measures; stringers and cross girders were reinforced more than the main girders.

Due to the continuity of the bridge over four spans, the influence line for the chord members (Fig. 4) shows both high compressive and tensile stresses at the zero-moment locations. The fatigue action is thus greater than the action effect that was considered for structural safety during design and strengthening. Consequently, the simplified deterministic method identifies the chord members at zero-moment locations between the nodes 7 and 8, 12 and 13 as well as 19 and 20 as the most fatigue critical members of the main girders (Fig. 1).

The minimum value for  $v_{fat}$  ( $= 0.69$ ) considering 850'000 trains is calculated for chord member 18/19. This is considerably smaller than 1, and a more thorough investigation based on probabilistic concepts is therefore performed.

### 4.3 Simplified probabilistic method

The reliability index for fatigue failure of a bridge member is evaluated as follows:

$$\beta_t = \frac{m_R - m_S(N_{fut})}{\sqrt{s_R^2 + s_S^2}} \quad (6)$$

- $m_R$  : mean of the fatigue strength ( $= \log \Delta \sigma_C + 2 \cdot s_R$ )
- $m_S(N_{fut})$  : mean of the fatigue load effect as a function of the number of future trains  $N_{fut}$
- $s_R$  : standard deviation of the fatigue strength ( $= 0.11$ )
- $s_S$  : standard deviation of the fatigue load effect ( $= 0.04$ )

The background and the assumptions as well as the results and the correction factors needed to calculate  $m_S$  are presented and discussed in [1, 2].

The reliability index  $\beta_f$  as a function of the number of future trains  $N_{fut}$  is calculated. The probability of crack detection due to inspections is not considered, thus  $\bar{p}(cd) = 0$ ; and from equation (2) follows:  $\beta_{rupt} = \beta_f$ . The result is shown in Figure 2 with  $N_{fut}$  represented on a log-scale.

The reliability index is now compared to the target value  $\beta_t = 3.7$ . The calculated  $\beta$ -value of chord members 18/19 is smaller than  $\beta_t$ ; a more detailed analysis is necessary. There are two ways to influence the calculated reliability index:

- (1) to optimise the **inspection intervals**, considering the probability of crack detection, and
- (2) to refine the assumptions and calculate  $p_f$  using a **detailed probabilistic method**.

### 4.4 Inspection intervals

By a fracture mechanics analysis, the critical crack length of the most likely crack in chord member 18/19 is calculated using the R6-method [9]. Assuming fracture toughness values  $K_{IC}$  of 1500 N/mm<sup>3/2</sup> and 2000 N/mm<sup>3/2</sup>, critical crack sizes  $a_c$  of 70 and 100 mm respectively are calculated. Subsequently, the probability of detecting a crack shorter than the critical crack is assessed. For this, the relation between the probability of crack detection and visible crack length must be known for steel bridges. Due to the lack of relevant information, an estimate based on literature regarding offshore structures is adopted [1].

Figure 3 shows the probability of crack detection  $\bar{p}(cd)$  as a function of the number of trains between two inspections  $N_{p,insp}$ . Inspection intervals can be fixed; for example for



$\bar{p}(\text{cd}) = 0.95$ , the chord member must be inspected after every 17'000 trains. Putting  $\bar{p}(\text{cd})$  equal to 0.95 in equation (2) a value of 3.3 is obtained for  $\beta_{\text{rupt}}$  for the present state, which is still smaller than the target value (Fig. 2).

#### 4.5 Detailed probabilistic method

For the detailed probabilistic analysis, refined rail traffic models for the past and future are needed. The rail traffic model in the past is based on statistical data provided by the Swiss Federal Railways regarding the number of trains and towed load. The rail traffic model for the future considers the expected freight traffic on this line.

The calculated reliability index as a function of the number of future trains is shown in Figure 2.  $\beta$  is equal to 3.4 for  $N_{\text{fut}} = 150'000$ . Fixing the inspection intervals so as to give a 95 % probability of crack detection, a reliability index  $\beta_{\text{rupt}}$  of 4.15 is obtained using equation (2), which is greater than the target value  $\beta_t$  of 3.7. Fatigue safety could also be verified for even more trains; yet the bridge owner is primarily interested in the reliability of the bridge for the next 25 years.

Figure 2 shows a striking increase in  $\beta$  from the simplified to the detailed probabilistic method. This is explained by the significantly smaller towed load and length of the trains on this branch line when compared to the traffic load models used in the simplified method. For main lines with usually higher loads and longer trains, there is a better agreement between service and traffic model loads, and consequently, the difference in  $\beta$  between the simplified and the detailed probabilistic method is smaller.

### 5 FIELD TESTING

The main objective of the field testing is to verify the structural models. Top and bottom chord members between the nodes 18 and 19 (Fig. 1) have been equipped with strain gauges, and the strain history due to an engine of six axle loads equal to 177 kN has been recorded. There is a small difference between the measured and calculated influence lines for the bottom chord member 18/19 (Fig. 4); such good agreement is frequently observed for truss girders.

### 6 BRIDGE INSPECTION

The field investigation included a thorough visual bridge inspection. Cracks have been detected at details with sharp corners located at the reinforced parts of the stringers. These cracks may not affect the structural integrity because crack propagation is likely to stop. Such "undangerous" cracks are usually not revealed by analysis, which emphasizes the importance of bridge inspection and study of construction details.

"Dangerous" fatigue cracks affecting the structural integrity (such as those investigated in the foregoing sections) could not be detected. This is in agreement with the theoretical

investigation predicting that - at present - any fatigue crack is likely to be shorter than the crack that could be detected by visual inspection.

## 7 CONCLUSIONS

1. Comprehensive assessment of the remaining service life of railway bridges includes theoretical studies of the structural reliability, bridge inspection and field testing.
2. A method for the evaluation of fatigue safety which proceeds by stages of deterministic and probabilistic calculations of increasing sophistication has been demonstrated. Probabilistic methods enable the consideration of the scatter of the parameters that influence both the fatigue strength and damage accumulation.
3. Based on fracture mechanics and probabilistic concepts, inspection intervals are assessed and considered in the evaluation of structural reliability.
4. By means of strain measurements on fatigue critical members, the load carrying behaviour of the structure is evaluated and a more accurate (and usually lower) value for the stress range is determined, which is the most dominant parameter influencing the fatigue safety.


As a consequence of this study, the severe load restriction imposed on the bridge was removed for the next 170'000 trains. In addition to the main inspection every 5 years, a supplementary inspection of the fatigue critical chord members of the main girders is now conducted at yearly intervals. This thorough evaluation is cost effective because it now allows for practically unrestricted rail traffic for the next 25 years.

## ACKNOWLEDGEMENTS


The Measurements and Instrumentation group of the Swiss Federal Railways is thanked for the carefully prepared and conducted bridge measurements.

## REFERENCES


- [1] KUNZ P., Probabilistic method for the evaluation of fatigue safety of existing steel bridges. Doctoral Thesis Nr. 1023, ICOM - Steel Structures, Swiss Federal Institute of Technology Lausanne, Switzerland, 1992. (in German)
- [2] KUNZ P. and HIRT M.A., Remaining fatigue life of steel railway bridges. Proceedings, IABSE - Colloquium "Remaining Structural Capacity", Copenhagen, Denmark, March 17-19, 1993.
- [3] SIA Code 160: Actions on structures. Swiss Society of Engineers and Architects. 1989.
- [4] UIC 702 V. Load model for the analysis of structures of international lines. International Union of Railways, 1974.
- [5] UIC 779-1 E. Recommendation for the evaluation of the load carrying capacity of existing steel bridges. International Union of Railways, 1986.
- [6] KULAK G., FISHER J.W., STRUIK J.H., A Guide to Design Criteria for Bolted and Riveted Joints. Second Edition. New York: John Wiley & Sons, 1987.
- [7] BRÜHWILER E., SMITH I.F., HIRT M.A., Fatigue and fracture of riveted bridge elements. Journal of Structural Division, ASCE, Vol. 116, No. 1, January 1990, pp. 198-214.
- [8] ECCS Publication Nr. 43. Recommendations for the Fatigue Design of Steel Structures. European Convention for Constructural Steelwork, Brussels, 1985.
- [9] HENSEN W., Concepts for the evaluation of the remaining service life of old steel bridges. Doctoral Thesis, Technical University RWTH Aachen, 1992. (in German)

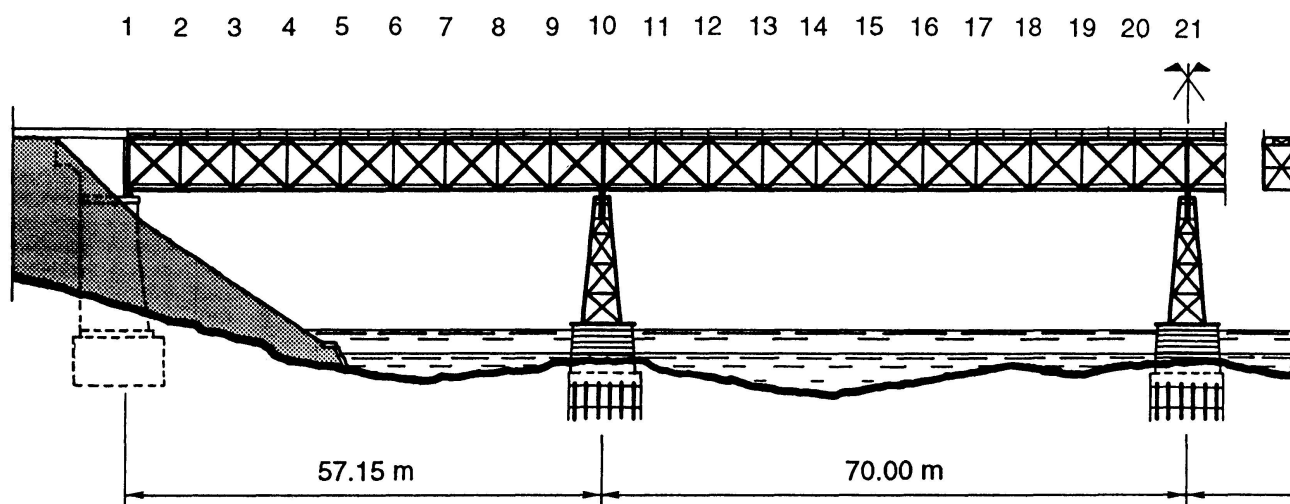


**Figure 1** View of the investigated truss bridge (one half)

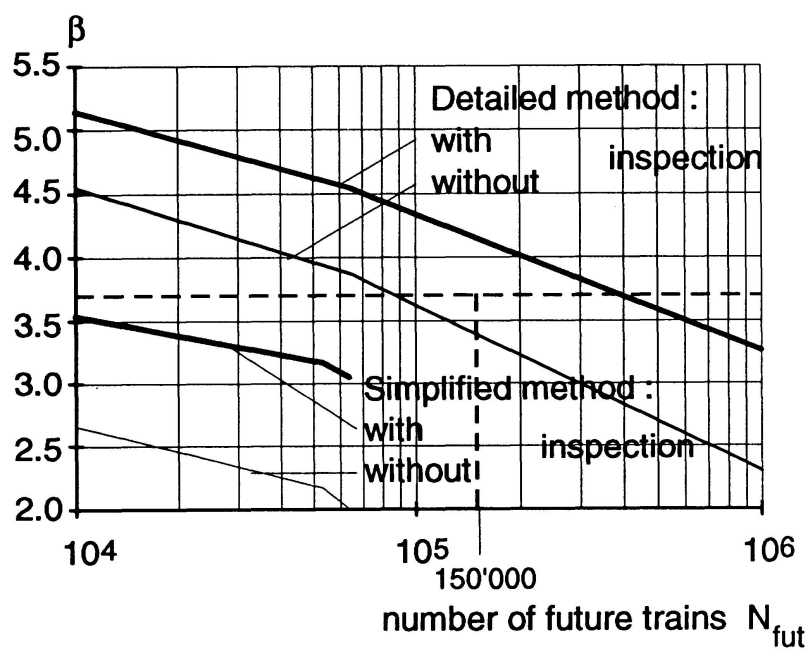

**Figure 2** Reliability index for chord member 18/19 as a function of the number of future trains for simplified and detailed probabilistic approach

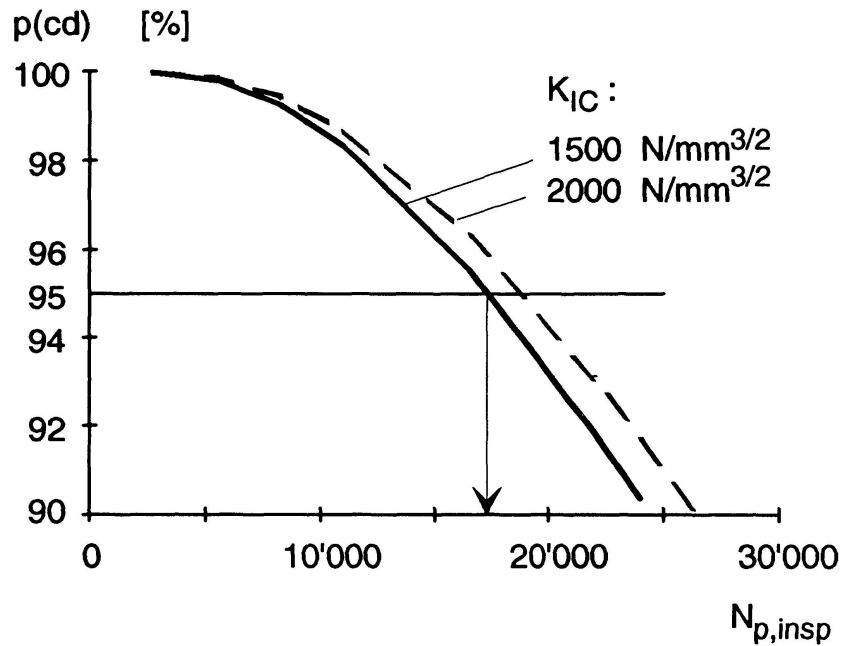

**Figure 3** Probability of crack detection in chord member 18/19 as a function of inspection intervals

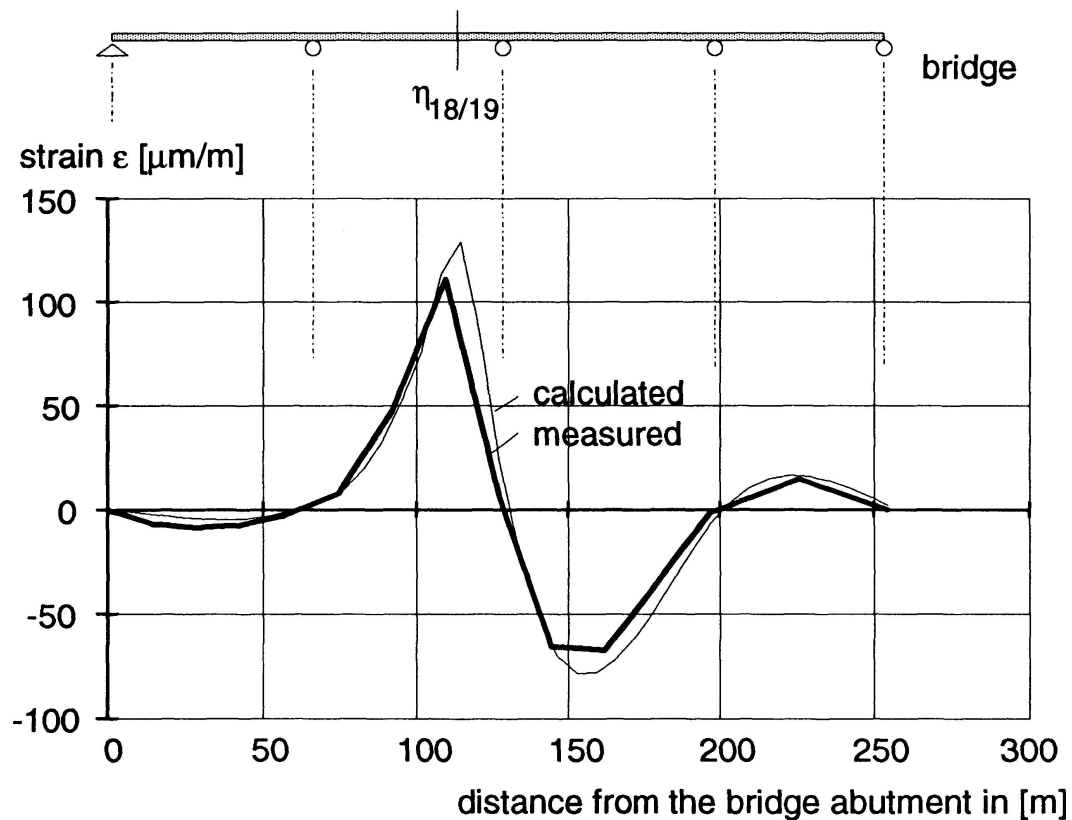

**Figure 4** Comparison between calculated and measured influence lines for bottom chord member 18/19 due to the passage of the engine. (The stress values are evaluated from the strain readings using an elastic modulus of 200'000 MPa.)

