

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 73/1/73/2 (1995)

Artikel: Load capacity of steel structures with cracked components
Autor: Rykaluk, Kazimierz / Czemplik, Andrzej
DOI: <https://doi.org/10.5169/seals-55351>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 19.02.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>


Load Capacity of Steel Structures with Cracked Components

Résistance des constructions métalliques avec des éléments fissurés

Tragfähigkeit von Stahlkonstruktionen mit gerissenen Gliedern

Kazimierz RYKALUK

Dr. Eng.
Technical University of Wrocław
Wrocław, Poland

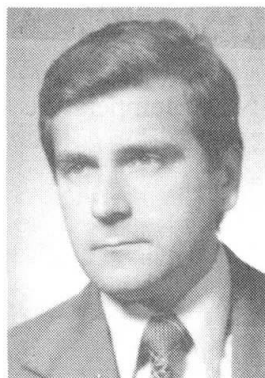

Kazimierz Rykaluk, born 1941, got his M.Sc, Ph.D. and D.Sc in civil engineering at Technical University of Wrocław. He is Professor of Structural Steel Design and a practising consultant engineer in structural steel projects.

Andrzej CZEMPLIK

Dr. Eng.
Technical University of Wrocław
Wrocław, Poland



Andrzej Czemplik, born 1955. M.Sc and Ph.D. in civil engineering at Technical University of Wrocław. Assistant Professor of Construction Technology, he is involved in technology problems of structural steel.

SUMMARY

The analysis of existing steel structures with cracked structural members is presented. The Fracture Analysis Diagram method is used in the analysis. Two components of the safety vector are considered: relative stress and stress intensity coefficient. The second component is adjusted in the analysis. Decrease of its value can be obtained by fixing the reinforcing ribs with the use of bolts and by elastic straps that fully cover the crack and which are elastically connected with a cracked member.

RÉSUMÉ

Le rapport présente l'analyse de constructions métalliques avec des éléments structuraux fissurés. La méthode de l'analyse du diagramme de la fissure est utilisée. Deux composantes du vecteur de la sécurité sont considérées: contrainte relative et coefficient de l'intensité des contraintes. La deuxième composante est ajustée dans l'analyse. La diminution de leur valeur peut être obtenue par la fixation de tôles de raidissement à l'aide de vis et par des fers plats élastiques, qui couvrent entièrement la fissure et qui sont fixés élastiquement à l'élément fissuré.


ZUSAMMENFASSUNG

Im Artikel ist die Analyse bestehender Stahlkonstruktionen mit gerissenen Konstruktionsgliedern vorgestellt. Für die Analyse wurde die Methode der Rissdiagrammanalyse angewendet. Zwei Komponenten des Sicherheitsvektors werden untersucht: Relative Spannung und der Koeffizient der Spannungsintensität. Die zweite Komponente wird in der Analyse errechnet. Die Verminderung ihres Wertes kann auf verschiedene Weisen erreicht werden. Zwei Möglichkeiten werden im Referat besprochen: die Befestigung der Verstärkungsrippen mit Schrauben einerseits und elastische Laschen, die den Riss vollkommen bedecken und mit dem gerissenen Glied elastisch verbunden sind andererseits.



1. INTRODUCTION

Brittle fractures have their origin in metallurgical discontinuities or in weld defects. The initial faults increase with the increase of monotonic load or cyclic load. Crack growth intensifies in winter seasons, when material ductility decreases. Irwin's constant K_{IC} represents the notch toughness of material and is correlated with fracture toughness measured with Charpy specimens [1]:

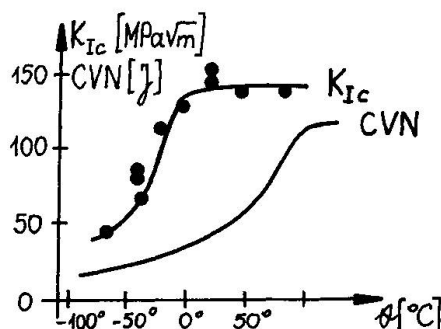

$$K_{IC} = \sqrt{0.22 (CVN)^{3/2} E}$$

where: CVN - Charpy V-notch impact,
E - elastic modulus.

K_{IC} vs. temperature and CVN vs. temperature curves [2] are shown in Fig.1.

Fig.1 CVN vs. temperature and K_{IC} vs. temperature curves [2]

2. LIMIT STATES OF CRACKED COMPONENTS

The existing crack in structural component can remain unchanged if its half-length is not greater than the critical value:

$$l_{cr} = \frac{K_{IC}^2}{M \cdot \sigma^2}$$

where:

l - half-length of a crack,

M - geometrical coefficient, representing position and shape of the crack,

σ - the applied stress.

Values of M for cases shown in Fig. 2 are presented by Tada, Paris and Irwin [8]. On the basis of the critical value l_{cr} and the basic Paris equation [4]:

$$\frac{dl}{dN} = C (\Delta K)^m$$

the ability of survival of the cracked structural member, measured by the number of load cycles, can be determined, as:

$$N_{cr} = N + \frac{1}{C(\Delta K)^m(m-2)} \left[1 - \left(\frac{1}{l_{cr}} \right)^{\frac{m}{2}-1} \right]$$

where $\Delta K = K_{max} - K_{min} = (\sigma_{max} - \sigma_{min}) \sqrt{Ml}$,

N - number of load cycles for the crack of length 2l,

C, m - material constants, proposed in [6] as $m = 3$, $C = 1.315 \times 10^{-4} / 895.4^m$.

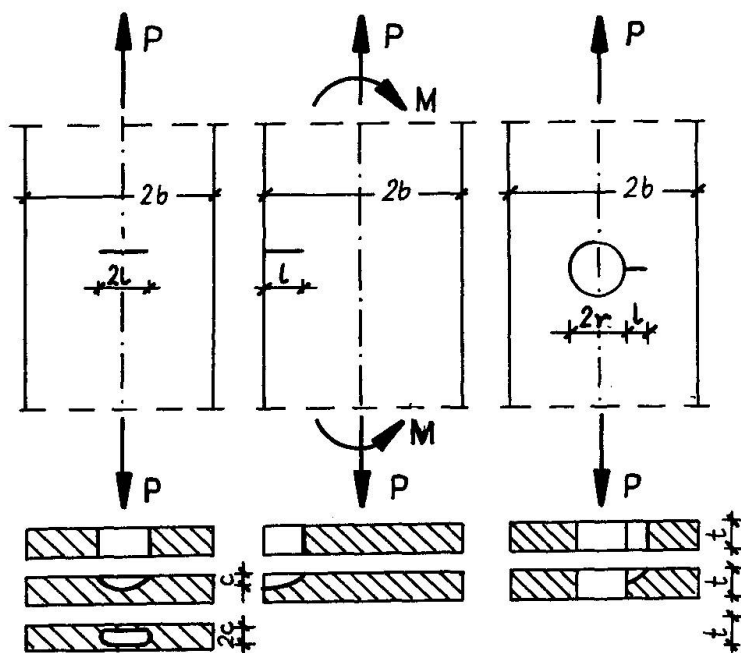


Fig.2 Characteristic cracks types

Further, for the case shown in Fig. 2a the two ways of safety improving are presented. Fitness for purpose second level criterion is suggested for load capacity analysis [6]:

$$K_r = S_r \left[\frac{8}{\pi^2} \ln \sec \left(\frac{\pi}{2} S_r \right) \right]^{-0.5}$$

where:

$$K_r = n_k K_I / K_{IC}, \quad K_I = \sigma \sqrt{Ml},$$

$$S_r = n_\sigma \sigma / \sigma_e,$$

$$\sigma_e = 0.5 (\sigma_y + \sigma_u),$$

σ_y - material yield strength,

σ_u - ultimate strength,

n_k, n_σ - safety coefficient for brittle and ductile fracture, respectively.

While safety coefficient n_σ for ductile fracture are fixed in specifications of many countries, value of the coefficient n_k is still under intensive investigation, nowadays. Many authors usually assume, that $n_k \geq 2$.

In case of elements too thin for plane-strain behavior, i.e. when

$$\beta_t = \frac{(K_{IC} / \sigma_y)^2}{t} < 0.4$$

instead of K_{IC} , the following alternate value should be used in calculations:

$$K_C = K_{IC} \sqrt{1 + 1.4 \beta_t^2}.$$

The idea of suggested methods of strengthening is to decrease the stress intensity coefficient K_{IC} to such an extent that the capacity of the structure would be described by parameters K_r and S_r which are below the limit capacity curve (Fig.3).

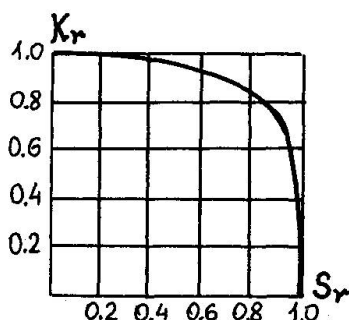


Fig.3 Limit capacity curve

3. STRENGTHENING METHODS

3.1 Method I

In the first method, strengthening of cracked structural member is recommended by drilling of two relieving holes on the axis which is perpendicular to the axis of the crack (Fig. 4). Moreover, two steel straps connected with the cracked member symmetrically on its both sides, as shown in Fig.4



are recommended. This method is far more safe than popular drilling two holes through two tips of the crack. It should be noted, that drilling just two holes is not secure method of strengthening. In such a case there is a danger that the crack propagation can be initiated by the following factors:

- additional mechanical energy yielded during drilling,
- careless drilling, crack tip can be beyond the drilled hole, in the stress concentration zone.

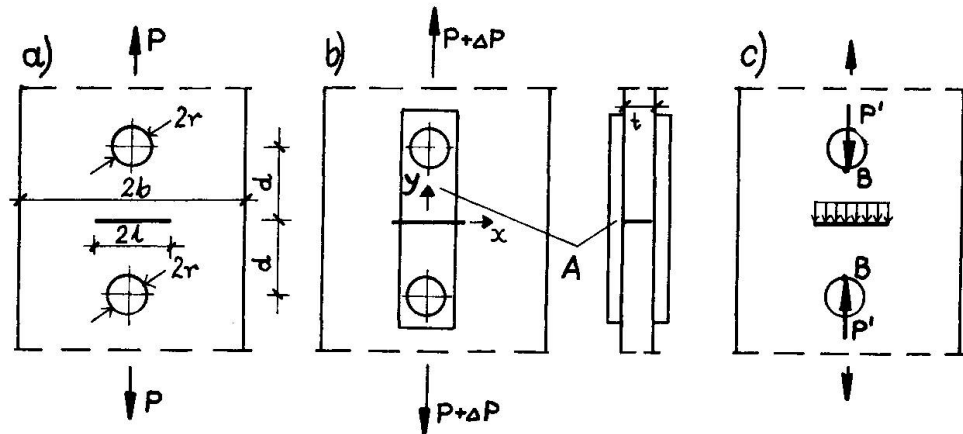


Fig.4 Strengthening method I

Newman's method [3] applied to the holes shown in Fig. 4a, gives:

$$K_I = \sigma \sqrt{Ml} \cdot F\left(\frac{d}{r}, \frac{1}{r+1}\right),$$

and the diagram of function F is presented in Fig.5. For $d/r = 2$ and $r/l = 1$, $F \approx 0.6$. Such a result allows to load the cracked component with the relative stress $S_r \approx 0.97$.

The holes drilled in a proposed way let to apply additional reinforcing straps (Fig.4b) connected with bolts or pins to the cracked component. The bolts or pins carry the force P' - part of load ΔP which increased the force P during strengthening. The force P' can be determined from the displacements compatibility condition in points B (Fig. 4c), as: $P' = VEA / d$, where:

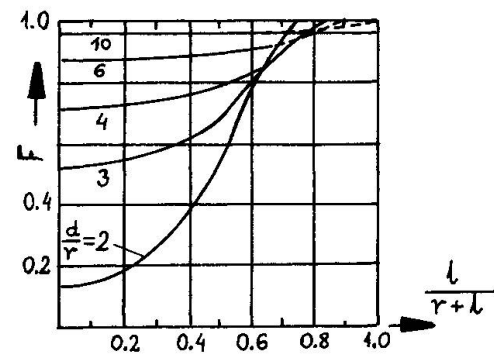


Fig. 5 Diagram of function F

$$V = \{1.82 \times \text{Im} \bar{Z} - 1.3 (d-r) \text{Re} \bar{Z}\}_{z=i(d-r)}, \quad \bar{Z} = \int Z dz, \quad z = x + iy,$$

$$\bar{Z} = \Delta \sigma \cdot z / \sqrt{z^2 - l^2} - P'l / \pi z \sqrt{z^2 - l^2} - \text{Westergaard's function.}$$

Force P' decreases the stress intensity coefficient K_I [5] by:

$$\Delta K_I = \Delta \sigma \sqrt{Ml} - \frac{(6.6 + l^2/c^2) \sqrt{2l/c} P'}{\sqrt{\pi c} (4 + l^2/c^2)^{3/2}}$$

3.2 Method II

In the second method the component is stiffened by two-dimensional finite strap. It is supposed that the elastic strap fully cover the crack and is elastically connected with a component along its contours (Fig.6).

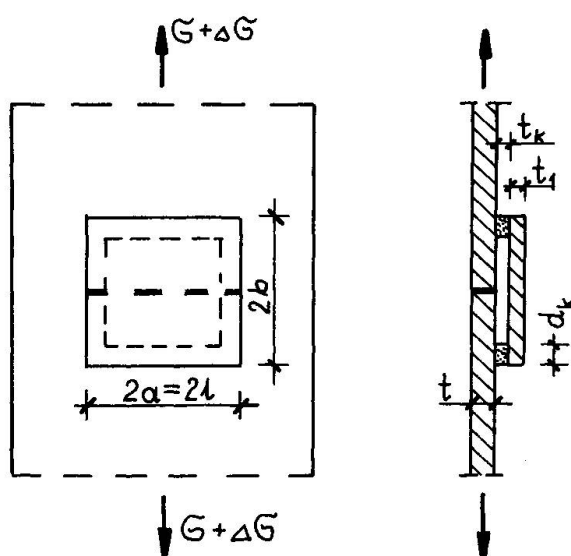


Fig.6 Strengthening method II

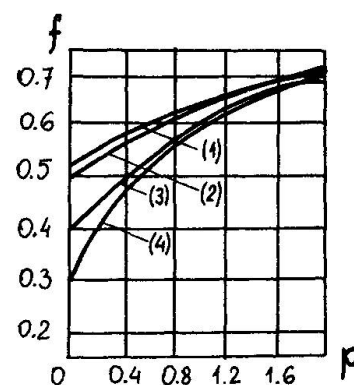


Fig.7 Diagram of function f [7]

For this method, the K_I can be calculated from the formula:

$$K_I = \sqrt{Ml} (\sigma + \Delta \sigma \cdot f),$$

where the function f depend on the shape of straps and on the flexibility of the glue:

$$p = 2\pi G_1 t_1 t_k / G_k d_k l.$$

Diagrams of function f for some kind of straps are shown in Fig. 7 [7]:

- (1) - circular shape of radius l ,
- (2) - ellipse with the semi-axes: l and $0.5l$
- (3) - square, of side $2l$,
- (4) - rectangular $2a * 2b$ ($b=0.38l$).



4. CONCLUSION

Steel structure with cracked structural members can be strengthened for its longer life in relatively easy ways. Obviously, the load capacity of such a strengthened structure is lower than before cracks have occurred, however, the value of capacity can be determined using clear engineering procedure.

REFERENCES

1. BARSOM J.M., ROLFE S.T., Fracture and Fatigue Control in Structures, Prentice-Hall, Inc. 1987.
2. HELLAN K., Introduction to Fracture Mechanics, McGraw-Hill Book Company, Inc., 1984.
3. NEWMAN J.C., Jr., An Improved Method of Collocation for the Stress Analysis of Cracked Plates with Various Shaped Boundaries, NASA TN D-6376, August 1971.
4. PARIS P.C., ERDOGAN F., J. Basic Eng., 85, 528÷534, 1963.
5. PARTON V.Z., MOROZOV E.M., Mechanics of elastoplastic fracture (in Russian), Nauka, Moskva 1985.
6. PD 6493: 1991. Guidance on methods for assessing the acceptability of flaws in fusion welded structures, BSI, August 1991.
7. SAVRUK M.P., KRAVEC V.C., The influence of strengthening straps on stress distribution in cracked disks (in Russian), Prikladnaja Mekhanika, 29, N°3, 1993, 48÷55.
8. TADA H., PARIS P., P., IRWIN G., The Stress Analysis of Cracks Handbook. Del Research Corporation, St. Louis, MO, 1985.