

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 73/1/73/2 (1995)

**Artikel:** Structural assessment of corrosion damaged steelwork  
**Autor:** Gallon, Michael J. / Sarveswaran, Velautham / Smith, J. William  
**DOI:** <https://doi.org/10.5169/seals-55262>

#### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

#### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

#### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 18.02.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## **Structural Assessment of Corrosion Damaged Steelwork**

### **Évaluation structurale des dégâts dûs à la corrosion des ouvrages en acier**

### **Tragfähigkeitsbeurteilung korrosionsgeschädigter Stahlbauteile**

**Michael J. GALLON**  
Structural Engineer  
ICI Technology  
Middlesborough, UK

Michael Gallon, born in 1957, joined G. Wimpey as a site engineer in 1973 and graduated in civil engineering from Teesside Polytechnic in 1979. After joining ICI in 1986 he is now involved in maintenance, design and construction of chemical plants, taking an interest in the real strength of structures.

**Velautham SARVESWARAN**  
Research Student  
University of Bristol  
Bristol, UK

Velautham Sarveswaran, born in 1962, graduated in civil engineering from Queen Mary and Westfield College, London, in 1993. He is currently a research student at the University of Bristol, studying the remaining capacity of steel structures.

**J. William SMITH**  
Senior Lecturer  
University of Bristol  
Bristol, UK

William Smith, born 1941, graduated in civil engineering at the University of Edinburgh, Scotland. He obtained his PhD (vibration of bridges) at the University of Bristol where he now studies the remaining capacity and life of structures.

#### **SUMMARY**

Four severely corroded universal beams were removed from a structural frame, that was undergoing refurbishment, and were load tested to failure in the laboratory. The failure loads were compared with several analytical models including one simulating their as-new condition. They were found to possess surprisingly high residual capacity, prompting a proposal to quantify current visual inspection procedures.

#### **RÉSUMÉ**

Quatre poutres sévèrement corrodées extraites d'une structure en cours de rénovation ont été testées jusqu'à la ruine en laboratoire. Les charges ultimes ont été comparées avec plusieurs modèles numériques, dont un simulant leurs nouvelles conditions. Les essais ont montré que les poutres possédaient une capacité résiduelle étonnamment élevée, conduisant à une proposition pour quantifier les procédures d'inspections visuelles courantes.

#### **ZUSAMMENFASSUNG**

Von einem Rahmentragwerk, das gerade überholt wurde, wurden vier stark korrodierte, allgemein gebräuchliche Träger entfernt und im Labor bis zum Bruch getestet. Die Bruchlast wurde mit mehreren Berechnungsmodellen verglichen, darunter einem, das den Neuzustand darstellte. Die Tests ergeben eine überraschend hohe Resttragfähigkeit, aufgrund derer ein Vorschlag zur Quantifizierung derzeit verwendeter Inspektionsverfahren ausgearbeitet wurde.



## 1. INTRODUCTION

In the UK there are literally thousands of exposed steel structures supporting chemical manufacturing plant and refineries. The aggressive atmosphere and exposed location of such plant can result in severe and rapid corrosion. Moreover, in the UK about 25% of steel structures in the chemical industry are more than 50 years old resulting in the need for substantial maintenance and repair which is difficult and costly because of the need to sustain continuous production.

Current practice in the management of inspection and repair of exposed structural steelwork has been described by Gallon [1]. He found that the current inspection and assessment methods, while being safe, were significantly conservative in some instances indicating the need for more realistic appraisal of the capacity of degraded structures.

Similar concerns exist for steel girder bridges. Kayser and Nowak [2] developed a theoretical corrosion damage model for typical short span steel highway bridges. They showed that the governing criteria, which depend on the relative thicknesses of the web and flange, change with time as corrosion progresses. However, the web is generally the most vulnerable element in the long term.

Regular inspection of steel structures in the chemical industry is usually based on visual examination and classification into categories which identify the need for appropriate action [3]. The most severe visual category refers to the presence of serious structural defects and the consequent need for full structural assessment and repair. However, as yet there is no clear relationship between the magnitude of structural defects and the corresponding reduction in capacity. There is an urgent need for this information to avoid the financial penalty of plant closure when the capacity of the supporting steelwork may be adequate.

The objectives of this paper are to compare a corrosion damage model with tests to failure on some severely corroded steel I-beams, and to use the model to help quantify visual inspection.

## 2. LOAD TESTS ON CORRODED BEAMS

### 2.1 Specimen beams

Four identical universal beams were recovered from the site of a plant undergoing demolition. The beams formed corner supports for a tank as shown in Fig 1 and were all in severely corroded condition. Detailed measurements of the thicknesses of the webs and flanges were made and are summarised in Table 1.

**Table 1** Average measured thicknesses of corroded I-beams (mm)

Element	As new	Beam 1	Beam 2	Beam 3	Beam 4
<b>Flanges</b>					
Top	10.20	7.25	7.55	6.55	7.94
Bottom	10.20	4.95	5.70	4.52	6.62
Average thickness	10.20	6.10	6.63	5.54	7.28
Thickness loss	nil	4.10	3.57	4.66	2.92
<b>Web</b>					
Average thickness	6.10	4.98	5.38	4.93	5.56
Thickness loss	nil	1.12	0.72	1.17	0.54

It will be noted in Table 1 that the loss of thickness on average was more significant in the flanges than in the webs. However, holes were found in the webs and flanges of two of the beams, one of which is shown in Fig 2.

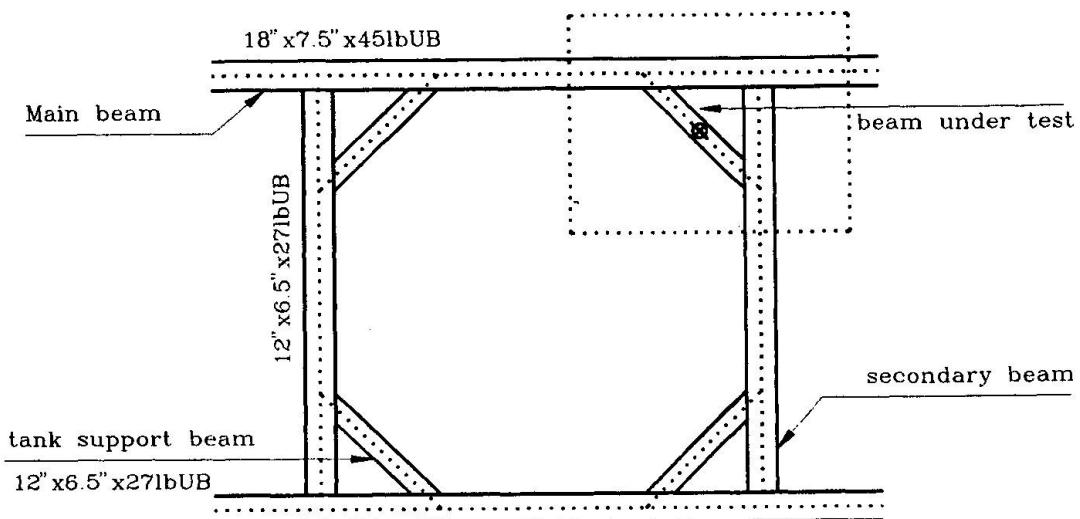


Fig 1 General arrangement of tank support beams

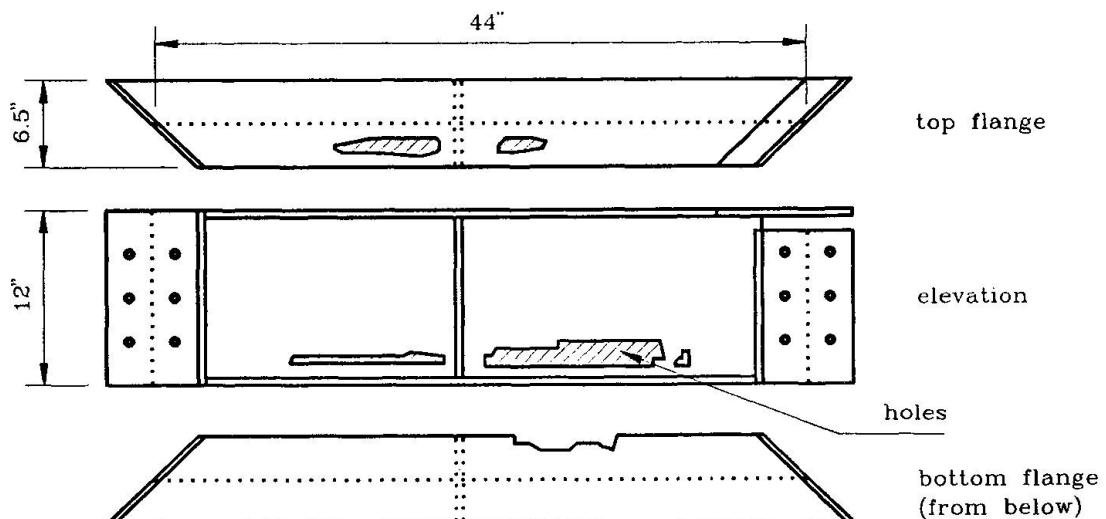
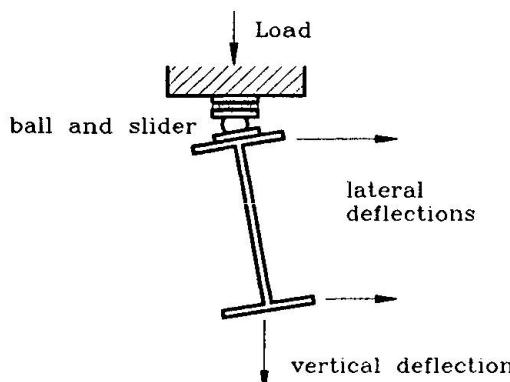


Fig 2 Details of holes in beam No 1

## 2.2 Load tests to failure

Each beam, when tested, was bolted at its ends to the webs of short lengths of I-beam designed to simulate the support conditions for the steel tank in service (see Fig 1). The assembly was installed in an hydraulic testing machine and the load was applied vertically to the test beam directly over the central stiffener. The load was applied through a ball and slider seating to permit rotation of the cross section of the test beam, as would be the case in service. The vertical deflection of the loaded point was recorded, together with lateral deflections of top and bottom flanges at the same section. This provided information on the onset of lateral torsional buckling and is shown in Fig 3.



**Fig. 3** Loading and deflection measurements at central section

The ultimate loads obtained in the tests are given in Table 2. It may be seen that there is a correlation between the condition of each beam and its failure load. The failure loads are compared with the capacity of a new beam calculated using the formulae in the UK code for structural steelwork [4]. Partial safety factors were not used for this purpose. The predominant mode of failure was by lateral torsional buckling originating from the cut-out portion of the top flange.

**Table 2** Ultimate loads in the tests compared with calculated as-new capacity

Beam No	Ultimate Load/kN	General condition of beam
1	277.0	Severe loss of material; holes in flanges and lower web
2	318.0	Loss of material all over but no holes
3	287.0	Severe loss of material; holes in flanges and lower web
4	440.0	Loss of material all over but no holes; fairly good condition
all	522.7	Calculated capacity of as-new beam

### 3. STUDY OF FAILURE MODES OF CORRODED BEAMS

A steel I-beam subjected to bending can fail in the following modes:

- a) exceeding moment capacity as determined by the yield strength;
- b) lateral torsional buckling;
- c) failure of the web in shear;
- d) bearing failure of the web under point loads or at the supports.

BS5950 [4] was used for the assessment of the moment capacity, which is mainly dependent on the yield strength of the steel and the flange area of the beam. Lateral torsional buckling was the most important failure mechanism for these beams, but this was largely because of the cut-out in the flange at one end. This is called a "coped beam" and the lateral end restraint is considerably reduced because rotation of the flange in plan is not resisted at the coped end. The method of assessment proposed by Cheng et al [5] was used in this case.

Failure of the web due to shear buckling was the next most significant failure mechanism. The effect of varying web thickness (VWT) was calculated using the formulae in BS5950. The effect of web holes (WH) was assessed by the method of Wang et al [6]. This assumes that plastic deformation occurs near each of the corners of the opening (rectangular openings). A moment-shear interaction curve is identified from which the capacity of a particular load case may be obtained.

While loss of thickness generally reduces the capacity of a loaded beam, it can also change the mode of failure from one mechanism to another depending on the relative thickness loss in the various parts. Three corrosion damage models were therefore analysed, as follows:

- i) the I-beam in its as-new condition;
- ii) uniform thickness loss in both flanges and web;

iii) variable thickness loss in flanges and web (the ratio of thickness loss in flange to web was the same as that of the beams tested)

The results are shown in Fig 4.

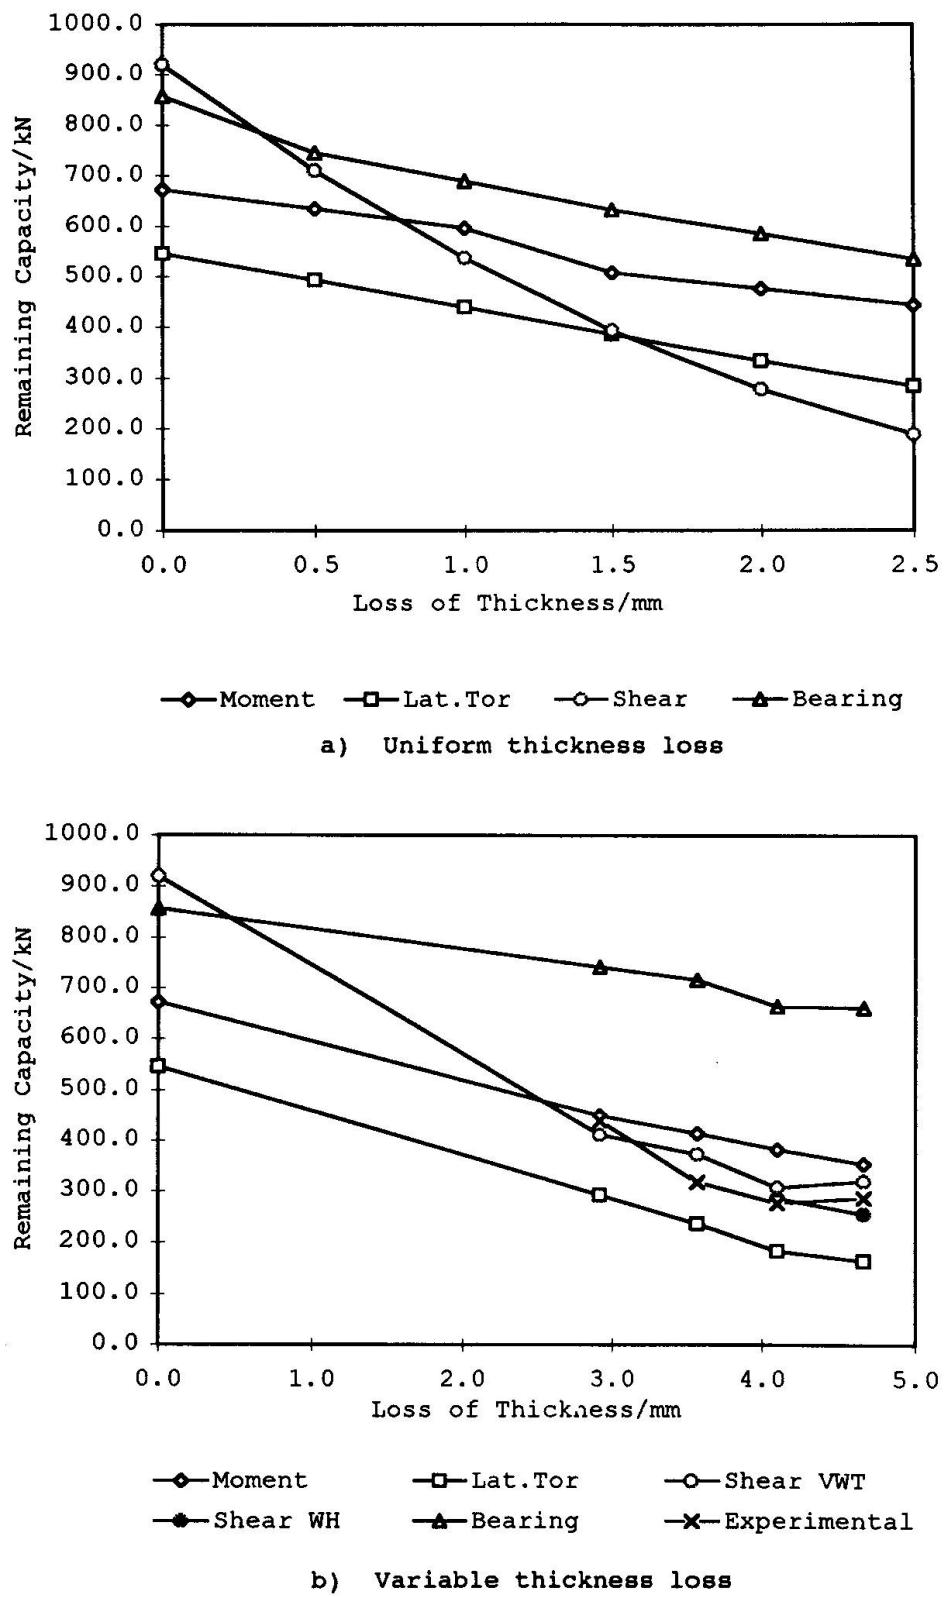


Fig 4 Remaining capacity of corrosion damaged I-beams



#### 4. APPLICATION TO VISUAL INSPECTION

Formal procedures for inspection of structural steelwork already exist in the petro-chemical industry [3]. This involves initial appraisal, preliminary inspection, detailed examination if necessary, and reporting. The preliminary inspection is basically a visual assessment and requires structural elements to be described using defined condition categories, for which subsequent actions are prescribed. Brief descriptions of typical visual categories are as follows:

- i) minimal deterioration; no need for immediate action
- ii) paint system generally defective, but loss of section estimated visually to be less than about 15%; action required to arrest deterioration
- iii) loss of section estimated to be greater than 15%, holes in members, distortion, damaged connections; requirement for further investigation, repair, replacement or removal.

These procedures, properly carried out, provide invaluable assurance that structures for production plant are safe. However, it would be most helpful if visual inspection could be related quantitatively to remaining capacity. It is proposed that the results of the study of failure mechanisms be used as a starting point to achieve this objective. It is evident from Fig 4 that lateral torsional buckling and web shear were the most critical mechanisms. In these cases it was found that if the loss of flange thickness was less than 15% then the remaining capacity was about 75% of the as-new condition. However, more work is required to define a generally acceptable lower bound for a wider range of load cases and configurations. Loss of moment capacity is almost proportional to loss of flange area, so this mechanism is less critical.

The existence of holes in a member is likely to reduce the capacity significantly, although this will depend on the size and location of the holes. At the present time no definitive guidance may be given. However, it should be noted that in this investigation it was found that even the most severely corroded beam possessed more than 50% of its calculated as-new strength.

#### ACKNOWLEDGEMENTS

The authors are grateful to ICI Engineering Technology for their assistance, and to the Engineering and Physical Sciences Research Council for their support.

#### REFERENCES

1. GALLON M J, Managing Structural Corrosion in Chemical Plants. *New Steel Construction*, p14, February 1993.
2. KAYSER J R and NOWAK A S, Capacity Loss Due to Corrosion in Steel-Girder Bridges. *J of Struct Engng, ASCE*, Vol 115, No 6, 1525-1537, June 1989.
3. ICI ENGINEERING, Requirements for Inspection of Plant Structures and Pipebridges. *ICI Engineering Procedure, EDP.CIV.52.40A*, June 1990.
4. BRITISH STANDARDS, Structural Use of Steelwork in Building. *BS5950: Part 1*, British Standards Institution, London, 1985.
5. CHENG J J R, YURA J A and JOHNSON C P, Lateral Buckling of Coped Steel Beams. *J of Struct Engng, ASCE*, Vol 114, No 1, 1-15, January 1988.
6. WANG T M, SNELL R R and COOPER P B, Strength of Beams with Eccentric Reinforced Holes. *J Struct Div, ASCE*, Vol 101, No ST9, 1783-1800, 1975.