

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 999 (1997)

Artikel: A design method for glass-adhesive-glass composite structural elements
Autor: Pye, Andrew / Ledbetter, Stephen
DOI: <https://doi.org/10.5169/seals-1077>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 07.01.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

A Design Method for Glass-Adhesive-Glass Composite Structural Elements

Andrew PYE
 Postgraduate Civil Engineer
 University of Bath
 Bath, UK

Andrew Pye, Born 1972, 1995
 gained a first degree in civil
 engineering at the University of
 Bath, 1996 postgraduate engineer
 in the School of Architecture and
 Civil Engineering at the University
 of Bath. Researches into bonded glass
 in load bearing structures.

Dr Stephen LEDBETTER
 Director
 Centre for Window and Cladding Techn.
 Bath, UK

Stephen Ledbetter, Born 1953,
 gained a first degree in civil engineering
 at Dundee University and a doctorate
 at Bristol University, appointed Director
 of CWCT 1990. Researches into
 all aspects of cladding and the building
 envelope.

Summary

The use of architectural glass in long span or high load applications is limited by the slenderness of glass plates which leads to excessive deflection. However, by using composite glass-adhesive-glass beam sections it is possible to carry greater loads, over longer spans with less deflection, Pye and Ledbetter (1997). This paper outlines current work at the University of Bath that will enable the quantitative design of T-beams fabricated from flat plates of toughened glass with a thin adhesive joint at the web-flange interface.


Composite Model

The authors have developed an expression which describes the behaviour of a thick-thin-thick composite with a flexible core, Equation (1). This demonstrates that the current practice of using fins to strengthen glass plates does not utilise the shear transfer at the plate-fin interface, Figure 1. It also demonstrates the increased degree of composite action which is possible using the adhesives that have been selected for this work. These are 3M 2216 B/A grey epoxy adhesive and 3M structural bonding tape 9245. The first is a flexible, two part, room temperature curing structural adhesive. The second is a new material that is applied as a tape and is heat cured to develop structural strength.

$$S_0 \frac{d^4 y}{dx^4} - CS_1 \frac{d^2 y}{dx^2} = \frac{d^2 M}{dx^2} - CM \quad (1)$$

S_0 is the stiffness of the equivalent layered section
 S_1 is the stiffness of the equivalent monolithic section
 x is the distance along the beam
 y is the deflection perpendicular to the span
 C is the composite constant
 M is the moment

The degree of composite behaviour is controlled by the composite constant, C, which is a function of the adhesive shear modulus, glass Young's modulus and the cross section geometry. However, in most practical designs it is the choice of the core material and joint dimensions that offers the greatest scope for improving composite action.

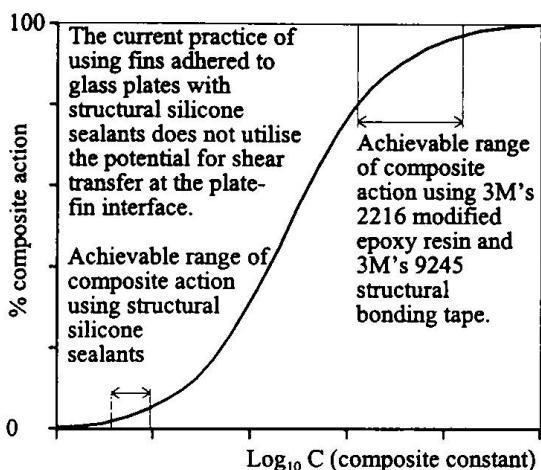

$$\text{percentage composite action} = \frac{\delta_C - \delta_L}{\delta_M - \delta_L} \times 100$$

δ_C deflection of the composite section
 δ_L deflection of the equivalent layered section
 δ_M deflection of the equivalent monolithic section

Figure 1 Comparing the performance of a glass-adhesive-glass T-beam constructed using a structural silicone sealant and a modified epoxy resin. Based upon equation (1).

Failure Mechanisms

The failure of a glass T-beam may be by one of the five mechanisms listed in Table 1. After having determined and appropriately factored the necessary loads and material properties, the occurrence of each mechanism must be checked

In addition to the composite failure mechanisms the glass may also fail because of very localised high stresses such as those generated by a stone impacting upon the glass. Fortunately it is possible to design against these types of failures by either over-designing the glass plates or by introducing a sacrificial layer.

A potential problem in assessing the performance of wide-flanged beams is that the full width of the flange does not work compositely with the web because of shear lag effects. By strain gauging the flange during physical testing the authors have quantified this behaviour and shown that it would be possible to approach the problem by determining an effective width as is currently practised with steel and concrete structures.

Failure Mechanism

Glass bending failure

Glass shear failure

Lateral torsional buckling

Adhesive shear failure

Adhesive tensile failure/glass plucking failure

Assessment

- Equation (1) may be developed to yield the maximum tensile glass stress and while this is below the surface compression of the toughened glass failure will not occur.
- The maximum shear stress may be determined in the same manner as steel sections. This must be less than the shear capacity of the glass. However, initial results from a series of punching shear tests conducted to determine the shear capacity of glass indicate that a glass shear failure is unlikely in most realistic support conditions.
- The distribution of compression stresses must be such that the section is stable. It is possible to design to a reduced moment capacity by considering the slenderness of the beam, position of restraints and distribution of load. Assessing the reduced capacity has been based upon a combination of physical testing and finite element modelling.
- This is dependent upon the ability of the adhesive to yield and redistribute stresses. It is also sensitive to the rate of loading. Difficulties arise in quantifying the complex elasto-plastic behaviour. Current work is based upon a combination of physical testing and finite element modelling.
- There may be a cohesive failure which is a function of the adhesive, an adhesive failure which is a function of the adhesive and the primer or a plucking failure which is a function of the glass. All of these mechanisms may be easily prevented by suitable joint detailing and increasing the adhesive contact area..

Table 1 A summary of the failure mechanisms of glass-adhesive-glass T-beams.

Conclusion

It is possible to predict the performance of composite glass-adhesive-glass T-beams and by applying a similar methodology it would be possible to assess the performance of other sections such as I's, π 's and boxes. However, the current process of determining critical stresses is complex and would need to be presented in a simplified manner if it were to be used in practice.

References

Pye, A, and Ledbetter, S, (1997), 'The engineering of composite glass beams', ICBEST - 97, Bath.