

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 999 (1997)

Artikel: Calculation of stresses for composite structures
Autor: Deretic-Stojanovic, Biljana
DOI: <https://doi.org/10.5169/seals-1086>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 17.01.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Calculation of Stresses for Composite Structures

Biljana DERETIC-STOJANOVIC

Assist. Prof.
Univ. of Belgrade
Beograd, Yugoslavia

B. Deretic-Stojanovic, born 1955,
received her doctor's degree 1992 from
Belgrade Univ. Yugoslavia.

Summary

The calculations of the stresses for the statically indeterminate composite structures as general, are presented. The approximate methods EM and AAEM and exact method are applied. The stresses, for the example of statically indeterminate composite structures due to uniformly distributed load and the shrinkage of concrete are determined. Using the limiting concrete creep functions the upper and lower limits of the stresses are determined.

1. The exact method (TM)

The cross section of the composite structures contain concrete (b), prestressing steel (p), steel member (n) and reinforcing steel (m). Concrete is considered as a linear viscoelastic material. The relaxation of the prestressing steel is taken into account.

$$\sigma_b = E_{bo} \hat{R}'(\varepsilon - \varepsilon_s), \quad \sigma_p = E_p \hat{R}'_p \varepsilon \quad (1.1)$$

Other kinds of steel: steel member (n) and reinforcing steel (m) obey Hook's law :

$$\sigma_k = E_k \varepsilon \quad k=n, m. \quad (1.2)$$

The exact method, established by Lazic, using linear integral operators, is applied. Starting from the integral stress-strain relationship the expressions for stress and strain, in the exact method, are derived without mathematical negligence. Calculation of statically indeterminate composite structures is same as calculation of the corresponding structures whose material is homogeneous and elastic except that in composite structures we solve integral equations.

2. The approximate methods (AAEM, EM)

The algebraic stress-strain relationship for concrete contain two independent parameters: the reduced creep coefficient $\phi(t, t_0)$ and the aging coefficient $\chi = \chi(t, t_0)$ (AAEM). When $\chi = 1$ the same equations represent the EM method.

$$\sigma_b = E_{bo} \zeta_b (\varepsilon - \varepsilon_s) - \rho_b \sigma_b, \quad \sigma_b = \sigma_b(t_0, t_0), \quad \zeta_b = \frac{1}{1 + \chi \phi_r}, \quad \rho_b = (1 - \chi) \phi_r. \quad (2.1)$$

When the relaxation of prestressing steel is introduced, the algebraic stress-strain

relationship for the prestressing steel may be written as:

$$\sigma_p = E_p \zeta_p \epsilon \quad (2.2)$$

Calculation of statically indeterminate composite structures is same as calculation of the corresponding structures whose material is homogeneous and elastic.




The redistribution of stresses for the example of composite structures due to uniformly distributed load and the shrinkage of concrete is calculated. Values of stresses are shown on the graphs 1,2 as follows.

Data: Concrete (b) $E_b = 30 \text{ GPa}$, $\varphi_r = 3,5$, $\epsilon_s = -30 \cdot 10^{-5}$

Prestressing steel (p): $E_p = 210 \text{ GPa}$, $F_p = 100 \text{ cm}^2$, $\zeta_p = 8\%$

Steel member (n): $E_n = 200 \text{ GPa} = E_u$

Reinforced steel (m): $E_m = 200 \text{ GPa}$, $F_m = 80 \text{ cm}^2$

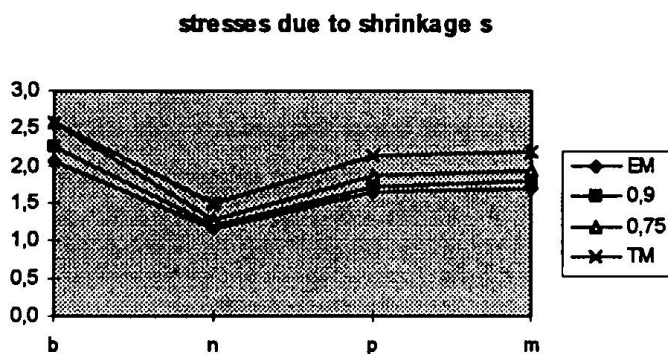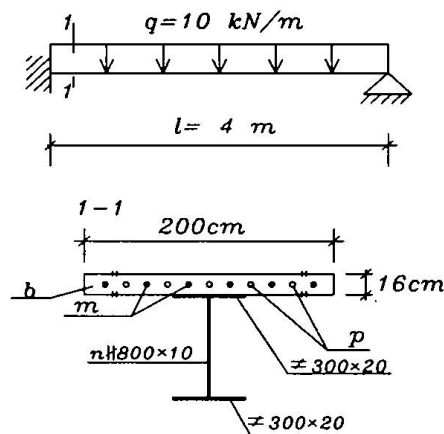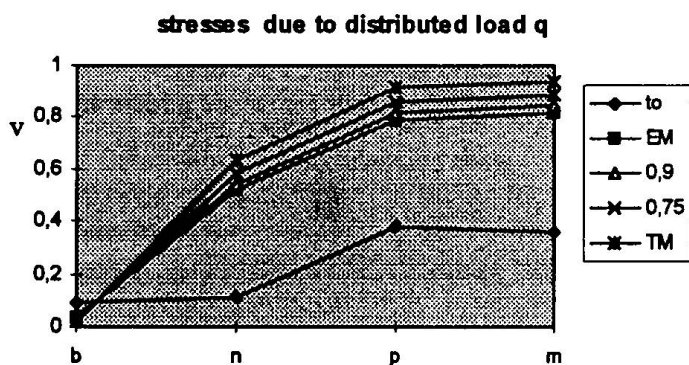

3. Conclusion

The redistribution of stresses for the composite section during in time, occurs due to viscoelastic properties of concrete and relaxation of prestressing steel. Stresses of concrete are reduced and stresses of steel parts are increased. Using the concrete creep function of the aging theory in the exact method and the hereditary function in the EM method the upper and the lower limits of the stresses are determined. We choose the aging coefficient χ in the AAEM method to lie within these limits. As we can see in graphs this conditions for the values of coefficient χ from 0,75 to 0,9 are fulfilled.