

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 999 (1997)

**Artikel:** Design of shear transfer in concrete-concrete composite structures  
**Autor:** Münger, Fritz / Wicke, Manfred / Randl, Norbert  
**DOI:** <https://doi.org/10.5169/seals-962>

#### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

#### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

#### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 16.01.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## Design of Shear Transfer in Concrete-Concrete Composite Structures

**Fritz MÜNGER**

Civil Engineer

Hilti AG, Schaan

Principality of Liechtenstein

Fritz Münger, born in 1944, graduated with a degree in civil engineering from the Swiss Fed. Inst. of Technology, Zurich in 1968. For 20 years he has worked in Switzerland and South Africa as a design engineer in industrial and bridge construction. Since 1989 he has been a project manager with Hilti Corporate Research.

**Manfred WICKE**

Professor

University of Innsbruck

Innsbruck, Austria

Manfred Wicke, born in 1933, has his civil engineering and Ph.D. degrees from Vienna Technical University. He worked in and later headed a design office of a firm, primarily involved in the design of buildings, bridges and power plants. Since 1971 he has been a full professor for concrete structures at Innsbruck University.

**Norbert RANDL**

Civil Engineer

University of Innsbruck

Innsbruck, Austria

Norbert Randl, born in 1967, graduated with a degree in civil engineering from the Innsbruck University. Since 1993 he has worked in the Institute for Concrete Structures at Innsbruck University.

### Summary

For the design of concrete composite constructions, the transfer of internal stresses across the bond interface between new and old concrete is a critical aspect. A design method has been developed with the aid of specific tests for rough, sand-blasted and smooth surfaces. Test results known from literature have been taken into account. This new design approach considers cohesion, friction and the shear resistance of the reinforcement in determining the effective shear transfer. It has been found that, contrary to the usual design approach, the full yield strength of the reinforcement cannot be equated to the tension clamping force across the interface.

### 1. Introduction

Placing new concrete on older concrete is a routine task in construction. It occurs at every joint in concrete construction work. For some time now, placing overlays has gained in importance as a result of the more frequent strengthening of existing structures. In such cases, a loadbearing layer of new concrete (overlay), is placed on the existing concrete structure. This overlay is usually cast directly or placed as shotcrete. It functions to augment the flexural compression or flexural tension zones, depending on the placement.

One of the problems encountered is the transfer of internal stresses acting across the bond interface between the old and the new concrete. In this respect, knowledge is required of the resistance of the bond interface to tensile and compressive forces in any direction. Initially, stresses in the bond interface result from a combination of external loads and internal forces of constraint. It must be borne in mind that stresses due to shrinkage and temperature gradients in the new concrete typically reach their maximum at the perimeter of the overlay. The



*Fig. 1: Strengthening of a bridge*

combination of external and internal stresses often exceeds the capacity of the initial bond, thus requiring the designer to allow for a debonded interface. This is particularly true in the case of bridge overlays which are subject to fatigue stresses resulting from traffic loads. Furthermore, these stresses are dependent on time, and bond failure can take place years after overlay placement.

## 2. State of the Art

Review of the literature reveals little research into the specific behavior of reinforced bond interfaces between new and old concrete. The majority of the existing studies concentrate on the transfer of shear forces across cracks [6]. The effect on the shear loading capacity of subsequent roughening the surface of the old concrete was first investigated in 1960 in the United States. A few years later, the so-called shear-friction theory was developed. This theory attempts to explain the phenomena with the aid of a simple saw-tooth model. According to this, the roughness of surfaces in the case of relative displacement always leads to a widening of the interface which sets up stresses in steel connectors passing across the interface. They, in turn, create clamping forces across the interface and thus also frictional forces. In the middle of the 1970's, further shear tests were conducted in New Zealand (Paulay [4]), in the United States (Mattock [5]) and in Germany (Daschner [7]).

In 1987, Tsoukantas and Tassios [8] presented analytical investigations into the shear resistance of connections between precast concrete components. They cover the different contributing mechanisms of friction and dowel action (fig. 2). In 1991/92, Menn [9], in Switzerland, looked into the behaviour of bond between old and new concrete using a series of beams which had been strengthened by additional reinforcement in a new layer of concrete placed on the underside of the beams. The results clearly demonstrated that a significant increase in loadbearing capacity can be achieved by proper roughening of the surfaces. If the surfaces are very rough, the steel connectors across the bond interface are primarily stressed in tension, whereas, if the surfaces are smooth, the shear resistance of the connectors themselves (dowel action) predominates.

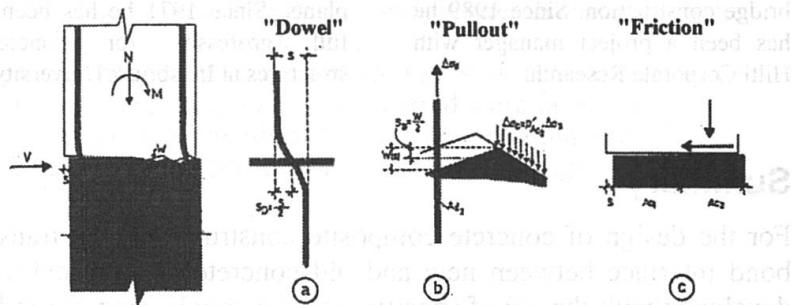


Fig. 2 Shear transfer in cracked concrete [8]

In 1991/92, Menn [9], in Switzerland, looked into the behaviour of bond between old and new concrete using a series of beams which had been strengthened by additional reinforcement in a new layer of concrete placed on the underside of the beams.

The results clearly demonstrated that a significant increase in loadbearing capacity can be achieved by proper roughening of the surfaces. If the surfaces are very rough, the steel connectors across the bond interface are primarily stressed in tension, whereas, if the surfaces are smooth, the shear resistance of the connectors themselves (dowel action) predominates.

## 3. Laboratory Tests by Hilti Corporate Research

Specific shear tests were carried out in the laboratories of Hilti corporate research to investigate the interrelationships of various degrees of roughness and transferable shear stresses with various amounts of reinforcement. Using an origine test design, it was possible to avoid any eccentric moments in the specimen and to allow for parallel separation of the interface surfaces (fig. 3). The roughened surfaces were treated with a de-bonding agent before the new concrete was placed.

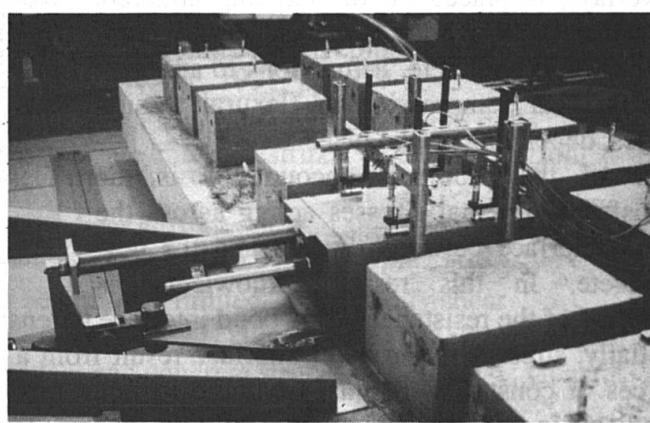


Fig. 3: Testing arrangement

The test results confirm the strong influence of roughness on shear resistance and shear stiffness. If the load-displacement curves are regarded in conjunction with the measured displacement, the three components of cohesion, friction and dowel action can be isolated and determined quantitatively. They make different contributions to the overall resistance (figs. 4, 5 and 6), depending on surface roughness and amount of reinforcement.

Hence, the frictional component predominates when the surface is blasted with a high-pressure water jet and larger amounts of reinforcement are provided. But small shear stresses can also be transferred even when no reinforcement is present, due to the good interlocking effect of the interface surfaces. In the case of sand-blasted surfaces, however, shear stresses are transferred by a combination of friction and dowel action, but the forces that can be resisted are generally far smaller than in the case of high-pressure water blasting.

It was also investigated whether the post installed rebar connectors are stressed to yield at ultimate shear transfer. For this purpose, the strain in the connectors at the level of the interface was measured. To avoid any disturbance of the bond, and in order to obtain the strain from tensile loading only, strain gauges were fixed in a central bore in the axis of the connectors.

These test results clearly show that, when surfaces have the above-mentioned degrees of roughness, the tensile force in the connectors does not reach the full tensile yield strength, contrary to assumptions for current design models. Tests carried out with connectors of various lengths confirm this result as they showed that reduced anchorage lengths are sufficient to carry the effective connector tensile force at maximum shear transfer capacity. Additional connector embedment (e. g., as required for theoretical connector tensile yield) did not result in increased shear transfer.

The loadbearing behaviour of smooth interface surfaces with connectors was also investigated. As displacement readings for the horizontal and vertical directions showed, there is in this case also a separation of the interface under shear loading and, thus, owing to the lack of roughness, a loss of contact between the shear surfaces. In this case, the entire resistance comes from dowel action.

On the basis of these findings, design approaches can now be developed which permit separate and realistic analyses of the various components of shear resistance. As a result, a standardised level of safety is ensured with respect to resistance, no matter whether the normal stresses at the interface are set up by an external normal force or internal connectors.

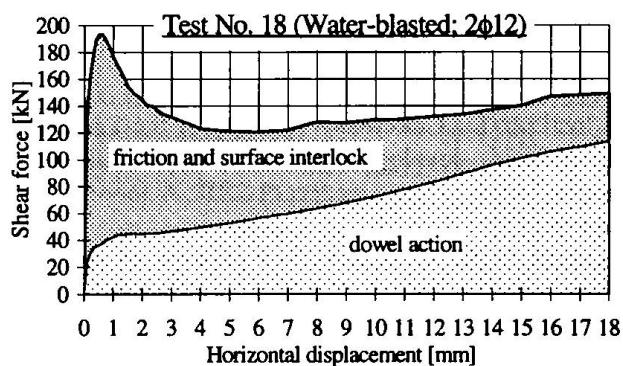


Fig. 4: Water-blasted surface

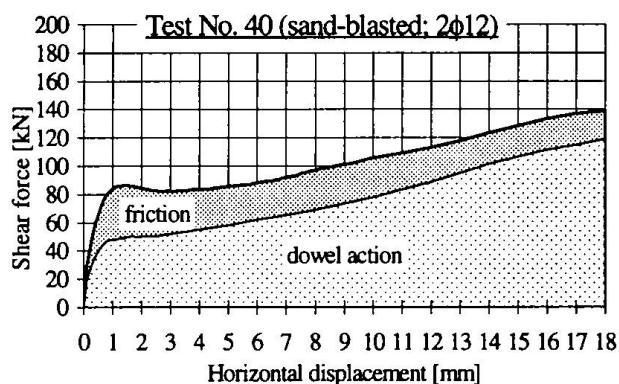


Fig. 5: Sand-blasted surface

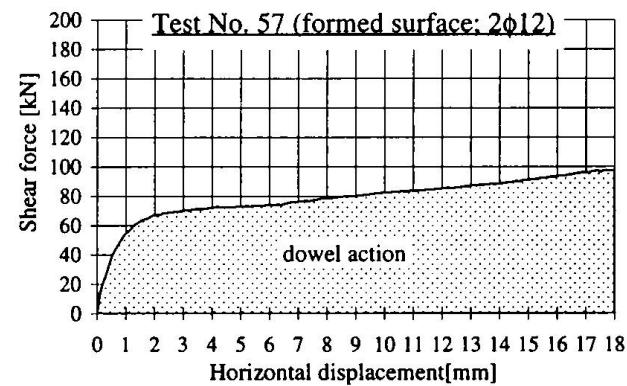


Fig. 6: Smooth surfaces

## 4. Design of Shear Transfer

### 4.1 Miscellaneous

The Institute for Concrete Structures of the University of Innsbruck, Austria, provided scientific support during development of this design method, which is based on EC2 [1]. The evaluation is contained in the thesis by Randl [10]. A more comprehensive description and examples can be found in [13].

Structures made of reinforced or prestressed concrete, which have a concrete overlay of at least 60 mm, may be designed as a monolithic building component if the shear forces acting in the interface between the new and the old concrete are resisted according to the following rules.

### 4.2. Loadbearing Capacity of Interface

Generally, an interface must be assumed to be cracked for design work. Connectors installed across the interface must be positioned in such a way that the shear force,  $V_{Rd}$ , between the new and the old concrete is transferred in the ultimate limit state.

$$V_{Rd} = \tau_{Rdj} \cdot b_j \cdot l_j \geq V_{Sd} \quad (1)$$

$V_{Rd}$  Design value of interface shear force resistance

$\tau_{Rdj}$  Design value of the transferable interface shear stress in zone under review as per formula (2)

$V_{Sd}$  Design value of interface shear force due to actions

$b_j$  Width of interface in zone under review

$l_j$  Length of interface in zone under review

The design value of transferable shear stress,  $\tau_{Rdj}$ , can be calculated using formula (2) [10]. When doing so, the upper limit is given by the transferable compressive stress in the strut model for concrete:

$$\tau_{Rdj} = k_T \cdot \tau_{Rd} + \mu \cdot (\rho \cdot \kappa \cdot f_{yd} + \sigma_n) + \alpha \cdot \rho \cdot \sqrt{f_{yd} \cdot f_{cd}} \leq \beta \cdot v \cdot f_{cd} \quad (2)$$

cohesion      friction      dowel action      compressive strut in concrete

$\tau_{Rd}$  basic value of design shear strength as per [1], section 4.3.2.3 (smaller value of new/old concrete)

$\rho = A_i / b_j l_j$  amount of reinforcement from connector in zone under review

$k_T$  cohesion factor as per [13], table 1

$\sigma_n \leq 0,6 f_{cd}$  normal stress to external loads acting on the interface (compression positive)

$\mu$  coefficient of friction as per [13], table 1

$f_{yd}$  design value of yield strength of connectors

$\alpha$  coefficient of dowel action as per [13], table 1

$f_{cd}$  design value of cylinder compressive strength of concrete (smaller value of new and old concrete)


$\beta$  coefficient as per [13], table 1

$r$  mean roughness derived from sandpatching method (i.e. difference between peaks and valleys = 2r)


$v$  coefficient as per [1] formula (4.20)

$\kappa$  coefficient for tensile force in the connector as per [13], table 1


An evaluation of equations (1) and (3) for S500 grade steel is provided in the diagrams 1 to 3.

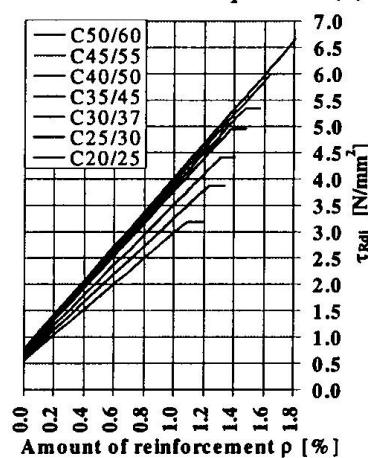

*Dia 1: Water blasted surfaces*

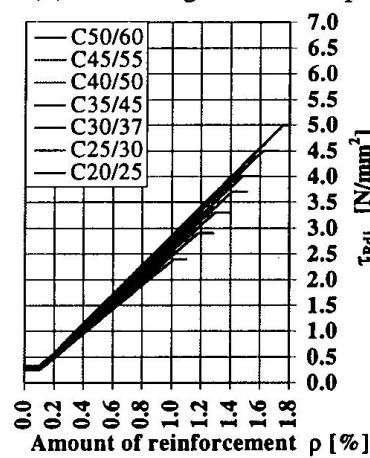

*Dia 2: Sand-blasted surfaces*

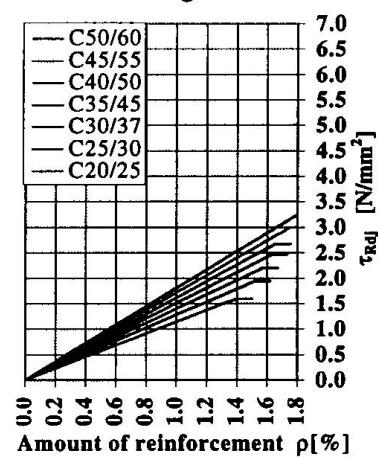

*Dia 3: Smooth surfaces*

### 4.3 Stressing of Interface

Normally, the design value of the interface shear force acting,  $V_{sd}$ , is determined from the flexural resistance of the cross-section. Consequently, bending is decisive for failure of the cross-section and reference is made to full connection, as in steel-concrete composite designs [2].

In the perimeter of the concrete overlay, the crack tensile force,  $F_{cr}$ , of the concrete overlay must be transferred in accordance with [1], section 4.4.2.2. Particular attention must then be given to transfer of the moment from the crack tensile force in order to avoid spalling effects.

### 4.4 Serviceability Limit State and Design Principles

For normal cases, where water blasting is used, the stiffness can be determined, at the strengthened cross-section assuming full composite action. Where sand-blasted or smooth interfaces are used, a reduction of the stiffness must be expected.

Variations in surface preparation for the same building component should only be allowed if resulting stiffnesses along the interface variations are compatible from a displacement standpoint. It must be noted here that interfaces with small shear stresses, without connectors according to section 4.3, may be assumed to be non-cracked for stiffness purposes.

The connectors must be adequately anchored in the old concrete and in the overlay. The actual tensile force,  $F_d$ , to be anchored may be taken as at least  $F_d \geq 0.5 \cdot A_s \cdot f_{yd}$  when surfaces are rough or sand-blasted.

To shorten the anchorage length in concrete overlays, heads or plates can be provided. The concrete cone as well as the bearing stresses in the concrete below the anchoring component must be checked. The methods of calculation are given in [14].

When surfaces are smooth, shear dowels must be anchored at depths of at least 6 times the diameter in each case, or, better still, to avoid dowel pull-out at large displacements a value of 9 times the diameter is recommended.

## 5. Comparison with Literature

In his thesis [10], Randl has proven through a study of literature and with reference to worldwide research results that the determined design equations are conservative. The results are shown in figs. 7 and 8.

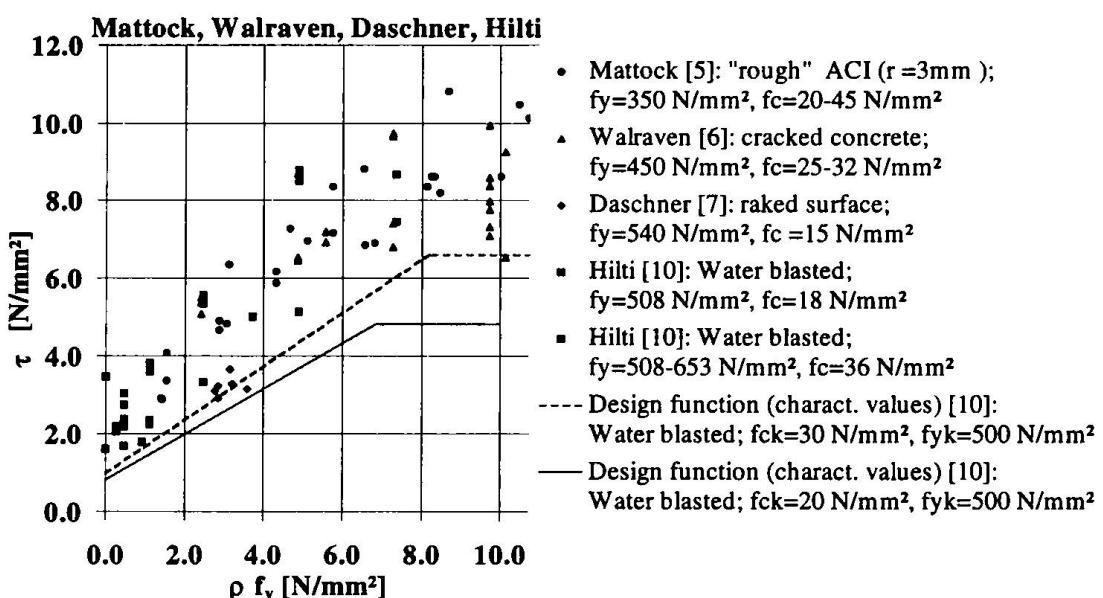


Fig. 7 Rough surfaces

Daschner, Mattock, Paulay, Hanson, Hilti

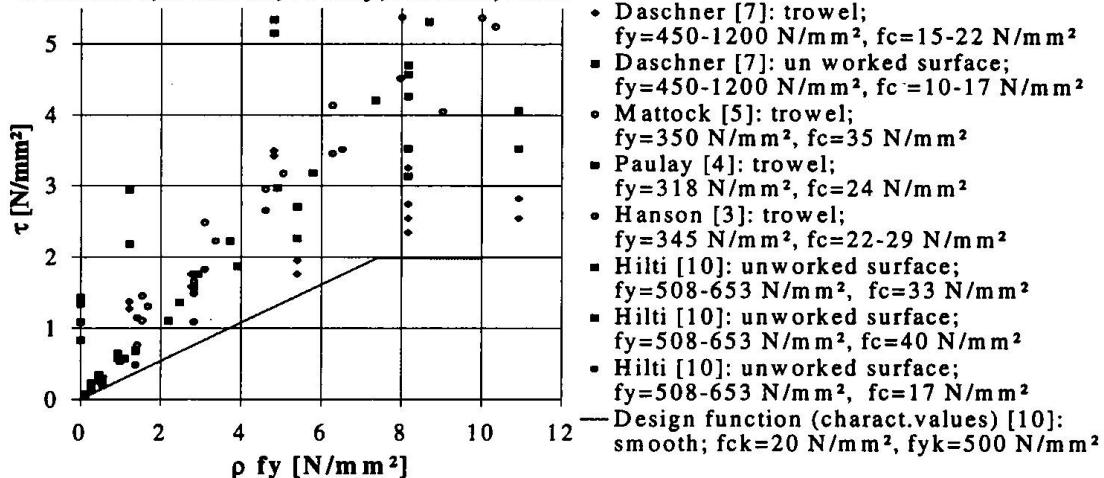


Fig. 8 Smooth surfaces

## 6. Summary

Contrary to design methods given in the literature, dowel resistance is considered along with cohesion and friction when determining shear resistance. With increasing roughness of surfaces, shear resistance and shear stiffness improve greatly. Furthermore, the distribution of total resistance shared by the three components changes considerably. The design method makes use of one single equation for calculating the resistance from the three components. In some cases, it is sufficient for the concrete overlay to be anchored at its perimeter.

This new design approach is particularly notable for its transparency. It is verified by the literature as well as by extensive testing conducted at Hilti Corporate Research. Through the use of design diagrams, the method can be made particularly straightforward for designers.

## Literature

- EC 2; Design of concrete structures: ENV 1992-1-1: 1991; Part 1. General rules and rules for buildings
- EC 4; Design of composite steel and concrete structures: ENV 1994-1-1: 1992; Part 1-1. General rules and rules for buildings
- Hanson, N.W.; Precast-Prestressed Concrete Bridges-. Horizontal Shear connections. Journal of the Portland Cement Association, Research and Development Laboratories, V.2, No.2, May 1960, pp.38-58
- Paulay, T., Park, R. and Phillips, M.H.; Horizontal Construction Joints in Cast in Place Reinforced Concrete, ACI-Special Publication SP.42 Shear in Reinforced Concrete, 1974, Vol. II, 99. 599-616
- Mattock, A. H.; Shear Transfer across an Interface between Concretes Cast at different Times, Structures & Mechanics Report SM76-3, University of Washington, Seattle, 1976, 68 pp.
- Walraven J. C., Reinhardt H. W.; Theory and experiments on the mechanical behaviour of cracks in reinforced concrete subjected to shear loading. Heron Vol.26/1981.
- Daschner, F.; Versuche zur notwendigen Schubbewehrung zwischen Betonfertigteilen und Ortbeton. Deutscher Ausschuss für Stahlbeton, H 372 Berlin, Ernst und Sohn, 1986
- Tsoukantas S. G., Tassios T. P.; Shear Resistance of Connections between Reinforced Concrete Linear Precast Elements. ACI Journal, May-June 1989.
- Menn, C.; Bonding of Old and New Concrete for Monolithic Behaviour Swiss Federal Institute of Technology, Zürich. Report No. 185, 1991.
- Randl, N.; „Untersuchungen zur Kraftübertragung zwischen Neu- und Altbeton bei unterschiedlichen Fugenrauigkeiten“; Dissertation in Vorbereitung, Universität Innsbruck.
- Hilti, Fastening Technology Manual, Rebar Fastening Guide B 2.2, 1994
- Hilti, Fastening Technology Manual, Adhesive Anchors B 3.2, 1994
- Hilti, Fastening Technology Manual, Rebar Fastening Guide for Overlays, B 2.3, 1997
- CEB-Guide; On the Design of Fastenings in Concrete, Part 3, Draft March 95  
Characteristic Resistance of Fastenings with Cast-in-Place Headed Anchors.