Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte

Band: 999 (1997)

Artikel: Stress-strain distribution in the contact surface of a two-layered RC

structural element

Autor: Sumec, Jozef / Jendzelovsky, Norbert

DOI: https://doi.org/10.5169/seals-976

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Mehr erfahren

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. En savoir plus

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. Find out more

Download PDF: 28.11.2025

ETH-Bibliothek Zürich, E-Periodica, https://www.e-periodica.ch

Stress-Strain Distribution in the Contact Surface of a Two-Layered RC Structural Element

Jozef SUMEC Assoc. Professor Fac. of Civil Eng. Bratislava, Slovakia

Jozef Sumec, born 1945, received his civil eng. degree 1968, PhD degree 1975, DSc degree 1990.

Norbert JENDZELOVSKY

Assoc. Professor Fac. of Civil Eng. Bratislava, Slovakia

Norbert Jendzelovsky, born 1958, received his civil eng. degree 1982, PhD degree 1981.

Summary

The contribution deals with the time-dependent analysis of the state of stress and strain distributions on the contact surface of a reinforced concrete two layered element (in the sense that "new material" means topping layer and "old material" means prestressed plate structure). We suppose that the structural system is linearly viscoelastic quasihomogenic isotropic continuum. The linear aging model for concrete creep is used. The theoretically derived solution procedures are examplified by particular numerical examples.

1. Mathematical Formulation of the Problem

We will deal in our analysis with the quasistatic problem of the two-layered planar composite structure with technologically conditioned defects. We suppose that the principles of the linear theory of viscoelasticity are valid. The mathematical representation of the discussed physical model is the operator equation [1]

$$L\left(\mathbf{u}\right)=\mathbf{f}\tag{1}$$

in the domain $\Omega = \Omega_1 \cup \Omega_2$ ($\Omega \subset E_3$) which is bounded per partes smooth surface $S = S_1 \cup S_2$ ($S_1 \cap S_2 = \emptyset$), $\mathbf{u} = \mathbf{u}(P, t) = \{\mathbf{u}(x, y, z, t), \mathbf{v}(x, y, z, t), \mathbf{w}(x, y, z, t)\}$ is a sufficiently smooth vector-function, where $P \in \Omega$, $t \ge 0$. The solution of the Eq.(1) satisfied the following conditions

$$u^{\lambda} = 0$$
 on S^a, S^b (2)

$$\sigma^{\lambda\kappa} n_{\kappa} + \sigma^{(0)\kappa\mu} n_{\kappa} u^{\lambda}_{,\mu} = \overline{F}^{\lambda} \qquad \text{on } S - (S^{\bullet} \cup S^{b}),$$
 (3)

$$u^{\lambda}\big|_{\Omega_1} = u^{\lambda}\big|_{\Omega_2}$$
 on $\Omega_1 \cap \Omega_2$. (4)

This problem is equivalent to the problem of finding the element of energetic space which minimalize energetical functional [1,2]

$$F(u) = (u,u)_{L(x)} - 2(u,f)$$
 (5)

The basic idea of FEM is to represent the displacement functions $\mathbf{u} = (u, v, w)$ within the element by continuum shape functions of the form

$$u(x, y, z, t) = \sum_{i=1}^{L} N_i(x, y, z) u_i(t), ...$$
 (6)

where N_i (i = 1,2,...L) are the shape functions associated with the L nodes and u_i (i = 1,2,...L) are nodal values of the displacement u(x,y,z,t), etc. The strain rate field within the element can be defined as [3]

$$\dot{\varepsilon}(x,y,z,t) = \mathbf{B}(x,y,z)\dot{\delta}(t),\tag{7}$$

where **B** is a matrix of gradients of the shape functions and δ is the nodal velocity vector. The equilibrium of the stress rates $\dot{\sigma}$ is given by

$$\sum_{\forall e} \int_{Ve} \mathbf{B}^{\mathrm{T}} \dot{\sigma} \, dV = \dot{\mathbf{R}}^{\mathrm{a}} \,, \tag{8}$$

where $\dot{\mathbf{R}}^{\bullet}$ is the applied nodal load rate vector. The stress-strain relationship for inelastic rate processes may be given by the formula

$$\dot{\sigma} = \mathbf{D}(\dot{\varepsilon} - \dot{\eta}), \tag{9}$$

where **D** is elasticity matrix and $\dot{\eta}$ is the creep strain rate (for instance)

$$\dot{\eta} = \Re(\sigma, t, T)$$
.

We may transform the system of equilibrium equations into the matrix equation

$$\mathbf{K}\dot{\delta} = \dot{\mathbf{R}}^{a} + \dot{\mathbf{R}}^{\eta}$$
 on Ω , (10)

where $\mathbf{K} = \sum_{e} \int_{\mathbf{V}e} \mathbf{B}^{T} \mathbf{D} \mathbf{B} dV$ is the assembled stiffness matrix and

$$\dot{\mathbf{R}}^{\eta} = \sum_{\epsilon} \int_{V^{\epsilon}} \mathbf{B}^{\mathsf{T}} \mathbf{D} \, \dot{\boldsymbol{\eta}} \, dV \tag{11}$$

is the vector of the creep process. After some rearrangements Eqs (10) and (11) can be written in he incremental form over a time interval

$$\mathbf{K}\Delta\delta = \Delta\mathbf{R}^a + \Delta\mathbf{R}^{\eta} \qquad \text{on } \Omega, \tag{12}$$

where

$$\Delta \mathbf{R}^{\,\eta} = \sum_{\mathbf{e}} \int_{\mathbf{V}^{\mathbf{e}}} \mathbf{B}^{\mathrm{T}} \mathbf{D} \, \Delta \eta \, \mathrm{dV} \,. \tag{13}$$

Numerical schemes for the solutions of Eqs (12), (13) are discussed in [4].

2. Linear Aging Concrete Creep and Shrinkage Model

The characteristic of concrete that distinguishes it from the traditional viscoelastic material is the aging effect. Experimental tests [5] indicate that response on the increment of load is independent of all other part load increments, so that the principle of superposition is valid. Due to this fact the integral-type creep law has the form [6]

$$\varepsilon(t) = \int_{0}^{t} \prod (t, t') d\sigma, \qquad (14)$$

where

$$\prod (t,t') = J(t,t') \begin{bmatrix} 1 & -v & -v & & & & \\ -v & 1 & -v & & & & \\ -v & -v & 1 & & & & \\ & & & \frac{1}{2}(1+v) & & & \\ & & & & \frac{1}{2}(1+v) \end{bmatrix}$$

and

$$J(t,t') = \frac{1}{E(t')} + \sum_{j=1}^n \widehat{A}_j^{-1}(t')(1-e^{-(t-t')/\tau_j}), \ E(t') = E_{28}\sqrt{\frac{t}{4+0.85t}} \ ,$$

where τ_j are constants (retardation times) and \hat{A}_j are aging coefficients. For shrinkage of concrete we can assume the relation [6]

$$\varepsilon_{ab}(t) = 0.0008c'(t-7)/(35+t-7)$$
(15)

in which t is in days and drying is assumed to begin at $t_0 = 7$ days, $c' = \prod_{i=1}^{6} c_i$ is correction factor [6].

3. Numerical Example

This section deals with the numerical solution of some viscoelastic aging creep problems - two layered reinforced concrete plate with a prestressed lower layer. The analysed plate is simply supported in positions a and b (Fig. 2). The length of the system is 6000 mm, width 1190 mm. The thickness of the lower layer is 70 mm and upper concrete layer 170 mm, respectively. The cross-section of the given structure is in Fig.1




Fig. 1 Cross-section of the plate system

The plate carries a uniformly distributed load with the intensity $q = 5.68 \text{ kN} / \text{m}^2$ (dead load) and a line load with the intensity p = 20.07 kN/m (Fig.2). The triangle represents the course of the prestressed force in the individual strings. The prestress on 8 wires ϕ 5mm is realised.

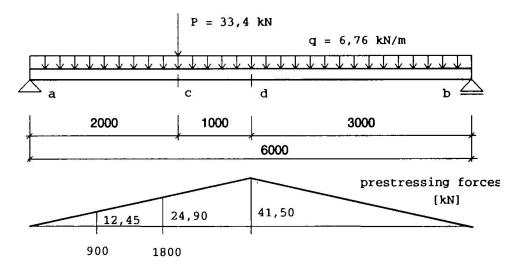


Fig. 2 Longitudinal section and values of prestressed forces

Characteristics of the materials are as follows: a lower concrete layer of type B 30 (E_1 = 32500 MPa) according to the code STN 73 1201 [7] and an upper layer B 20 (E_2 = 27000 MPa), respectively. The following cases were considered:

- 1) upper layer shrinking, lower layer non creeping □ s/nc
- 2) both layers creeping

O c/c

The time intervals taken: 0, 5, 10, 20, 50, 100, 300, 500, 1000 and 3000 days. We assume a 28 day time interval for hardening of concrete. The top layer was laid down after 200 days. Between the layers the conditional technological horizontal defect range of the half-span was taken into account, too (case B). It means, that the following cases were solved:

- A without defect on section a b
- B with defect on the section a d.

Figs 3 and 4 represent the time - dependet vertical deflections in the half-span of the system.

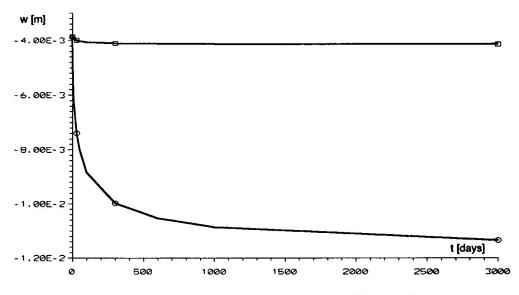


Fig. 3 Vertical deflections w(d,t) for case A, \square s/nc, O c/c

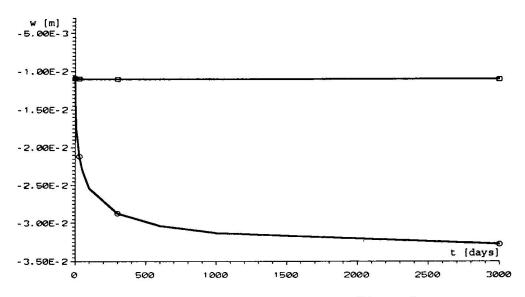


Fig. 4 Vertical deflections w(d,t) for case B, \square s/nc, O c/c

Normal and shear stresses for individual cases (A and B) under line - load (position c - where max. bending moment was expected) were calculated. Courses of normal stresses σ_x for cases A and B are given in Figs 5 and 6.

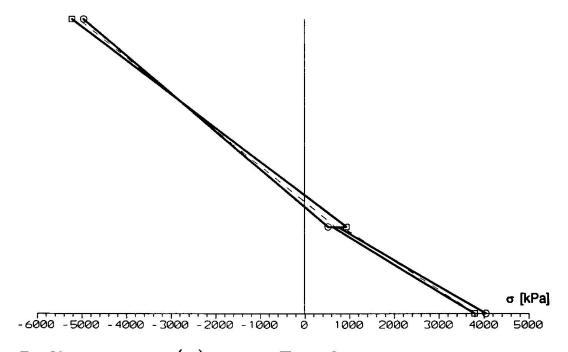


Fig. 5 Normal stresses $\sigma_x(c,t)$ for case A; \square s/nc, O c/c. The full lines represent values $\sigma_x(c,t\to\infty)$ and dashed line $\sigma_x(c,t\equiv0)$

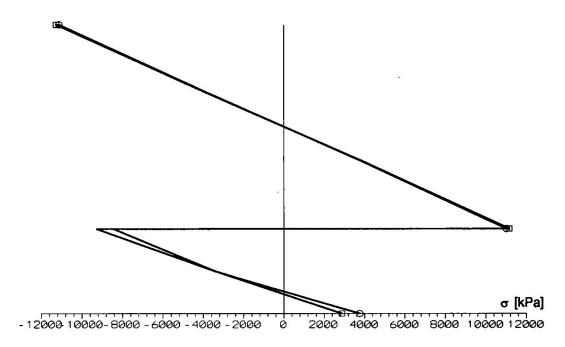


Fig. 6 Normal stresses $\sigma_x(c,t)$ for case B; \square s/nc, O c/c. The full lines represent values $\sigma_x(c,t\to\infty)$ and dashed line $\sigma_x(c,t\equiv0)$

4. Conclusions

- on the interface of the layers cumulation of the shear stresses on the perimeter of the structure occured
- creep deflection was 3 time larger than classical elastic deflection, that positively influence the course of the stresses
- the presence of technologically conditioned defects on the interface of the layers negatively influenced the stiffness of the system, in spite of the prestress on the lower layer
- a very significant element of the layered system is the technological surfacing, of the interface of the layers.

Acknowledgement: The writers are grateful for support from the Grant Agency VEGA, Grant No. 2/1264/94

References

- 1. Mikchlin, S. G.: Variational Methods in Mathematical Physics (in Russian), Nauka, Moscow 1970.
- 2. Washizu, K.: Variational Methods in Elasticity and Plasticity. 3rd Ed., Pergamon Press, N.Y., Oxford, Tokyo, 1982.
- 3. Zienkiewicz, O.C.: The Finite Element Method. 3rd Ed. McGraw-Hill, N.Y., 1977
- 4. Wiliam, K.J.: Numerical solution of inelastic rate processes. Comp. & Struct., <u>8</u>,1978, pp. 511-531.
- 5. Sumec, J.: Mathematical modelling of materials with time-dependent physical properties (in Slovak). Internal Research Report III-3-4/9.4, USTARCH SAV, Bratislava 1983
- 6. Bažant, Z.P.: Theory of creep and shrinkage in concrete structures: a precis of recent developments. Mech. Today, 2, 1975, pp 1-93.
- 7.STN 73 1201. Design of concrete structures.