

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 77 (1998)

Artikel: Tests of reinforced concrete strengthened with CFRP plates
Autor: Kaminska, Maria / Kotynia, Renata
DOI: <https://doi.org/10.5169/seals-58216>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 01.04.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>



Tests of Reinforced Concrete Strengthened with CFRP Plates

Maria KAMINSKA

PhD, M.Sc.
Technical Univ.
Lodz, Poland



Renata KOTYNIA

M.Sc.
Technical Univ.
Lodz, Poland



Summary

This paper presents the results of the research carried out on five beams strengthened with CFRP plates (Sika CarboDur - System). The model of failure of the beams was discussed and compared with an examination of strains and loading capacity of a section. The last one based on the nonlinearity of concrete, reinforcing steel and linear relationships σ - ϵ of the CFRP plates and the glue was in accordance with an experimental test. The influence of plates bonded to the both vertical sides of the beam in a support region on a load-bearing capacity was firstly considered.

1. Introduction

The investigations presented below were carried out in order to provide with data for verifying the assumed analytical model concerning the bending and also to test the influence of additional carbon plates attached to side surfaces of the element in its support zones for anchorage conditions of the plates.

2. Experimental investigations of the beams strengthened with the plates

Five single-span beams (dimensions and loading scheme shown in fig.1) have been tested. CFRP plates were attached to properly cleaned beam surface with CFK-Sikadur-30 adhesive, recommendations of applying given by the producer of the strengthening system were precisely followed.

Basic information concerning the beams reinforcement and the mode of strengthening is presented in table 1.

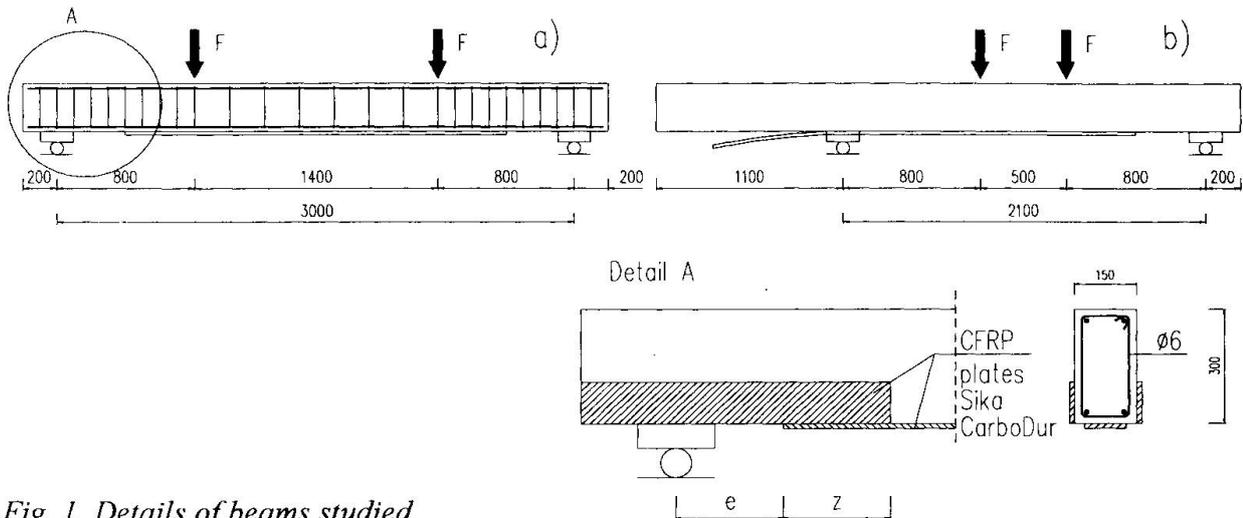


Fig. 1. Details of beams studied

Table 1. Details of test beams

Beam	Reinforcement ratio/bars	CFRP-plate (see Fig. 1)			Concrete strength ²⁾ , MPa				Ultimate load 2F, kN
		type	e, mm	z, mm	$f_{c,cube}$	f_c	$f_{ct,sp}$	E_c	
B-04/S1	0.0039 2#10	S	150	-	33.8	28.4	2.8	23400	120
B-04/S2			300	-	51.3	36.6	3.2	29000	90
B-04/M		M	150 ¹⁾	-	33.2	29.7	3.0	25000	120 (M) 120 (S)
B-06/S	0.0056 2#12	S	250	200	35.4	32.3	2.9	27400	140
			250	500					145
B-08/S	0.0084 3#12	S	150	-	43.0	33.8	3.0	27300	180

1) half plate on both vertical sides of the beam
 2) cubes 150×150×150mm, cylinders 150×300mm, E_c after DIN 1048

Conclusions

The investigations confirmed full cooperation within the pure bending zone of CFRP plate with the section strengthened in this manner. Thus it is reasonable to assume in the analysis the plane section principle. In the analysis as well material nonlinearity of the concrete and the tension stiffening principle were assumed. The proposal calculation model enables to evaluate the bending moment - curvature (or strain) relationship within the whole range of loading and thereby to estimate the value of cracking moment, reinforcement yielding moment and the ultimate moment resulted from limiting the strain of any of the materials in the section. It is also easy to estimate how much the load capacity of the plate may be used, if we know dimensions, the reinforcement ratio and material characteristics of the strengthening element.

Further investigations concerning anchorage zones of the plates are necessary. They are continued in Concrete Structures Department of Technical University in Lodz. Test on beams strengthened with CFRP plates and subjected to the cyclic load are foreseen to undertake soon.