

**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte  
**Band:** 77 (1998)

**Artikel:** Strengthening beams in the shear zone  
**Autor:** Kosinska, Anna  
**DOI:** <https://doi.org/10.5169/seals-58227>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 01.04.2026

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**



## Strengthening Beams in the Shear Zone

**Anna KOSINSKA**  
Dr. Engineer  
Technical University of Lodz  
Lodz, Poland



Anna Kosinska received her civil engineering degree from Technical University of Lodz in 1971 and PhD in 1981. She is currently an lecturer in the Department of Concrete Structures at Technical University of Lodz.

### Summary


The paper consists of two parts. The first one presents the problem of strengthening the beams damaged in the shear zone in real industrial building. The analysis of serviceability and limit states was made and two ways of strengthening were design. Second part presents the experimental study on two reinforced concrete beams, underreinforced in the shear zone. One of them was strengthened by externally epoxy bonded steel plates, after loading of about 70% of its ultimate capacity.

### 1. Strengthening the concrete girders in the Textile Factory in Lodz

Two of all two-span box-girdes of the saw-tooth roof konstruktion of the spinning mill building were significantly cracked, closed to the intermediate support. The roof consists of triangular concrete prefabricated frames supported on these girders and covered with bearing bush plates. The main beams have the cross-section dimensions of  $1.00 \times 1.35\text{m}$  and the spans of 18.0m. Their inner spaces are used to pull out air from the air-conditioning. Structural, statical and limit state analysis has been done, based on the investigation carried out in the building. There are few diagonal cracks on the side surfaces of the girders with the widths of 0.3 to 1.0mm, exceeding the limit values. The study of this case shows, that diagonal cross-section with the maximum crack width works in the worse conditions of the combined shear and bending. There are also effects of stresses due to shrinkage caused by the pull out air inside the girders and dry of the concrete. Ultimate shear capacity of the craced sections was calculated by the Polish Code method. The design shear resistance exceeds the shear force due to load, but with respect to serviceability limit state, two alternatives of strengthening the craced region were design as shown in fig. 1. Alternative b) represents the plate bonding technique and alternative a) is the traditional method of mechanical bonded external stirrups.

### 2. Experimental tests

There were tests made in the laboratory of the Concrete Structures, Technical Univ. of Lodz, to check out shear behaviour of RC beam strengthened by epoxy resins bonded steel plates under repeated load (see fig. 2).

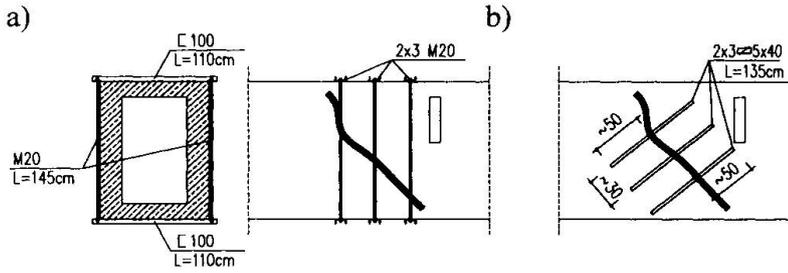

Two beams ( $b=0.20\text{m}$ ,  $h=0.30\text{m}$ ) were made as underreinforced in the shear zone. The control beam BS-0 was not repaired and the beam BS-2 was first preloaded to about 65% of its ultimate load and precracked. Next it was strengthened by steel plates  $5\times 40\text{mm}$ , bonded and

Fig. 1. Designed alternatives of strengthening

anchored to side faces in the support region using epoxy resins. Both beams failed as the result of diagonal tension cracking in the shear span regions. The effectiveness of the strengthening was 19 percent. The strengthened beam BS-2 failed prematurely by tearing off the concrete and plates before yielding of the external reinforcement. The stresses in the steel plates at failure were only  $0.19f_y$ . Their full ultimate capacity was not developed. But the stirrups were significantly unloaded (about 70%) by the external reinforcement comparing with the control beam, short before failure - see fig 3. It appeared to be important problem how to design the strengthening to avoid the premature failure of the beam. The strength of repaired concrete should be high enough and the maximum shear and peeling stresses at the interface should not exceed the limiting values at which tearing of the concrete takes place.

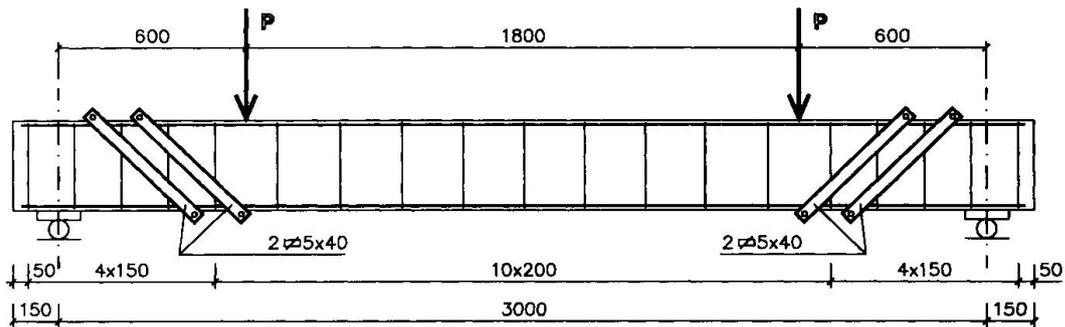


Fig. 2. Beam BS-2

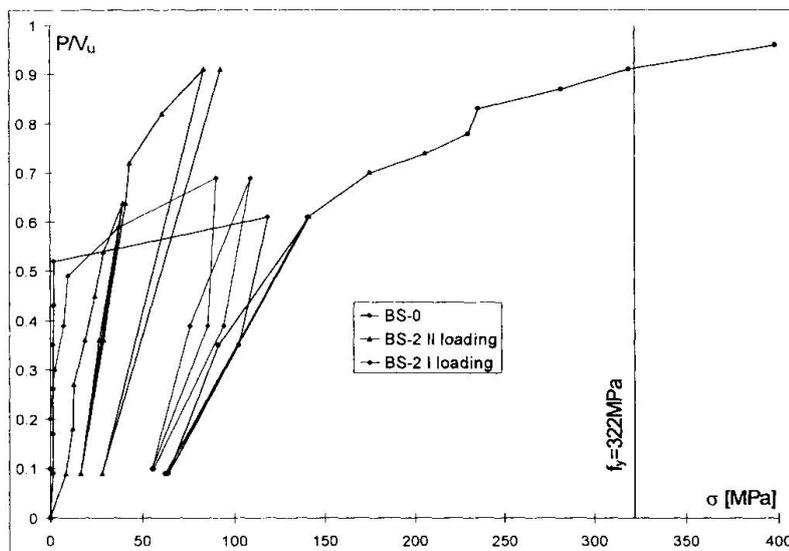


Fig. 3. Stresses in stirrups