Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte

Band: 79 (1998)

Artikel: Aramid fibers used for bridge repair and strengthening

Autor: Salvaverria, Jorge H. / Casas, Joan R.

DOI: https://doi.org/10.5169/seals-59893

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Mehr erfahren

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. En savoir plus

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. Find out more

Download PDF: 26.11.2025

ETH-Bibliothek Zürich, E-Periodica, https://www.e-periodica.ch



Aramid Fibers Used for Bridge Repair and Strengthening

Jorge H. SALAVERRIA Research Assistant Techn. Univ. of Catalunya Barcelona, Spain Joan R. CASAS Prof. Techn. Univ. of Catalunya Barcelona, Spain

Summary

The paper presents the experimental tests designed to improve the existing techniques of bridge repair by the combination of external prestressing and aramid fibers (AFRP). The external prestressing substitutes the damaged prestressing steel and aramid strips will play, in the repaired bridge, the role of the corroded reinforcing steel. The first phase comprises the study of the bond characteristics of the composite when applied to a concrete surface considering different epoxi adhesive and placement. The sechond phase consists on the strengthening in shear and bending of a two span (7m + 7m) continuous prestressed concrete box-girder model previously damaged. The original beam was firstly loaded ocurring an important damage. After load removing, the beam is repaired and strengthened using AFRP and loaded again up to failure to compare the ultimate capacity.

1. SCOPE OF THE EXPERIMENTAL TESTS

The experimental work comprises two phases. In phase one the objective is to develop a theoretical model of the interface aramid-adhesive-concrete. To this end, a set of concrete-aramid specimens are considered. In the bottom face of the specimens a strip of aramid is glued using different adhesives and different preparation of the concrete and fiber surface before bonding. With the correct surface preparation before bonding and the most appropriate properties of the adhesive with the composite, the tension in the interface is increased to 3.5 MPa; this value is approximatelly the concrete tensile strength. Good bonding properties were obtained in the dynamic tests too, where the specimens resist more than 2 million cycles of a 2 Hz armonic force without debonding of the aramid strip. The force amplitude ranges from 0.3 to 0.7 of the failure load measured in the static tests.

Tests in the undamaged beam. The beam V1 is loaded up to failure. The two loads(Q) are only applied in one of the spans (Figure 1). During the test to failure different variables are continuously monitored as load increases. The monitoring of slip of prestressing tendon at deviators is very important in order to compare the experimental results with those coming from a theoretical model, where the possibility or not of tendon slip should be considered.


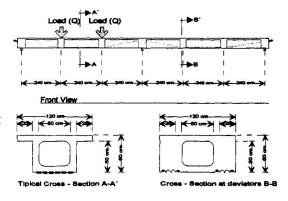


Figure 1. Definition of the two-span prestressed box girder beam.



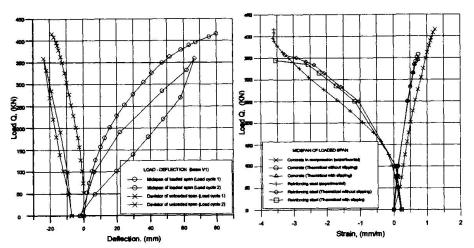


Results- In figure 2 are shown some load-deflection curves obtained in the original undamaged beam in the test up to failure. The strains in concrete and reinforcing steel measured with strain gages are presented too.

Figure 2. Results in the original undamaged beam in the test up to failure.

Repair and strengthening. Severe damage was provoked to the beam in the test up to failure. The repair method tried to simulate as close as possible the repair sequence that will be used in an existing bridge. The original reinforcing steel is replaced by bonding aramid strips (Length: 3000mm., Width: 20 mm., Thickness: 4 mm. each).

Tests in the repaired beam. The same experimental arrangement and instrumentation as in the undamaged beam were disposed to obtain the experimental results in the same locations monitored in the previous test to compare the behaviour of undamaged and repaired beam.

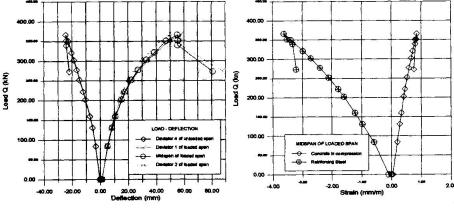

Results- (see figure 3)
The ultimate load was
360 kN which is very
close to the final load
400 kN in the
undamaged beam. The
final failure was quite
brittle. The ultimate load
was achieved by the
sudden and progressive
2005 failure of the bonding
between aramid strips
and concrete. Once the
strips failed, the load

Figure 3. Experimental results in the repaired beam.

carried by them was suddenly transmitted to the prestressing steel that was beyond the yield limit, causing the final rupture of the beam.

2. CONCLUSIONS

The tests show how the repair and strengthening technique based on the use of AFRP strips and external prestressing seems to be very promising even for heavily damaged structures. In fact the ultimate load in the repaired beam was almost 90% the ultimate load in the undamaged beam. The strips externally bonded to the concrete seem to provide some crack control. Due to the brittleness of the rupture of concrete in tension, the failure of bonding concrete-aramid is brittle too, and so is the global failure of the repaired beam. The high tensile strength of the aramid material is under-used.