**Zeitschrift:** IABSE reports = Rapports AIPC = IVBH Berichte

**Band:** 79 (1998)

**Artikel:** Estimation of the remaining fatigue life of a railway bridge

Autor: Kim, Sang-Hyo / Mha, Ho-Seong / Lee, Sang-Woo

**DOI:** https://doi.org/10.5169/seals-59894

#### Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Mehr erfahren

#### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. En savoir plus

#### Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. Find out more

**Download PDF: 28.11.2025** 

ETH-Bibliothek Zürich, E-Periodica, https://www.e-periodica.ch



# Estimation of the Remaining Fatigue Life of a Railway Bridge

Sang-Hyo Kim
Head of Dept of Civil Eng.
Yonsei Univ.
Seoul, Korea

Ho-Seong MHA Researcher Yonsei Univ. Seoul, Korea

Sang-Woo LEE Grad. Student Yonsei Univ. Seoul, Korea Sang-Hyo Kim, born 1956, received his civil engineering degree from Yonsei Univ. in 1979 and Ph.D. from Univ. of Illinois in 1986.

Ho-Seong Mha, born 1963, received his civil engineering degree from Yonsei Univ. in 1986 and Ph.D. from Oregon State Univ. in 1996.

Sang-Woo Lee, born 1969, received his civil engineering degree in 1996 and MS from Yonsei Univ. in 1998.

### Summary

The *Dangsan* steel railway bridge was located in Seoul, Korea, crossing the famous Han river for subway traffics (The old bridge was disassembled and a new bridge is under construction at the same location). Upon requests, the bridge had undergone many inspections near the end of its service life since it was reported that there were several fatigue cracks found, and the city authority considered deeply about the safety of the bridge. The remaining life of the bridge had been estimated through the field measurements and the corresponding fatigue test conducted. The results are briefly presented herein.

### 1. The Bridges



Fig. 1 The Dangsan bridge

The bridge consisted of three units of three-spancontinuous steel Pratt truss with length 90-90-90m for its main spans in the middle and plate girder bridges on both ends. The picture, profile and corresponding FEM model are depicted in Fig. 1, 2, and 3, respectively. The bridge was made to serve the subway traffics only, and was experiencing about 510 trains daily in two way system.

Via both visual and ultra sonic inspections, most cracks were found from the floor systems (specially, stringers), and improper welding were also found. Based on the inspection and structural analysis, the critical members, which

was assumed to dominate the remaining life of the whole bridge, were determined. Some peculiar details, of which the category was hard to be determined, were observed, and corresponding experimental models were manufactured to conduct fatigue test to determine the appropriate category for the details.



Fig. 2 Profile of the bridge

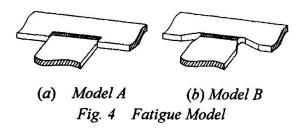


Fig. 3 FEM model




### 2. Fatigue test

Some upper chords connected with bracings were found to have peculiar details at the connections of gusset plates due to the bad manufacture (See Fig. 4a). About 2cm of flange edges were cut off, and then the gusset plates were attached. Fatigue tests were carried out to identify the fatigue strength of these particular details. Based on visual inspections, experimental fatigue models were made to simulate the actual welding and



manufacturing conditions by applying the improper cutting and welding to the flange edges. Repairing method was proposed by finishing the rectangular corner at the welding parts in the round shape according to AASHTO, which may improve the fatigue strength of the detail. Two models were prepared: with actual condition (model A); with proposed condition (model B) shown in Fig. 4a, b, respectively. In addition, the experimental models with typical details were also prepared for fatigue test to compare the results with those of other two models. Upon the test results, the Fatigue strengths for each model were measured and plotted on the AASHTO's S-N curves (Fig. 5). Fig. 5a is the result of the model A which simulates the actual detail condition, and Fig. 5b is the result of model B with the repaired detail. The model A shows that the fatigue strength is a little lower than Category E due to the improper details, but clearly higher than Category E'. The model B shows an apparent improvement.

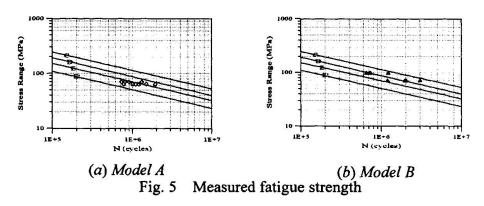

## 3. Estimation of Remaining Fatigue Life

The stresses due to the applied loads on the bridge vary randomly, and this results from the uncertain nature of the input variables, which are traffic schedules, passenger volumes, and so The coincident incidents of two trains crossing the bridge at the same location were also considered, since it produced the worst loading conditions. The coincident rate was numerically simulated based upon the provided time schedules of subway trains. It is not possible to obtain all the stress time histories for each loading condition from field measurements, due to the complexity of loading conditions. Consequently, a finite element method (See Fig. 3) was utilized to provide the time history for each loading condition, and the simulation results were modified according to the measured field data. Field measurements were conducted mainly through strain gages on the critical main members, which were selected from structural analysis. Two loading conditions for field measurements were considered: One was the normal traffic condition; The other was the controlled traffic condition. Under normal condition, tests were performed in a day while the trains traveled at the normal speed The passenger volumes were obtained from visual survey at the station with passengers. nearby. Under controlled situation, the tests were performed with the empty trains transferred The trains were traveling at speeds from 5km/h to 80km/h. emission tests were also conducted to verify the possibility of crack growth, and some cracks were found to be growing. By using the stress ranges obtained from the loading simulations, the remaining fatigue lives of main truss members were estimated and found to be reasonable.