

Zeitschrift: IABSE reports = Rapports AIPC = IVBH Berichte
Band: 82 (1999)

Artikel: CFRP-tendons - development and testing
Autor: Roos, Frank / Noisternig, J.F.
DOI: <https://doi.org/10.5169/seals-62164>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 05.08.2025

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

CFRP-Tendons - Development and Testing

Dipl.-Ing. Frank ROOS

Lehrstuhl für Massivbau
Technische Universität München
Munich, Germany

Frank Roos, born 1969, received his civil engineering degree in 1997. He is now a research assistant at the Lehrstuhl für Massivbau at the Technische Universität München conducted by Univ.-Prof. Dr.-Ing. Konrad Zilch.

Dr. J.F. NOISTERNIG

Dywidag Systems
International GmbH (DSI)
Munich, Germany

Johannes F. Noisternig, born 1966, received his doctoral degree in mechanical engineering in 1995. 1991 - 1995 he was a research assistant at the Institute for Composite Materials (IVW) at the University of Kaiserslautern. Since 1996 he is the head of the polymer group in the technical department of DSI.

Abstract

CFRP (Carbon Fibre Reinforced Plastics), developed for the aerospace and aircraft industry, are increasingly becoming an interesting material for civil engineering. Especially the strength and stiffness in relation to weight makes them an ideal material for cable-stayed bridges.

The aim of a common research project, sponsored by the Bavarian Ministry of Economy, Traffic and Technology and conducted by the Technische Universität München (Lehrstuhl für Massivbau) and DSI (DYWIDAG Systems International), was to develop a CFRP-tendon.

Since 1983 stay cable specimens and anchoring systems have been tested at the Technische Universität München. With the testing machine (figure 1) it is possible to apply forces up to 19000 kN in dynamic and static tests.


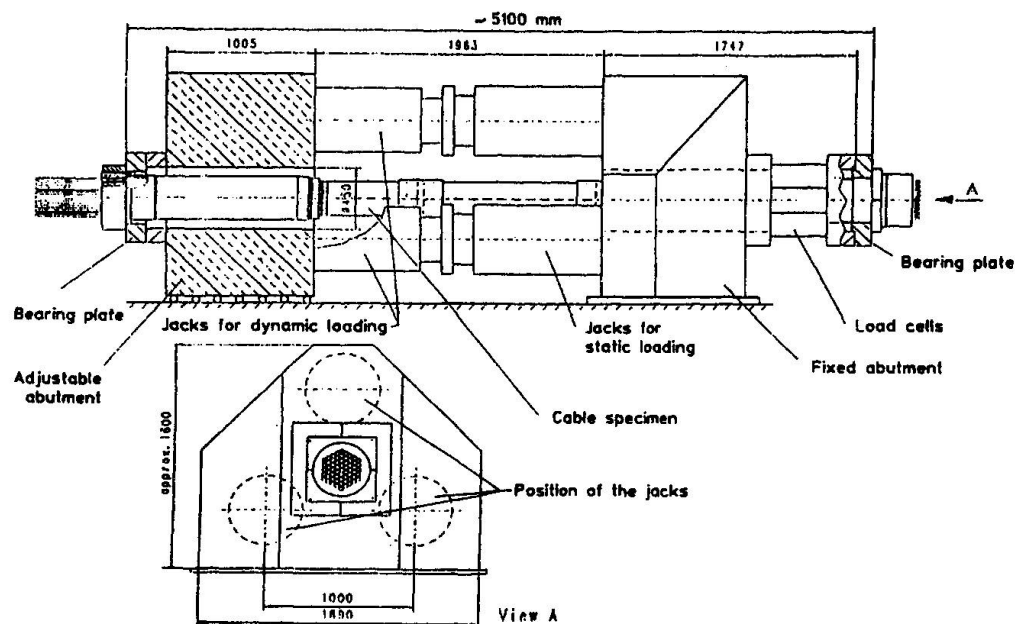



Figure 1: Stay cable testing equipment at the Technische Universität München




This paper deals with the development and the testing of this CFRP-tendon. The major problem are the anchorage systems where high forces have to be applied to the cable specimen. A FEM calculation verified by tests builds up the foundation for a practical anchorage system. The constant development led to the anchorage system for 91 CFRP wires, which was tested under dynamic (according to the PTI recommendations for stay cables) and subsequent static load in 1998.

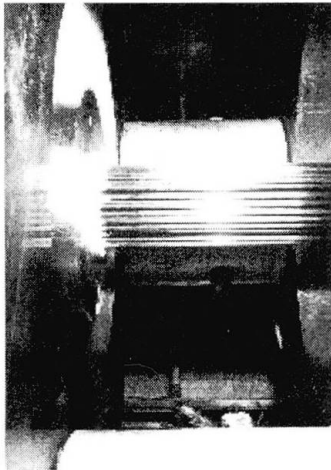

*Figure 2:
Anchorage before the
ultimate strength test*

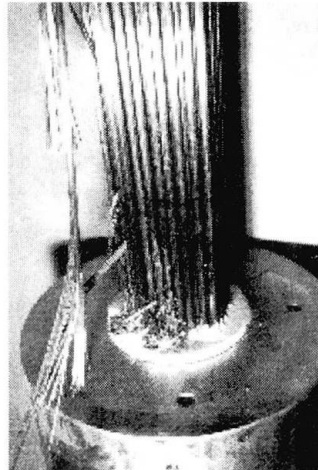

*Figure 3:
Wire fracture at the
anchorage*

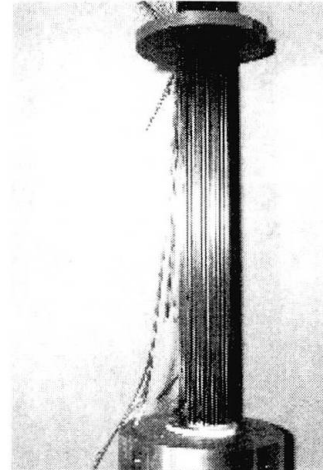

*Figure 4:
part of the free length of the
specimen*

During the fatigue test no wire fracture occurred in the free length or in the anchorage of the cable specimen. The displacement of the adjustable abutment (anchor block) at maximum load increased due to the application of two million load cycles by 1.10 mm. This elongation was mainly caused by the pull-out of the potting material from both steel hulls. The stay cable showed very good dynamic properties as expected from CFRP. After the fatigue test was completed the static load test was performed. The cable was loaded up to a load of 3600 kN. The ultimate load of a single CFRP-wire was 50 kN. Corresponding to these value the ultimate load of the cable is equivalent to 78% of the theoretical ultimate strength. The specific elongation of the whole cable specimen corresponding to this load was about 1,9 %. The test was stopped after six wire fractures of which the first occurred at a load of 3500 kN. Due to the type of material the wires failed in the linear elastic region of the stress elongation line. The cable specimen broke wire by wire not as suspected with a sudden fracture of the whole cable specimen. Figure 2 shows the specimen at the anchorage before the ultimate strength test. The wire fractures are shown in figure 3 and 4.