

Zeitschrift: Helvetica Physica Acta

Band: 51 (1978)

Heft: 1

Artikel: Magnetoelastic effects on the elastic constants of HoAl₂

Autor: Godet, M. / Walker, E.

DOI: <https://doi.org/10.5169/seals-114940>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 22.02.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Magnetoelastic effects on the elastic constants of HoAl_2

by **M. Godet** and **E. Walker**

Université de Genève, Département de Physique de la Matière Condensée,
32, Bd. d'Yvoy – 1211 Genève 4 – Switzerland

(27. X. 1977)

Abstract. Measurements of the elastic constants C_{11} and C_{44} of single crystalline HoAl_2 are reported from 4.2 K up to 280 K. In the paramagnetic region the results are interpreted in terms of the magneto-elastic coupling.

Introduction

Magnetoelastic coupling in the paramagnetic region of RE- Al_2 (RE = rare earth) intermetallic compounds has been the subject of several recent works. At present, single crystal elastic constants of CeAl_2 [1] (only two constants), PrAl_2 [2], NdAl_2 [2], GdAl_2 [3, 4], TbAl_2 [5] and DyAl_2 [6] (only two combinations) are reported. The analysis of these results in terms of the interaction between the strains and the crystal electric field (CEF) leads to the quantitative evaluation of the magneto-elastic coefficient [1, 2, 7].

The object of this paper is to present the temperature dependence of the elastic constants C_{11} and C_{44} of single crystalline HoAl_2 . Moreover we give the value of the magnetoelastic parameter of the C_{44} constant.

Experimental results

RE- Al_2 intermetallic compounds crystallize all in the cubic MgCu_2 Laves phase [8]. At low temperature, HoAl_2 orders ferromagnetically and the Curie point is $T_c = 29$ K [9]. Below this temperature the magnetic moment rotates from the (110) direction to (100) at 20 K [10], this anomaly appears in particular on the magnetic specific heat curves [9].

The CEF that acts on the free Ho^{3+} ion gives rise to the triplet Γ_5 [1] as ground state and the B_l^m crystal field parameters are [11]:

$$B_4^0 = -7.54 \times 10^{-4} \text{ K}$$

$$B_6^0 = 7.43 \times 10^{-6} \text{ K}$$

The HoAl₂ compounds were prepared from 99.9% pure RE and 99.999% pure aluminium. The single crystal has been grown by the Czochralski method [12]. As HoAl₂ corrodes very strongly the tungsten crucible, it was extremely difficult to obtain a good quality (110) orientated crystal. The one we got did not allow us to measure the complete set of elastic constants C_{11} , C_{12} and C_{44} with sufficient accuracy. We shall present here only the C_{11} and C_{44} modes for a (100) orientated crystal.

By spark cutting and polishing we obtained a sample of approximately 4 mm diameter and 10 mm length with faces parallel within 0.1 μ , the misorientation was smaller than 1°. Room temperature density was 6.047 ± 0.005 gr/cm³ which compares well with the theoretical density of 6.085 gr/cm³ [13].

Ultrasonic velocity was determined by the usual ultrasonic technique at a 10 MHz frequency. From 4.2 K to 35 K temperature was measured with a germistor and for higher temperature up to 280 K with a copper konstantan thermocouple. The absolute temperature accuracy was ± 0.5 K in the region of 25–45 K and ± 0.1 otherwise.

We measured the velocity in the (100) direction of propagation, this leads to the C_{11} and C_{44} elastic constants.

Results are shown on Fig. 1. At 20 K a sharp pic appears on both modes which

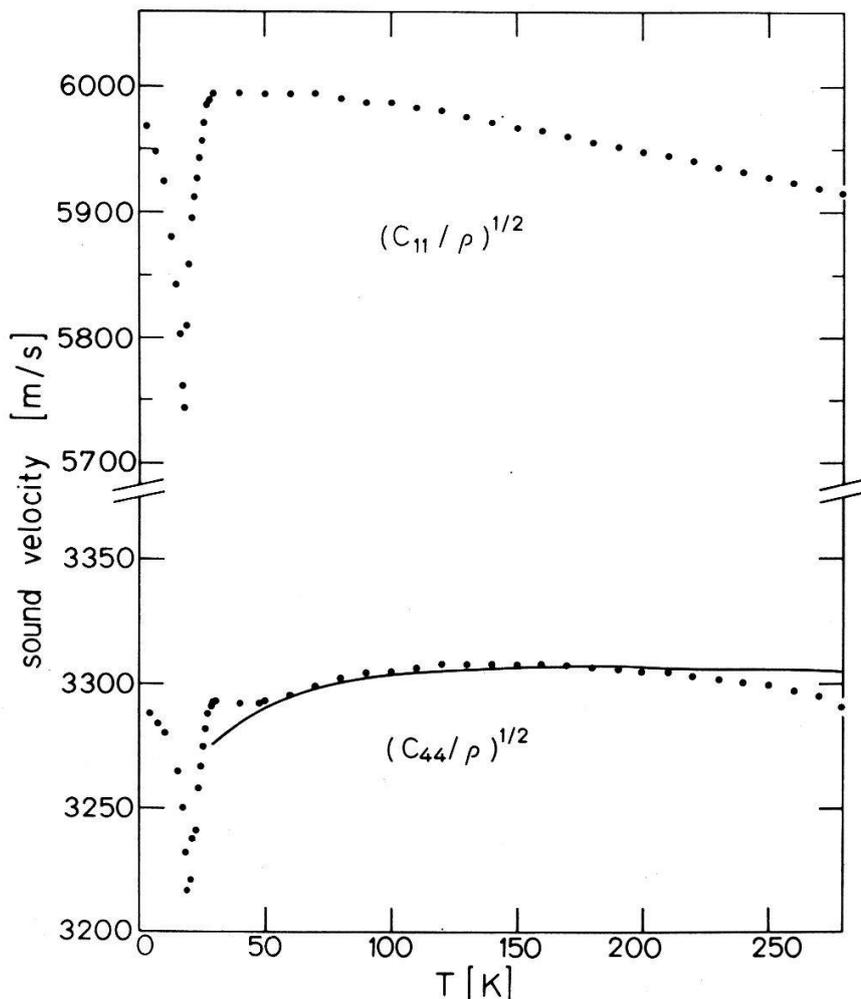


Figure 1
Sound velocity of HoAl₂ for the C_{11} - and C_{44} -modes.

corresponds to the rotation of the magnetic moment [10]. In the case of the C_{11} -mode this pic represents a decrease of 3.8% of the sound velocity and 1.5% of the C_{44} -mode. We found $T_c = 29$ K for the Curie temperature in good agreement with literature [9, 10, 11]. Values of the C_{11} and C_{44} elastic constants are given in Table 1.

Table 1
 C_{11} and C_{44} elastic constants of HoAl₂

T [K]	$C_{11} \times (10^{11} \text{ N/m}^2)$	$C_{44} \times (10^{11} \text{ N/m}^2)$
4.2	2.153	0.654
10	2.122	0.650
20	2.075	0.627
25	2.146	0.648
30	2.172	0.656
40	2.172	0.658
50	2.172	0.660
60	2.172	0.660
70	2.172	0.661
80	2.169	0.662
90	2.167	0.662
100	2.167	0.662
110	2.165	0.662
120	2.162	0.662
130	2.159	0.662
140	2.156	0.661
150	2.153	0.661
160	2.151	0.661
170	2.148	0.661
180	2.145	0.661
190	2.142	0.661
200	2.139	0.660
210	2.137	0.660
220	2.134	0.659
230	2.130	0.659
240	2.128	0.658
250	2.124	0.658
260	2.121	0.657
270	2.118	0.656
280	2.115	0.654

Discussion

According to the magnetoelastic theory, the temperature dependence of sound velocity in the paramagnetic region is [14, 2]:

$$V(T) = v_0(1 - \alpha_3 T)^{1/2}(1 - g_3^2 \chi_3(T))^{1/2} \quad (1)$$

where v_0 is the background velocity, α_3 is a coefficient issued from all non-crystal electric field effects, g_3 is the magnetoelastic coupling constant and $\chi_3(T)$ the elastic susceptibility [14]. By a least square fit, from equation (1) we calculated the full line on Fig. 1. We have:

$$g_3^2 = 0.20 \times 10^{-3} \text{ K}$$

$$\alpha = 3 \times 10^{-5} \text{ K}$$

Furthermore the theory states that g^2 should decrease from one RE-Al₂ to another as:

$$g^2 \sim \alpha \langle r^2 \rangle^2 / a^6 \quad (2)$$

where α is the Stevens factor [15], r^2 the free ion matrix element [16] and a is the lattice parameter. Table II shows how the ratio varies $g_3^2(\text{RE-Al}_2)/g_3^2(\text{CeAl}_2)$ across this series of compounds. The agreement between theory and experiment is only qualitative. In general the experimental ratio is greater than the theoretical one.

Table 2

Values of the $g_3^2(\text{RE-Al}_2)/g_3^2(\text{CeAl}_2)$ ratio

RE-Al ₂	Experiment	Theory	Ref.
PrAl ₂	0.4	0.1	1, 2
NdAl ₂	0.1	0.01	1, 2
TbAl ₂	0.003	0.01	7, this work
HoAl ₂	0.002	0.0005	7, this work

On the other hand, the same comparison with respect to the α_3 parameter indicates a maximum at the beginning of the RE-Al₂ series of compounds [2, 3, 4, 7]. But it is difficult to decide whether this parameter still contains a small magneto-elastic contribution or this variation is the real one.

REFERENCES

- [1] M. GODET and H.-G. PURWINS, *Solid State Comm.* 21, 761 (1977).
- [2] M. GODET and H.-G. PURWINS, *Helv. Phys. Acta* 49, 821 (1976).
- [3] R. J. SCHILTZ, Thesis, Iowa State University, Ames Iowa (1972).
- [4] R. J. SCHILTZ and J. F. SMITH, *J. Appl. Phys.* 45, 4681 (1974).
- [5] M. GODET, *Helv. Phys. Acta* 46, 770 (1973).
- [6] G. DUBLON, H. KLIMKER, U. ATZMONY, M. P. DANIEL, M. ROSEN, A. GRAYEWSKI and D. FEKETE, *Phys. Lett.* 53A, 23 (1975).
- [7] M. GODET, Thesis, Université de Genève, Genève, 1976.
- [8] J. H. WERNICK and S. GELLER, *Trans. AIME* 218, 866 (1960).
- [9] T. W. HILL, W. E. WALLACE, R. S. CRAIG and I. INONE, *J. Sol. State Chem.* 8, 364 (1973).
- [10] B. BARBARA, J. X. BOUCHERLE and M. F. ROSSIGNOL, *Phys. Lett.* 55A, 321 (1975).
- [11] H. G. PURWINS, E. WALKER, B. BARBARA, M. F. ROSSIGNOL and A. FURRER, *J. Phys.* C9, 1025 (1976).
- [12] M. GODET, E. WALKER and H.-G. PURWINS, *J. Less Common Metals* 30, 301 (1973).
- [13] I. R. HARRIS, R. C. MANSEY and G. V. RAYNOR, *J. Less Common Metals* 9, 270 (1965).
- [14] P. M. LEVY, *J. Phys.* C6, 3545 (1973).
- [15] K. W. STEVENS, *Proc. Phys. Soc.* A65, 209 (1952).
- [16] W. B. LEWIS, *Proc. XVIth Congress AMPERE*, Ed. I. Ursu, p. 717 (Bucharest 1970).