

Zeitschrift: Helvetica Physica Acta
Band: 62 (1989)
Heft: 6-7

Artikel: Pyrolysis and ozone in the YBCO fabrication process
Autor: Celani, F. / Saggese, A. / Sparvieri, N.
DOI: <https://doi.org/10.5169/seals-116143>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 22.02.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

PYROLYSIS AND OZONE IN THE YBCO FABRICATION PROCESS

F.Celani, A.Saggese, N.Sparvieri, INFN-LNF Via E.Fermi, 40
00044 FRASCATI, Italy

L.Liberatori, S.Pace, B.Polichetti, R.Scafuro, Dip. Fisica
Universita' di Salerno, 84100 SALERNO, Italy

Abstract: Pellets of YBCO have been fabricated by citrate pyrolysis; the annealing is done using a mixture of oxygen and ozone. The process generates textured samples with large micro-crystals. A.C. susceptometers were used for sample characterization which shows remarkable improvements by the use of ozone.

1. Introduction

The high T_c superconducting peroxides are easily obtained by powder mixing and a solid state reaction followed by oxygen annealings and sinterization. In these processes the non-ideal mixing of the components can lead to poor quality samples. An improvement of the YBCO fabrication is obtained by using the pyrolytic method [1] and an ozone enriched oxygen in all thermal treatments.

2. Preparation method and experimental results

The preparation method starts with a nitrate mixture prepared by using Y and Cu oxides and Ba carbonate. Citric acid is added and a neutralization (PH=6.7) with NH_4OH is done [1]. Best results are achieved by a direct optical method observing the formation of a clear light blue solution. The liquid is heated up until it fires leading to a very fine powder. A single thermal treatment in an ozone atmosphere with usual thermal cycles leads to the 123 phase with very few spurious materials undetectable by x-ray and neutron diffraction analysis. The

superconducting powder is sintered in pellets with density 5.5-5.9 g/cm³ which show the presence of quite large crystals (300 μ m) with a preferential orientation [2].

The volume superconducting properties are measured by an a.c. susceptibility technique which detects the absence of spurious phases, the homogeneity of the samples and the grain coupling strength. A simple two coil system is used, where the sample is surrounded by the pick up coil inside a coaxial exciting coil. A two phase lock-in amplifier detects the susceptibility components. The temperature is monitored by a suitable silicon diode. As shown in fig.1, at low magnetic field, the transition

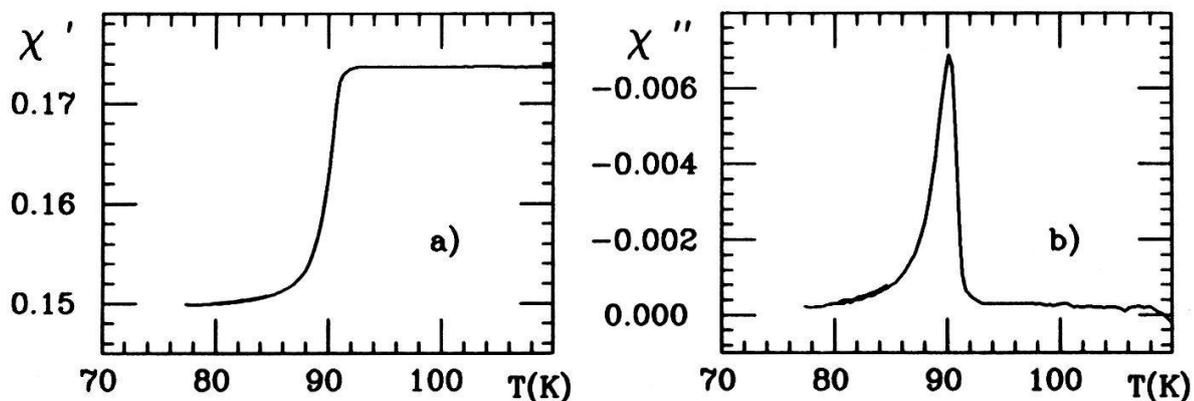


Fig.1. In phase a) and out of phase b) susceptibility signal: frequency 1KHz, amplitude of the exciting field 5 Gauss.

width (interval between 10% and 90% of the complete shielding), is very narrow (≈ 2 K). The increase of the magnetic field does not reduce T_c but enlarges ΔT_c . Up to 5 Gauss it is hard to separate the grain coupling from the grain transitions. Several comparative measures between samples made with oxygen and samples made with ozone, confirm improvements by using ozone for the YBCO fabrication and in particular a stronger resistance against water and moisture.

3. References

- [1] D.H.A.Blank et al., Physica 145B, 222 (1987).
- [2] F.Celani et al., ASC-88 to be pub. on IEEE Trans. on Magn.