

Zeitschrift: Helvetica Physica Acta
Band: 62 (1989)
Heft: 6-7

Artikel: Tunneling Study of High T_c YBa₂Cu₃O₇- ceramic
Autor: Suzuki, M. / Nishizaki, T. / Rinderer, L.
DOI: <https://doi.org/10.5169/seals-116147>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 05.03.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Tunneling Study of High T_c $YBa_2Cu_3O_{7-\delta}$ CeramicM. Suzuki,[†] T. Nishizaki,^{††} and L. Rinderer

Institut de Physique Experimentale, Universite de Lausanne, CH-1015 Lausanne,
Switzerland

[†]On leave from Saga University, Saga 840, Japan

^{††}Faculty of Science and Engineering, Saga University, Saga 840, Japan

Abstract: The Pb-SiO- $YBa_2Cu_3O_{7-\delta}$ junctions were fabricated on the ceramic $YBa_2Cu_3O_{7-\delta}$ and the $V-dI/dV$ characteristic was measured at temperatures ranging over from 4.4 to 94.1 K, and furthermore under several magnetic fields at 4.4 K. It was found that the temperature dependence of energy gap almost agrees with the one of the BCS theory, and the value of $2\Delta_0/k_B T_c$ is 4.06. This suggests that the superconducting mechanism of high T_c $YBa_2Cu_3O_{7-\delta}$ is something like the BCS theory.

Since the high T_c ceramic superconductor, Ba-La-Cu-O system had been discovered by Bednorz and Muller [1] at 1986, many high T_c ceramic superconductors have been developed. These oxide superconductors have not only a high critical temperature but also extraordinary properties which are different from predictions of the BCS theory. Thereby, it is most exciting problem for a physicist to make clear a microscopic mechanism of the superconducting state. The mechanism intimately relates to the electronic states near the Fermi energy.

The tunneling spectroscopy is powerful probe in elucidating the mechanism, because it gives direct informations about the electronic states near the Fermi energy with high resolving power.

The tunnel junctions were fabricated by depositing SiO as a tunnel barrier and then Pb on $YBa_2Cu_3O_{7-\delta}$ ceramic with $T_c=88.5$ K (the off-set temperature in a temperature dependence characteristic of resistance). The $V-dI/dV$ characteristics were traced at temperatures ranging over from 4.4 to 94.1 K as shown in Fig. 1. The scale of vertical axis is for the characteristic at 4.4 K. The $V-dI/dV$ characteristic at 4.4 K has a valley centered at zero-bias and two peaks at ± 5 mV. These structures weaken with increasing temperature and disappear at temperature higher than 6.8 K and under the magnetic field higher than 1.2 kOe. Thereby, these structures come from a superconducting state of Pb.

The characteristic has two gentle curves ranging over from 10 mV (-10 mV) to

50 mV (-50 mV). These structures weaken with increasing temperature, and disappear higher than 80.5 K. Thereby, these structures come from the superconducting state of $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$. Each characteristic is normalized with the one at 94.1 K, which is in the normal state, and then an energy gap Δ at each temperature is obtained by using the Dynes' formula (2)

$$N_S(E)/N_N(0) = (E - i\Gamma) / \sqrt{(E - i\Gamma)^2 - \Delta^2}$$

The temperature dependence of energy gap is shown in Fig. 2, where $\Delta_0 = 15.5$ meV, $T_c = 88.5$ K. Here, the value of energy gap at 4.4 K, 15.5 meV is assumed to be equal to a value at 0 K, Δ_0 . A solid line is the characteristic obtained by the BCS theory, and an open circle is the present value. As seen in Fig. 2, the present value agrees with the characteristic of BCS theory. Using $\Delta_0 = 15.5$ meV and $T_c = 88.5$ K, we obtain $2\Delta_0/k_B T_c = 4.06$. The value, 4.06 is near 4.3 for the strong coupling superconductor Pb. Recently, Tachiki and Takahashi theoretically showed that the BCS theory modified with a charge fluctuation gives a high T_c and a weak isotope effect. Our results seem to support Tachiki's theory.

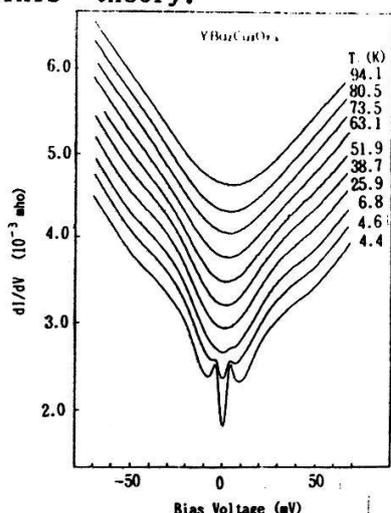


Fig. 1 V-dI/dV characteristics of Pb-SiO- $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ junction at temperatures ranging over from 4.4 to 94.1 K.

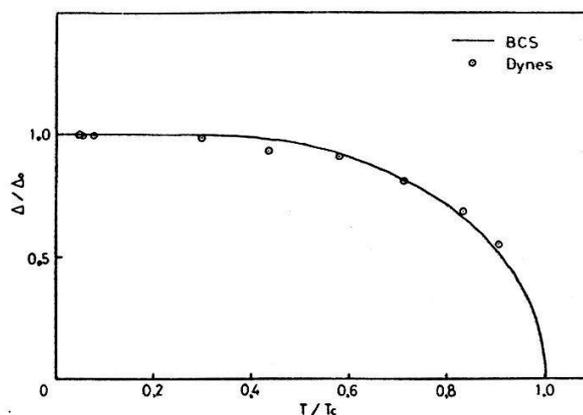


Fig. 2 Temperature dependence of energy gap for $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$. A solid line is the BCS characteristic, and a circle the experimental value.

References

- (1) J. G. Bednorz and K. A. Muller: Z. Phys. B 64, 189(1986).
- (2) R. C. Dynes, J. P. Garno, G. B. Hertel, and T. P. Orlando: Phys. Rev. Lett. 53, 2437(1984).
- (3) M. Tachiki and S. Takahashi: Phys. Rev. B 39, 294(1989).