

Zeitschrift: Helvetica Physica Acta
Band: 65 (1992)
Heft: 2-3

Artikel: Magnetotransport in 2D system in parallel and tilted magnetic fields
Autor: Vašek, P. / Cukr, M.
DOI: <https://doi.org/10.5169/seals-116433>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 16.01.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Magnetotransport in 2D system in parallel and tilted magnetic fields

P. Vašek and M. Cukr

Institute of Physics, Czechoslovak Academy of Sciences
CS 162 00 Praha 6, Cukrovarnická 10, Czechoslovakia

Abstract. Study of the magnetoresistivity $\rho(B)$ has been performed on GaAs-GaAlAs heterostructures in the magnetic field parallel to the 2D plane or tilted by a small angle α from this plane. The influence of relative orientation of the magnetic field and the current through the sample has been also investigated. The results are discussed in the terms of different models proposed recently. It is suggested that also quantum correction e.g. the weak localization should be taken into account to explain observed results.

Introduction

The magnetotransport properties of 2DEG system confined in a narrow quantum well have attracted attention for many years namely for the configuration with magnetic field \mathbf{B} perpendicular to the confinement plane. It is interesting, however, to study also the case with \mathbf{B} parallel to the 2DEG plane or tilted by a small angle from it. Such investigation has been done recently by Leadley et al [1] for transport current \mathbf{I} perpendicular to \mathbf{B} . They have offered an explanation of their results in terms of nonsymmetrical distortion of Fermi surface [2] formed by the combined influence of triangular confining potential well and parallel magnetic field. Recently another model has been presented [3] that takes into account the third dimension playing decisive role in the behavior of the magnetoresistance of 2D systems in the presence of parallel component of magnetic field.

Experiment

The samples under study were prepared from $\text{GaAs}-\text{Ga}_{1-x}\text{Al}_x\text{As}$ heterostructures grown by MBE. The carrier densities at liquid He temperature for the two measured samples have been found to be $5.5 \times 10^{15} \text{ m}^{-2}$ and $3.5 \times 10^{15} \text{ m}^{-2}$, respectively, the corresponding mobilities have been $30.4 \text{ m}^2/\text{Vs}$ and $21.5 \text{ m}^2/\text{Vs}$, respectively. The relatively small carrier densities ensure that only one subband is occupied and intersubband scattering and/or depopulation effect can be excluded.

Results and discussion

The effect of magnetic field tilted by a few degrees from the direction parallel to the plane of the 2DEG was studied for two different configurations: perpendicular ($B \perp I$) and parallel ($B \parallel I$) ones. The result can be seen in Fig. 1 for different values of magnetic field B as a function of the component B_{\perp} perpendicular to the 2DEG plane. For magnetic fields B greater than 1.5 T a sharp dip has been found around $B_{\perp} = 0$ with the depth proportional to B in accordance with the measurements of Leadley et al [1] for the perpendicular configuration. For smaller B , however, the dips disappear and broad maxima have been observed around $B_{\perp} = 0$. At higher values of B_{\perp} a decrease of resistivity has been detected even for all values of B . The results are qualitatively the same for both configurations. The magnetoresistance for different tilt angles is shown in Fig. 2. The positive magnetoresistivity observed for zero angle has changed with increasing angle (i.e. increasing B_{\perp}) to negative one both for lowest and highest fields B .

It does not seem to be possible to explain qualitatively such a complicated behaviour of $\rho(\alpha, B)$ on the bases of the two above mentioned models only. It can hardly be supposed that a simple two

type carrier model based on the distorted Fermi surface could describe results for small B and/or high B_{\perp} . On the other hand the calculation taking into account the third dimension shows that for parallel configuration ($B \parallel I$) the magnetoresistance should be proportional to B_{\perp}^2 [4]. Such results can however be due to less realistic assumption of harmonic confining potential.

Our results seem to support the idea that quantum corrections i.e. weak localization and electron-electron interaction should also be considered. One can suppose that observed dependences stem from a combined influence of parallel and perpendicular components of applied magnetic field. While B_{\parallel} gives positive magnetoresistance due to the magnetic field dependence of the relaxation time, B_{\perp} , reducing the weak localization [5-7], leads to a negative magnetoresistance for small B_{\perp} . In small magnetic fields the term due to B_{\perp} should prevail and maxima can be observed in $\rho(\alpha)$ dependences. At high B_{\perp} negative contribution due to the shortening of cyclotron radius with respect to the mean free path [8] should again reduce the observed magnetoresistance.

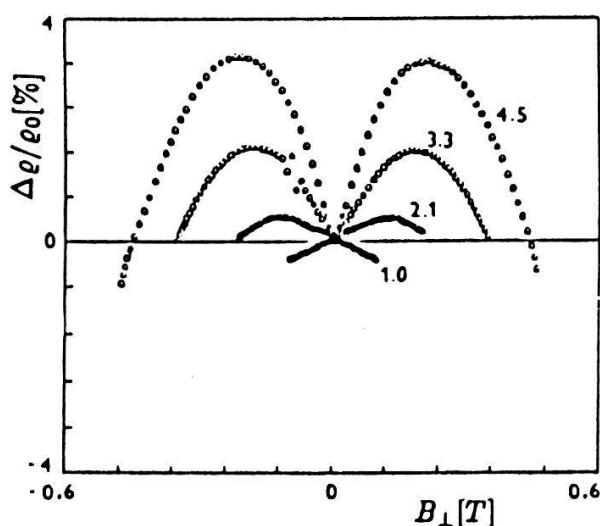


Fig.1 : Relative magnetoresistance $\Delta\rho/\rho_0$ as a function of B_{\perp} for different applied magnetic fields $B[T]$ ($B \parallel I$)

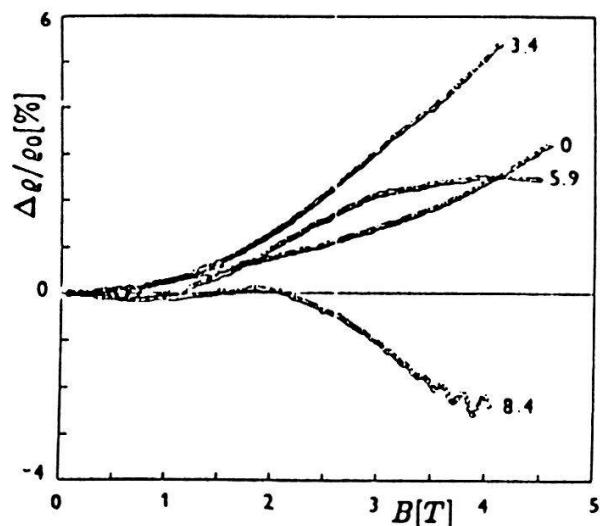


Fig.2 : Relative magnetoresistance $\Delta\rho/\rho_0$ as a function of B for different tilt angles α [deg] ($B \parallel I$)

References

- [1] D. R. Leadley, R. J. Nicholas, J. J. Harris and C. T. Foxon, *20th International Conference on Physics of Semiconductors*, p. 1609, eds. E. M. Anastassakis and J. D. Joannopoulos, World Scientific Publishing Co., Singapore (1990)
- [2] W. Zawadzki, S. Klahn, U. Merkt, *Phys. Rev. B* **33** (1986) 6916
- [3] L. Smrčka, *International Conference on Physics in Two Dimensions*, Neuchâtel, (1991)
- [4] L. Smrčka, submitted to *Solid State Communications*
- [5] S. Hikami, A. I. Larkin, Y. Nagaoka, *Prog. Theor. Phys.* **63** (1980) 707
- [6] A. Kawabata, *J. Phys. Soc. Japan* **53** (1984) 3540
- [7] R. Taboryski, E. Veje, P. E. Lindelof, *Surf. Sci.* **229** (1990) 105
- [8] A. Houghton, J. R. Senna, S. C. Ying, *Phys. Rev. B* **25** (1982) 6468