

<b>Zeitschrift:</b>	Helvetica Physica Acta
<b>Band:</b>	65 (1992)
<b>Heft:</b>	2-3
<b>Artikel:</b>	The effects of inherent bond disorder on the rf properties of SNS Josephson junction arrays
<b>Autor:</b>	Lee, Hyun C. / Newrock, Richard S. / Mast, David B.
<b>DOI:</b>	<a href="https://doi.org/10.5169/seals-116441">https://doi.org/10.5169/seals-116441</a>

### Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 07.08.2025

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## The Effects of Inherent Bond Disorder on the rf Properties of SNS Josephson Junction Arrays

Hyun C. Lee, Richard S. Newrock, and David B. Mast

Department of Physics, University of Cincinnati  
Cincinnati, OH 45221, USA

**Abstract.** Bond disorder in SNS arrays can arise from non-identical junction lengths. This disorder disrupts the global phase coherence, responsible for the observed giant Shapiro steps, and results in finite step slopes and step rounding. We compare our experimental results with numerical simulations.

### Introduction

Recently, integer giant Shapiro steps were observed in two-dimensional (2D) NxN arrays of SNS junctions[1],[2]. Numerical simulations [3] suggest that coherent motion of rf current induced phase slips are responsible for these giant steps. For an array of ideal junctions, at T=0, the step slopes are infinite; however, in experiments, the slopes are all finite indicating that complete phase coherence is being disrupted. Sample fabrication processes of SNS arrays result in varying junction lengths; thus, inherent bond disorder cannot be avoided and is a likely cause for the observed rounding and finite slopes.

### Experiments

Figure 1 shows the giant Shapiro steps in the dc IV characteristic for a 300x300 array at T=4.2K with  $\nu_{rf}=90\text{MHz}$ . These steps occur at voltages  $V=Nn(h\nu_{rf}/2e)$ , where  $n(h\nu_{rf}/2e)$ ,  $n=1, 2, \dots$ , are the Shapiro steps voltages of a single junction. Non-identical junction lengths result in different critical currents  $I_c$ , normal state resistances  $R_n$ , and thus different characteristic frequencies,  $\nu_c=2eR_nI_c/h$ , and time-dependent voltage drops, for each junction in the array. Therefore, coherent phase locking will occur for a range of voltages , resulting in a finite step slopes and rounding.

### Numerical Simulations

Simulations were performed on an M x N lattice of superconducting crosses with methods similar to that described elsewhere [3]. A uniform distribution of the junction lengths, out to some maximum value  $\sigma$ , were used. The critical current, normal state resistance, and  $\nu_c$  were, thus, different for each junction. The junctions were randomly arranged on the array.

Figure 2 shows an IV characteristic of a 15x4 array, with a uniform distribution for  $\sigma = 0.05$ . The step rounding and finite step slopes agree with experiment.

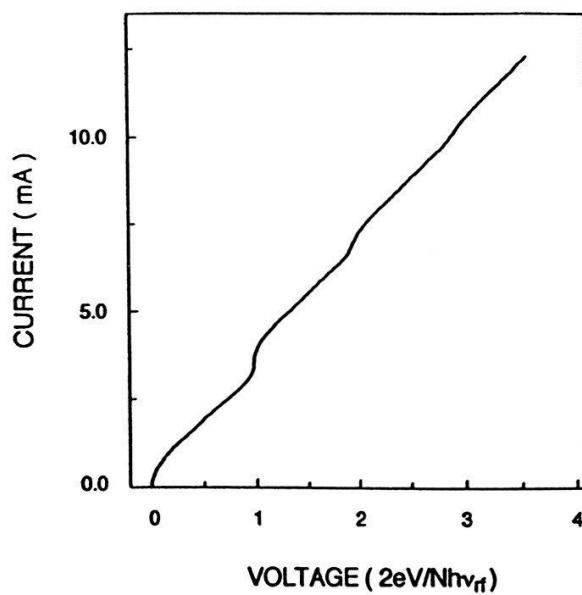


Fig. 1. Giant Step. The I-V characteristics in zero field at  $T=4.2K$  with  $\nu_{rf}=90MHz$  and  $I_r/I_c=2.1$ .

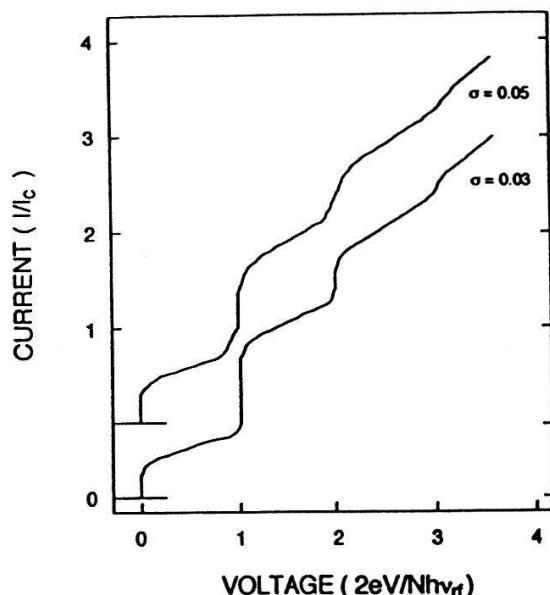


Fig. 2. Numerical simulation with uniform distribution of gap distances and periodic boundary conditions.  $\Omega=1.0$  and  $I_r/I_c=2.0$

## Conclusions

We have shown, with experiments and numerical simulations, that inherent bond disorder (non-identical junction lengths) in 2D arrays of SNS Josephson junctions introduces finite step slopes and rounding in the integer giant Shapiro steps. The simulations are in good agreement with our experimental data in terms of the degree of step rounding and finite step slope.

The authors are indebted to D. C. Harris for fabricating and J. C. Garland for providing the arrays. This research was conducted with support from USAF Wright Laboratories, Materials Directorate through Aerotherm Corp.

## References

- [1] S. P. Benz, M. S. Rzchowski, M. Tinkham and C. J. Lobb, Phys. Rev. Lett. **64**, 693 (1990).
- [2] H. C. Lee, D. B. Mast, R. S. Newrock, L. Bortner, K. Brown, F. P. Esposito, D. C. Harris, and J. C. Garland, Physica B, 165&166, 1571 (1990).
- [3] K. H. Lee, D. Stroud, and J. S. Chung, Phys. Rev. Lett. **64**, 962 (1990); J. U. Free, S. P. Benz, M. S. Rzchowski, M. Tinkham, C. J. Lobb and M. Octavio, Phys. Rev. B**41**, 7267 (1990); M. Octavio, J. U. Free, S. P. Benz, R. S. Newrock, D. B. Mast, and C.J. Lobb, to be published.