**Zeitschrift:** Helvetica Physica Acta

**Band:** 65 (1992)

**Heft:** 2-3

**Artikel:** Giant tunneling anisotropy of a high temperature superconductor

Autor: Forro, L. / Mandrus, D. / Hartge, J.

**DOI:** https://doi.org/10.5169/seals-116452

### Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Mehr erfahren

#### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. En savoir plus

## Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. Find out more

**Download PDF: 29.11.2025** 

ETH-Bibliothek Zürich, E-Periodica, https://www.e-periodica.ch

# GIANT TUNNELING ANISOTROPY OF A HIGH TEMPERATURE SUPERCONDUCTOR

L. Forro\*, D. Mandrus, J. Hartge, D. Koller and L. Mihaly SUNY at Stony Brook, Stony Brook N.Y. 11794-3800

Abstract. We have performed tunneling measurements on break junctions from Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8</sub> single crystals. We have found that for tunneling parallel and perpendicular to the CuO planes the tunneling spectra, and their temperature dependence, are entirely different. For plane" tunneling a gap structure is visible at low temperatures (  $2\Delta=55$ meV), while the conductance is nearly independente of the voltage and temperature above T<sub>c</sub>. For "perpendicular" tunneling the temperature dependence is well approximated with a logarithmic function, with no reference to T<sub>c</sub>


The two dimensional (2D) naure of the normal state electronic transport in copper oxide based high temperature superconductors is well estabilished by now, but little is known about the anisotropy of the superconducting energy gap (  $2\Delta$  ). Somewhat controversary results on the gap anisotropy reported in the literature ( summarysized by Kirtley in ref. 1) are probably due to the ill-defined tunneling geometry.

In order to study the energy gap in the CuO plane ( ab plane ) and between the planes (c axis) we have performed tunneling measurements on break junctions of Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8</sub> single crystals in the following way.

For the "ab plane" tunneling measurements we cleaved an approximately 1000 A thick, 100µm wide strip from a single crystal of Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8</sub> and mounted it on a crystal of Bi<sub>2</sub>Sr<sub>2</sub>YCu<sub>2</sub>O<sub>8</sub> ( a high resistance semiconductor). Electrical contacts to gold wires were made by silver epoxy. After heat treatment the contact resistances were typical room temperature sample resistance was 300Ω. The Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8</sub> /Bi<sub>2</sub>Sr<sub>2</sub>YCu<sub>2</sub>O<sub>8</sub> assembly was glued to an elastic strip of metal and fixed on the cold finger of a He flow cryostat. A precision-mounted screw pushed the back side of the metal strip. When the temperature reached around 10K, a "break junction" was produced by bending the metal strip with the screw. The screw was driven manually by a screwdriver, inserted through the wall of the cryostat.

For "c axis" tunneling we first prepared electrical contacts on the opposite, cleaved surfaces of a crystal. We glued the sample to the inside of a U shaped elastic strip so that the electrical contacts were facing the two arms of the U. We cooled the device in vacuum and we observed typical c

axis conductance: resistivity increasing with decreasing temperature, turning to superconductivity at  $T_{\rm c}$ . At low temperature the crystal was cleaved by increasing the separation between the arms of the U with the screw mechanism. The break junction was formed between the freshly cleaved surfaces.

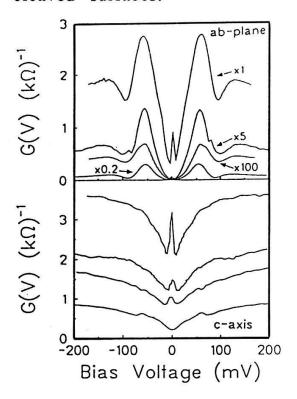

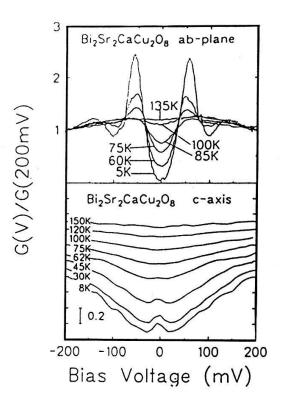


Fig.1. Differential conductance G vs. bias voltage at T=9K for several "ab plane"and "c axis" break junctions.

Fig.2. Tunneling conductance for "ab plane" and "c axis" tunneling at several temperatures as indicated in the Figure.

The results of tunneling conductances are shown in figs 1 and 2. The conclusions are the following:

- a. The "ab-plane" tunneling exhibits a gaplike structure around V=55mV, while no well pronounced structure is seen in the c direction.
- b. At low temperatures the zero bias conductance is zero for ab-plane tunneling while it is finite for c-axis tunneling.
- c. At large bias the ab-plane tunneling conductance decreases while the c-axis conductance increases with increasing bias voltage.

Detailed description and discussion of the results is given in ref. 2.

This work has been supported by NSF Grant DMR 9016456.

\* Present address: EPFL-IGA, PH-B Ecublens, 1015 Lausanne, Switzerland

#### References

/1/ J.R. Kirtley, Int. J. Mod. Phys. B4 201 (1990) /2/ D. Mandrus et al. Nature 351 460 (1991)