

Crystallization of rapidly quenched metal droplets with high melting point

Autor(en): **Soares, V. / Meyer, E. / Rinderer, L.**

Objektyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **62 (1989)**

Heft 6-7

PDF erstellt am: **25.09.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116094>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern. Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden. Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

CRYSTALLIZATION OF RAPIDLY QUENCHED METAL DROPLETS WITH HIGH MELTING POINT

V. Soares, E. Meyer* and L. Rinderer

Institut de Physique Expérimentale, Université de Lausanne
CH-1015 Lausanne, Switzerland*Instituto de Física, Universidade Federal do Rio de Janeiro
RJ-21945 Rio de Janeiro, Brazil

Abstract: The crystallization process of rapidly quenched liquid metal droplets has been studied by using photographic techniques. Cooling rates of these droplets have been obtained and they have shown appreciable supercooling before a sharply phase transition occurs which is contrary to classical nucleation theory. The instability of the liquid phase is investigated within the framework of an adiabatic nucleation model.

The mechanism by which a crystalline solid forms in the freezing of a pure liquid is controlled essentially by the nucleation rate of small crystallites in the supercooled liquid phase. However, the nucleus itself cannot be studied directly and this limits experimental information to the measuring of the limit temperature T_L to which the liquid can be supercooled before crystallizing.

Small droplets has been used in the study of the solidification mechanism to minimize the probability of nucleation due to the presence of foreign nuclei inside the liquid. By using this technique, this limit temperature T_L has been measured for a variety of liquid metals .

We have applied the technique of dendritic crystal growth to obtain dendritic crystals from rapidly quenched metal droplets with high melting point. This technique improved with an stereophotographic apparatus has permitted to obtain the cooling rate of these droplets and, then, to determine the amount of supercooling these metals can sustain.

This procedure was described previously. (1,2) A metal wire is overloaded by a high current inside a chamber and the sample is liquefied. Liquid metal droplets are produced and these radiating spheres are then fall down in the chamber, being cooled during the time of flight.

Calibrated curves of color density ratio on photographic film vs temperature and position of free falling droplet vs time enable us to plot the temperature of droplet at given position vs time as is represented in Figure 1. It should be noted that the limit temperature T_L to the supercooling the liquid droplet undergoes is just the minimum temperature before the sudden increase of temperature at which the solid phase appears.

This curve also has the following characteristics: (i) the temperature at which the solid appears is not a plateau-like but

immediately falls; (ii) the cooling rate after this limit temperature corresponds to a radiative cooling droplet; and (iii) the temperature attainable by the solid phase is lower than that predicted upon release of the latent heat during the nucleation process.

As is suggested by Nelson(3) the characteristic (iii) merely indicates that only a fraction of the mass of the supercooled droplet could crystallize rapidly, the remainder of the solidification being rate-limited by the process of heat loss from the outer surface of the droplet. However, this picture estimates that only after a time of the order of 30 msec or larger the Ta droplet of Figure 1 should present a radiative cooling behavior.

The present results suggest that nucleation phenomenon may not be regarded as an isothermal one as considered by the classical nucleation theory. It seems the solid can nucleate at higher temperature than the liquid phase but this temperature may be lower than the associated melting temperature, the resulting evolution towards equilibrium occurring very fast, as predicted from the adiabatic theory of nucleation.(4)

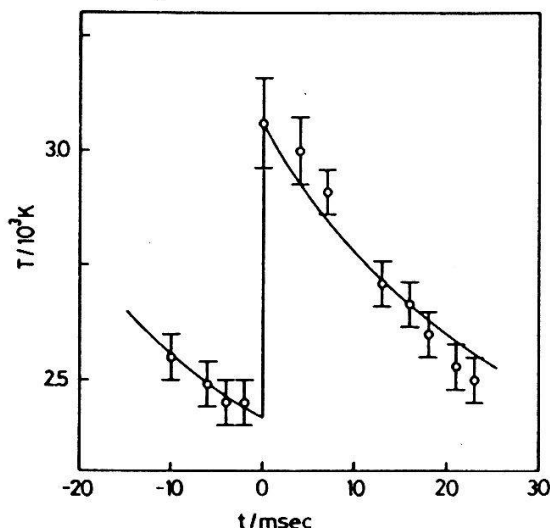


Fig.1 Typical cooling rate to 400 μ m Ta droplets

Acknowledgements: We thank Prof. N. Melamed the suggestion of this technique and the valuable support from the Fonds National de la Recherche Scientifique and Conselho Nacional de Desenvolvimento Científico e Tecnológico.

References:

- (1) V. Soares et al., *Helv. Phys. Acta*, 61, 857 (1988)
- (2) E. Meyer and L. Rinderer, *J. Crystal Growth*, 28, (1975)
- (3) L. Nelson, 12th International Symposium on Combustion, Poitiers, France, 1968
- (4) E. Meyer, *J. Crystal Growth*, 74, 425 (1986); 76, 525 (1986)