

The effects of inherent bond disorder on the rf properties of SNS Josephson junction arrays

Autor(en): **Lee, Hyun C. / Newrock, Richard S. / Mast, David B.**

Objektyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **65 (1992)**

Heft 2-3

PDF erstellt am: **26.04.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116441>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

The Effects of Inherent Bond Disorder on the rf Properties of SNS Josephson Junction Arrays

Hyun C. Lee, Richard S. Newrock, and David B. Mast

Department of Physics, University of Cincinnati
Cincinnati, OH 45221, USA

Abstract. Bond disorder in SNS arrays can arise from non-identical junction lengths. This disorder disrupts the global phase coherence, responsible for the observed giant Shapiro steps, and results in finite step slopes and step rounding. We compare our experimental results with numerical simulations.

Introduction

Recently, integer giant Shapiro steps were observed in two-dimensional (2D) $N \times N$ arrays of SNS junctions[1],[2]. Numerical simulations [3] suggest that coherent motion of rf current induced phase slips are responsible for these giant steps. For an array of ideal junctions, at $T=0$, the step slopes are infinite; however, in experiments, the slopes are all finite indicating that complete phase coherence is being disrupted. Sample fabrication processes of SNS arrays result in varying junction lengths; thus, inherent bond disorder cannot be avoided and is a likely cause for the observed rounding and finite slopes.

Experiments

Figure 1 shows the giant Shapiro steps in the dc IV characteristic for a 300×300 array at $T=4.2\text{K}$ with $\nu_{rf}=90\text{MHz}$. These steps occur at voltages $V=Nn(h\nu_{rf}/2e)$, where $n(h\nu_{rf}/2e)$, $n=1, 2, \dots$, are the Shapiro steps voltages of a single junction. Non-identical junction lengths result in different critical currents I_c , normal state resistances R_n , and thus different characteristic frequencies, $\nu_c=2eR_nI_c/h$, and time-dependent voltage drops, for each junction in the array. Therefore, coherent phase locking will occur for a range of voltages, resulting in a finite step slopes and rounding.

Numerical Simulations

Simulations were performed on an $M \times N$ lattice of superconducting crosses with methods similar to that described elsewhere [3]. A uniform distribution of the junction lengths, out to some maximum value σ , were used. The critical current, normal state resistance, and ν_c were, thus, different for each junction. The junctions were randomly arranged on the array.

Figure 2 shows an IV characteristic of a 15×4 array, with a uniform distribution for $\sigma = 0.05$. The step rounding and finite step slopes agree with experiment.

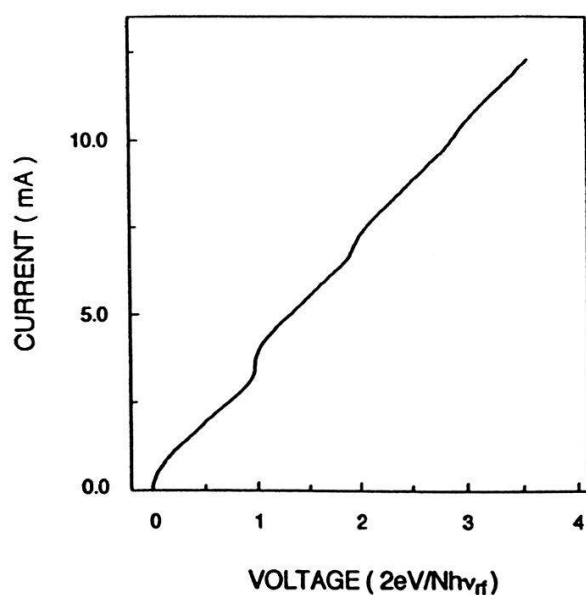


Fig. 1. Giant Step. The I-V characteristics in zero field at $T=4.2\text{K}$ with $\nu_{rf}=90\text{MHz}$ and $I_{rf}/I_c=2.1$.

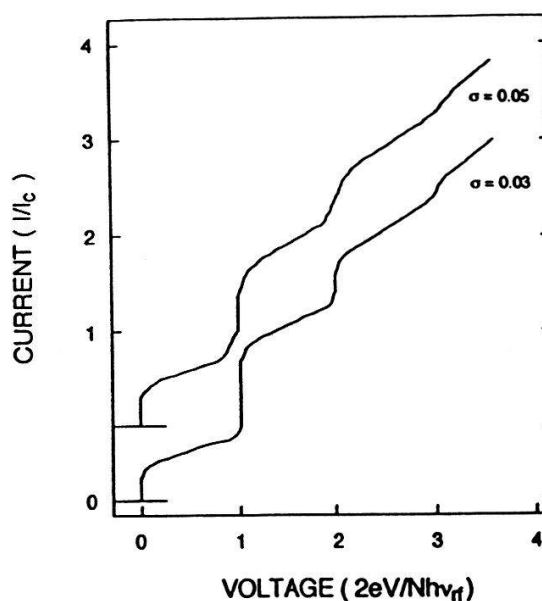


Fig. 2. Numerical simulation with uniform distribution of gap distances and periodic boundary conditions. $\Omega=1.0$ and $I_{rf}/I_c=2.0$

Conclusions

We have shown, with experiments and numerical simulations, that inherent bond disorder (non-identical junction lengths) in 2D arrays of SNS Josephson junctions introduces finite step slopes and rounding in the integer giant Shapiro steps. The simulations are in good agreement with our experimental data in terms of the degree of step rounding and finite step slope.

The authors are indebted to D. C. Harris for fabricating and J. C. Garland for providing the arrays. This research was conducted with support from USAF Wright Laboratories, Materials Directorate through Aerotherm Corp.

References

- [1] S. P. Benz, M. S. Rzchowski, M. Tinkham and C. J. Lobb, Phys. Rev. Lett. **64**, 693 (1990).
- [2] H. C. Lee, D. B. Mast, R. S. Newrock, L. Bortner, K. Brown, F. P. Esposito, D. C. Harris, and J. C. Garland, Physica B, 165&166, 1571 (1990).
- [3] K. H. Lee, D. Stroud, and J. S. Chung, Phys. Rev. Lett. **64**, 962 (1990); J. U. Free, S. P. Benz, M. S. Rzchowski, M. Tinkham, C. J. Lobb and M. Octavio, Phys. Rev. B **41**, 7267 (1990); M. Octavio, J. U. Free, S. P. Benz, R. S. Newrock, D. B. Mast, and C.J. Lobb, to be published.