

Experimental investigation of two-dimensional arrays of ultrasmall Josephson junctions

Autor(en): **Chiidong, Chen / Delsing, P. / Haviland, D.B.**

Objektyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **65 (1992)**

Heft 2-3

PDF erstellt am: **26.09.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116457>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

Experimental Investigation of Two-Dimensional Arrays of Ultrasmall Josephson Junctions

Chen Chiidong, P. Delsing, D.B. Haviland, and T. Claeson
Department of Physics, Chalmers University of Technology
S-412 96 Göteborg, Sweden

Abstract. We have investigated two-dimensional arrays of low capacitance (C) aluminum Josephson junctions with varying values of the normal state resistance R_N and the ratio E_J/E_C , where E_J is the Josephson coupling energy and E_C is the charging energy ($e^2/2C$). For low resistance, $R_Q/R_N \gg 1$ ($R_Q = h/4e^2 = 6.5 \text{ k}\Omega$) and $E_J/E_C > 1$, the Josephson current prevails. When $R_Q/R_N \ll 1$ and $E_J/E_C < 1$ the arrays are dominated by the Coulomb blockade. In an intermediate region of the parameter space, $R_Q/R_N \leq 1$, $E_J/E_C \approx 1$, we find a "back-bending" I-V curve with negative differential resistance. For the Coulomb-blockade-dominated arrays we find that the low voltage conductance decreases strongly with lowered temperature but find no evidence for a Kosterlitz-Thouless-Berezinskii phase transition of charge unbinding. On the contrary, we find no significant difference between a 2-D and a 1-D array.

Introduction

In order to explore the parameter space for 2-D arrays of small tunnel junctions we have measured I-V characteristics of a large number of arrays with different parameters R_Q/R_N and E_J/E_C . We have produced 18 arrays with resistances ranging from 1 k Ω to 1 M Ω for the individual junctions. The ratio of E_J to E_C ranged from 0.003 to 7.5. Here E_C is estimated from the nominal junction areas, and it corresponds well with the measured offset voltages. E_J are calculated from R_N and the superconducting gap Δ , $E_J = (R_Q/R_N)(\Delta/2)$. Similar measurements were done by Geerligs et al [1].

A Kosterlitz-Thouless-Berezinskii (KTB) phase transition may occur in 2-D arrays of Josephson junctions. An interesting duality between vortices and charges exists in these arrays. The KTB transition can describe the vortex unbinding transition from the superconducting state when $E_J/E_C \gg 1$ [2], and the charge unbinding transition from the insulating state when $E_J/E_C \ll 1$ [3]. Evidence for the charge unbinding transition in arrays where $E_J/E_C \approx 0.5$ is claimed in recent experiments [4].

Josephson Current vs. Coulomb Blockade in I-V Curves. Back Bending

Square arrays with sizes from 20x20 to 86x86 junctions were fabricated using electron beam lithography and a suspended bridge technique. The junctions of the arrays were made of aluminum and they were measured in the superconducting state. Going from the upper right corner to the lower left corner of the phase diagram (R_Q/R_N vs. E_J/E_C , see Fig.1) we encounter different types of I-V characteristics. Note that this is not a true Schmid diagram since we plot R_Q/R_N and not the real damping R_Q/R_S , R_S being an ohmic shunt resistance seen by the junction.

In the upper right corner of the diagram (region A), the I-V curve shows the general Josephson behavior, however there is a finite slope of the "super"-current due to the relatively strong charging energy leading to phase fluctuations. Going downwards/leftwards (region B) a small "foot" starts to develop at the origin due to the stronger Coulomb blockade. In a region where $R_Q/R_N < 1$ and $E_J/E_C \leq 1$ (region C), the "foot" has developed to a strong Coulomb blockade and the curve starts to bend back towards the current axis due to the Josephson coupling. At higher currents, the voltage increases again due to Zener tunneling. In the lower left corner of the diagram (region D), the Coulomb blockade is dominating completely. In the region where $R_Q/R_N \ll 1$ and $E_J/E_C \leq 1$ (region E), the I-V characteristics show a behavior similar to the arrays in the region B, but with a sharper Coulomb blockade. The crossover to this region from the back-bending region is not yet understood, since one would expect to strengthen the back-bending instead of weakening it when R_N is increased. The behavior in the other regions is qualitatively what is expected from theoretical arguments. Where our data overlap with that of ref.1 we observe a good agreement.

Comparison between 1-D and 2-D Arrays

We compare measurements of 2-D and 1-D arrays for $E_J/E_C \gg 1$ and $R_N \gg R_Q$. As no KTB transition occurs in 1-D, this comparison should allow us to see that part of the transition which is truly due to 2-D effects. For the 1-D array $R=88k\Omega$, and E_J/E_C is estimated to be 0.022. For the 2-D array, $R=100k\Omega$ and $E_J/E_C \approx 0.018$. The low bias conductance $(R_L)^{-1}$ is plotted in Fig.2. In both the normal and superconducting cases, there is a striking similarity between the 1-D and 2-D data. The shape of the curves for the 2-D array is similar to that found in Ref.3. The very similar temperature dependences of the low bias conductance in the 2-D and 1-D case for both the superconducting and normal states, suggest that the transition to the insulating state is governed by similar charging phenomena in both the 2-D and 1-D arrays, and that no intrinsic 2-D character of the transition is present. This observation is not remarkable considering the small charge soliton [5] length ($M \approx 10$ junctions). However, our 2-D array should have a larger value of M than previous experiments [4] where evidence of a 2-D transition was claimed.

References

- [1] L.J.Geerligs, M.Peters, L.E.M.de Groot, A.Verbruggen, and J.E.Mooij, Phys. Rev. Lett. **63**, 326 (1989).
- [2] B.J.van Wees, H.S.J.van der Zant, and J.E.Mooij, Phys. Rev. B **35**, 7291 (1987).
- [3] A.Widom and S.Bajou, Phys. Rev. B **37**, 7915 (1988).
- [4] J.E.Mooij, B.J.van Wees, L.J.Geerligs, M.Peters, R.Fazio, and G.Schön, Phys. Rev. Lett. **65**, 645 (1990).
- [5] N.S.Bakhvalov, G.S.Kazacha, K.K.Likharev, and S.I.Serdyukova, Physica B **165&166**, 963 (1990).

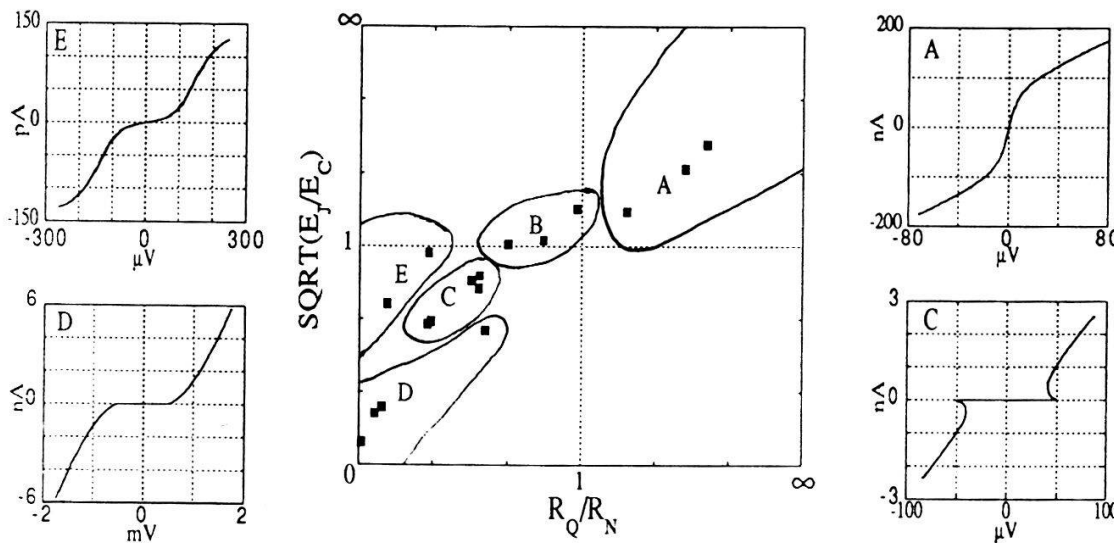


Fig.1. Representative I-V curves for different regions of the diagram relating E_J/E_C to normal state resistance. Curves in the region B are similar to those in the region A but with a slight Coulomb blockade. The curves were registered at temperatures of about 40 mK.

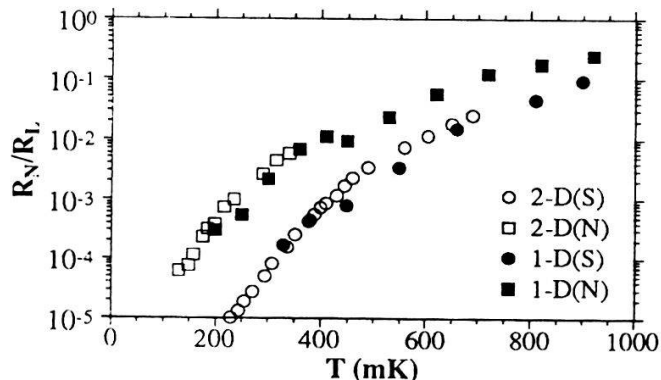


Fig.2. Normalized low voltage conductance as a function of temperature. Open symbols denote 2-D arrays, filled ones 1-D arrays with similar junction parameters. Circles give superconducting state data, squares normal state data. The normal state was obtained by applying a large magnetic field.