

Zeitschrift: Schweizerische mineralogische und petrographische Mitteilungen =
Bulletin suisse de minéralogie et pétrographie

Band: 39 (1959)

Heft: 1-2

Artikel: Dixeyite : a new natural hydrous aluminiumsilicate

Autor: Marmo, Vladi

DOI: <https://doi.org/10.5169/seals-30390>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 07.02.2026

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Dixeyite — a new natural hydrous aluminiumsilicate

By *Vladi Marmo* (Otaniemi, Finland)¹⁾

Abstract

A new hydrous isotropic mineral in an amphibolite from Sierra Leone is described. It is named dixeyite, in honour of Dr. Dixey — the first geologist of Sierra Leone.

Introduction

During the mapping in 1954 of the schist belt of the Kangari Hills, Central Sierra Leone, small boulders of a peculiar amphibolite were collected. That happened about 1 mile to the North of a small native village called Belihun, the location of which is approximately $8^{\circ} 22' 30''$ N and $11^{\circ} 36' 15''$ W. This amphibolite (of which a small outcrop was also found in 1956) consisted of abundant hornblende in a matrix composed of some isotropic, colourless mineral with remarkably low refractive index, and of minor amounts of quartz. The isotropic mineral was taken to be a zeolite. Later it was classed as analcime, and the rock itself was named "analcime amphibolite". As such it was described by the author in the Annual Reports of the Geological Survey Department of Sierra Leone (1955 and 1956), the petrologist of which department the present writer was at that time.

In 1957, after his return to Finland, the author reexamined the "analcime", and then found, that the powder diagram of this material was not that of analcime. Neither did it correspond to that of any other known mineral. Examination revealed, furthermore, that the refractive index of this mineral is too high for analcime. The chemical analysis of the separated material confirmed the results of the X-ray study, and indicated the probability of the mineral in question, which is an aluminiumsilicate, conspicuously hydrous, being new one.

¹⁾ Outokompu Co., Finland.



Fig. 1. Amphibolite containing isotropic unknown mineral N of Belihun, Sierra Leone. Thin section $40 \times$. N // . 1 = dixeyite; 2 = hornblende; 3 = quartz; 4 = magnetite.



Fig. 2. Amphibolite containing isotropic unknown mineral N of Belihun, Sierra Leone. Thin section $40 \times$. N + . 1 = dixeyite; 2 = hornblende; 3 = quartz; 4 = magnetite.

Amphibolite containing unknown mineral

Owing to the overburden masking the geology, it was not possible to ascertain the exact geological setting of the amphibolite containing the new mineral. This rock-type was found on the path along the Yandeye Stream, on its northern side, and also in a small outcrop, approx. 50 m N of the path. It is supposed, that this amphibolite occupies a very narrow zone along the western margin of the well-outcropped body of an ultrabasic rock, and at its contact with the embracing granodiorite. The occurrence of this peculiar amphibolite is at the southern end of a large schist belt including the Sula Mountains and the Kangari Hills (see for instance, MARMO, 1958), where the schist belt mainly consists of amphibolites. To the North of Belihun, the amphibolite contains a minor patch of an ultrabasic rock consisting of pyroxene and tremolite, and containing pleonaste and magnetite. At the border of this body, the amphibolite with the odd mineral occurs.

The amphibolite containing the isotropic mineral is a medium- and even-grained rock with a distinct but not strong orientation. In the hand specimens it does not differ in any way from the ordinary medium-grained amphibolites of the area. The texture of this rock is shown in figures 1 and 2. The main constituent is common green hornblende embedded in a mixture of the isotropic mineral and of minor amounts of quartz. There is no evidence to support the view that the zeolite-like mineral could have originated by some kind of alteration of any pre-existing mineral; on the contrary one gets the impression, that it is in fact an original constituent of the rock, and of more or less the same age as the hornblende. Quartz, however, seems to be somewhat younger than the isotropic unknown mineral.

Chemistry

The chemical analysis of this peculiar amphibolite is shown in table 1. The composition of the rock is, according to this analysis, rather strange. If the high water content is neglected, then the material corresponds to the following mineral association:

| | |
|--------|---------------------------------|
| 28.3 % | Quartz |
| 14.35% | Pyroxene |
| 26.2 % | Plagioclase (An ₉₀) |
| 1.7 % | Orthoclase |
| 4.7 % | Corundum |

| |
|------------------|
| 1.9 % Apatite |
| 3.65 % Ilmenite |
| 12.1 % Magnetite |
| <hr/> 92.90 |

Obviously, this mineral composition was not attained because of the presence of much water (4.74% combined). The actual mineral composition consists of quartz, hornblende, magnetite and the highly hydrous Al-mineral.

Table 1. *Chemical composition of amphibolite containing the isotropic mineral. Sierra Leone. Analyst: AULIS HEIKKINEN*

| | | Normative composition | Niggli values |
|--------------------------------|-------------|-----------------------------|---------------|
| SiO ₂ | 51.10% | Apatite 1.90% | al = 25.0 |
| TiO ₂ | 1.91 | Ilmenite 3.65 | fm = 58.0 |
| Al ₂ O ₃ | 13.94 | Orthoclase 1.67 | c = 15.0 |
| Fe ₂ O ₃ | 8.31 | Albite 4.40 | alk = 2.0 |
| FeO | 7.02 | Anorthite 21.82 | <hr/> 100.0 |
| MnO | 0.21 | Corundum 4.74 | |
| MgO | 4.53 | Magnetite 12.06 | si = 150 |
| CaO | 4.75 | Enstatite 11.30 | k = 0.265 |
| Na ₂ O | 0.52 | Ferrosilite 2.84 | mg = 0.36 |
| K ₂ O | 0.27 | MnO · SiO ₂ 0.21 | qz = + 42 |
| P ₂ O ₅ | 0.26 | Quartz 28.31 | ti = 0.044 |
| CO ₂ | 0.00 | H ₂ O + 4.74 | p = 0.004 |
| H ₂ O + | 4.74 | H ₂ O - 2.39 | h = 0.48 |
| H ₂ O - | 2.39 | Total 100.03 | o = 0.328 |
| SO ₃ | 0.00 | | |
| Cl | 0.00 | | |
| Total | <hr/> 99.95 | | |

Using bromoform-ethanol mixture, an attempt was made to separate the unknown mineral for chemical analysis. Because abundant and extremely fine needle-like inclusions of hornblende are present in the mineral, it was not possible to obtain sufficiently pure material. Nevertheless the material obtained by the separation was also analyzed (table 2).

From the analyses of tables 1 and 2 an attempt was made to calculate the possible chemical composition of the zeolite-like isotropic mineral.


The separation by bromoform-ethanol yielded 30% by weight of material very enriched in the unknown mineral. Thus, the analysis of table 2 represents the composition of 30% of the total rock. If 30% of the mole values of this analysis are taken and subtracted from the total mole values of analysis 1, it should be possible to estimate the compo-

Table 2. *Chemical composition of the concentrate predominantly containing the unknown isotropic mineral, Sierra Leone. Analyst: AULIS HEIKKINEN*

| | |
|--------------------------------|--------|
| SiO ₂ | 51.72 |
| TiO ₂ | 0.55 |
| Al ₂ O ₃ | 21.15 |
| Fe ₂ O ₃ | 2.68 |
| FeO | 2.76 |
| MnO | 0.15 |
| MgO | 2.17 |
| CaO | 2.56 |
| Na ₂ O | 0.34 |
| K ₂ O | 0.32 |
| P ₂ O ₅ | 0.45 |
| CO ₂ | 0.00 |
| H ₂ O + | 10.26 |
| H ₂ O - | 5.03 |
| Total | 100.14 |

sition of hornblende of the rock, which is also the main impurity of the material represented by the analysis of table 2. This calculation yields a composition for the hornblende of $\text{Na}_2\text{O} \cdot 2\text{CaO} \cdot 4(\text{Mg}, \text{Fe})\text{O} \cdot 2(\text{Al}_2\text{O}_3, \text{TiO}_2) \cdot 6\text{SiO}_2 + 3 \times (2\text{CaO} \cdot 3.5(\text{Mg}, \text{Fe})\text{O} \cdot 2\text{Al}_2\text{O}_3 \cdot 6\text{SiO}_2 = \text{Na}_2\text{O} \cdot 8\text{CaO} \cdot 14.5(\text{Mg}, \text{Fe})\text{O} \cdot 8(\text{Al}_2\text{O}_3, \text{TiO}_2) \cdot 24\text{SiO}_2$.

If this composition (and magnetite) be subtracted from the analysis of table 2, there remain

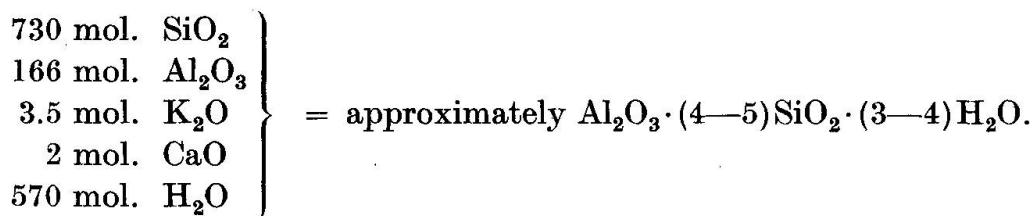

From this calculation it may be deduced, that the zeolite-like isotropic mineral has, in the main, the composition of a highly hydrous aluminiumsilicate, possibly containing a little potassium and calcium. Because the material analyzed contained some inclusions of quartz, the true composition of the isotropic mineral may well be $\text{Al}_2\text{O}_3 \cdot 4\text{SiO}_2 \cdot (3-4)\text{H}_2\text{O}$. By prolonged separation of the odd mineral, a portion amounting to a few mg of reasonable pure material was obtained. Because of the scarcity of material, only CaO, Al₂O₃ and SiO₂ were determined. The result: 0.05% CaO, traces of total iron, 23.65% Al₂O₃, and 63.14% SiO₂ well confirms the above-made calculation, as well as the suggested formula of the odd mineral ($\text{Al}_2\text{O}_3 : \text{SiO}_2 = 1 : 4.5$).

It is interesting to compare this composition with that of analcime, which is $\text{Na}_2\text{O} \cdot \text{Al}_2\text{O}_3 \cdot 4\text{SiO}_2 \cdot \text{aq}$. Thus, the new mineral resembles analcime without Na_2O . Though nothing seems to replace the sodium, the optical properties and isotropy of the new mineral nevertheless indicate that the latter is very similar to analcime.

The new mineral could hardly be classed definitely as a zeolite since it contains neither alkalies or lime.

URBAIN (1936), however, considers that the water of hydrated Al-silicates, is mainly "zeolitic" as is also obviously the case in the mineral considered in this paper. The composition of this mineral is that of hydrous pyrophyllite ($\text{Al}_2\text{O}_3 \cdot 4\text{SiO}_2 + \text{aq}$) or of paramontmorillonite ($\text{Al}_2\text{O}_3 \cdot 4\text{SiO}_2 \cdot 6\text{H}_2\text{O}$). The former composition was mentioned by SEDLETZKY (1940) as a hypothetical metastable member between pyrophyllite gel and pyrophyllite, but it definitely has not a cubic structure.

Returning to the bulk composition of this rock (table 1) and remembering that it very probably occurs at the contact between pyroxene-spinel-magnetite-rich ultrabasic rock and granodiorite, it may be of interest to compare this bulk composition with that of the ultrabasic rock. Recalculation of the analysis of table 1 into minerals characteristic of this ultrabasic rock, one gets the following composition (neglecting the water content of the rock, and taking the excess of Al_2O_3 , in accordance with the composition of the unknown, hydrous Al-mineral, as pyrophyllite).

| | |
|--------------|--------|
| diopside | 18.36% |
| spinel | 6.23% |
| magnetite | 12.06% |
| ilmenite | 3.65% |
| pyrophyllite | 25.65% |
| albite | 4.40% |
| orthoclase | 1.67% |
| apatite | 1.90% |
| quartz | 18.78% |
| | 92.70% |

This calculation reveals, that the amphibolite of odd composition may well have derived as a marginal variety from the above-mentioned ultrabasic rock, by addition of much alumina, silica and water, which in turn could have derived from solutions circulating along the contact zone during and immediately after the emplacement of the ultrabasic material.

Dixeyite

The unknown mineral was separated from the well-crushed rock by means of a bromoform-ethanol mixture and the centrifuge. This procedure revealed that the specific gravity of the unknown mineral is approximately 2.51—2.52. The refractive index of the mineral is 1.5057.

Because of the intense intergrowth of the new mineral with extremely thin needles of amphibole it was not possible to separate sufficiently pure material for very exact examination. It was, however, possible to obtain a small amount of reasonably pure material for a diffraction picture. This gave the pattern of table 3.

In this table, a_0 values for all reflections are also indicated and show some variation; this suggests that the lattice may not be exactly cubic. Optically, however, the mineral is perfectly isotropic. The average value of column 1 for $a_0 = 7.55 \text{ \AA}$, of column 2, $a_0 = 7.7 \text{ \AA}$, and the mean of both, $a_0 = 7.6 \text{ \AA}$, should give the approximate size of the unit cell. The size of the unit cell will at least lie near that of such a cubic cell.

If the oxygen-atom content of the unit cell be calculated from what remains when the analysis (table 2) is subtracted from the analysis (table 1) and taking into consideration both the known approximate value of the specific gravity of the examined mineral and the value $a_0 = 7.6 \text{ \AA}$, the result obtained is 22.55 atoms of oxygen per unit cell. This suggests, that the size of a_0 should be doubled, which is also in agreement with the fact that the mineral is highly hydrous, and zeolite-like.

Table 3. *Reflections of dixeyite*

| 1 | | | | 2 | | | |
|------|-----|------------|--------------------|------|---|------------|--------------------|
| d | | hkl | a_0 | d | | hkl | a_0 |
| 3.32 | s | (210) | 7.404 \AA | 3.40 | s | (210) | 7.582 \AA |
| 3.09 | s | (211) | 7.570 \AA | 3.19 | s | (211) | 7.813 \AA |
| 2.69 | v.w | (220) | 7.613 \AA | 2.74 | d | (220) | 7.56 \AA |
| 2.33 | d | (310) | 7.369 \AA | 2.58 | d | (300, 221) | 7.74 \AA |
| 2.27 | s | (311) | 7.536 \AA | 2.46 | d | (310) | 7.774 \AA |
| 2.15 | w | (222) | 7.390 \AA | 1.85 | w | (410, 322) | 7.622 \AA |
| 2.01 | w | (321) | 7.517 \AA | | | | |
| 1.83 | w | (410, 322) | 7.539 \AA | | | | |
| 1.79 | w | (411, 330) | 7.589 \AA | | | | |
| 1.72 | w | (331) | 7.479 \AA | | | | |
| 1.68 | w | (421) | 7.694 \AA | | | | |

s = strong; d = distinct; w = weak; v.w = very weak

1. according to the X-ray diffraction chart,
2. according to the photograph of the powder diagram.

Thus it is assumed that the examined mineral has 180 oxygen atoms in the unit cell, providing this cell deviates but little from a cubic cell with $a_0 = 15.2 \text{ \AA}$.

The chemical composition, optical examination and the X-ray study suggest, that the mineral described in this paper, is a new mineral with a structure resembling that of zeolites.

It will be named *dixeyite*, in honour of Dr. F. Dixey, Director of the British Overseas Geological Surveys, because he was the first geologist appointed by the government of Sierra Leone, and it was he who first described the geology of this country more extensively.

References

Geological Deptm. of Sierra Leone. Annual Report 1955 and 1956.
MARMO, V. (1958): Serpentinites of Central Sierra Leone. Bull. Comm. géol. Finlande 180, pp. 1—30.
SEDLETZKY, J. D. (1940): On the principles of classification of argillaceous minerals. — Compt. Rend. (Doklady) Acad. Sci. USSR, vol. 26, pp. 240—243.
URBAIN, P. (1936): Classification des silicates d'alumine hydratés (lato sensu), du point de vue du pétrographe, et du géologue. — Compt. Rend. soc. géol. France, 1936, fasc. 8—9, pp. 147—149.

Received: 17th of October 1958.