

Off-axis configuration of F_A(Li) centres in KF

Autor(en): **Scacco, A. / Somma, F. / Rossi, M.**

Objektyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **62 (1989)**

Heft 6-7

PDF erstellt am: **20.09.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116077>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

OFF-AXIS CONFIGURATION OF $F_A(\text{Li})$ CENTRES IN KF

A. Scacco, F. Somma, M. Rossi, F. De Matteis, Dipartimento di Fisica, Università *La Sapienza*, P.le A. Moro 2, 00185 Roma, Italy

G. Baldacchini, ENEA, Dip.TIB, U.S. Fisica Applicata, CRE Frascati, C.P.65, 00044 Frascati, Italy

U.M. Grassano, Dipartimento di Fisica, Università di Roma-Tor Vergata, V. O. Raimondo, 00173 Roma, Italy

Abstract: The off-axis configuration of F_A dipoles was identified in $\text{KF}:\text{Li}^+$. The centre tilt from the crystal axis is, as expected, larger in $\text{KF}:\text{Li}^+$ than in $\text{KCl}:\text{Li}^+$ and in $\text{RbCl}:\text{Li}^+$.

1. Introduction

The off-centre displacement of Li^+ ions in crystals of alkali halides, showing a sufficiently large lattice parameter, was experimentally observed in KCl [1] and in RbCl [2], and theoretically calculated for several systems [3]. Such a peculiar configuration of the isolated impurity seems to be correlated in the above systems to a tilt from the crystal axis of the F_A dipole, formed by association of the impurity ion with a nearest-neighbour anion vacancy trapping an electron. The off-axis deviation of the $F_A(\text{Li})$ centres was quantitatively determined both in $\text{KCl}:\text{Li}^+$ [4] and $\text{RbCl}:\text{Li}^+$ [5] by means of optical measurements. In this work the investigation on the configuration of $F_A(\text{Li})$ dipoles is extended to $\text{KF}:\text{Li}^+$.

2. Experimental results and discussion

The technique used for studying the off-axis geometry of the $F_A(\text{Li})$ centres is the analysis of their photostimulated reorientation under polarized optical pumping into the range of the F_A absorption [6]. The alignment process was theoretically treated, by taking into account both the off-axis effect of the dipoles and the overlap of the two F_A absorption bands, for experiments in equilibrium conditions [4] or during transient phenomena [7].

In $\text{KF}:\text{Li}^+$ preliminary absorption measurements have been performed on transient effects. After thorough orientation of the centres by irradiation with monochromatic F_A light polarized along one of the crystal axes, the polarization plane of the incident beam was suddenly rotated: as a consequence, a depopulation occurs for centres lying parallel to the above direction, while the centre population along perpendicular directions increases correspondingly. The initial absorption $\alpha(0)$ and the steady-state absorption $\alpha(\infty)$, measured for two different rotations of the polarization plane of the exciting light (Figure 1),

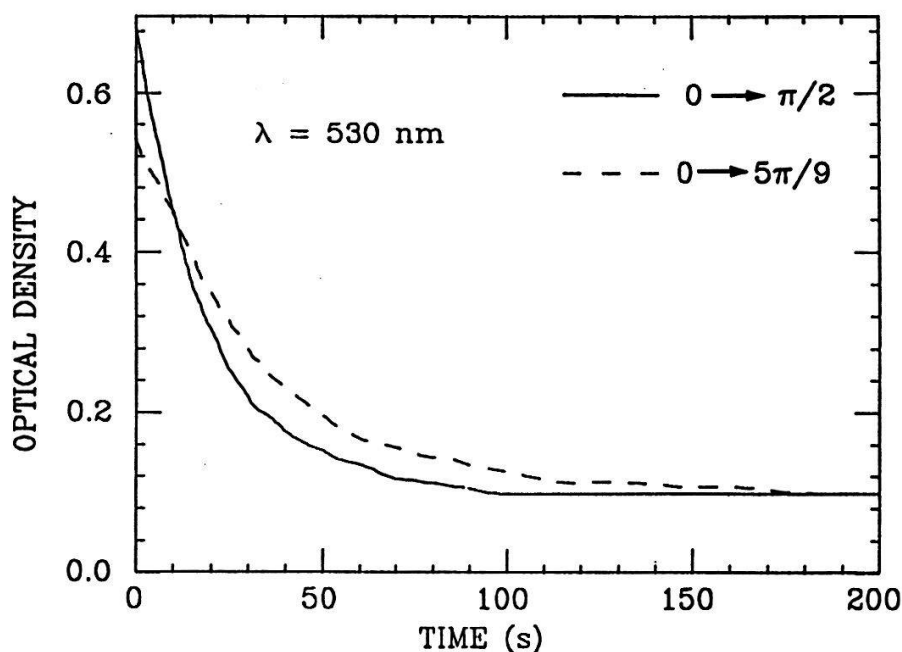


Figure 1: Kinetics of the $F_A(\text{Li})$ centre photostimulated reorientation in $\text{KF}:\text{Li}^+$ at 77 K.

allow the calculation of both the off-axis angle θ of the F_A dipoles and the ratio R of the cross sections related to the two F_A transitions.

From these and other results, obtained at various wavelengths of the pumping light, it is possible to deduce a first approximate evaluation of θ in $\text{KF}:\text{Li}^+$, which is slightly bigger than 10° . Such value, to be confirmed by luminescence experiments at various temperatures, is larger than those in $\text{KCl}:\text{Li}^+$ and in $\text{RbCl}:\text{Li}^+$, as expected because of the more pronounced displacement of the isolated Li^+ ion in this system [3].

3, References

- [1] F. Rosenberger and F. Lüty, *Solid State Commun.* **7**, 983 (1969).
- [2] K. Thörmer and F. Lüty, *Phys. Status Solidi (b)* **90**, 277 (1978).
- [3] C.R.A. Catlow, K.M. Diller, N.J. Norgett, J. Corish, B.M.C. Parker, and P.W.M. Jacobs, *Phys. Rev. B* **18**, 2739 (1978).
- [4] G. Baldacchini, K. Somaiah, U.M. Grassano, A. Scacco, and F. Somma, *Il Nuovo Cimento* **9D**, 1105 (1987).
- [5] G. Baldacchini, F. De Matteis, E. Giovenale, A. Scacco, F. Somma, and U.M. Grassano, *Phys. Rev. B* **37**, 7014 (1988).
- [6] F. Lüty, in *Physics of Color Centers*, ed. W.B. Fowler (Academic, New York, 1968), Chap. 3.
- [7] G. Baldacchini, U.M. Grassano, A. Scacco, and F. Somma, *Phys. Scripta* **37**, 381 (1988).